

MAR 24 1965

83975

CONTRIBUTION FROM THE LOS ALAMOS SCIENTIFIC LABORATORY  
UNIVERSITY OF CALIFORNIA, LOS ALAMOS, NEW MEXICO

1 CRYSTAL STRUCTURES OF THE TRIFLUORIDES, TRICHLORIDES, TRIBROMIDES,  
AND TRI-IODIDES OF AMERICIUM AND CURIUM<sup>1</sup>

By L. B. ASPREY, T. K. KEENAN, AND F. H. KRUSE

Received \_\_\_\_\_

NOT FOR PUBLIC RELEASE - OFFICIAL  
DISTRIBUTION MAY BE MADE. OFFICIAL  
REQUESTS MAY BE FILLED. REPORT  
CONTAINS NOTHING OF PATENT INTEREST.  
PROCEDURES ON FILE IN RECEIVING  
SECTION.

The previously unreported lattice constants and crystal symmetries of the trifluoride, trichloride, tribromide, and tri-iodide of curium are given. Similar data for the isostructural trihalides of americium (except for the trifluoride) have been redetermined to a higher degree of precision. Correlations have been made between these actinide trihalides and the corresponding lanthanide trihalides.

Curium trifluoride is hexagonal,  $\text{LaF}_3$  type, space group  $P6_3/mmc - D_{6h}^4$ . Americium and curium trichlorides are hexagonal,  $\text{UCl}_3$  type, space group  $P6_3/m - C_{6h}^2$ . The tribromides are orthorhombic,  $\text{PuBr}_3$  type, space group  $\text{Cmcm} - D_{6h}^{17}$ . The tri-iodides are hexagonal,  $\text{BiI}_3$  type, space group  $R\bar{3} - C_{3i}^2$ .

When treated with hydrogen at elevated temperatures, no reduction of these trivalent americium or curium trihalides was observed.

LEGAL NOTICE

This report was prepared as an account of Government sponsored work. Neither the United States, nor the Commission, nor any person acting on behalf of the Commission:

A. Makes any warranty or representation, expressed or implied, with respect to the accuracy, completeness, or usefulness of the information contained in this report, or that the use of any information, apparatus, method, or process disclosed in this report may not infringe privately owned rights; or

B. Assumes any liabilities with respect to the use of, or for damages resulting from the use of any information, apparatus, method, or process disclosed in this report.

As used in the above, "person acting on behalf of the Commission" includes any employee or contractor of the Commission, or employee of such contractor, to the extent that such employee or contractor of the Commission, or employee of such contractor prepares, disseminates, or provides access to, any information pursuant to his employment or contract with the Commission, or his employment with such contractor.

## DISCLAIMER

**This report was prepared as an account of work sponsored by an agency of the United States Government. Neither the United States Government nor any agency Thereof, nor any of their employees, makes any warranty, express or implied, or assumes any legal liability or responsibility for the accuracy, completeness, or usefulness of any information, apparatus, product, or process disclosed, or represents that its use would not infringe privately owned rights. Reference herein to any specific commercial product, process, or service by trade name, trademark, manufacturer, or otherwise does not necessarily constitute or imply its endorsement, recommendation, or favoring by the United States Government or any agency thereof. The views and opinions of authors expressed herein do not necessarily state or reflect those of the United States Government or any agency thereof.**

## **DISCLAIMER**

**Portions of this document may be illegible in electronic image products. Images are produced from the best available original document.**

### Introduction

Since their discovery, there has been a continuing interest in the solid state chemistry of the actinide elements. With the advent of macro (i.e. multi-milligram) amounts of the longer-lived isotopes,  $\text{Am}^{243}$  and  $\text{Cm}^{244}$ , it has been possible to carry out quite definitive experiments with these elements. More elegant purification schemes can be employed and the overall handling difficulties are diminished due to the lower rate of gamma emission. In general, such work confirmed the early tracer or microgram scale investigations. Occasionally, some of the early results could not be confirmed. In addition, the availability of modern computer programs for processing X-ray data has aided in the determination of more precise values for various crystal parameters.

Some values for the lattice constants of the trichloride, tribromide, and tri-iodide of americium were reported some time ago.<sup>2</sup> However, these results were based on work with  $\text{Am}^{241}$ , difficult to purify and to use for X-ray data because of its strong gamma emission. The crystal properties of  $\text{AmF}_3$  had been investigated more recently.<sup>3</sup> The purposes of the present work then were three-fold: (1) to re-examine the trichloride, tribromide, and tri-iodide of americium using long-lived  $\text{Am}^{243}$ , (2) to prepare all the analogous trihalides of curium using  $\text{Cm}^{244}$ , (3) to study the possible reduction of these trihalides by hydrogen at elevated temperatures.

### Experimental

Unless otherwise stated, all chemicals were of AR grade. Americium as  $\text{Am}^{243}$  and curium as  $\text{Cm}^{244}$  were purified by conventional means.<sup>4</sup> Tank

hydrogen was purified by passing it through a heated palladium alloy valve  
5 using a commercial apparatus.<sup>5</sup>

The insolubility of  $\text{CmF}_3$  allowed its preparation directly from aqueous solution. Hydrofluoric acid was added to a solution of  $\text{Cm(III)}$ ; the resulting  $\text{CmF}_3$  precipitate was washed with dilute HF, water, methyl alcohol, and acetone. The air-dried pellet of  $\text{CmF}_3$  was treated with HF gas for 5 hours at  $400^\circ$ . Hydrogen gas was mixed with HF gas for some experiments to study the effect of this reductant. X-ray capillaries were loaded with the curium fluoride following such equilibrations.

The general technique used for preparing the other actinide halides has  
6 been described more fully elsewhere.<sup>6</sup> The trichloride starting material was formed by evaporation in air of an HCl solution of a 10:1 mole mixture of  $\text{NH}_4\text{Cl}/\text{MCl}_3$ . The ammonium chloride was sublimed from this material in a quartz capillary. The appropriate ammonium halide was then used to convert  $\text{AmCl}_3$  or  $\text{CmCl}_3$  to the desired halide at  $400 - 450^\circ$  in a stream of hydrogen. The conversion reaction yielding the desired halide salt was carried out in the same quartz capillary from which a portion could be sealed for X-ray examination of the final product.

An attempt was made in all cases to reduce  $\text{MX}_3$  to  $\text{MX}_2$  by hydrogen at elevated temperatures. However, treatment of all of these trihalides with hydrogen (at ca. 3 psig) at temperatures up to  $900^\circ$  gave no evidence of reduction. Using samarium as a stand-in resulted in formation of samarium dihalides in good yield.

A Norelco X-ray unit was used with 114.6 mm Debye-Scherrer cameras and Ilford "G" film. The X-ray films of the trihalide compounds were read three times and the results averaged.

A "proposed" powder pattern (using the information from Ref. 2) was initially generated using the POWD<sup>7</sup> or ANIFAC<sup>8</sup> programs; this was used for preliminary indexing of lines. Lattice constants from the initial indexing were estimated by least-squares calculations using the MET-124<sup>9</sup> program. The constants were refined by two or three additional cycles between the programs until the overall standard deviations and the individual variances of each line reached a satisfactory level.

#### Results and Discussion

In Table I are listed the values for the lattice constants of these halides. With the exception of the iodides, the actinide contraction is exhibited by all dimensions of the crystal lattices. The larger error for the iodides reflects the greater instability of the iodide compounds, possibly due to the disruptive effect of the alpha particles. Even using the relatively long-lived Am<sup>243</sup>, the iodide compound was more unstable than the other halides.

No evidence could be obtained for an orthorhombic phase (PuBr<sub>3</sub> type) of AmI<sub>3</sub> as was reported some years ago.<sup>2</sup> Although a phase transition is known for the NdI<sub>3</sub> system,<sup>10</sup> orthorhombic AmI<sub>3</sub> was never obtained even though the conversion temperature was varied from 400 - 900°. Annealing of the hexagonal AmI<sub>3</sub> at various temperatures for as long as possible (considering the relative instability of the compound) showed no evidence for growth of an orthorhombic phase.

Table I

Lattice Constants and Molecular Volumes for Americium and Curium Trihalides

Error Limits are Standard Deviation

A. Fluorides: Hexagonal, LaF<sub>3</sub> type, space group P6<sub>3</sub>/mmc - D<sub>6h</sub><sup>4</sup>, Z = 2

	$\frac{a_0}{\text{Å}}$	$\frac{b_0}{\text{Å}}$	$\frac{c_0}{\text{Å}}$	Mol. Vol. $\text{Å}^3$
AmF <sub>3</sub> <sup>(3)</sup>	4.067 ± 0.001		7.225 ± 0.002	51.75
CmF <sub>3</sub>	4.041 ± 0.001		7.179 ± 0.002	50.76

B. Chlorides: Hexagonal, UCl<sub>3</sub> type, space group P6<sub>3</sub>/m - C<sub>6h</sub><sup>2</sup>, Z = 2

AmCl <sub>3</sub>	7.390 ± 0.003		4.234 ± 0.002	100.1
CmCl <sub>3</sub>	7.368 ± 0.006		4.228 ± 0.004	99.4

C. Bromides: Orthorhombic, PuBr<sub>3</sub> type, space group Cmcm - D<sub>2h</sub><sup>17</sup>, Z = 4

AmBr <sub>3</sub>	4.064 ± 0.001	12.661 ± 0.006	9.144 ± 0.004	117.6
CmBr <sub>3</sub>	4.048 ± 0.002	12.66 ± 0.01	9.124 ± 0.007	116.9

D. Iodides: Hexagonal, BiI<sub>3</sub> type, space group R $\bar{3}$  - C<sub>3i</sub><sup>2</sup>, Z = 6

AmI <sub>3</sub>	7.42 ± 0.04		20.55 ± 0.08	163.3
CmI <sub>3</sub>	7.44 ± 0.09		20.4 ± 0.1	163.0

The failure of these compounds, particularly  $\text{AmI}_3$ , to form divalent salts is somewhat disappointing but does provide additional evidence for the stability of the trivalent state in the actinide series as compared to the lanthanides samarium and europium. Even with the thermodynamic advantage of flowing a stream of hydrogen over the tri-iodide, no evidence for reduction was obtained under conditions where  $\text{SmI}_2$  was formed in good yield.


It will be of interest to observe whether the structure types exhibited by the americium and curium trihalides continue into the transcurium elements. Figure 1 shows a plot of molecular volume vs. atomic number for the known trivalent actinide trihalides. A change in structure type has already been observed for the bromides and iodides. In the lanthanide series, a change in structure type of all halides (including fluorides and chlorides) takes place at the approximate

11, 12, 13, 14 midpoint of the series: <sup>2, 6, 11, 12, 13, 14</sup> In fact, terbium (the homolog of berkelium) <sup>15</sup> trichloride exhibits a unique structure of its own between the  $\text{UCl}_3$  type of the first half of the lanthanides and the  $\text{YCl}_3$  type of the second half. Since terbium is the transition point of the lanthanide chlorides, berkelium or californium may indeed show analogous behavior in the actinides.



Fig. 1. — Plot of Molecular Volume vs. Atomic Number for Actinide Halides.

MOL.  
VOL.,  
 $\text{\AA}^3$

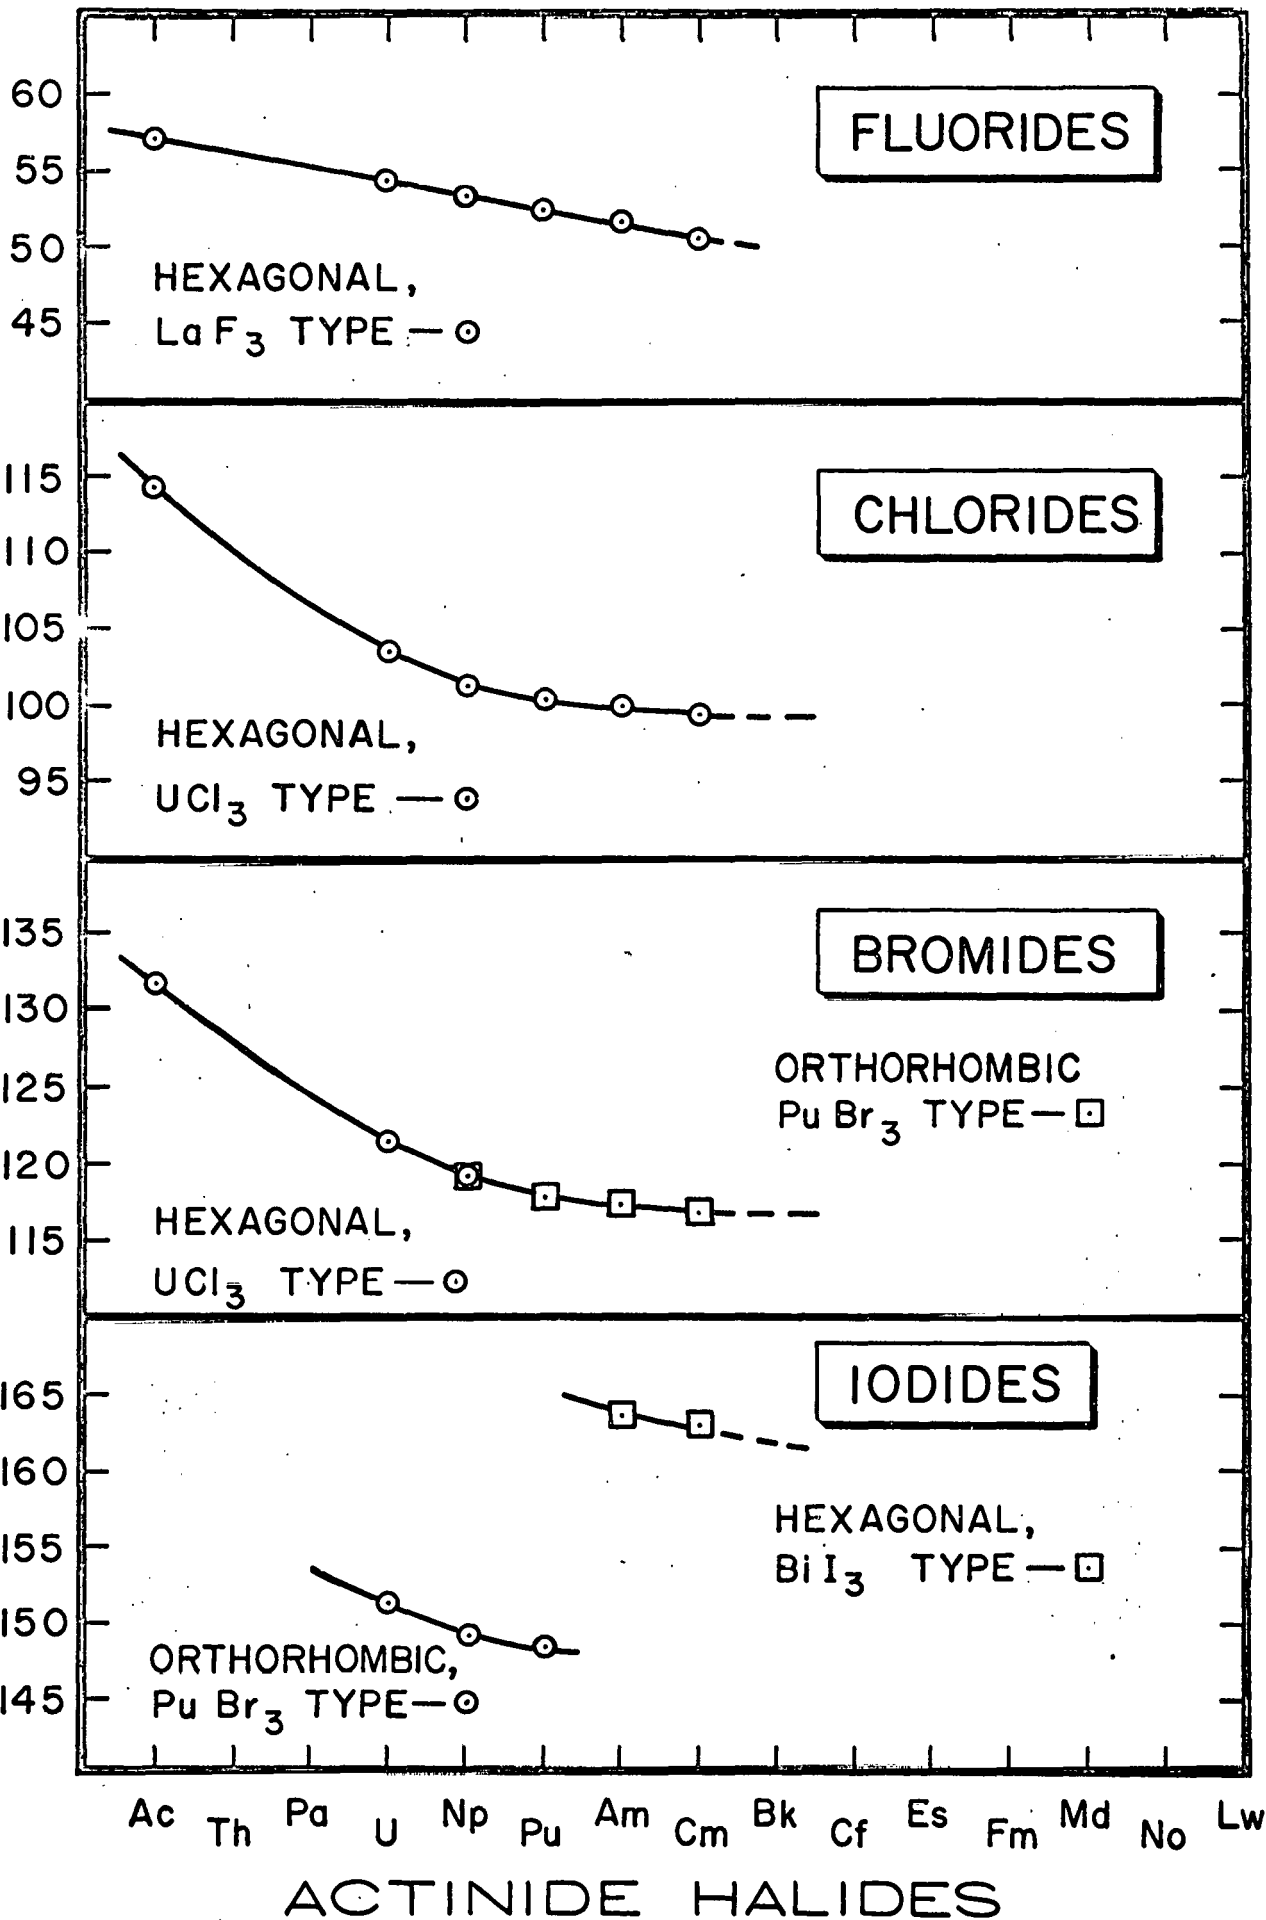

References

- (1) This work was performed under the auspices of The U. S. Atomic Energy Commission.
- (2) W. H. Zachariasen, Acta Cryst. 1, 265 (1948).
- (3) D. H. Templeton and C. H. Dauben, J. Am. Chem. Soc. 75, 4560 (1953).
- (4) T. K. Keenan, J. Inorg. Nucl. Chem. 20, 185 (1961).
- (5) Manufactured by The Milton Roy Company, Monterey Park, California.
- (6) L. B. Asprey, T. K. Keenan, and F. H. Kruse, Inorg. Chem. 3, 1137 (1964).
- (7) D. K. Smith, "A Fortran Program for Calculating X-ray Powder Diffractions", University of California Report UCRL-7196 (1963).
- (8) A. C. Larson, Los Alamos Scientific Laboratory, unpublished work.
- (9) M. H. Mueller and L. Heaton, "Determination of Lattice Parameters with the Aid of a Computer", Argonne National Laboratory Report ANL-6176 (1961).
- (10) L. F. Druding and J. D. Corbett, J. Am. Chem. Soc. 83, 2462 (1961).
- (11) A. Zalkin and D. H. Templeton, J. Am. Chem. Soc. 75, 2453 (1953).
- (12) D. H. Templeton and G. F. Carter, J. Phys. Chem. 58, 940 (1954).
- (13) D. H. Templeton and C. H. Dauben, J. Am. Chem. Soc. 76, 5237 (1954).
- (14) A. J. C. Wilson, "Structure Reports", Oosthoek, Utrecht, Netherlands, 1948, Vol. 11, pp. 276-282.
- (15) J. D. Forrester, A. Zalkin, D. H. Templeton, and J. C. Wallman, Inorg. Chem. 3, 185 (1964).