


Thermodynamic Properties of Minerals and
Related Substances at 298.15 K and 1 Bar
(10^5 Pascals) Pressure and at Higher Temperatures

U.S. GEOLOGICAL SURVEY BULLETIN 2131

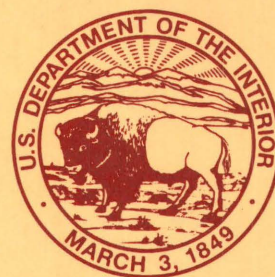

AVAILABILITY OF BOOKS AND MAPS OF THE U.S. GEOLOGICAL SURVEY

Instructions on ordering publications of the U.S. Geological Survey, along with prices of the last offerings, are given in the current-year issues of the monthly catalog "New Publications of the U.S. Geological Survey." Prices of available U.S. Geological Survey publications released prior to the current year are listed in the most recent annual "Price and Availability List." Publications that may be listed in various U.S. Geological Survey catalogs (see **back inside cover**) but not listed in the most recent annual "Price and Availability List" may be no longer available.

Order U.S. Geological Survey publications **by mail** or **over the counter** from the offices given below.

BY MAIL

Books

Professional Papers, Bulletins, Water-Supply Papers, Techniques of Water-Resources Investigations, Circulars, publications of general interest (such as leaflets, pamphlets, booklets), single copies of Earthquakes & Volcanoes, Preliminary Determination of Epicenters, and some miscellaneous reports, including some of the foregoing series that have gone out of print at the Superintendent of Documents, are obtainable by mail from

**U.S. Geological Survey, Information Services
Box 25286, Federal Center, Denver, CO 80225**

Subscriptions to periodicals (Earthquakes & Volcanoes and Preliminary Determination of Epicenters) can be obtained **ONLY** from the

**Superintendent of Documents
Government Printing Office
Washington, DC 20402**

(Check or money order must be payable to Superintendent of Documents.)

Maps

For maps, address mail orders to

**U.S. Geological Survey, Information Services
Box 25286, Federal Center, Denver, CO 80225**

Residents of Alaska may order maps from

**U.S. Geological Survey, Earth Science Information Center
101 Twelfth Ave. - Box 12
Fairbanks, AK 99701**

OVER THE COUNTER

Books and Maps

Books and maps of the U.S. Geological Survey are available over the counter at the following U.S. Geological Survey Earth Science Information Centers (ESIC), all of which are authorized agents of the Superintendent of Documents:

- **ANCHORAGE, Alaska**—Rm. 101, 4230 University Dr.
- **LAKEWOOD, Colorado**—Federal Center, Bldg. 810
- **MENLO PARK, California**—Bldg. 3, Rm. 3128, 345 Middlefield Rd.
- **RESTON, Virginia**—USGS National Center, Rm. 1C402, 12201 Sunrise Valley Dr.
- **SALT LAKE CITY, Utah**—Federal Bldg., Rm. 8105, 125 South State St.
- **SPOKANE, Washington**—U.S. Post Office Bldg., Rm. 135, West 904 Riverside Ave.
- **WASHINGTON, D.C.**—Main Interior Bldg., Rm. 2650, 18th and C Sts., NW.

Maps Only

Maps may be purchased over the counter at the following U.S. Geological Survey offices:

- **FAIRBANKS, Alaska**—New Federal Bldg., 101 Twelfth Ave.
- **ROLLA, Missouri**—1400 Independence Rd.
- **STENNIS SPACE CENTER, Mississippi**—Bldg. 3101

Thermodynamic Properties of Minerals and Related Substances at 298.15 K and 1 Bar (10^5 Pascals) Pressure and at Higher Temperatures

By Richard A. Robie and Bruce S. Hemingway

U. S. GEOLOGICAL SURVEY BULLETIN 2131

A summary of the thermodynamic data for minerals at 298.15 K together with calculated values for the functions $C_{p,T}^\circ$, $\Delta_f H_T^\circ$, $\Delta_f G_T^\circ$, S_T° , $(H_T^\circ - H_{298}^\circ)T^{-1}$, and $(G_T^\circ - H_{298}^\circ)T^{-1}$ at temperatures up to 1800 K



UNITED STATES GOVERNMENT PRINTING OFFICE, WASHINGTON : 1995

U.S. DEPARTMENT OF THE INTERIOR
BRUCE BABBITT, Secretary

U.S. GEOLOGICAL SURVEY
GORDON P. EATON, Director

For sale by U.S. Geological Survey, Information Services
Box 25286, Federal Center, Denver, CO 80225

Any use of trade, product, or firm names in this publication is for descriptive purposes only and does not imply endorsement by the U.S. Government.

Published in the Eastern Region, Reston, Va.
Manuscript approved for publication March 23, 1995.

Library of Congress Cataloging in Publication Data

Robie, Richard A., 1928-

Thermodynamic properties of minerals and related substances at 298.15 K and 1 bar (10 Pascals) pressure and at higher temperatures / by Richard A. Robie and Bruce S. Hemingway.

p. cm.— (Geological Survey bulletin ; 2131)

Includes bibliographical references and indexes.

Supt. of Docs. no. : I 19.3:B2131

1. Minerals—Tables. 2. Thermodynamics—Tables. I. Hemingway, Bruce S. II. Title. III.

Series: U.S. Geological Survey bulletin ; 2131.

QE75.B9 no. 2131

[QE366.8]

557.3 s—dc20

[549'. 12]

95-19844

CIP

CONTENTS

Abstract	1
Introduction	1
Physical Constants and Atomic Weights	2
Reference States	3
Methods of Calculation	3
Additional Comments	4
Thermodynamic Properties at 298.15 K	5
Elements	5
Sulfides and Sulfosalts	11
Oxides and Hydroxides	15
Multiple Oxides	21
Halides	23
Carbonates and Nitrates	25
Sulfates and Borates	28
Phosphates, Molybdates, and Tungstates	30
Ortho and Ring Structure Silicates	31
Chain and Band Structure Silicates	34
Framework Structure Silicates	36
Sheet Structure Silicates	39
Coefficients for Heat Capacity Equations	41
Elements	41
Sulfides and Sulfosalts	45
Oxides and Hydroxides	47
Multiple Oxides	51
Halides	53
Carbonates and Nitrates	55
Sulfates and Phosphates	56
Ortho and Ring Structure Silicates	58
Chain and Band Structure Silicates	61
Framework Structure Silicates	63
Sheet Structure Silicates	65
Thermodynamic Properties at High Temperature of Individual Phases	67
References Cited	397
Name Index	454
Formula Index	458

TABLE

1. Atomic weights of the elements for 1985	4
--	---

SYMBOLS, CONSTANTS, AND CONVERSION FACTORS

T	Temperature in Kelvins.
T_{tn}	Temperature of transition in Kelvins.
K	Kelvin, the unit of temperature. It is the fraction 1/273.16 of the thermodynamic temperature of the triple point of water.
J	Joule, the unit of energy (or work). One joule = 1/4.1840 thermochemical calories or 10 cm ³ •bar.
mol	Mole, the amount of substance of a system that contains as many elementary entities as there are atoms in 0.012 kilograms of carbon 12. It is identical with the gfw (gram formula weight).
p	Pressure in bars. One bar = 10 ⁵ Pascals or 0.1 MPa. The standard atmosphere is equal to 101325 Pascals. The kilogram•cm ⁻² is equal to 98065.5 Pascals.
°	Superscript indicates that the substance is in its standard state, 1 bar (10 ⁵ Pascals) for a condensed phase.
$H_T^\circ - H_{298}^\circ$	Enthalpy at temperature T relative to 298.15 K in J•mol ⁻¹ , also called the heat content.
$(H_T^\circ - H_{298}^\circ)T^{-1}$	Enthalpy function in J•mol ⁻¹ •K ⁻¹ (See note below).
S_T°	Entropy at temperature T, in J•mol ⁻¹ •K ⁻¹ .
$(G_T^\circ - H_{298}^\circ)T^{-1}$	Gibbs energy function in J•mol ⁻¹ •K ⁻¹ .
C_p°	Heat capacity at constant pressure in J•mol ⁻¹ •K ⁻¹ .
V_{298}°	Volume of 1 mol of a substance at 1 bar pressure and at 298.15 K, in cm ³ , or J•bar ⁻¹ .
$\Delta_{\text{fus}}H^\circ$	Enthalpy of melting at 1 bar pressure in J•mol ⁻¹ .
$\Delta_{\text{tn}}H^\circ$	Enthalpy of transition at 1 bar pressure in J•mol ⁻¹ .
$\Delta_{\text{vap}}H^\circ$	Enthalpy of vaporization to the ideal gas at 1 bar pressure at the normal boiling point in J•mol ⁻¹ .
Δ_fH°	Enthalpy of formation from the elements in their reference states in J•mol ⁻¹ .
Δ_fG°	Gibbs energy of formation from the elements in their reference states in J•mol ⁻¹ .
K_f	Equilibrium constant of formation.
R	Gas constant, 8.31451±0.00007 J•K ⁻¹ •mol ⁻¹ .
F	Faraday constant, 96,485.309±0.029 J•V ⁻¹ •mol ⁻¹ .
N_A	Avogadro constant, (6.0221367±0.0000036) x 10 ²³ mol ⁻¹ .
log	Common logarithm, base 10.
ln	Natural logarithm, base e = 2.71828...
atm	Standard atmosphere.
$m=1$	The standard state for an electrolyte in aqueous solution is the hypothetical ideal solution at unit activity and with the ions at infinite dilution.

When multiple units appear in the denominator of the symbol (for example, enthalpy function), the SI system does not recommend a particular order. For example, the units for entropy are given as J mol⁻¹ K⁻¹ in table 2.11 and as J K⁻¹ mol⁻¹ in table 3.5 of the Greenbook (278).

Thermodynamic Properties of Minerals and Related Substances at 298.15 K and 1 Bar (10^5 Pascals) Pressure and at Higher Temperatures

By Richard A. Robie and Bruce S. Hemingway

ABSTRACT

Selected values for the entropy (S°), molar volume (V°), and for the enthalpy and Gibbs energy of formation ($\Delta_f H^\circ$ and $\Delta_f G^\circ$) are given for 50 reference elements, 55 sulfides, 93 oxides and hydroxides, 141 silicates, and 154 other minerals and related substances at 298.15 K. For those minerals for which high-temperature heat-capacity or heat-content data are also available ($(H_T^\circ - H_{298}^\circ)T^{-1}$, S_T° , $(G_T^\circ - H_{298}^\circ)T^{-1}$, C_p° , $\Delta_f H_T^\circ$, $\Delta_f G_T^\circ$ and $\log K_{f,T}$ are tabulated at 100 K intervals for temperatures up to 1800 K.

INTRODUCTION

In the 17 years since the predecessor to this bulletin was published, an enormous body of new thermochemical and equilibrium measurements for minerals has been published, personal computers have become almost universally available, and a number of "internally consistent thermodynamic property databases" (ICTDB) have been published (37, 67, 117, 149, 150, 159, 187, 188, 374). (In this section, references are indicated by numbers in parentheses.) This report is an updated revision and expansion of U.S. Geological Survey (USGS) Bulletin 1452 (361) and entirely supersedes it. As an example of growth of the thermodynamic properties of mineral database, USGS Bulletin 1452 contained data for 58 silicate minerals whereas in the current set of tables this number has been increased to 141.

The purpose of these tables is to present a critical summary of the available thermodynamic data for minerals and related substances in a convenient form for the use of earth scientists. To make the tables as useful as possible, we have tried (1) to include enough auxiliary data so that a single set of tables would suffice for most calculations, (2) to ensure internal consistency, and (3) to provide the means for rapid revision and expansion as new data become available.

The tables in this compilation are divided into three sections. In the first section, values are given for the entropy (S_{298}°), molar volume (V_{298}°), enthalpy of formation

($\Delta_f H_{298}^\circ$), Gibbs energy of formation ($\Delta_f G_{298}^\circ$), and the logarithm of the equilibrium constant of formation ($\log K_{f,298}$) for the reference elements, minerals, and other substances of geological interest (properties at 298.15 K and 1 bar). In the second section, coefficients for the polynomial used to represent the heat capacity at high temperature are tabulated together with the temperature limits of applicability. In the third section, values are given for the thermodynamic properties at 100 K intervals for temperatures up to 1800 K. The data are arranged in order of their conventional mineralogical groups. Within each group (for example, the oxides) the listing is by alphabetical order of the chemical symbol of the principal cation.

The data have been taken from the original literature, recent critical evaluations, or have been evaluated by the present authors and estimated uncertainties have been assigned to the thermodynamic properties at 298.15 K. The primary sources of data are indicated numerically in the thermodynamic table of properties at 298.15 K, as "S" for the reference to the data for the entropy, "H/G" for the reference to the formation properties, and "C" to references to measured heat capacities above 298.15 K. The references are listed in complete form following the tables. The entropy and heat-capacity values tabulated are based almost exclusively on calorimetric measurements whereas the values for the enthalpy or Gibbs energy of formation were obtained from both equilibrium and calorimetric measurements. The values for the thermodynamic properties of the reference elements have been taken from the JANAF tables (67), the CODATA (85) recommended values, or in the case of calcium, from measurement at the USGS (360). For those silicate glasses for which $S_T^\circ - S_0^\circ$ has been determined calorimetrically and for which the enthalpy of fusion of the crystalline equivalent could be evaluated, the residual entropy (that is, S_0°) of the glass has been evaluated and added to the calorimetric entropy to obtain the correct entropy for use in thermodynamic calculations. Glasses and other phases for which $S_T^\circ - S_0^\circ$ has been measured but for which the residual entropy has not been evaluated are indicated by a "+" sign and the user must be aware that the

value tabulated does not include the configurational entropy.

Although a number of different forms of equations for the representation of the heat capacity at high temperatures have been proposed over the past 10 years, for example Berman (37), Fei and Saxena (104), Richet and Fiquet (342), we have retained the form adopted in the previous version of these tables,

$$C_p = A_1 + A_2 \cdot T + A_3 \cdot T^{-2} + A_4 \cdot T^{-0.5} + A_5 \cdot T^2$$

This equation can not be extrapolated beyond its upper limit. Inasmuch as most users will have access to a personal computer, the conversion from one form of equation to an alternative form is possible and is left up to the individual user's preference. The entropies listed in the table of coefficients for the C_p° polynomials corresponds to the temperature at the lower limit of the temperature range for the polynomial. This is usually 298.15 K.

For several phases, the existence of multiple transitions at high temperature makes it impractical to provide a simple polynomial expression for the heat capacity. For such phases, for example Fe, $\text{Cu}_{1.9}\text{S}$, and several pyrrhotites, we have listed only the heat capacity at 298.15 K.

For these phases, one must go to the high-temperature table for the particular phase (if tabulated) to get the heat capacity (and entropy) above room temperature.

Internally consistent thermodynamic property data sets for silicate minerals have been published by Haas et al. (149), Holland and Powell (187, 188), Berman (37), Halbach and Chatterjee (150), and Saxena and Chatterjee (374) among others. Inasmuch as most of the authors relied on the same sources of calorimetric and equilibrium data to derive their adopted values, it is surprising that significant differences in their listed values for such important phases as grossular, anorthite, phlogopite and muscovite exist. For example, between the most frequently cited ICTDB, those of Berman (37) and Holland and Powell (188), the values of $\Delta_f G_{298}^\circ$ calculated from their listed values of S_{298}° and $\Delta_f H_{298}^\circ$ differ by 5.7, 3.7 and 3.7 $\text{kJ}\cdot\text{mol}^{-1}$ for grossular, anorthite, and muscovite, respectively, and for analbite and muscovite the tabulated entropies differ by 4.4 and 9.1 $\text{J}\cdot\text{mol}^{-1}\cdot\text{K}^{-1}$, respectively. The point is, of course, that internal consistency does not imply that the derived values are accurate.

The reason for these discrepancies is most likely in the assumptions that the individual compiler makes concerning the state of internal Al/Si order. For a 1:3 Al/Si compound such as the alkali feldspars or micas the complete random mixing of the 3 Si and 1 Al over the 4 tetrahedral sites leads to a contribution to the entropy of 18.7 $\text{J}\cdot\text{mol}^{-1}\cdot\text{K}^{-1}$. However, if the aluminum-avoidance model is valid, the configurational entropy will be considerably smaller and of the order of 13 to 14 $\text{J}\cdot\text{mol}^{-1}\cdot\text{K}^{-1}$. The aluminum-avoidance model has not been calculated exactly and only approxi-

mate values are available. The values for the configurational entropies that have been derived from phase equilibrium studies by Holland and Powell (188) and by Berman (37) are 12.6 and 17.0 $\text{J}\cdot\text{mol}^{-1}\cdot\text{K}^{-1}$ for analbite and 16.0 and 15.1 $\text{J}\cdot\text{mol}^{-1}\cdot\text{K}^{-1}$ for sanidine, respectively. It appears that these calculated values for the entropy of disorder do not unequivocally support the aluminum-avoidance model but rather tend to yield a configurational entropy that is greater than that estimated by the aluminum-avoidance value, but definitely less than the fully random model. Any value of ΔS greater than that calculated from aluminum-avoidance would presumably mean that this model was inapplicable at high temperatures; for example, at temperatures greater than 1300 K for analbite the disordering entropy would approach 18.7 $\text{J}\cdot\text{mol}^{-1}\cdot\text{K}^{-1}$. Moreover Goldsmith and Jenkins (123) have shown that the Al/Si disorder in $\text{NaAlSi}_3\text{O}_8$ is a continuous function of the temperature and that it occurs over a range of several hundred degrees (500–1050 K) and occurs without change in symmetry.

As a consequence of these points the question arises whether one can extract meaningful (unique) values for the entropy of the disordered phase of an alumino-silicate from phase equilibrium studies without having additional information on the Al/Si distribution. For this reason, we have adopted the fully random model for tabulating the high-temperature properties for the Al/Si disordered feldspars and micas. For an extended discussion of the contribution to the entropy of silicate minerals arising from Al/Si or magnetic spin disorder, see Ulbrich and Waldbaum (413).

The differences in the derived values for the thermodynamic properties of phases in the CASH system is due in part to the existence of two calorimetric values for the entropy of grossular which differ from one another by 4.6 $\text{J}\cdot\text{mol}^{-1}\cdot\text{K}^{-1}$. The value of Westrum et al. (438) was determined on a natural sample and involved a substantial correction for impurities. The value given by Haselton and Westrum (157) was derived from measurements on a synthetic sample. The heat capacity of the synthetic sample used by Haselton and Westrum (157) was later remeasured at the USGS by the present authors (359), who found an entropy $S^\circ(\text{Ca}_3\text{Al}_2\text{Si}_3\text{O}_{12}, 298.15 \text{ K})$ of 259.9 $\text{J}\cdot\text{mol}^{-1}\cdot\text{K}^{-1}$ which agrees with the Haselton and Westrum value to within 0.2 $\text{J}\cdot\text{mol}^{-1}\cdot\text{K}^{-1}$ (0.08 percent). For this reason we have accepted the Haselton-Westrum value for the entropy of grossular in evaluating the thermodynamic properties of phases in the CASH system.

PHYSICAL CONSTANTS AND ATOMIC WEIGHTS

The symbols and constants used to prepare these tables are listed in the table of contents. The units adopted for reporting the thermodynamic properties are those of the International System of Units (SI). A formal description of

the SI system is given by Goldman and Bell (122). The recommended symbols and terminology used are those from the International Union of Pure and Applied Chemistry (IUPAC), "Quantities, Units and Symbols in Physical Chemistry", by Mills et al. (278) and commonly called the "Greenbook". The Greenbook is also a convenient source for the CODATA values of the fundamental physical constants, the 1985 atomic weights of the elements, and contains a detailed description of the SI system of units.

Values for the gas constant (R), the Faraday constant (F), and the Avogadro constant (A) used in the calculations are those adopted by the CODATA Task Group from the least squares evaluation of Cohen and Taylor (75). For convenience, we also give values for the atomic weights for 1985 (scale $C^{12} = 12.000$, Mills et al. (278)) in alphabetical order by their chemical symbol in table 1.

REFERENCE STATES

The reference pressure for the standard state adopted for these tables is 1 bar, that is 10^5 Pascals. For a gaseous phase, C_p° , $(H_T^\circ - H_{298}^\circ)T^{-1}$, and $\Delta_f H^\circ$ are independent of pressure, but the numerical values of S° , $(G_T^\circ - H_{298}^\circ)T^{-1}$, $\Delta_f G^\circ$ depend upon the choice of pressure. The change in pressure from $p = 1$ atm (1.0135 bar) to 1 bar yields $\Delta S = 0.11 \text{ J}\cdot\text{mol}^{-1}\cdot\text{K}^{-1}$. For a condensed phase (liquid or solid), it can be shown that the effect of changing the reference pressure from 1 atm to 1 bar has only a trivial effect upon all the thermodynamic properties tabulated in this report except for $\Delta_f G^\circ$, where a change will occur if one of the reference elements (usually oxygen) is a gas.

The standard states for the condensed elements are the most stable form at 1 bar pressure and the stated temperature. For gaseous elements, the standard state is the ideal gas at 1 bar pressure. Data are listed for the elements in their standard reference states, and for a few in nonstandard states; for example, S^2 gas and the diamond form of carbon. The reference state adopted for an element above its normal boiling or sublimation temperature is not necessarily its equilibrium state. Thus, at equilibrium, liquid sulfur boils at 1 bar pressure and approximately 716.9 K to a gas composed of S, S_2 , S_4 , S_6 , S_8 , etc., but for our reference table, we have assumed the gas phase to be only S_2 . For the reference state table for sulfur we have followed the JANAF (67) tables procedure using 882.12 K as the fictive boiling temperature at which liquid sulfur is in equilibrium with S_2 gas at 1 bar pressure. Because of the convenience of using diatomic sulfur gas in calculations of sulfide mineral equilibria we have included a second set of high-temperature tables for which the reference state for calculating $\Delta_f G^\circ$, and $\Delta_f H^\circ$ and $\log K_f$ for the sulfide phase is S_2 gas. The user is cautioned not to intermix values from the two different reference states in their calculations. In other ambiguous cases, we have chosen either the dominant species in the gas

or that species for which the best thermodynamic data are available as the reference state.

The reference states for $\Delta_f H^\circ$, $\Delta_f G^\circ$, and $\log K_f$ of the compounds are the elements in their standard states at 1 bar pressure and the stated temperature.

METHODS OF CALCULATION

Having chosen what we believe are the currently "best available" values for $H_T^\circ - H_{298}^\circ$, or $C_p^\circ(T)$, S_{298}° and either $\Delta_f H_{298}^\circ$ or $\Delta_f G_{298}^\circ$, we have calculated the Gibbs energy function, and the enthalpy, Gibbs energy, and the equilibrium constant of formation at 100 K intervals using the following relations:

$$(G_T^\circ - H_{298}^\circ)T^{-1} = (H_T^\circ - H_{298}^\circ)T^{-1} - S_T^\circ$$

$$\Delta_f H_T^\circ = \Delta_f H_{298}^\circ + \Delta(H_T^\circ - H_{298}^\circ)$$

$$\Delta_f G_T^\circ = \Delta_f H_{298}^\circ + T\Delta[(G_T^\circ - H_{298}^\circ)T^{-1}]$$

and

$$\log K_{f,T} = \Delta_f G_T^\circ / (2.30258 RT) = -\Delta_f G_{298}^\circ / (19.145T) - 1$$

These values together with C_p° , S_T° and $(H_T^\circ - H_{298}^\circ)T^{-1}$ are tabulated in the third section.

Transitions in heat capacity are treated in the standard manner: heat capacity curves are fit to the experimental values above and below the transition; values calculated from an extrapolation of the equation to the transition temperature are compared to the experimental values; and differences are summed to give an enthalpy of transition that is applied at the transition temperature.

The uncertainties assigned to the properties apply only to the values at 298.15 K. The principal source has been the original report of the experimental data. By convention, the uncertainty interval reported for calorimetric measurements is twice the standard deviation of the mean; that is,

$$\delta = 2[\sum (x_i - x_m)^2 / n(n-1)]^{1/2}$$

where x_i is the value for an individual measurement, x_m is the arithmetic mean of all the measurements, and n is the number of measurements.

For generating the high-temperature tables, the input data supplied to the computer are the identifying name of the substance, the entropy, the enthalpy of formation at 298.15 K, the number of atoms of each element in the chemical formula, and the coefficients for the heat capacity equation. A commercial spreadsheet is used to compute the formula weight of the compound and values for S_T° , $\Delta_f H_T^\circ$, $\Delta_f G_T^\circ$, $\log K_{f,T}$, C_p° , $(H_T^\circ - H_{298}^\circ)T^{-1}$, and $(G_T^\circ - H_{298}^\circ)T^{-1}$, at 100 K intervals up to 1800 K. Auxiliary data such as the melting and boiling points and enthalpies of melting and vaporization are also included. In addition, coefficients

from a regression performed on the calculated values of $\Delta_f G_T^\circ$ are included. The equation adopted is:

$$\Delta_f G_T^\circ = A + BT + CT^{-2}$$

The coefficients for the equations are listed, in scientific notation, at the bottom of the page for the individual high-temperature tables. The equations are given only for those minerals for which the regression yielded a fit of better than 1 percent.

ADDITIONAL COMMENTS

Small numbers of some groups are presented with other groups for convenience and economy. Examples

include tellurides, selenides and arsenides that are included with sulfides and sulfosalts, and methane, cohenite, and ammonia that are included with the elements.

The data available in this publication are also available on diskette for a nominal fee through the Generic Mineral Technology Center for Pyrometallurgy at the University of Missouri at Rolla as a part of the FREED database. FREED is a thermodynamic database program for storing, retrieving, editing, and manipulating thermodynamic data on a computer. FREED was developed with support from the U.S. Department of Interior's Mineral Institute Program, administered by the U.S. Bureau of Mines, and the U.S. Department of Energy through the Westinghouse Savannah River Plant.

Table 1. Atomic weights of the elements for 1985.

Element	Symbol	Atomic Weight	Element	Symbol	Atomic Weight
Actinium	Ac	(227)	Sodium	Na	22.98977
Silver	Ag	107.8682	Niobium	Nb	92.90638
Aluminum	Al	26.98154	Neodymium	Nd	144.24
Americium	Am	(243)	Neon	Ne	20.1797
Argon	Ar	39.948	Nickel	Ni	58.69
Arsenic	As	74.92159	Neptunium	Np	(237)
Astatine	At	(210)	Oxygen	O	15.9994
Gold	Au	196.96654	Osmium	Os	190.2
Boron	B	10.811	Phosphorus	P	30.97376
Barium	Ba	137.327	Protactinium	Pa	231.03588
Beryllium	Be	9.01218	Lead	Pb	207.2
Bismuth	Bi	208.98037	Palladium	Pd	106.42
Bromine	Br	79.904	Polonium	Po	(209)
Carbon	C	12.011	Promethium	Pm	(145)
Calcium	Ca	40.078	Praseodymium	Pr	140.90765
Cadmium	Cd	112.411	Platinum	Pt	195.08
Cerium	Ce	140.115	Plutonium	Pu	(244)
Chlorine	Cl	35.4527	Radium	Ra	(266)
Cobalt	Co	58.9332	Rubidium	Rb	85.4678
Chromium	Cr	51.9961	Rhenium	Re	186.207
Cesium	Cs	132.90543	Rhodium	Rh	102.90550
Copper	Cu	63.546	Radon	Rn	(222)
Dysprosium	Dy	162.50	Ruthenium	Ru	101.07
Erbium	Er	167.26	Sulfur	S	32.066
Europium	Eu	151.965	Antimony	Sb	121.75
Fluorine	F	18.99840	Scandium	Sc	44.95591
Iron	Fe	55.847	Selenium	Se	78.96
Francium	Fr	(223)	Silicon	Si	28.0855
Gallium	Ga	69.723	Samarium	Sm	150.36
Gadolinium	Gd	157.25	Tin	Sn	118.710
Germanium	Ge	72.61	Strontium	Sr	87.62
Hydrogen	H	1.00794	Tantalum	Ta	180.9479
Helium	He	4.00260	Terbium	Tb	158.92534
Hafnium	Hf	178.49	Technetium	Tc	(98)
Mercury	Hg	200.59	Tellurium	Te	127.60
Holmium	Ho	164.93032	Thorium	Th	232.0381
Iodine	I	126.90447	Titanium	Ti	47.88
Indium	In	114.82	Thallium	Tl	204.3833
Iridium	Ir	192.22	Thulium	Tm	168.93421
Potassium	K	39.0983	Uranium	U	238.0289
Krypton	Kr	83.80	Vanadium	V	50.9415
Lanthanum	La	138.9055	Tungsten	W	183.85
Lithium	Li	6.941	Xenon	Xe	131.29
Lutetium	Lu	174.967	Yttrium	Y	88.90585
Magnesium	Mg	24.3050	Ytterbium	Yb	173.04
Manganese	Mn	54.93805	Zinc	Zn	65.39
Molybdenum	Mo	95.94	Zirconium	Zr	91.224
Nitrogen	N	14.00674			

ELEMENTS

5

THERMODYNAMIC PROPERTIES OF ELEMENTS IN THEIR REFERENCE STATE AT 298.15 K

NAME AND FORMULA	WEIGHT g	ENTROPY	VOLUME	ENTHALPY	FREE ENERGY	LOG(K)	REFERENCES		
		S° $J \cdot mol^{-1} \cdot K^{-1}$	V° cm^3	$\Delta_f H^\circ$ $kJ \cdot mol^{-1}$	$\Delta_f G^\circ$ $kJ \cdot mol^{-1}$		S	H/G	C
SILVER (REFERENCE STATE) Ag	107.868	42.55 0.21	10.272 0.002	0.0	0.0	0.00	85		85
Ag ⁺ (AQUEOUS ION) STD. STATE, m = 1	107.868	73.45 0.40		105.8 0.1	77.1 0.1	-13.50 0.02	85		85
ALUMINUM (REFERENCE STATE) Al	26.982	28.30 0.08	9.999 0.001	0.0	0.0	0.00	67 92		92 67
Al ³⁺ (AQUEOUS ION) STD. STATE, m = 1	26.982	-332 10		-538.4 1.5	-489.4 1.4	86.11 0.79	85 170		85 330
ARSENIC (REFERENCE STATE) As	74.922	35.69 0.84	12.963 0.020	0.0	0.0	0.00	361		361
GOLD (REFERENCE STATE) Au	196.967	47.49 0.21	10.215 0.002	0.0	0.0	0.00	361		
BORON (REFERENCE STATE) B	10.811	5.83 0.08	4.386 0.007	0.0	0.0	0.00	67 85		67 85
BARIUM (REFERENCE STATE) Ba	137.327	62.42 0.84	38.21 0.02	0.0	0.0	0.00	361		361
Ba ²⁺ (AQUEOUS ION) STD. STATE, m = 1	137.327	8.40 0.50		-532.5 1.0	-555.4 1.0	97.30 0.18	54		54
BERYLLIUM (REFERENCE STATE) Be	9.012	9.50 0.08	4.880 0.002	0.0	0.0	0.00	85 67		85 67
BISMUTH (REFERENCE STATE) Bi	208.980	56.74 0.42	21.31 0.01	0.0	0.0	0.00	361		361 127
BROMINE (REFERENCE STATE) Br ₂ (LIQUID)	159.808	152.20 0.30	54.58 0.20	0.0	0.0	0.00	85		67
BROMINE (IDEAL GAS) Br ₂	159.808	245.47 0.05	24789.7 0.2	30.9 0.1	3.1 0.3	-0.55 0.05	85		85 67
Br ⁻ (AQUEOUS ION) STD. STATE, m = 1	79.904	82.55 0.20		-121.4 0.2	-103.8 0.2	18.18 0.04	85		85
GRAPHITE (REFERENCE STATE) C	12.011	5.74 0.10	5.298 0.001	0.0	0.0	0.00	85		85
DIAMOND C	12.011	2.38 0.20	3.417 0.001	1.9 0.0	2.9 0.1	-0.51 0.02	419	419	419

THERMODYNAMIC PROPERTIES OF ELEMENTS IN THEIR REFERENCE STATE AT 298.15 K

NAME AND FORMULA	WEIGHT g	ENTROPY	VOLUME	ENTHALPY	FREE ENERGY	LOG(K)	REFERENCES		
		S° $J \cdot mol^{-1} \cdot K^{-1}$	V° cm^3	$\Delta_f H^\circ$ $kJ \cdot mol^{-1}$	$\Delta_f G^\circ$ $kJ \cdot mol^{-1}$		S	H/G	C
CALCIUM (REFERENCE STATE) Ca	40.078	42.90 0.10	26.19 0.04	0.0	0.0	0.00	360		117
Ca^{2+} (AQUEOUS ION) STD. STATE, $m = 1$	40.078	-56.2 1.0		-543.0 1.0	-553.6	96.99	85	85	419
CADMIUM (REFERENCE STATE) Cd	112.411	51.80 0.15	13.005 0.003	0.0	0.0	0.00	85		85
Cd^{2+} (AQUEOUS ION) STD. STATE, $m = 1$	112.411	-72.8 1.5		-75.9 0.6	-77.6 0.6	-13.59 0.11	85	85	
CERIUM (REFERENCE STATE) Ce	140.115	72.0 4.0	20.77 0.02	0.0	0.0	0.00	419		361
CHLORINE (REFERENCE STATE) Cl_2 (IDEAL GAS)	70.905	223.08 0.01	24789.7 0.2	0.0	0.0	0.00	67 85		67 85
Cl^- (AQUEOUS ION) STD. STATE, $m = 1$	35.453	56.60 0.20		-167.1 0.1	-131.2 0.1	22.99	85	85	
COBALT (REFERENCE STATE) Co	58.933	30.04 0.42	6.670 0.002	0.0	0.0	0.00	361		361
CHROMIUM (REFERENCE STATE) Cr	51.996	23.62 0.21	7.231 0.001	0.0	0.0	0.00	67		67
CESIUM (REFERENCE STATE) Cs	132.905	85.23 0.40	69.73 0.40	0.0	0.0	0.00	85		
Cs^+ (AQUEOUS ION) STD. STATE, $m = 1$	132.905	132.1 0.5		-258.0 0.5	-291.5 1.0	51.07 0.18	85	85	
COPPER (REFERENCE STATE) Cu	63.546	33.14 0.03	7.113 0.003	0.0	0.0	0.00	365		443 67
Cu^+ (AQUEOUS ION) STD. STATE, $m = 1$	63.546	40.60 0.40		71.7 0.1	50.0 0.1	-8.76 0.02	419	419	
Cu^{2+} (AQUEOUS ION) STD. STATE, $m = 1$	63.546	-98.0 4.0		64.9 1.0	65.1 0.1	-11.40 0.02	85	85	
FLUORINE (REFERENCE STATE) F_2 (IDEAL GAS)	37.997	202.79 0.02	24789.7 0.2	0.0	0.0	0.00	67 85		67 85
F^- (AQUEOUS ION) STD. STATE, $m = 1$	18.998	-13.8 0.8		-335.4 0.7	-281.5 0.7	49.32 0.12	85	85	

ELEMENTS

7

THERMODYNAMIC PROPERTIES OF ELEMENTS IN THEIR REFERENCE STATE AT 298.15 K

NAME AND FORMULA	WEIGHT g	ENTROPY	VOLUME	ENTHALPY	FREE ENERGY	LOG(K)	REFERENCES		
		S° J·mol ⁻¹ ·K ⁻¹	V° cm ³	Δ _f H° kJ·mol ⁻¹	Δ _f G° kJ·mol ⁻¹		S	H/G	C
IRON (REFERENCE STATE)	55.847	27.09	7.092	0.0	0.0	0.00	90		90
Fe		0.13	0.004				67		67
Fe ²⁺ (AQUEOUS ION)	55.847	-107.1		-91.1	-90.0	15.77	411	411	
STD. STATE, m = 1		2.0		3.0	2.0	0.35			
Fe ³⁺ (AQUEOUS ION)	55.847	-280.0		-49.9	-16.7	2.93	411	411	
STD. STATE, m = 1		13.0		5.0	2.0	0.35			
GERMANIUM (REFERENCE STATE)	72.61	31.09	13.630	0.0	0.0	0.00	85		361
Ge		0.15	0.005						
HYDROGEN (REFERENCE STATE)	2.016	130.68	24789.7	0.0	0.0	0.00	67		67
H ₂ (IDEAL GAS)		0.02	0.2				85		85
H ⁺ (AQUEOUS ION)	1.008	0.00	0	0.0	0.0	0.00			
STD. STATE, m = 1									
MERCURY (REFERENCE STATE)	200.59	75.90	14.822	0.0	0.0	0.00	85		361
Hg (LIQUID)		0.12	0.002						
Hg ²⁺ (AQUEOUS ION)	200.59	-36.2		170.2	163.5	-28.64	85	85	
STD. STATE, m = 1		0.8		0.2	0.2	0.04			
Hg ₂ ²⁺ (AQUEOUS ION)	401.18	65.74		166.9	153.6	-26.91	85	85	
STD. STATE, m = 1		0.80		0.5	0.5	0.09			
IODINE (REFERENCE STATE)	253.809	116.14	51.29	0.0	0.0	0.00	85	67	67
I ₂		0.30	0.06						
IODINE (IDEAL GAS)	253.809	260.69	24789.7	62.4	19.3	-3.39	67		67
I ₂		0.02	0.2	0.1	0.1	0.01			
I ⁻ (AQUEOUS ION)	126.904	106.45		-56.8	-51.7	9.06	85	85	
STD. STATE, m = 1		0.30		0.1	0.1	0.02			
POTASSIUM (REFERENCE STATE)	39.098	64.67	45.36	0.0	0.0	0.00	85		85
K		0.20	0.09				67		67
K ⁺ (AQUEOUS ION)	39.098	101.20		-252.1	-282.5	49.48	85	85	
STD. STATE, m = 1		0.20		0.1	0.1	0.01			
LITHIUM (REFERENCE STATE)	6.941	29.09	13.017	0.0	0.0	0.00	67		67
Li		0.20	0.007						85
Li ⁺ (AQUEOUS ION)	6.941	12.24		-278.5	-292.9	51.31	85	85	
STD. STATE, m = 1		0.15		0.1	0.1	0.01			

THERMODYNAMIC PROPERTIES OF ELEMENTS IN THEIR REFERENCE STATE AT 298.15 K

NAME AND FORMULA	WEIGHT g	ENTROPY	VOLUME	ENTHALPY	FREE ENERGY	LOG(K)	REFERENCES		
		S° J·mol ⁻¹ ·K ⁻¹	V° cm ³	$\Delta_f H^\circ$ kJ·mol ⁻¹	$\Delta_f G^\circ$ kJ·mol ⁻¹		S	H/G	C
MAGNESIUM (REFERENCE STATE) Mg	24.305	32.67 0.10	13.996 0.007	0.0	0.0	0.00	85		85
Mg ²⁺ (AQUEOUS ION) STD. STATE, m = 1	24.305	-137.0 4.0		-467.0 0.6	-455.4 0.6	79.78 0.11	85		85
MANGANESE (REFERENCE STATE) Mn	54.938	32.01 0.08	7.354 0.007	0.0	0.0	0.00	91		91
Mn ²⁺ (AQUEOUS ION) STD. STATE, m = 1	54.938	-73.60 1.00		-220.8 0.5	-228.1 0.5	39.96 0.09	419		419
MOLYBDENUM (REFERENCE STATE) Mo	95.94	28.66 0.21	9.387 0.005	0.0	0.0	0.00	91		91
NITROGEN (REFERENCE STATE) N ₂	28.013	191.61 0.02	24789.7 0.2	0.0	0.0	0.00	67 85		67 85
SODIUM (REFERENCE STATE) Na	22.990	51.46 0.20	23.81 0.01	0.0	0.0	0.00	67 85		67 85
Na ⁺ (AQUEOUS ION) STD. STATE, m = 1	22.990	58.45 0.15		-240.3 0.1	-261.5 0.1	45.81 0.01	85		85
NICKEL (REFERENCE STATE) Ni	58.69	29.87 0.08	6.588 0.003	0.0	0.0	0.00	67		67
Ni ²⁺ (AQUEOUS ION) STD. STATE, m = 1	58.69	-128.9 2.0		-54.0 0.9	-45.6 0.9	7.99 0.15	419		419
OXYGEN (REFERENCE STATE) O ₂ (IDEAL GAS)	31.999	205.15 0.02	24789.7 0.2	0.0	0.0	0.00	67 85		67 85
PHOSPHORUS (REFERENCE STATE) P (WHITE)	30.974	41.09 0.25	17.3 0.3	0.0	0.0	0.00	85		85
LEAD (REFERENCE STATE) Pb	207.2	64.8 0.5	18.267 0.006	0.0	0.0	0.00	67		67
Pb ²⁺ (AQUEOUS ION) STD. STATE, m = 1	207.2	18.5 1.0		0.9 0.3	-24.2 0.2	4.24 0.04	85		85
PLATINUM (REFERENCE STATE) Pt	195.08	41.63 0.21	9.091 0.004	0.0	0.0	0.00	361		361
SULFUR (REFERENCE STATE) S ORTHORHOMBIC	32.066	32.05 0.05	15.511 0.005	0.0	0.0	0.00	67 85		67 85

THERMODYNAMIC PROPERTIES OF ELEMENTS IN THEIR REFERENCE STATE AT 298.15 K

NAME AND FORMULA	WEIGHT g	ENTROPY	VOLUME	ENTHALPY	FREE ENERGY	LOG(K)	REFERENCES		
		S° $J \cdot mol^{-1} \cdot K^{-1}$	V° cm^3	$\Delta_f H^\circ$ $kJ \cdot mol^{-1}$	$\Delta_f G^\circ$ $kJ \cdot mol^{-1}$		S	H/G	C
SULFUR	32.066	33.03		0.3	0.0	0.00	67	419	67
S MONOCLINIC		0.05		0.1					
S^{2-} (AQUEOUS ION)	32.066	-14.6		33.1	85.8	-15.03	419	419	
STD. STATE, $m = 1$		1.0		1.0	1.0	0.18			
DIATOMIC SULFUR	64.132	228.17	24789.7	128.6	79.7	-13.96	67	67	67
S_2 (IDEAL GAS)		0.02	0.2	0.3	0.3	0.05			
ANTIMONY (REFERENCE STATE)	121.75	45.52	18.178	0.0	0.0	0.00	361		361
Sb		0.21	0.009						
SELENIUM (REFERENCE STATE)	78.96	42.27	16.42	0.0	0.0	0.00	62		126
Se		0.05	0.01						
SILICON (REFERENCE STATE)	28.086	18.81	12.056	0.0	0.0	0.00	67		67
Si		0.08	0.002				85		
$H_4SiO_4^\circ$ (AQUEOUS ION)	96.115	180.0		-1460.0	-1307.5	229.12		179	422
STD. STATE, $m = 1$		4.2		1.7	2.1	0.37		285	414
TIN (REFERENCE STATE)	118.710	51.18	16.29	0.0	0.0	0.00	85		85
Sn (WHITE, TET.)		0.08	0.01						
STRONTIUM (REFERENCE STATE)	87.62	55.69	33.92	0.0	0.0	0.00	39		67
Sr		0.20	0.02						
Sr^{2+} (AQUEOUS ION)	87.62	-31.5		-550.9	-563.8	98.78	55	55	
STD. STATE, $m = 1$		2.0		0.5	0.8	0.14			
TELLURIUM (REFERENCE STATE)	127.60	49.71	20.48	0.0	0.0	0.00	361		361
Te		0.20	0.01						
THORIUM (REFERENCE STATE)	232.038	51.83	19.79	0.0	0.0	0.00	319		319
Th		0.50	0.01						
TITANIUM (REFERENCE STATE)	47.88	30.76	10.63	0.0	0.0	0.00	67		67
Ti		0.10	0.01						
URANIUM (REFERENCE STATE)	238.029	50.2	12.50	0.0	0.0	0.00	85		85
U		0.2	0.02						
VANADIUM (REFERENCE STATE)	50.942	28.94	8.350	0.0	0.0	0.00	67		67
V		0.42	0.004						
TUNGSTEN (REFERENCE STATE)	183.85	32.65	9.545	0.0	0.0	0.00	67		67
W		0.10	0.004						

THERMODYNAMIC PROPERTIES OF ELEMENTS IN THEIR REFERENCE STATE AT 298.15 K

NAME AND FORMULA	WEIGHT g	ENTROPY	VOLUME	ENTHALPY	FREE ENERGY	LOG(K)	REFERENCES		
		S° $J \cdot mol^{-1} \cdot K^{-1}$	V° cm^3	$\Delta_f H^\circ$ $kJ \cdot mol^{-1}$	$\Delta_f G^\circ$ $kJ \cdot mol^{-1}$		S	H/G	C
ZINC (REFERENCE STATE) Zn	65.39	41.63 0.15	9.162 0.007	0.0	0.0	0.00	67		67
Zn ²⁺ (AQUEOUS ION) STD. STATE, m = 1	65.39	-109.8 0.5		-153.4 0.2	-147.3 0.2	25.79 0.04	85	85	
ZIRCONIUM (REFERENCE STATE) Zr	91.224	38.87 0.20	14.016 0.007	0.0	0.0	0.00	67		67
METHANE (IDEAL GAS) CH ₄	16.043	186.26 0.21	24789.7 0.2	-74.8 0.3	-50.7 0.4	8.88 0.07	419 67	419 67	67
COHENITE Fe ₃ C	179.552	104.4 3.4	23.23 0.01	24.9 1.3	19.7 1.7	-3.45 0.30	361	361	361
AMMONIA (IDEAL GAS) NH ₃	17.031	192.77 0.03	24789.7 0.2	-45.9 0.4	-16.4 0.4	2.87 0.06	67	67	67
NH ₄ ⁺ (AQUEOUS ION) STD. STATE, m = 1	18.039	111.17 0.40		-133.3 0.3	-79.4 0.3	13.91 0.05	85	85	

THERMODYNAMIC PROPERTIES OF SULFIDE MINERALS AT 298.15 K

NAME AND FORMULA	WEIGHT g	ENTROPY	VOLUME	ENTHALPY	FREE ENERGY	LOG(K)	REFERENCES		
		S° J·mol ⁻¹ ·K ⁻¹	V° cm ³	Δ _f H° kJ·mol ⁻¹	Δ _f G° kJ·mol ⁻¹		S	H/G	C
ACANTHITE (ARGENTITE) Ag ₂ S	247.802	142.9 0.3	34.19 0.04	-32.0 1.0	-39.7 1.0	6.96 0.18	141	121	141 306
REALGAR AsS	106.988	63.5 0.6	29.80 0.24	-30.9 5.0	-29.6 5.0	5.19 0.88	429	419	270
ORPIENT As ₂ S ₃	246.041	163.6 1.6	70.51 0.25	-91.6 4.2	-90.4 4.2	15.84 0.74	372	50	210
BISMUTHINITE Bi ₂ S ₃	514.159	200.4 3.3	75.52 0.04	-135.2 2.4	-132.4 2.6	23.20 0.46	372	52	
TELLUROBISMUTHITE Bi ₂ Te ₃	800.761	261.1 5.0	101.85 0.09	-78.7 2.1	-78.2 2.6	13.71 0.46	201	279	
OLDHAMITE CaS	72.144	56.7 1.3	27.72 0.09	-474.9 2.1	-469.5 2.1	82.25 0.37	67	67	279
GREENOCKITE CdS	144.477	72.2 0.3	29.93 0.02	-149.6 1.3	-146.1 1.3	25.60 0.23	38	3	38
CATTIERITE CoS ₂	123.065	74.8 0.2	25.52 0.01	-150.9 4.9	-145.1 4.9	25.42 0.86	399	60	326 376
LINNAEITE Co ₃ S ₄	305.064	176.0 0.4	62.55 0.02	-347.5 7.3	-334.9 7.3	58.66 1.28	399	60	98
COVELLITE CuS	95.612	67.4 0.1	20.42 0.02	-54.6 0.3	-55.3 0.3	9.69 0.05	109	337	109 442
ANILITE Cu _{1.75} S	143.272	107.5 0.2	25.79 0.02	-73.3 0.3	-78.5 0.3	13.76 0.05	133	337	133 140
DIGENITE Cu _{1.80} S	146.449	109.6 0.2	25.63 0.05	-73.0 0.5	-78.3 0.5	13.72 0.09	133	337	133
DJURLEITE Cu _{1.95} S	155.981	114.8 0.2	26.89 0.02	-78.8 0.4	-84.2 0.4	14.75 0.07	394	337	394
CHALCOCITE Cu ₂ S	159.158	116.2 0.2	27.48 0.02	-83.9 1.1	-89.2 1.1	15.62 0.19	142	369	109 48 142
CHALCOPYRITE CuFeS ₂	183.525	124.9 0.2	43.92 0.02	-194.9 1.6	-195.1 1.6	34.18 0.28	371	369	325 371 369
BORNITE Cu ₅ FeS ₄	501.841	398.5 0.8	98.73 0.05	-371.6 2.1	-394.7 2.1	69.32 0.37	369	369	325 369

THERMODYNAMIC PROPERTIES OF SULFIDE MINERALS AT 298.15 K

NAME AND FORMULA	WEIGHT g	ENTROPY	VOLUME	ENTHALPY	FREE ENERGY	LOG(K)	REFERENCES		
		S° $J \cdot mol^{-1} \cdot K^{-1}$	V° cm^3	$\Delta_f H^\circ$ $kJ \cdot mol^{-1}$	$\Delta_f G^\circ$ $kJ \cdot mol^{-1}$		S	H/G	C
CUBANITE $CuFe_2S_3$	271.438	205.0 0.8	67.44 0.06				388		280
NUKUNDAMITE $Cu_{5.5}FeS_{6.5}$	613.779		278.0 0.5		-564.5 3.4	98.90 0.59			369
TROILITE FeS	87.913	60.3 0.2	18.20 0.03	-101.0 1.5	-101.3 1.5	17.75 0.26	143 347	69 3	79 131
PYRRHOTITE $Fe_{.875}S$	80.932	60.7 0.2	17.49 0.05	-97.5 2.0	-98.9 2.0	17.33 0.35	143	131	131
PYRRHOTITE $Fe_{.90}S$	82.328	63.2 0.1	16.88 0.10	-97.6 2.0	-99.6 2.0	14.45 0.35	135	375	135
PYRITE FeS_2	119.979	52.9 0.1	23.94 0.01	-171.5 1.7	-160.1 1.7	28.05 0.30	138	409 67	79
MARCASITE FeS_2	119.979	53.9 0.1	24.58 0.02	-169.5 2.1	-158.4 2.1	27.75 0.37	139	139	139
LOELLINGITE $FeAs_2$	205.690	80.1 0.7	27.51 0.02	-57.8 5.0	-52.3 5.0	9.17 0.88	332		25
FERROSELITE $FeSe_2$	213.767	86.9 0.3	29.96 0.05						138
FROHBERGITE $FeTe_2$	311.047	100.2 0.2	38.43 0.05	-72.4 4.2	-64.6 4.2	11.31 0.74	437		279
HYDROGEN SULFIDE (IDEAL GAS) H_2S	34.082	205.8 0.2	24789.70 0.20	-20.6 0.6	-33.4 0.6	5.86 0.11	85 67	85 67	85 67
HS^- (AQUEOUS ION) STD. STATE, $m = 1$	33.074	67.0 0.9		16.3 0.2	44.8 0.3	-7.86 0.05	85		85
CINNABAR HgS	232.656	82.5 2.1	28.42 0.02	-54.3 2.1	-40.7 2.7	7.13 0.47	233		326 279
METACINNABAR HgS	232.656	96.2 4.2	30.17 0.02	-46.7 1.5	-43.3 0.8	7.59 0.15	217		120
NININGERITE MgS	56.371	50.3 0.4	21.17 0.02	-345.7 4.2	-341.4 4.2	59.81 0.74	67		67 67
ALABANDITE MnS	87.004	80.3 0.8	21.46 0.01	-213.9 0.8	-218.7 0.9	38.31 0.17	279		3 79 203

THERMODYNAMIC PROPERTIES OF SULFIDE MINERALS AT 298.15 K

NAME AND FORMULA	WEIGHT g	ENTROPY	VOLUME	ENTHALPY	FREE ENERGY	LOG(K)	REFERENCES		
		S° J·mol ⁻¹ ·K ⁻¹	V° cm ³	Δ _r H° kJ·mol ⁻¹	Δ _r G° kJ·mol ⁻¹		S	N/G	C
HAUERITE MnS ₂	119.070	99.9 0.1	34.20 0.01	-223.8 10.0	-224.6 10.0	39.35 1.75	441	279	
MOLYBDENITE MoS ₂	160.072	62.6 0.2	32.02 0.02	-271.8 4.9	-262.8 4.9	46.04 0.86	275	305	114
MILLERITE NiS	90.756	53.0 0.4	16.89 0.01	-91.0 3.0	-63.9 3.0	14.97 0.53	429	58	271 271
HEAZLEWOODITE Ni ₃ S ₂	240.202	133.2 0.3	40.95 0.02	-216.3 3.0	-210.2 3.0	36.83 0.53	395	58	107 67 276
PENTLANDITE Ni _{4.5} Fe _{4.5} S ₈	771.944		155.40 0.20	-837.4 14.6					59
VIOLARITE (Ni _{0.7} Fe _{0.3}) ₃ S ₄	301.775		63.80 0.30	-378 11.8					59
GALENA PbS	239.266	91.7 0.7	31.49 0.01	-98.3 2.0	-96.8 2.0	16.96 0.35	67	397	67 326 245 326
CLAUSTHALITE PbSe	286.160	102.5 2.1	34.61 0.01	-100.1 2.3	-98.7 2.1	17.30 0.37	279	279	
ALTAITE PbTe	334.800	110.0 2.1	40.60 0.01	-70.7 1.4	-69.4 1.5	12.15 0.27	217	419	
COOPERITE PtS	227.146	55.1 0.1	22.15 0.01	-82.4 3.4	-76.9 3.4	13.46 0.59	136	136	
STIBNITE Sb ₂ S ₃	339.698	182.0 3.3	73.41 0.04	-151.4 2.3	-149.9 2.1	26.26 0.37	234	382	211 53 51
HERZENBERGITE SnS	150.776	77.0 0.8	29.01 0.02	-106.5 1.5	-104.6 1.5	18.33 0.26	229	347	315
BERNDTITE SnS ₂	182.842	87.5 0.2	40.96 0.02	-149.8 5.0	-141.5 5.0	24.79 0.88	229	326	315
TUNGSTENITE WS ₂	247.982	67.8 0.3	32.07 0.02	-241.6 2.5	-233.0 2.5	40.82 0.44	304	303	304 304
SPHALERITE ZnS	97.456	58.7 0.2	23.83 0.01	-204.1 1.5	-199.6 1.5	34.97 0.26	398	378	324
WURTZITE ZnS	97.456	58.8 0.2	23.85 0.01	-203.8 1.5	-199.3 1.5	34.92 0.26	398	338	324

THERMODYNAMIC PROPERTIES OF SULFIDE MINERALS AT 298.15 K

NAME AND FORMULA	WEIGHT g	ENTROPY	VOLUME	ENTHALPY	FREE ENERGY	LOG(K)	REFERENCES		
		S° $J \cdot mol^{-1} \cdot K^{-1}$	V° cm^3	$\Delta_f H^\circ$ $kJ \cdot mol^{-1}$	$\Delta_f G^\circ$ $kJ \cdot mol^{-1}$		S	H/G	C
PROUSTITE Ag_3AsS_3	494.724	303.7 0.5	88.42 0.02				146		
SMITHITE $AgAsS_2$	246.922	150.5 0.2	50.12 0.30				146		
ENARGITE Cu_3AsS_4	393.824	257.6 0.6	88.24 0.12				381		
ARSENOPYRITE $FeAs_{1.08}S_{0.92}$	166.263	68.8 0.4	26.42 0.07				331		
LIVINGSTONITE $HgSb_4S_8$	944.118	470.5 1.5	192.90	-373.2 6.5	-360.2 6.5	63.10 1.14	145	454	
BERTHIERITE $FeSb_2S_4$	427.611	245.0 1.0	92.22 0.20	-256.2 6.5	-255.8 6.5	44.82 1.14	97	382	382
CHALCOSTIBITE $CuSbS_2$	249.428	149.2 3.8	50.06 0.10	-130.8 4.4	-132.7 4.2	23.25 0.74	382	382	382
Fe-TENNANTITE $Cu_{10}Fe_2As_4S_{13}$	1463.698	1024.2	332.10				380		
Fe-TETRAHEDRITE $Cu_{10}Fe_2Sb_4S_{13}$	1651.012	1061.0	336.70				380		
Zn-TENNANTITE $Cu_{10}Zn_2As_4S_{13}$	1482.784	1025.6	332.10				380		
Zn-TETRAHEDRITE $Cu_{10}Zn_2Sb_4S_{13}$	1670.098	1062.4	336.70				380		
PYRARGYRITE Ag_3SbS_3	541.553		92.56 0.04	-131.5 3					51
MIARGYRITE $\alpha\text{-}AgSbS_2$	293.750		52.03 0.09	-95.8 2.6					51
MATILDITE $\beta\text{-}AgBiS_2$	380.980		54.44 0.10	-165.3 8					52

THERMODYNAMIC PROPERTIES OF OXIDE AND HYDROXIDE MINERALS AT 298.15 K

NAME AND FORMULA	WEIGHT g	ENTROPY	VOLUME	ENTHALPY	FREE ENERGY	LOG(K)	REFERENCES		
		S° J·mol ⁻¹ ·K ⁻¹	V° cm ³	Δ _f H° kJ·mol ⁻¹	Δ _f G° kJ·mol ⁻¹		S	H/G	C
CORUNDUM Al ₂ O ₃	101.961	50.9 0.1	25.58 0.01	-1675.7 1.3	-1582.3 1.3	277.20 0.23	93 94	268 85	94 57
BOEHMITE AlO(OH)	59.988	37.2 0.1	19.54 0.03	-996.4 2.2	-918.4 2.2	160.90 0.39	176	176 12	
DIASPORE AlO(OH)	59.988	35.3 0.2	17.76 0.03	-1001.3 2.2	-922.7 2.1	161.53 0.88	334 230	12 176	
GIBBSITE Al(OH) ₃	78.004	68.4 0.1	31.96 0.02	-1293.1 1.2	-1154.9 1.2	202.33 0.21	178	171 212	178
ARSENOLITE As ₂ O ₃	197.841	107.4 0.1	51.12 0.07	-657.0 1.7	-576.0 1.9	100.90 0.33	61	419	
CLAUDETITE As ₂ O ₃	197.841	113.3 0.1	47.26 0.03	-654.8 1.7	-575.6 1.1	100.83 0.18	61		
DIBORON TRIOXIDE B ₂ O ₃	69.620	54.0 0.3	27.26 0.06	-1273.5 1.4	-1194.4 1.4	209.24 0.25	85	85 67	67
BARIUM MONOXIDE BaO	153.326	72.1 0.4	25.59 0.01	-548.1 2.1	-520.4 2.1	91.17 0.37	85	77 111	85 262
BROMELLITE BeO	25.012	13.8 0.1	8.31 0.03	-609.4 2.5	-580.1 2.5	101.63 0.44	85	85	67 418
BISMITE Bi ₂ O ₃	465.959	151.5 2.1	49.73 0.06	-573.9 1.3	-493.5 1.5	86.45 0.26	419	419 269	319
CARBON MONOXIDE CO (IDEAL GAS)	28.010	197.3 0.0	24789.70 0.20	-110.5 0.2	-137.1 0.2	24.01 0.03	67 117	67 117	67 117
CARBON DIOXIDE CO ₂ (IDEAL GAS)	44.010	213.8 0.0	24789.70 0.20	-393.5 0.1	-394.4 0.2	69.09 0.03	67 117	67 117	67 117
CO ₃ ²⁻ (AQUEOUS ION) STD. STATE, m = 1	60.009	-50.0 1.0		-675.2 0.1	-527.0 0.3	92.33 0.05	85 36	85 36	
HCO ₃ ⁻ (AQUEOUS ION) STD. STATE, m = 1	61.017	98.4 0.5		-689.9 0.2	-586.8 0.3	102.81 0.04	85 36	85 36	
H ₂ CO ₃ (UN-IONIZED) STD. STATE, m = 1	62.025	184.7 0.9		-699.7 0.1	-623.2 0.1	109.17 0.02	419	419	
LIME CaO	56.077	38.1 0.4	16.76 0.01	-635.1 0.9	-603.1 0.9	105.66 0.16	67 117	67 117	67 117

THERMODYNAMIC PROPERTIES OF OXIDE AND HYDROXIDE MINERALS AT 298.15 K

NAME AND FORMULA	WEIGHT g	ENTROPY	VOLUME	ENTHALPY	FREE ENERGY	LOG(K)	REFERENCES		
		S° $J \cdot mol^{-1} \cdot K^{-1}$	V° cm^3	$\Delta_f H^\circ$ $kJ \cdot mol^{-1}$	$\Delta_f G^\circ$ $kJ \cdot mol^{-1}$		S	H/G	C
PORTLANDITE $Ca(OH)_2$	74.093	83.4 0.4	33.06 0.02	-986.1 1.3	-898.0 1.3	157.33 0.23	67 158	67 158	67 117
MONTEPONITE CdO	128.400	54.8 1.5	15.59 0.01	-258.4 0.4	-228.7 0.6	40.07 0.11	85	85	267
CERIANITE CeO_2	172.114	62.3 0.1	23.85 0.03	-1088.7 1.5	-1025.4 1.9	179.64 0.34	436	14	227
COBALT MONOXIDE CoO	74.933	52.8 0.3	11.64 0.02	-237.9 1.3	-214.1 1.3	37.52 0.23	287	308	319 125
TRICOBALT TETRAOXIDE Co_3O_4	240.797	109.3 0.3	39.77 0.02	-918.8 2.0	-802.2 2.0	140.54 0.35	222	319	319 307
ESKOLAITE Cr_2O_3	151.990	81.2 1.3	29.09 0.03	-1134.7 8.4	-1053.1 8.4	184.49 1.47	67	67	67 267
DICESIUM MONOXIDE Cs_2O	281.810	146.9 0.4	59.62 0.07	-346.0 1.2	-308.4 1.2	54.02 0.21	112	384	112
TENORITE CuO	79.545	42.6 0.2	12.22 0.03	-156.1 2.0	-128.3 2.0	22.48 0.35	67	67	272 272
CUPRITE Cu_2O	143.091	92.4 0.3	23.44 0.02	-170.6 0.1	-147.8 0.1	25.89 0.02	67	190	272 67
MUSTITE $Fe_{.947}O$	68.887	56.6 0.4	12.04 0.04	-266.3 0.8	-244.9 0.8	42.91 0.14	67	198	83 67
FERROUS OXIDE (STOICHIOMETRIC) FeO	71.846	60.6 1.7	12.00 0.05	-272.0 2.1	-251.4 2.2	44.05 0.38	67	67	67 132
HEMATITE Fe_2O_3	159.692	87.4 0.2	30.27 0.01	-826.2 1.3	-744.4 1.3	130.41 0.23	137	161	83 130
MAGNETITE Fe_3O_4	231.539	146.1 0.4	44.52 0.01	-1115.7 2.1	-1012.7 2.1	177.42 0.37	440	161	161 134
GOETHITE $FeO(OH)$	88.854	60.4 0.6	20.82 0.04	-562.6 2.1	-491.8 2.1	86.16 0.12	235	221	18
WATER H_2O (LIQUID)	18.015	70.0 0.1	18.07 0.00	-285.8 0.1	-237.1 0.1	41.55 0.01	85	85	117 67
OH^- (AQUEOUS ION) STD. STATE, $m = 1$	17.007	-10.7 0.2		-230.0 0.1	-157.3 0.1	27.56 0.02	85	85	

THERMODYNAMIC PROPERTIES OF OXIDE AND HYDROXIDE MINERALS AT 298.15 K

NAME AND FORMULA	WEIGHT g	ENTROPY	VOLUME	ENTHALPY	FREE ENERGY	LOG(K)	REFERENCES		
		S° $J \cdot mol^{-1} \cdot K^{-1}$	V° cm^3	$\Delta_f H^\circ$ $kJ \cdot mol^{-1}$	$\Delta_f G^\circ$ $kJ \cdot mol^{-1}$		S	H/G	C
STEAM	18.015	188.8	24789.70	-241.8	-228.6	40.05	85	85	67
H ₂ O (IDEAL GAS)		0.0	0.20	0.0	0.1	0.02			117
HAFNIUM DIOXIDE	210.489	59.3	20.82	-1117.6	-1061.1	185.90	319	256	319
HfO ₂		0.4	0.01	1.3	1.3	0.23		319	
MONTROYDITE	216.589	70.3	19.32	-90.8	-58.5	10.25	85	85	67
HgO		0.3	0.02	0.1	0.1	0.01		415	
DIPOTASSIUM MONOXIDE	94.196	94.1	40.38	-363.2	-322.1	56.43	67	67	67
K ₂ O		6.3	0.20	2.1	2.8	0.49			
POTASSIUM HYDROXIDE	56.106	78.9	27.45	-424.7	-378.9	66.39	67	67	67
KOH		0.8	0.02	0.6	0.6	0.11		254	
DILITHIUM MONOXIDE	29.881	37.6	14.76	-597.9	-561.2	98.31	319	209	319
Li ₂ O		0.3	0.01	2.1	2.1	0.37	419	67	
PERICLASE	40.304	26.9	11.25	-601.6	-569.3	99.74	85	85	418
MgO		0.2	0.00	0.3	0.3	0.05	67	321	117
BRUCITE	58.320	63.2	24.63	-924.5	-833.5	146.02	419	419	228
Mg(OH) ₂		0.1	0.07	0.4	0.4	0.07		193	
MANGANOSITE	70.937	59.7	13.22	-385.2	-362.9	63.58	319	419	391
MnO		0.4	0.00	0.5	0.5	0.09			319
PYROLUSITE	86.937	52.8	16.61	-520.0	-465.0	81.47	357	357	357
MnO ₂		0.1	0.02	0.7	0.7	0.12			
BIXBYITE	157.874	113.7	31.37	-959.0	-882.1	154.53	357	357	357
Mn ₂ O ₃		0.2	0.05	1.0	1.0	0.18			
HAUSMANNITE	228.812	164.1	46.95	-1384.5	-1282.5	224.68	357	357	357
Mn ₃ O ₄		0.2	0.06	1.4	1.4	0.25			
BRAUNITE	604.645	416.4	125.08	-4260.0	-3944.7	691.08	367	367	367
Mn ₇ SiO ₁₂		0.8	0.05	4.0	4.0	0.70			
MOLYBDITE	143.938	77.7	30.56	-745.2	-668.1	117.04	85	85	85
MoO ₃		0.4	0.04	0.4	0.4	0.07			200
NITROGEN DIOXIDE	46.006	240.1	24789.70	33.1	51.2	-8.98	67	67	67
NO ₂ (IDEAL GAS)		0.1	0.20	0.4	0.4	0.07			
NO ₃ ⁻ (AQUEOUS ION)	62.005	146.7		-206.9	-110.8	19.42	85	85	
STD. STATE, $\mu = 1$		0.4		0.4	0.4	0.07			

THERMODYNAMIC PROPERTIES OF OXIDE AND HYDROXIDE MINERALS AT 298.15 K

NAME AND FORMULA	WEIGHT g	ENTROPY	VOLUME	ENTHALPY	FREE ENERGY	LOG(K)	REFERENCES		
		S° J·mol ⁻¹ ·K ⁻¹	V° cm ³	Δ _f H° kJ·mol ⁻¹	Δ _f G° kJ·mol ⁻¹		S	H/G	C
DISODIUM MONOXIDE Na ₂ O	61.979	75.3 0.8	25.88 0.08	-414.8 0.3	-376.0 0.4	65.87 0.07	67	302	67
SODIUM HYDROXIDE NaOH	39.997	64.4 0.8	18.78 0.06	-425.8 0.1	-379.6 0.3	66.50 0.05	67	67	67
BUNSENITE NiO	74.689	38.0 0.2	10.97 0.02	-239.3 0.4	-211.1 0.4	36.99 0.07	271	161	161
PHOSPHORUS PENTOXIDE P ₂ O ₅	141.945	114.4 0.4	59.40 0.20	-1504.9 0.5	-1361.6 0.5	238.54 0.10	319	319	67
PO ₄ ⁻⁻⁻⁻ (AQUEOUS ION) STD. STATE, m = 1	94.971	-222.0 4.2		-1259.6 0.9	-1001.6 0.9	175.47 0.15	419	419	
LITHARGE (RED) PbO	223.199	66.5 0.2	23.91 0.05	-219.0 0.8	-188.9 0.8	33.10 0.14	72	419	319
MASSICOT (YELLOW) PbO	223.199	68.7 0.2	23.15 0.03	-217.3 0.3	-187.9 0.3	32.92 0.06	419	15	319
PLATTNERITE PbO ₂	239.199	71.8 0.4	25.01 0.01	-277.4 2.9	-218.3 2.9	38.25 0.51	319	419	319
MINIUM Pb ₃ O ₄	685.598	212.0 6.7	76.81 0.09	-718.7 6.3	-601.6 6.6	105.40 1.16	67	67	67
SULFUR DIOXIDE SO ₂ (IDEAL GAS)	64.065	248.2 0.1	24789.70 0.20	-296.8 0.2	-300.1 0.2	52.57 0.04	85	85	67
SULFUR TRIOXIDE SO ₃ (IDEAL GAS)	80.064	256.8 0.8	24789.70 0.20	-395.7 0.7	-371.0 0.7	64.99 0.12	419	419	67
SO ₃ ⁻⁻⁻ (AQUEOUS ION) STD. STATE, m = 1	80.064	-29.0 4.2		-635.5 0.9	-486.5 0.9	85.23 0.15	419	419	
SO ₄ ⁻⁻⁻⁻ (AQUEOUS ION) STD. STATE, m = 1	96.064	18.5 0.4		-909.3 0.4	-744.0 0.4	130.34 0.07	85	85	
VALENTINITE Sb ₂ O ₃	291.498	123.0 2.5	50.01 0.05	-708.6 2.9	-626.4 3.0	109.75 0.53	319	419	
SILICON MONOXIDE SiO (IDEAL GAS)	44.085	211.6 0.8	24789.70 0.20	-100.4 8.4	-127.3 8.4	22.30 1.47	67	67	67
QUARTZ SiO ₂	60.084	41.5 0.1	22.69 0.00	-910.7 1.0	-856.3 1.0	150.01 0.18	435	444	160
							317	419	341

THERMODYNAMIC PROPERTIES OF OXIDE AND HYDROXIDE MINERALS AT 298.15 K

NAME AND FORMULA	WEIGHT g	ENTROPY	VOLUME	ENTHALPY	FREE ENERGY	LOG(K)	REFERENCES		
		S° J·mol ⁻¹ ·K ⁻¹	V° cm ³	Δ _f H° kJ·mol ⁻¹	Δ _f G° kJ·mol ⁻¹		S	H/G	C
H ₄ SiO ₄ (UN-IONIZED) STD. STATE, m = 1	96.115	180.0 4.2		-1460.0 1.7	-1307.8 2.1	229.12 0.37	179 285	422 414	
CRISTOBALITE SiO ₂	60.084	43.4 0.1	25.74 0.03	-908.4 2.1	-854.6 2.1	149.71 0.37	435 404	67 341	286 341
TRIDYMITE SiO ₂	60.084	43.9 0.4	26.53 0.20	-907.5 2.4	-853.8 2.4	149.58 0.43	361		286 404
COESITE SiO ₂	60.084	38.5 1.0	20.64 0.01	-907.8 2.1	-852.5 2.1	149.35 0.37	6 189	6	361 423
STISHOVITE SiO ₂	60.084	27.8 0.4	14.01 0.01	-861.3 2.1	-802.8 2.1	140.65 0.37	6 189	189	361
SILICALITE SiO ₂	60.084	46.3 0.2	33.29 0.5	-905.2 0.8	-852.2 0.8	149.30 0.14	213	213	
SILICA GLASS SiO ₂	60.084	48.5 1.0	27.27 0.10	-901.6 2.1	-849.3 2.1	148.79 0.37	341 435	341 444	341
CASSITERITE SnO ₂	150.709	49.0 0.2	21.55 0.03	-577.6 0.2	-515.8 0.2	90.36 0.04	449	85 16	85
STRONTIUM OXIDE SrO	103.619	55.5 0.4	20.69 0.01	-591.3 1.0	-560.7 1.0	98.22 0.18	67	46 77	67 262
TELLURITE TeO ₂	159.599	70.4 0.3	27.75 0.02	-319.7 3.0	-264.8 3.1	46.39 0.54	333	419 78	319
THORIANITE ThO ₂	264.037	65.2 0.2	26.37 0.01	-1226.4 3.5	-1169.2 3.5	204.84 0.61	419	419	417 389
RUTILE TiO ₂	79.879	50.6 0.6	18.82 0.01	-944.0 0.8	-888.8 1.0	155.70 0.14	85 67	85 294	67 85
ANATASE TiO ₂	79.879	49.9 0.3	20.52 0.03	-938.7 2.1	-883.2 2.1	154.74 0.37	67	67 419	294
DITITANIUM TRIOXIDE Ti ₂ O ₃	143.758	77.3 1.0	31.43 0.02	-1520.9 8.4	-1433.9 8.4	251.21 1.47	67	67	67 294
URANINITE UO ₂	270.028	77.0 0.2	24.62 0.01	-1084.9 1.0	-1031.7 1.0	180.75 0.18	199 248	419 248	113 128
KARELIANITE V ₂ O ₃	149.881	98.1 1.3	29.85 0.03	-1218.8 6.3	-1139.0 6.3	199.55 1.11	67	67	76

THERMODYNAMIC PROPERTIES OF MINERALS AND RELATED SUBSTANCES

THERMODYNAMIC PROPERTIES OF OXIDE AND HYDROXIDE MINERALS AT 298.15 K

NAME AND FORMULA	WEIGHT g	ENTROPY	VOLUME	ENTHALPY	FREE ENERGY	LOG(K)	REFERENCES		
		S° $J \cdot mol^{-1} \cdot K^{-1}$	V° cm^3	$\Delta_f H^\circ$ $kJ \cdot mol^{-1}$	$\Delta_f G^\circ$ $kJ \cdot mol^{-1}$		S	H/G	C
TUNGSTEN DIOXIDE WO_2	215.849	50.6 0.3	20.03 0.05	-589.7 0.9	-533.9 0.9	93.53 0.16	67	67	67
TUNGSTEN TRIOXIDE WO_3	231.848	75.9 1.3	31.61 0.10	-842.9 0.8	-764.1 0.9	133.86 0.16	67	67	236
ZINCITE ZnO	81.389	43.2 0.1	14.34 0.01	-350.5 0.3	-320.4 0.3	56.12 0.05	352	85	352 319
BADDELEYITE ZrO_2	123.223	50.4 0.3	21.15 0.01	-1100.6 1.7	-1042.9 1.7	182.70 0.30	319	196	82 419

THERMODYNAMIC PROPERTIES OF MULTIPLE OXIDE MINERALS AT 298.15 K

NAME AND FORMULA	WEIGHT g	ENTROPY	VOLUME	ENTHALPY	FREE ENERGY	LOG(K)	REFERENCES		
		S° J·mol ⁻¹ ·K ⁻¹	V° cm ³	Δ _f H° kJ·mol ⁻¹	Δ _f G° kJ·mol ⁻¹		S	N/G	C
TIALITE Al ₂ TiO ₅	181.840	109.6 0.8	48.75 0.05				361		43
CHRYSOBERYL BeAl ₂ O ₄	126.973	66.3 0.1	34.32 0.02	-2298.5 2.8	-2176.2 2.8	381.3 0.5	116 164	164 164	164
CALCIUM FERRITE CaFe ₂ O ₄	215.770	145.4 0.8	44.98 0.05	-1520.3 0.2	-1412.4 0.2	247.4 0.0	419	419	42
DICALCIUM FERRITE Ca ₂ Fe ₂ O ₅	271.847	188.8 1.3	67.18 0.10	-2138.3 0.9	-1999.9 0.9	350.4 0.2	419	419	42
PEROVSKITE CaTiO ₃	135.956	93.6 0.4	33.63 0.01	-1660.6 1.7	-1574.8 1.8	275.9 0.3	419	419	295
HERCYNITE FeAl ₂ O ₄	173.808	117.0 3.0	40.75 0.05	-1950.5 8.5	-1838.1 10.0	322.0 1.8	373 188	188 450	450
CHROMITE FeCr ₂ O ₄	223.837	146.0 1.7	44.01 0.10	-1445.5 5.0	-1344.5 6.0	235.5 1.1	361	373	292
ILMENITE FeTiO ₃	151.725	108.9 0.3	31.69 0.08	-1232.0 2.5	-1155.5 2.5	202.4 0.4	11	11	11 295
ULVOSPINEL Fe ₂ TiO ₄	223.572	180.40 2.5	46.82 0.05	-1493.8 2.0	-1399.9 2.1	245.3 0.4	216 312	216	43
PSEUDOBROOKITE Fe ₂ TiO ₅	239.571	156.5 1.3	54.53 0.05						43
SPINEL MgAl ₂ O ₄	142.266	88.7 4.0	39.71 0.03	-2299.1 2.0	-2176.6 2.3	381.3 0.4	67 37	67 64	44 386
MAGNESIOCHROMITE MgCr ₂ O ₄	192.295	106.0 0.8	43.56 0.05	-1783.6 0.9	-1669.1 0.9	292.4 0.1	373	373	292
MAGNESIOFERRITE MgFe ₂ O ₄	199.997	121.8 2.0	44.57 0.05	-1441.5 3.0	-1329.6 3.1	232.9 0.5	290	373	42 249
GEIKIELITE MgTiO ₃	120.183	74.6 0.2	30.86 0.07	-1572.8 1.2	-1484.4 1.2	260.1 0.2	352	425	352 295
PYROPHANITE MnTiO ₃	150.816	104.9 0.2	32.77 0.05	-1360.1 4.0	-1280.9 4.0	224.4 0.7	393	103	103 102
TREVORITE NiFe ₂ O ₄	234.382	140.9 5.0	43.65 0.05	-1070.5 2.0	-965.1 2.5	169.1 0.4	450	271	271 290

THERMODYNAMIC PROPERTIES OF MULTIPLE OXIDE MINERALS AT 298.15 K

NAME AND FORMULA	WEIGHT g	ENTROPY	VOLUME	ENTHALPY	FREE ENERGY	LOG(K)	REFERENCES		
		S° $J \cdot mol^{-1} \cdot K^{-1}$	V° cm^3	$\Delta_f H^\circ$ $kJ \cdot mol^{-1}$	$\Delta_f G^\circ$ $kJ \cdot mol^{-1}$		S	H/G	C
FRANKLINITE $ZnFe_2O_4$	241.082	150.7 0.3	44.94 0.05	-1188.1 4.0	-1082.1 4.0	189.6 0.7	439	290	21
HETAEROLITE $ZnMn_2O_4$	239.264	149.7 0.5	45.57 0.05	-1337.0 4.0	-1227.8 4.0	215.1 0.7	71	290	
ZINC TITANIUM SPINEL Zn_2TiO_4	242.658	143.1 3.0	45.58 0.02	-1652.1 2.0	-1538.4 2.0	269.5 0.4	406	290	43

THERMODYNAMIC PROPERTIES OF HALIDE MINERALS AT 298.15 K

NAME AND FORMULA	WEIGHT g	ENTROPY	VOLUME	ENTHALPY	FREE ENERGY	LOG(K)	REFERENCES		
		S° J·mol ⁻¹ ·K ⁻¹	V° cm ³	Δ _f H° kJ·mol ⁻¹	Δ _f G° kJ·mol ⁻¹		S	H/G	C
BROMARGYRITE AgBr	187.772	107.1 0.4	28.99 0.01	-100.4 0.2	-97.0 0.2	16.99 0.03	419	419	361 318
POTASSIUM BROMIDE KBr	119.002	95.9 0.2	43.28 0.01	-393.8 0.2	-380.4 0.2	66.65 0.03	419	419	67 320
CHLORARGYRITE AgCl	143.321	96.2 0.2	25.73 0.01	-127.1 0.1	-109.8 0.1	19.24 0.02	85	85	361 318
HYDROPHILITE CaCl ₂	110.983	104.6 1.3	50.75 0.01	-795.8 0.7	-747.7 0.8	130.99 0.14	67	67	320 284
NANTOKITE CuCl	98.999	86.2 2.0	23.92 0.04	-137.2 10.0	-119.9 10.0	21.01 1.75	419	419	
LAWRENCITE FeCl ₂	126.752	118.0 0.4	39.46 0.21	-341.7 0.4	-302.2 0.4	52.95 0.07	67	67	284 250
MOLYSITE FeCl ₃	162.205	142.3 0.4	57.86 0.10	-399.5 0.4	-334.0 0.4	58.51 0.07	67	250	284 419
HYDROGEN CHLORIDE HCl (IDEAL GAS)	36.461	186.9 0.0	24789.70 0.20	-92.3 0.1	-95.3 0.1	16.70 0.02	85	85	67 85
CALOMEL HgCl	236.043	95.8 0.4	32.94 0.08	-132.7 0.2	-105.2 0.2	18.43 0.04	85	85	
SYLVITE KCl	74.551	82.6 0.2	37.52 0.00	-436.5 0.2	-408.6 0.2	71.58 0.04	117	117	117 67
CHLOROMAGNESITE MgCl ₂	95.210	89.6 0.8	40.81 0.10	-641.3 0.7	-591.8 0.7	103.68 0.13	67	320	284 85
SCACCHITE MnCl ₂	125.844	118.2 0.2	42.11 0.17	-481.3 0.8	-440.5 0.8	77.17 0.14	73	250	284 419
SALAMMONIAC NH ₄ Cl	53.491	94.6 0.4	35.06 0.05	-314.4 0.3	-202.9 0.3	35.55 0.05	419	419	67
HALITE NaCl	58.442	72.1 0.2	27.02 0.00	-411.3 0.1	-384.2 0.1	67.30 0.02	419	419	67 320
NICKELOUS CHLORIDE NiCl ₂	129.595	98.2 0.2	36.70 0.07	-304.9 2.0	-258.8 2.0	45.33 0.35	67	67	80 419
COTUNNITE PbCl ₂	278.105	136.0 2.1	47.09 0.05	-359.4 0.3	-314.1 0.7	55.03 0.12	67	67	67 320

THERMODYNAMIC PROPERTIES OF HALIDE MINERALS AT 298.15 K

NAME AND FORMULA	WEIGHT g	ENTROPY	VOLUME	ENTHALPY	FREE ENERGY	LOG(K)	REFERENCES		
		S° J·mol ⁻¹ ·K ⁻¹	V° cm ³	Δ _f H° kJ·mol ⁻¹	Δ _f G° kJ·mol ⁻¹		S	H/G	C
FLUORITE CaF ₂	78.075	68.9 0.3	24.54 0.01	-1228.0 2.0	-1175.3 2.0	205.90 0.35	117	117	293 67
HYDROGEN FLUORIDE HF (IDEAL GAS)	20.006	173.8 0.0	24789.70 0.20	-273.3 0.7	-275.4 0.7	48.25 0.12	85	85	67
SELLAITE MgF ₂	62.302	57.2 0.5	19.61 0.01	-1124.2 1.2	-1071.1 1.2	187.64 0.21	117	117	117
VILLIAUMITE NaF	41.988	51.5 0.1	14.98 0.01	-573.6 0.7	-543.4 0.7	95.20 0.12	419	419	300 67
CRYOLITE Na ₃ AlF ₆	209.941	238.5 0.5	70.81 0.20	-3316.8 6.0	-3152.1 6.0	552.22 1.05	10	10	10 301
CHIOLITE Na ₅ Al ₃ F ₁₄	461.871	515.3 0.8	154.08 0.10	-7546.3 20.0	-7174.7 20.0	1256.95 3.50	400	400	400
IODARGYRITE AgI	234.773	115.5 1.7	41.30 0.04	-61.8 1.7	-66.2 1.8	11.60 0.31	419	419	320
MARSHITE CuI	190.450	96.6	33.35 0.02	-67.8 5.0	-69.4 5.0	12.16 0.88	320	320	108
COCCINITE HgI ₂	454.399	180.0 6.3	71.84 0.10	-105.4 1.7	-101.7 2.6	17.82 0.45	419	419	67 67

THERMODYNAMIC PROPERTIES OF CARBONATE AND NITRATE MINERALS AT 298.15 K

NAME AND FORMULA	WEIGHT g	ENTROPY	VOLUME	ENTHALPY	FREE ENERGY	LOG(K)	REFERENCES		
		S° J·mol ⁻¹ ·K ⁻¹	V° cm ³	Δ _f H° kJ·mol ⁻¹	Δ _f G° kJ·mol ⁻¹		S	H/G	C
WITHERITE BaCO ₃	197.336	112.1 2.1	45.81 0.06	-1210.9 2.2	-1132.2 2.2	198.35 0.39	54	1	262
ARAGONITE CaCO ₃	100.087	88.0 0.2	34.15 0.05	-1207.4 1.4	-1127.4 1.5	197.51 0.26	392	336	
CALCITE CaCO ₃	100.087	91.7 0.2	36.93 0.01	-1207.4 1.3	-1128.5 1.4	197.70 0.24	392	246	202
VATERITE CaCO ₃	100.087		37.63 0.40		-1125.5 1.5	197.19 0.26		336	412
MONOHYDROCALCITE CaCO ₃ ·H ₂ O	118.102	131.1 3.0	48.70 0.40	-1498.3 1.2	-1361.6 1.1	238.54 0.20	197	197	
IKAITE CaCO ₃ ·6H ₂ O	208.179	370.0 5.0		-2954.1 5.0	-2540.9 5.0	445.15 0.88	273	273	273
DOLomite CaMg(CO ₃) ₂	184.401	155.2 0.3	64.34 0.03	-2324.5 1.5	-2161.3 1.7	378.64 0.29	396	175	257
HUNTITE CaMg ₃ (CO ₃) ₄	353.030	299.5 0.9	122.58 0.10	-4529.6 1.6	-4203.1 1.6	736.34 0.29	168	169	253
OTAVITE CdCO ₃	172.419	92.5 5.5	34.30 0.02	-750.6 2.5	-669.4 2.6	117.28 0.46	63	419	63
MALACHITE Cu ₂ (CO ₃)(OH) ₂	221.116	166.3 2.5	54.86 0.08	-1054.0 2.1	-890.2 2.2	155.96 0.39	241	339	
AZURITE Cu ₃ (OH) ₂ (CO ₃) ₂	344.671	254.4 3.8	91.01 0.13	-1632.2 2.0	-1391.4 2.2	243.75 0.39	241	419	
SIDERITE FeCO ₃	115.856	95.5 0.2	29.38 0.01	-755.9 5.5	-682.8 5.5	119.63 0.96	351	351	351
MAGNESITE MgCO ₃	84.314	65.1 0.1	28.02 0.01	-1113.3 1.3	-1029.5 1.4	180.36 0.24	178	347	359
NESQUEHONITE MgCO ₃ ·3H ₂ O	138.360	195.6 0.6	75.47 0.05	-1977.3 0.3	-1723.8 0.5	301.99 0.09	353	354	
HYDROMAGNESITE 4MgCO ₃ ·Mg(OH) ₂ ·4H ₂ O	467.638	503.7 1.6	211.10 0.10	-6514.9 1.1	-5864.2 1.1	1027.37 0.19	353	354	
ARTINITE Mg ₂ (OH) ₂ CO ₃ ·3H ₂ O	196.680	232.9 0.7	96.43 0.10	-2920.6 0.7	-2568.4 0.8	449.95 0.13	168	169	

THERMODYNAMIC PROPERTIES OF CARBONATE AND NITRATE MINERALS AT 298.15 K

NAME AND FORMULA	WEIGHT g	ENTROPY	VOLUME	ENTHALPY	FREE ENERGY	LOG(K)	REFERENCES		
		S° $J \cdot mol^{-1} \cdot K^{-1}$	V° cm^3	$\Delta_f H^\circ$ $kJ \cdot mol^{-1}$	$\Delta_f G^\circ$ $kJ \cdot mol^{-1}$		S	H/G	C
RHODOCHROSITE $MnCO_3$	114.947	98.0 0.1	31.07 0.01	-892.9 0.5	-819.1 0.6	143.50 0.10	351	351	283
NAHCOLITE $NaHCO_3$	84.007	102.1 1.7	38.08 0.25	-949.0 0.2	-851.2 0.6	149.12 0.10	36	36	
THERMONATRITE $Na_2CO_3 \cdot H_2O$	124.004	168.1 0.8	54.99 0.27	-1429.7 0.4	-1286.1 0.5	225.32 0.09	424	36	129
TRONA $Na_2CO_3 \cdot NaHCO_3 \cdot 2H_2O$	226.026		107.00 0.50	-2682.1 0.4					416
WEGSCHEIDERITE $Na_2CO_3 \cdot 3NaHCO_3$	358.010		153.30 0.80	-3984.0 0.8					416
SODIUM CARBONATE Na_2CO_3	105.989	135.0 0.6	41.60	-1129.2 0.3	-1045.3 0.4	183.13 0.06	424	36	
DAWSONITE $NaAlCO_3(OH)_2$	143.995	132.0 0.5	59.30 0.30	-1964.0 2.9	-1786.0 3.0	312.89 0.52	110	110	110
GASPEITE $NiCO_3$	118.699	85.4 2.0	27.05 0.02				255		
CERUSSITE $PbCO_3$	267.209	131.0 3.4	40.59 0.06	-699.2 1.2	-625.5 1.6	109.58 0.27	217	419	4
STRONTIANITE $SrCO_3$	147.629	97.1 1.7	39.01 0.06	-1218.7 1.5	-1137.6 1.5	199.29 0.26	55	55	262
SMITHSONITE $ZnCO_3$	125.399	81.2 0.2	28.28 0.01	-817.0 3.1	-735.3 3.1	128.82 0.54	352	153	153
NITROBARITE $Ba(NO_3)_2$	261.337	213.8 0.9	80.58 2.10	-992.1 2.5	-796.6 0.4	139.55 0.08	419	419	361
CALCIUM NITRATE $Ca(NO_3)_2$	164.088	193.3 0.4	66.09 0.03	-938.4 1.5	-742.6 1.8	130.10 0.31	419	419	361
NITER KNO_3	101.103	133.1 0.7	48.04 0.06	-494.5 0.4	-394.6 0.5	69.13 0.08	419	419	361
MAGNESIUM NITRATE $Mg(NO_3)_2$	148.315	164.0 1.6	62.93 0.03	-790.6 1.3	-589.2 1.4	103.22 0.25	419	419	361
AMMONIA-NITER NH_4NO_3	80.043	151.1 0.2	46.49 0.10	-365.6 0.8	-183.8 0.9	32.20 0.15	419	419	361

THERMODYNAMIC PROPERTIES OF CARBONATE AND NITRATE MINERALS AT 298.15 K

NAME AND FORMULA	WEIGHT g	ENTROPY	VOLUME	ENTHALPY	FREE ENERGY	LOG(K)	REFERENCES		
		S° $J \cdot mol^{-1} \cdot K^{-1}$	V° cm^3	$\Delta_f H^\circ$ $kJ \cdot mol^{-1}$	$\Delta_f G^\circ$ $kJ \cdot mol^{-1}$		S	H/G	C
SODA-NITER $NaNO_3$	84.995	116.5 0.7	37.60 0.02	-468.0 0.4	-367.1 0.4	64.32 0.07	419	419	361
STRONTIUM NITRATE $Sr(NO_3)_2$	211.630	194.6 0.5	70.93 0.04	-978.2 1.0	-779.0 1.3	136.47 0.23	419	419	361

THERMODYNAMIC PROPERTIES OF SULFATE AND BORATE MINERALS AT 298.15 K

NAME AND FORMULA	WEIGHT g	ENTROPY	VOLUME	ENTHALPY	FREE ENERGY	LOG(K)	REFERENCES		
		S° J·mol ⁻¹ ·K ⁻¹	V° cm ³	Δ _f H° kJ·mol ⁻¹	Δ _f G° kJ·mol ⁻¹		S	H/G	C
ALUMINUM SULFATE Al ₂ (SO ₄) ₃	342.154	239.3 1.2	73.41 0.20	-3441.8 1.8	-3100.6 1.9	543.20 0.33	88	88	88
BARITE BaSO ₄	233.391	132.2 0.8	52.10 0.06	-1473.6 1.0	-1362.5 1.3	238.70 0.23	88	88	88 419
ANHYDRITE CaSO ₄	136.142	107.4 0.2	46.01 0.01	-1434.4 4.2	-1321.8 4.3	231.57 0.75	368	88	368 419
GYPSUM CaSO ₄ ·2H ₂ O	172.172	193.8 0.3	74.69 0.22	-2023.0 4.3	-1797.0 4.4	314.82 0.77	368	88	88
CHALCOCYANITE CuSO ₄	159.610	109.5 0.6	40.88 0.03	-771.4 1.3	-662.3 1.4	116.03 0.25	106	4	106 419
CHALCANTHITE CuSO ₄ ·5H ₂ O	249.686	301.2 0.6	108.97 0.22	-2279.7 3.4	-1880.0 3.6	329.36 0.63	87	87	87 419
BROCHANTITE Cu ₄ (SO ₄)(OH) ₆	452.292		113.60 0.20		-1818.0 2.5	318.49 0.44			26 419
FERRIC SULFATE Fe ₂ (SO ₄) ₃	399.885	282.8 0.9	130.80 0.20	-2581.9 2.9	-2254.4 3.0	394.96 0.52	328	19	328
SZOMOLNOKITE FeSO ₄ ·H ₂ O	169.926		55.90 0.40	-1244.3 0.5			87	2	87
MELANTERITE FeSO ₄ ·7H ₂ O	278.018	409.2 1.3	146.50 0.30	-3014.3 0.6	-2509.5 1.3	439.64 0.23	87	2	87
SULFURIC ACID (LIQUID) H ₂ SO ₄	98.080	156.9 0.2	53.57 0.07	-814.0 0.4	-690.0 0.5	120.88 0.08	419	419	419 124
ARCANITE K ₂ SO ₄	174.260	175.6 0.4	65.50 0.07	-1437.7 0.5	-1319.6 0.5	231.18 0.09	67	67	387 67
K-AL SULFATE KAl(SO ₄) ₂	258.207	204.6 1.3	92.33 0.08	-2470.9 1.3	-2240.4 1.4	392.50 0.24	419	419	217
ALUNITE KAl ₃ (OH) ₆ (SO ₄) ₂	414.214	321.0 5.0	293.60 0.40	-5176.5 2.4	-4663.5 2.4	817.00 0.42	452	452	219 219
LANGBEINITE K ₂ Mg ₂ (SO ₄) ₃	414.997	389.3 1.0	146.95 0.04	-4071.0 3.0	-3733.4 3.0	654.05 0.52	368	419	368 40
MAGNESIUM SULFATE MgSO ₄	120.369	91.4 0.8		-1284.9 0.6	-1170.5 0.8	205.07 0.14	67	247	67 88

THERMODYNAMIC PROPERTIES OF SULFATE AND BORATE MINERALS AT 298.15 K

NAME AND FORMULA	WEIGHT g	ENTROPY	VOLUME	ENTHALPY	FREE ENERGY	LOG(K)	REFERENCES		
		S° J·mol ⁻¹ ·K ⁻¹	V° cm ³	Δ _f H° kJ·mol ⁻¹	Δ _f G° kJ·mol ⁻¹		S	H/G	C
EPSOMITE MgSO ₄ ·7H ₂ O	246.476	372.0 4.0	146.80 0.20	-3388.7 0.1	-2871.2 0.9	503.01 0.15	419	419	88
MANGANESE SULFATE MnSO ₄	151.002	127.0 1.5	43.62 0.04	-1065.7 1.1	-962.1 1.5	168.56 0.26	450	87	87
MASCAGNITE (NH ₄) ₂ SO ₄	132.141	220.5 1.3	74.68 0.09	-1182.7 1.3	-903.5 1.6	158.29 0.28	419	88	387
THENARDITE Na ₂ SO ₄	142.043	149.6 0.1	53.33 0.06	-1387.8 0.4	-1269.8 0.4	222.46 0.07	88	88	81
MIRABILITE Na ₂ SO ₄ ·10H ₂ O	322.196	591.9 0.6	219.80 0.40	-4327.3 4.0	-3645.8 3.4	638.71 0.59	47	47	81
NICKELOUS SULFATE NiSO ₄	154.754	101.3 0.3	38.57 0.03	-873.2 1.0	-762.7 1.0	133.61	401	401	401
RETGERSITE (ALPHA, GREEN) NiSO ₄ ·6H ₂ O	262.845	334.5 0.4	126.60 0.20	-2683.4 0.5	-2225.1 0.5	389.82 0.09	87	87	419
MORENOSITE NiSO ₄ ·7H ₂ O	280.861	378.9 0.4	143.80 0.50	-2976.5 0.5	-2461.9 0.5	431.30 0.09	87	87	419
ANGLESITE PbSO ₄	303.264	148.5 0.6	47.95 0.06	-920.0 0.4	-813.1 0.5	142.44 0.09	85	85	88
CELESTITE SrSO ₄	183.684	117.0 4.2	46.25 0.06	-1453.2 4.2	-1339.6 4.4	234.69 0.77	419	419	129
ZINKOSITE ZnSO ₄	161.454	110.5 1.3	41.57 0.07	-980.1 0.8	-868.7 0.9	152.20 0.16	87	87	87
BIANCHITE ZnSO ₄ ·6H ₂ O	269.545	363.6 1.3	130.20 0.50	-2777.8 1.0	-2324.6 1.0	407.26 0.18	87	87	419
GOSLARITE ZnSO ₄ ·7H ₂ O	287.561	388.7 1.3	145.80 0.10	-3077.5 0.1	-2562.3 0.1	448.89 0.02	87	87	419
BORAX Na ₂ B ₄ O ₇ ·10H ₂ O	381.372	586.0 2.3	222.70 0.20	-6288.6 8.5	-5516.2 8.5	966.39 1.49	419	419	

THERMODYNAMIC PROPERTIES OF PHOSPHATE, MOLYBDATE AND TUNGSTATE MINERALS AT 298.15 K

NAME AND FORMULA	WEIGHT g	ENTROPY	VOLUME	ENTHALPY	FREE ENERGY	LOG(K)	REFERENCES		
		S° J·mol ⁻¹ ·K ⁻¹	V° cm ³	Δ _f H° kJ·mol ⁻¹	Δ _f G° kJ·mol ⁻¹		S	H/G	C
BERLINITE AlPO ₄	121.953	90.8 0.2	46.58 0.10	-1733.8 5.0	-1617.9 5.0	283.44 0.88	419	419	181
WHITLOCKITE Ca ₃ (PO ₄) ₂	310.177	236.0 0.8	97.62 0.09	-4120.8 5.0	-3883.6 5.0	680.38 0.88	419	419	361
FLUORAPATITE Ca ₅ (PO ₄) ₃ F	504.302	387.9 1.7	157.56 0.12	-6872.0 5.0	-6489.7 5.0	1136.95 0.88	419	419	99
HYDROXYAPATITE Ca ₅ (PO ₄) ₃ OH	502.311	390.4 1.7	159.60 0.20	-6738.5 5.0	-6337.1 5.0	1110.22 0.88	419	419	99
STRENGITE FePO ₄ ·2H ₂ O	186.849	171.3 1.3	64.50 0.30	-1888.2 0.9	-1657.5 1.0	290.37 0.18	100	419	100
POWELLITE CaMoO ₄	200.016	122.6 0.8	47.00 0.09	-1541.4 0.9	-1434.7 0.9	251.34 0.15	431	419	12
WULFENITE PbMoO ₄	367.138	166.1 2.1	53.86 0.10	-1051.9 0.9	-951.2 1.2	166.65 0.20	320	419	89
SCHEELITE CaWO ₄	287.926	126.4 0.8	47.05 0.09	-1645.2 0.9	-1538.0 0.9	269.51 0.16	232	419	17
FERBERITE FeWO ₄	303.695	131.8 1.7	40.38 0.05	-1154.8 8.5	-1054.0 8.5	184.64 1.49	430	419	265 7
MUEBNERITE MnWO ₄	302.786	132.5 0.2	41.89 0.06	-1337.6 7.0	-1235.4 7.1	216.44 1.24	304	7	
STOLZITE PbWO ₄	455.048	168.2 2.1	54.10 0.06	-1127.2 2.0	-1026.0 2.0	179.74 0.35	428	89	
SANMARTINITE ZnWO ₄	313.238	119.3 0.3	39.79 0.04	-1232.6 1.3	-1123.7 1.4	196.86 0.25	260	266	260 266

THERMODYNAMIC PROPERTIES OF ORTHO AND RING STRUCTURE SILICATE MINERALS AT 298.15 K

NAME AND FORMULA	WEIGHT g	ENTROPY	VOLUME	ENTHALPY	FREE ENERGY	LOG(K)	REFERENCES		
		S° J·mol ⁻¹ ·K ⁻¹	V° cm ³	Δ _f H° kJ·mol ⁻¹	Δ _f G° kJ·mol ⁻¹		S	H/G	C
TOPAZ Al ₂ SiO ₄ F ₂	184.043	105.4 0.2	51.53 0.03	-3084.5 4.7	-2910.6 4.7	509.9 0.8	24	23	24
KYANITE Al ₂ SiO ₅	162.046	82.8 0.5	44.15 0.05	-2593.8 2.0	-2443.1 2.0	428.0 0.4	355	177	177
ANDALUSITE Al ₂ SiO ₅	162.046	91.4 0.5	51.52 0.05	-2589.9 2.0	-2441.8 2.0	427.8 0.4	355	177	177
SILLIMANITE Al ₂ SiO ₅	162.046	95.4 0.5	49.86 0.05	-2586.1 2.0	-2439.1 2.0	427.3 0.4	355	177	177
MULLITE Al ₆ Si ₂ O ₁₃	426.052	275.0 5.0	134.55 0.07	-6819.2 10.0	-6441.8 10.0	1128.6 1.8	67	67	67
DUMORTIERITE Al _{6.75} [□ _{0.25} Si ₃ BO _{17.25} (OH) _{.75}	565.938	334.9 5.0	168.4 0.4	-9109.0 20.0	-8568.2 20.0	1501.1 3.5	163	163	163
EUCLASE BeAlSiO ₄ (OH)	145.084	89.1 0.4	46.86 0.06	-2532.9 3.0	-2370.2 3.0	415.2 0.5	164	164	164
PHENAKITE Be ₂ SiO ₄	110.107	63.4 0.3	37.18 0.02	-2143.1 4.0	-2028.4 4.0	355.4 0.7	164	164	164
BERYL Be ₃ Al ₂ (Si ₆ O ₁₈)	537.502	346.7 4.7	203.3 0.1	-9006.6 7.0	-8500.5 6.4	1489.2 1.1	164	164	164
BERTRANDITE Be ₄ Si ₂ O ₇ (OH) ₂	238.230	172.1 0.8	91.8 0.1	-4580.5 5.5	-4295.1 5.5	752.5 1.0	164	164	164
EPIDOTE Ca ₂ Al ₂ FeSi ₃ O ₁₂ (OH)	483.223	328.9 2.5	138.1 0.6				147		239
LAWSONITE CaAl ₂ [Si ₂ O ₇ (OH) ₂]H ₂ O	314.238	230.0 2.1	101.32 0.12	-4869.0 2.1	-4512.9 2.1	790.6 0.4	335	68	335
GEHLENITE Ca ₂ Al ₂ SiO ₇	274.200	210.1 0.6	90.15 0.02	-3985.0 5.0	-3785.5 5.0	663.2 0.9	172	66	323
ZOISITE Ca ₂ Al ₃ Si ₃ O ₁₂ (OH)	454.357	295.9 0.6	136.5 0.4	-6901.1 3.3	-6504.5 3.3	1139.5 0.6	335	239	335
GROSSULAR Ca ₃ Al ₂ Si ₃ O ₁₂	450.446	260.1 0.5	125.28 0.05	-6640.0 3.2	-6278.5 3.2	1099.9 0.6	157	68	258
GLASS Ca ₃ Al ₂ Si ₃ O ₁₂	450.446	329.2+	158.8 0.3				345		

THERMODYNAMIC PROPERTIES OF ORTHO AND RING STRUCTURE SILICATE MINERALS AT 298.15 K

NAME AND FORMULA	WEIGHT g	ENTROPY	VOLUME	ENTHALPY	FREE ENERGY	LOG(K)	REFERENCES		
		S° J·mol ⁻¹ ·K ⁻¹	V° cm ³	Δ _f H° kJ·mol ⁻¹	Δ _f G° kJ·mol ⁻¹		S	H/G	C
DATOLITE CaB(SiO ₄)(OH)	159.979	110.2 0.6	53.32 0.05	-2477.8 2.3	-2318.1 2.3	406.1 0.4	448	383	274 5
ILVAITE CaFe ₂ Fe(Si ₂ O ₇)O(OH)	408.793	292.3 0.6	101.07 0.10	-3692.8 5.0	-3437.0 5.0	602.1 0.9	349	349	349
ANDRADITE Ca ₃ Fe ₂ Si ₃ O ₁₂	508.177	316.4 2.0	132.04 0.05	-5771.0 5.9	-5427.0 5.9	950.8 1.0	348	281	348 242 244
MONTICELLITE CaMgSiO ₄	156.466	108.1 0.3	51.3 0.1	-2251.0 3.0	-2132.8 3.1	373.6 0.5	385	49	385 385
AKERMANITE Ca ₂ MgSi ₂ O ₇	272.628	212.5 0.4	92.54 0.02	-3864.8 2.0	-3667.5 2.0	642.5 0.4	165	165	165 427 49 323
MERWINITE Ca ₃ Mg(SiO ₄) ₂	328.705	253.1 2.1	98.5 0.1	-4536.2 3.0	-4307.7 3.0	754.7 0.5	427	49	323
TITANITE (SPHENE) CaTiSiO ₅	196.041	129.2 0.8	55.74 0.07	-2596.6 3.0	-2454.6 3.2	430.0 0.6	406	37	361 188
LARNITE α-Ca ₂ SiO ₄	172.239	127.6 0.8	51.60 0.30	-2306.7 1.5	-2191.2 1.5	383.9 0.3	225	149	84 149
CALCIO-OLIVINE γ-Ca ₂ SiO ₄	172.239	120.5 0.8	58.01 0.04	-2316.5 2.5	-2198.9 2.5	385.2 0.4	149	149	149 405 84
HATURITE (ALITE) Ca ₃ SiO ₅	228.317	168.6 0.3	72.74 0.05	-2933.1 2.5	-2786.5 2.5	488.2 0.4	149	410	149 405
RANKINITE Ca ₃ Si ₂ O ₇	288.401	210.6 2.9	96.51 0.05	-3949.0 10.0	-3748.1 10.0	656.6 1.8	149	410	149
ROSENHAHNITE Ca ₃ Si ₃ O ₈ (OH) ₂	366.500	281.8 3.0	126.46 0.05	-5198.1 3.0	-4882.1 3.0	855.3 0.5	68	68	68
SPURRITE Ca ₅ (SiO ₄) ₂ CO ₃	444.565	331.0 2.0	146.97 0.30	-5840.2 5.7	-5525.6 5.9	968.0 1.0	450	188	450 188 410
TILLEYITE Ca ₅ Si ₂ O ₇ (CO ₃) ₂	488.575	394.0 4.0	170.5 0.3	-6372.2 5.7	-6013.5 6.0	1053.5 1.1	450	188	450 410
COBALT-OLIVINE Co ₂ SiO ₄	209.950	142.6 0.2	44.49 0.01	-1412.0 2.0	-1308.7 2.0	229.3 0.3	364	215	363 308
FAYALITE Fe ₂ SiO ₄	203.777	151.0 0.2	46.31 0.01	-1478.2 1.3	-1379.1 1.3	241.6 0.2	350	350	350 309 314

THERMODYNAMIC PROPERTIES OF ORTHO AND RING STRUCTURE SILICATE MINERALS AT 298.15 K

NAME AND FORMULA	WEIGHT g	ENTROPY	VOLUME	ENTHALPY	FREE ENERGY	LOG(K)	REFERENCES		
		S° $J \cdot mol^{-1} \cdot K^{-1}$	V° cm^3	$\Delta_f H^\circ$ $kJ \cdot mol^{-1}$	$\Delta_f G^\circ$ $kJ \cdot mol^{-1}$		S	H/G	C
ALMANDINE $Fe_3Al_2Si_3O_{12}$	497.753	342.6 1.4	115.32 0.04	-5264.7 3.0	-4942.0 3.3	865.8 0.6	9 277	69 445	447 151
STAUROLITE $Fe_4Al_{18}Si_8O_{46}(OH)_2$	1703.727	985.0 4.0	445.9 1.7				172		172
OSUMILITE $KMg_2Al_3[Si_{10}Al_2O_{30}] \cdot H_2O$	1001.468		379.2 0.3						180
CORDIERITE $Mg_2Al_3(AlSi_5O_{18})$	584.953	407.2 3.8	233.22 0.22	-9161.5 5.9	-8651.1 5.9	1515.6 1.0	427	297	323
SAPPHIRINE $Mg_2Al_4O_6(SiO_4)$	344.616	197.5 2.0	98.9 0.7				186		
FORSTERITE Mg_2SiO_4	140.693	94.1 0.1	43.65 0.03	-2173.0 2.0	-2053.6 2.0	359.8 0.4	364	364	364
PYROPE $Mg_3Al_2Si_3O_{12}$	403.127	266.3 0.8	113.12 0.15	-6285.0 4.0	-5934.5 4.0	1039.7 0.7	157	188	453
GLASS $Mg_3Al_2Si_3O_{12}$	403.127	346.3 12.0	146.1 0.2	-6163.0 15.0	-5836.3 15.0	1022.5 2.6	402	402	402
PYROPE-GROSSULAR ss. $(Mg_{1.8}Ca_{1.2})Al_2Si_3O_{12}$	422.055	268.3+ 0.5	118.35 0.05				157	298	
GLASS $(Mg_{1.5}Ca_{1.5})Al_2Si_3O_{12}$	426.787	311.8+ 0.6	152.5 0.2				345		
TEPHROITE Mn_2SiO_4	201.959	155.9 0.5	48.99 0.03	-1731.5 3.0	-1631.0 3.0	285.7 0.5	364	364	364
LIEBENBERGITE Ni_2SiO_4	209.463	128.1 0.2	42.57 0.02	-1396.5 3.0	-1288.9 3.0	225.8 0.5	363	363	363
Ni_2SiO_4 -SPINEL Ni_2SiO_4	209.463	124.1 0.4	39.81 0.01	-1389.7 3.5	-1280.9 3.5	224.4 0.6	363	363	423
WILLEMITE Zn_2SiO_4	222.863	131.4 0.8	52.42 0.08	-1636.7 5.0	-1523.1 5.0	266.8 0.9	405	223	
ZIRCON $ZrSiO_4$	183.307	84.0 1.3	39.26 0.07	-2034.2 3.1	-1919.7 3.1	336.3 0.5	361	101	361

THERMODYNAMIC PROPERTIES OF CHAIN AND BAND STRUCTURE SILICATE MINERALS AT 298.15 K

NAME AND FORMULA	WEIGHT g	ENTROPY	VOLUME	ENTHALPY	FREE ENERGY	LOG(K)	REFERENCES		
		S° J·mol ⁻¹ ·K ⁻¹	V° cm ³	$\Delta_f H^\circ$ kJ·mol ⁻¹	$\Delta_f G^\circ$ kJ·mol ⁻¹		S	H/G	C
WOLLASTONITE CaSiO ₃	116.162	81.7 0.1	39.90 0.03	-1634.8 1.4	-1549.0 1.4	271.4 0.2	259	348	389
PSEUDOWOLLASTONITE CaSiO ₃	116.162	87.2 0.9	40.08 0.14	-1627.6 1.4	-1543.5 1.4	270.4 0.2	149	344	344
GLASS CaSiO ₃	116.162	94.8 3.0	40.13 0.15	-1608.7 3.0	-1526.8 3.0	267.5 0.5	344	344	344
Ca-AL PYROXENE CaAl ₂ SiO ₆	218.123	141.0 2.0	63.57 0.01	-3306.3 2.5	-3129.6 2.6	548.3 0.5	154	68	154
GLASS CaAl ₂ SiO ₆	218.123	155.3+ 0.3	78.13 0.08				154		
FERROBUSTAMITE CaFeSi ₂ O ₆	248.092	180.5 0.3	73.00 0.02				156		156
HEDENBERGITE CaFeSi ₂ O ₆	248.092	174.2 0.3	67.95 0.01	-2839.9 3.0	-2676.3 3.0	468.9 0.5	156	281	156
GLASS CaFeSi ₂ O ₆	248.092	185.7+ 0.4					156		
DIOPSIDE CaMgSi ₂ O ₆	216.550	142.7 0.3	66.09 0.10	-3201.5 2.0	-3026.8 2.0	530.3 0.4	259	165	257
GLASS CaMgSi ₂ O ₆	216.550	166.0 3.0	76.09 0.20	-3156.1 5.0	-2988.4 5.1	523.5 0.9	343	340	343
FERROSILITE FeSiO ₃	131.931	94.6 0.3	33.00 0.02	-1195.2 3.0	-1118.0 3.0	195.9 0.5	41	41	188
α -SPODUMENE LiAlSi ₂ O ₆	186.090	129.3 0.8	58.37 0.02	-3053.5 2.8	-2880.2 3.0	504.6 0.5	327	171	327
β -SPODUMENE LiAlSi ₂ O ₆	186.090	154.4 1.2	78.25 0.04	-3025.3 2.8	-2859.5 3.0	501.0 0.5	327	171	327
ENSTATITE MgSiO ₃	100.389	66.3 0.1	31.31 0.02	-1545.6 1.5	-1458.3 1.6	255.5 0.3	259	37	257
GLASS MgSiO ₃	100.389	74.1 0.2	36.60 0.25	-1542.5 2.0	-1457.5 2.0	255.3 0.4	345	345	
CLINOENSTATITE MgSiO ₃	100.389	67.9 0.4	31.28 0.02	-1545.0 1.5	-1458.1 1.6	255.5 0.3	361	296	361

THERMODYNAMIC PROPERTIES OF CHAIN AND BAND STRUCTURE SILICATE MINERALS AT 298.15 K

NAME AND FORMULA	WEIGHT g	ENTROPY	VOLUME	ENTHALPY	FREE ENERGY	LOG(K)	REFERENCES		
		S° J·mol ⁻¹ ·K ⁻¹	V° cm ³	Δ _f H° kJ·mol ⁻¹	Δ _f G° kJ·mol ⁻¹		S	H/G	C
MgSiO ₃ -PEROVSKITE	100.389	63.6	24.50	-1445.1	-1357.0	237.7	105	105	
MgSiO ₃		3.0	0.05	5.0	5.0	0.9			
MgSiO ₃ -ILMENITE	100.389	60.4	26.36	-1486.6	-1397.5	244.8	105	13	13
MgSiO ₃		3.0	0.02	5.0	5.0	0.9		288	
HYPERSTHENE	105.120	69.0	31.53					367	
(Mg _{0.85} Fe _{0.15})SiO ₃		0.2	0.05						
RHODONITE	131.022	100.5	34.94	-1321.6	-1244.7	218.0	367	367	390
MnSiO ₃		1.0	0.05	2.0	2.2	0.4		289	224
PYROXMANGITE	131.022	99.4	34.72	-1322.3	-1245.0	218.1	367	367	
MnSiO ₃		2.0	0.02	2.0	2.4	0.4		32	
JADEITE	202.139	133.5	60.40	-3029.3	-2850.6	499.4	220	166	220
NaAlSi ₂ O ₆		1.3	0.10	3.6	4.0	0.7		184	
GLASS	202.139	170.5						345	
NaAlSi ₂ O ₆		0.4							
ACMITE	231.004	170.6	64.60	-2584.5	-2417.2	423.5	248	31	31
NaFeSi ₂ O ₆		0.8	0.11	4.0	4.2	0.7	33	188	
TREMOLITE	812.366	548.9	272.90	-12303.0	-11574.6	2027.8	370	205	257
Ca ₂ Mg ₅ Si ₈ O ₂₂ (OH) ₂		1.3	0.73	7.0	7.0	1.2		426	
GRUNERITE	1001.614	725.0	278.7	-9623.0	-8964.8	1570.6	264	264	252
Fe ₇ Si ₈ O ₂₂ (OH) ₂		7.0	0.5	10.0	10.2	1.8	252	8	34
ANTHOPHYLLITE	780.820	534.5	265.4	-12070.0	-11343.4	1987.3	162	162	162
Mg ₇ Si ₈ O ₂₂ (OH) ₂		3.5	0.4	8.0	8.5	1.5		70	
RIEBECKITE	935.900	691.0	274.7					450	
Na ₂ Fe ₃ Fe ₂ Si ₈ O ₂₂ (OH) ₂		6.0	0.9						
GLAUCOPHANE	783.543	541.2	262.1	-11964.0	-11230.8	1967.6	362	188	185
Na ₂ Mg ₃ Al ₂ Si ₈ O ₂₂ (OH) ₂		3.0	0.2	9.0	10.0	1.8			118
PARGASITE	835.825	582.0	272.0	-12719.8	-11981.5	2099.1	433	188	
NaCa ₂ Mg ₄ Al(Al ₂ Si ₆)O ₂₂ (OH) ₂		4.0	0.2	22.0	19.0	3.3	186	433	
FLUOR-PARGASITE	839.807	583.0	270.6	-12800.5	-12102.2	2120.2	450	434	
NaCa ₂ Mg ₄ Al(Al ₂ Si ₆)O ₂₂ F ₂		5.0	0.2	14.0	14.0	2.5	434		

THERMODYNAMIC PROPERTIES OF FRAMEWORK STRUCTURE SILICATE MINERALS AT 298.15 K

NAME AND FORMULA	WEIGHT g	ENTROPY	VOLUME	ENTHALPY	FREE ENERGY	LOG(K)	REFERENCES			
		S° $J \cdot mol^{-1} \cdot K^{-1}$	V° cm^3	$\Delta_f H^\circ$ $kJ \cdot mol^{-1}$	$\Delta_f G^\circ$ $kJ \cdot mol^{-1}$		S	H/G	C	
EDINGTONITE (ordered) $BaAl_2Si_3O_{10} \cdot 3H_2O$	489.586	434.8 1.5	180.40 0.60				27			
ANORTHITE $CaAl_2Si_2O_8$	278.207	199.3 0.3	100.79 0.05	-4234.0 2.0	-4007.9 2.0	702.2 0.4	366 56	150 68	446 258	
HEXAGONAL ANORTHITE $CaAl_2Si_2O_8$	278.207	214.8 1.3	99.85 0.79				231	171		
$CaAl_2Si_2O_8$ -glass $CaAl_2Si_2O_8$	278.207	237.3 2.5	103.0 0.2	-4163.2 4.0	-3948.4 4.0	691.7 0.7	366	450	258	
STILBITE $Ca_{1.02}Na_{0.14}K_{0.01}(Al_{2.18}Si_{6.82}O_{18}) \cdot 7.33H_2O$	714.893	805.9 1.6	333.4 1.0	-11038.0 6.6	-10146.0 6.6	1777.5 1.2	195	195		
HEULANDITE $Ca_{0.59}Sr_{0.18}Ba_{0.06}Na_{0.38}K_{0.13}Al_{2.16}Si_{6.84}O_{18} \cdot 6H_2O$	707.942	767.2	317.6 1.0	-10594.6 10.2	-9779.0 10.2	1713.2 1.8	208	208	208	74
WAIRAKITE $CaAl_2Si_4O_{12} \cdot 2H_2O$	434.406	440.0 10.0	190.4 0.5				159			
LAUMONTITE $CaAl_2Si_4O_{12} \cdot 4H_2O$	470.437		211.3 1.0		-6772.0 7.0	1186.4 1.2		195		
SCOLECITE $CaAl_2Si_3O_{10} \cdot 3H_2O$	392.337	367.4 0.7	172.3 0.5	-6049.0 5.0	-5597.6 5.0	980.7 0.9	207	207		
LEONHARDITE $Ca_2Al_4Si_8O_{24} \cdot 7H_2O$	922.859	922.2 10.9	409.3 2.0				231			
BICCNULITE $Ca_2Al_2SiO_6(OH)_2$	292.216	213.1 5.0	103.68 0.10	-4341.2 5.0	-4073.0 5.0	713.6 0.9	68	68	68	144
MEIONITE (Al/Si ordered) $Ca_4Al_6Si_6O_{24}CO_3$	934.709	715.2 1.0	340.36 0.08	-13881.4 6.2	-13131.8 6.2	2300.6 1.1	282	282	450	
DANBURITE $CaB_2Si_2O_8$	245.866	155.3 0.4	82.20 0.40	-3902.8 2.9	-3677.0 2.9	644.2 0.5	448	383	5	274
CLINOPTILOLITE $(Na_{0.56}K_{0.98}Ca_{1.50}Mg_{1.23})(Al_{6.7}Fe_{0.3})Si_{29}O_{72} \cdot 22H_2O$	2701.506	2872.3+	1267.6 7.0				173			214
POLLUCITE $(Cs_{.65}Na_{.19}Rb_{.03})Al_2Si_4O_{12} \cdot H_2O$	245.488	207.2 0.4	83.0 2.0				30			
MICROCLINE $KAlSi_3O_8$	278.332	214.2 0.4	108.72 0.10	-3974.6 3.9	-3749.3 3.9	656.8 0.6	313	166	167	

THERMODYNAMIC PROPERTIES OF FRAMEWORK STRUCTURE SILICATE MINERALS AT 298.15 K

NAME AND FORMULA	WEIGHT g	ENTROPY	VOLUME	ENTHALPY	FREE ENERGY	LOG(K)	REFERENCES		
		S° J·mol ⁻¹ ·K ⁻¹	V° cm ³	Δ _f H° kJ·mol ⁻¹	Δ _f G° kJ·mol ⁻¹		S	H/G	C
SANIDINE KAlSi ₃ O ₈	278.332	232.8 0.5	109.05 0.10	-3965.6 4.1	-3745.8 4.1	656.2 0.7	313 155	166 194	167
GLASS KAlSi ₃ O ₈	278.332	261.6 1.8	116.50 1.00	-3920.8 4.2	-3709.6 4.2	649.9 0.6	366	166 421	258
KALIOPHILLITE (KALSILITE) KAlSiO ₄	158.163	133.3 1.2	59.89 0.05	-2124.7 3.1	-2008.8 3.1	351.9 0.5	220	188	317
LEUCITE KAlSi ₂ O ₆	218.247	200.2 1.7	88.27 0.05	-3037.8 2.7	-2875.1 2.7	503.7 0.5	220	188	317 263
EUCRYPTITE LiAlSiO ₄	126.006	103.8 0.8	53.63 0.08	-2123.3 2.0	-2009.2 2.0	352.0 0.4	327	171 20	327
PETALITE LiAlSi ₄ O ₁₀	306.259	233.2 0.6	128.40 0.50	-4886.5 6.3	-4610.7 6.3	807.8 1.1	180 35	180 28	180 35
ALBITE NaAlSi ₃ O ₈	262.223	207.4 0.4	100.07 0.13	-3935.0 2.6	-3711.6 2.6	650.2 0.5	313 123	166 171	167 220
ANALBITE NaAlSi ₃ O ₈	262.223	225.6 0.4	100.43 0.09	-3923.6 2.6	-3705.6 2.6	649.2 0.5	313 155	166 171	167
GLASS NaAlSi ₃ O ₈	262.223	251.9 1.5	110.10 0.20	-3875.5 3.7	-3665.3 3.7	642.1 0.6	366	421	258
NA-K FELDSPAR SS. (Na _{0.85} K _{0.15})AlSi ₃ O ₈	264.639	231.3 0.4	102.18 0.10	-3932.1 4.0	-3715.2 4.0	650.9 0.7	155	155	
NA-K FELDSPAR SS. (Na _{0.55} K _{0.45})AlSi ₃ O ₈	269.472	237.0 0.4	105.22 0.10	-3945.1 4.0	-3728.7 4.0	653.2 0.7	155	155	
NA-K FELDSPAR SS. (Na _{0.25} K _{0.75})AlSi ₃ O ₈	274.304	237.4 0.4	107.37 0.10	-3954.5 4.0	-3737.1 4.0	654.7 0.7	155	155	
NEPHELINE NaAlSiO ₄	142.054	124.4 1.3	54.19 0.06	-2090.4 3.9	-1975.8 3.9	346.1 0.7	220	188	220 183
CARNEGIEITE NaAlSiO ₄	142.054	118.7 0.3	56.03 0.02	-2104.3 4.0	-1988.0 4.0	348.3 0.7	346	450	220
GLASS NaAlSiO ₄	142.054	134.5 0.5	56.86 0.06	-2089.0 4.0	-1977.4 4.0	346.4 0.7	346	346	346
ANALCIME NaAlSi ₂ O ₆ ·H ₂ O	220.154	227.7 0.3	97.4 0.2	-3310.1 3.3	-3090.0 3.3	541.3 0.6	206	206	206

THERMODYNAMIC PROPERTIES OF FRAMEWORK STRUCTURE SILICATE MINERALS AT 298.15 K

NAME AND FORMULA	WEIGHT g	ENTROPY	VOLUME	ENTHALPY	FREE ENERGY	LOG(K)			REFERENCES		
		S° J·mol ⁻¹ ·K ⁻¹	V° cm ³	Δ _f H° kJ·mol ⁻¹	Δ _f G° kJ·mol ⁻¹	S	H/G	C	S	H/G	C
DEHYDRATED ANALCIME NaAlSi ₂ O ₆	202.139	172.5 0.2		-2983.1 3.5	-2816.0 3.5	493.4 0.6	206	206	317 206		
NATROLITE Na ₂ Al ₂ Si ₃ O ₁₀ ·2H ₂ O	380.224	359.7 0.7	169.2 0.2	-5718.6 5.0	-5316.5 5.0	931.4 0.9	207	207			
PHILLIPSITE (Na _{1.1} K _{0.8})Al _{1.9} Si _{6.1} O ₁₆ ·6H ₂ O	643.236	771.9+ 2.4	303.0 8.0						173		
MESOLITE Na _{0.68} Ca _{0.66} (Al _{1.99} Si _{3.01} O ₁₀)·2.65H ₂ O	388.050	363.0+ 2.0	171.1 0.4	-5947.1 5.4	-5512.7 6.0	965.8 1.1	207	207			
MORDENITE Na _{0.36} Ca _{0.29} Al _{0.94} Si _{5.06} O ₁₂ ·3.47H ₂ O	441.880	486.5+ 1.0	209.8 1.2	-6736.7 4.5	-6227.9 4.5	1091.1 0.8	212	212			
DEHYDRATED MORDENITE Na _{0.36} Ca _{0.29} Al _{0.94} Si _{5.06} O ₁₂	379.367	299.1+ 0.6		-5642.3 4.6	-5318.9 4.6	931.8 0.8	212	212			
MERLINOITE Na _{0.81} K _{0.19} AlSi _{1.94} O _{5.88} ·2.13H ₂ O	239.967	282.4+ 0.4	150.6 0.5	-3591.2 2.9	-3312.0 2.9	580.2 0.5	95	95	96		
MERLINOITE K _{0.80} Na _{0.20} AlSi _{1.94} O _{5.88} ·1.81H ₂ O	244.028	276.6+ 0.4	152.2 0.5	-3519.0 2.9	-3258.0 2.9	570.8 0.5	95	95	96		
MERLINOITE KAlSi _{1.94} O _{5.88} ·1.69H ₂ O	245.088	274.3+ 0.4	151.2 0.5	-3481.8 3.0	-3227.6 3.0	565.4 0.5	95	95	96		
MERLINOITE Na _{0.81} K _{0.19} AlSi _{1.81} O _{5.62} ·2.18H ₂ O	233.057	274.6+ 0.4	153.6 0.5	-3488.3 2.8	-3212.0 2.8	562.7 0.5	95	95	96		
MERLINOITE K _{0.91} Na _{0.09} AlSi _{1.81} O _{5.62} ·1.79H ₂ O	237.629	260.5+ 0.4	151.5 0.5	-3387.3 2.8	-3131.1 2.8	548.5 0.5	95	95	96		
MERLINOITE KAlSi _{1.81} O _{5.62} ·1.69H ₂ O	237.277	259.7+ 0.5	149.8 0.5	-3360.0 2.8	-3110.2 2.8	544.9 0.5	95	95	96		

THERMODYNAMIC PROPERTIES OF SHEET STRUCTURE SILICATE MINERALS AT 298.15 K

NAME AND FORMULA	WEIGHT g	ENTROPY	VOLUME	ENTHALPY	FREE ENERGY	LOG(K)	REFERENCES		
		S° J·mol ⁻¹ ·K ⁻¹	V° cm ³	Δ _f H° kJ·mol ⁻¹	Δ _f G° kJ·mol ⁻¹		S	H/G	C
DICKITE Al ₂ Si ₂ O ₅ (OH) ₄	258.160	197.1 1.3	98.56 0.04	-4118.5 2.0	-3796.0 2.1	665.0 0.4	230	171	149
KAOLINITE Al ₂ Si ₂ O ₅ (OH) ₄	258.160	200.4 0.5	99.34 0.01	-4119.0 1.5	-3797.5 1.5	665.3 0.3	358	179	179 68
HALLOYSITE Al ₂ Si ₂ O ₅ (OH) ₄	258.160	203.0 1.3		-4101.5 10.0	-3780.7 10.0	662.4 1.8	230	171	
PYROPHYLLITE Al ₂ Si ₄ O ₁₀ (OH) ₂	360.314	239.4 0.4	128.10 0.08	-5640.0 1.5	-5266.2 1.5	922.6 0.3	365	258	258 68
ILLITE K ₃ (Al ₇ Mg)(Al ₂ Si ₁₄)O ₄₀ (OH) ₈	1553.665	1104.2 2.5	577.00 10.00				365		
MARGARITE CaAl ₂ [Al ₂ Si ₂ O ₁₀](OH) ₂	398.184	263.6 0.3	129.63 0.06	-6244.0 2.6	-5858.9 2.6	1026.4 0.5	335	68	335
PREHNITE Ca ₂ Al[AlSi ₃ O ₁₀](OH) ₂	412.384	292.8 0.7	141.10 0.10	-6202.6 2.0	-5824.7 2.0	1020.4 0.4	335	68	335
MUSCOVITE (Al/Si disordered) KAl ₂ [AlSi ₃ O ₁₀](OH) ₂	398.308	306.4 0.6	140.81 0.10	-5974.8 4.9	-5598.8 4.9	980.9 0.9	365	166	258 432 152 316
MUSCOVITE (Al/Si ordered) KAl ₂ [AlSi ₃ O ₁₀](OH) ₂	398.308	287.7 0.6	140.81 0.10	-5990.0 4.9	-5608.4 4.9	982.6 0.9	365	166	258 432 152 316
ANNITE KFe ₃ [AlSi ₃ O ₁₀](OH) ₂	511.886	415.0 10.0	154.30 0.50	-5149.3 4.0	-4798.3 4.0	840.6 0.7	186	188	188 174
PHLOGOPITE (Al/Si disordered) KMg ₃ [AlSi ₃ O ₁₀](OH) ₂	417.260	334.6 1.0	149.65 0.10	-6226.0 6.0	-5846.0 6.0	1024.2 1.0	356	356	356
PHLOGOPITE (Al/Si ordered) KMg ₃ [AlSi ₃ O ₁₀](OH) ₂	417.260	315.9 1.0	149.65 0.10	-6246.0 6.0	-5860.5 6.0	1026.7 01.0	356	356	356
FLUORPHLOGOPITE (Al/Si disorder) KMg ₃ [AlSi ₃ O ₁₀]F ₂	421.242	336.3 2.1	146.52 0.10	-6355.5 4.0	-6015.7 4.2	1053.9 0.7	218	171	218 434
FLUORPHLOGOPITE (Al/Si ordered) KMg ₃ [AlSi ₃ O ₁₀]F ₂	421.242	317.6 2.1	146.52 0.10	-6375.5 4.0	-6030.1 4.2	1056.4 0.7	218	356	218
TALC Mg ₃ Si ₄ O ₁₀ (OH) ₂	379.266	260.8 0.6	136.20 0.20	-5900.0 2.0	-5520.2 2.1	967.1 0.4	370	162	257
CHRYSOTILE (ANTIGORITE) Mg ₃ Si ₂ O ₅ (OH) ₄	277.112	221.3 0.8	107.50 0.40	-4360.0 3.0	-4032.4 3.1	706.4 0.5	226	171	226

THERMODYNAMIC PROPERTIES OF SHEET STRUCTURE SILICATE MINERALS AT 298.15 K

NAME AND FORMULA	WEIGHT g	ENTROPY	VOLUME	ENTHALPY	FREE ENERGY	LOG(K)	REFERENCES		
		S° $J \cdot mol^{-1} \cdot K^{-1}$	V° cm^3	$\Delta_f H^\circ$ $kJ \cdot mol^{-1}$	$\Delta_f G^\circ$ $kJ \cdot mol^{-1}$		S	H/G	C
CLINOCHLORE $Mg_5Al(AlSi_3O_{10})(OH)_8$	555.797	421.0 15.0	211.00 0.50	-8919.0 20.0	-8255.8 20.0	1446.3 3.5	180	182	182 204
PARAGONITE (Al/Si disordered) $NaAl_2[AlSi_3O_{10}](OH)_2$	382.200	295.8 0.9	132.1 0.1	-5933.0 3.8	-5555.7 3.9	973.3 0.7	356	356	356
PARAGONITE (Al/Si ordered) $NaAl_2[AlSi_3O_{10}](OH)_2$	382.200	277.1 0.9	132.1 0.1	-5949.3 3.8	-5568.5 3.9	975.6 0.7	356	356	356 37

COEFFICIENTS FOR HEAT CAPACITY EQUATIONS FOR SELECTED ELEMENTS

NAME AND FORMULA	ENTROPY J·mol ⁻¹ ·K ⁻¹	A1	A2 (T)	A3 (T ²)	A4 (T ^{0.5})	A5 (T ²)	T range K	T _m K	Δ _m H° kJ·mol ⁻¹
SILVER Ag (crystal)	42.55 0.21	1.126E+01	1.169E-02	-2.124E+05	2.253E+02		298 1235	1234.9	11.95
ALUMINUM Al (crystal)	28.30 0.08	4.132E+01	-1.988E-02	-1.265E+05	-1.816E+02	1.93E-05	298 933.5	933.5	10.70
ARSENIC As	35.69 0.84	2.0845E+01	6.3265E-03	-9.8777E+04	5.2398E+01		298 875		
GOLD Au (crystal)	47.49 0.21	4.197E+01	-1.770E-02		-2.161E+02	1.123E-05	298 1337.3	1337.3	12.36
BORON B (crystal)	5.83 0.08	4.758E+01	-5.227E-03	-5.903E+04	-5.899E+02	1.372E-06	298 2350		
BERYLLIUM Be (crystal)	9.50 0.08	1.8735E+01	9.293E-03	-4.502E+05			298 1550		
BISMUTH Bi	56.74 0.42	2.6852E+01	-1.7289E-02			4.1802E-05	298 544.52		
BROMINE Br ₂ (ideal gas)	249.34 0.05	4.211E+01	-2.470E-03	-3.021E+04	-8.739E+01	9.370E-07	332.5 2200		
GRAPHITE C (crystal)	5.74 0.10	6.086E+01	-1.024E-02	7.139E+05	-9.922E+02	1.669E-06	298 2500		
DIAMOND C (crystal)	2.38 0.20	9.845E+01	-3.655E-02	1.217E+06	-1.659E+03	1.098E-05	298 1800		
CALCIUM Ca (α-crystal)	42.90 0.10	-2.659E+01	5.236E-02	-4.877E+05	7.442E+02	-9.772E-06	298 716		
CADMIUM Cd (crystal)	51.80 0.15		-3.8115E-02	-1.3402E+05	3.0044E+02	-1.4336E-05	298 594.18		
CERIUM Ce (crystal)	72.00 4.00	1.4017E+01	1.9292E-02	-1.0802E+05	1.4469E+02		298 999		
CHLORINE Cl ₂ (ideal gas)	223.08 0.02	4.591E+01	-3.699E-03	-4.094E+04	-1.811E+02	1.009E-06	298 2500		
COBALT Co (crystal)	30.04 0.42		4.1844E-02	-1.5646E+05	2.6875E+02	-1.6498E-05	298 700		
CHROMIUM Cr (crystal)	23.62 0.21	-1.625E+01	2.293E-02	-1.222E+06	8.032E+02	1.232E-06	298 2100		

COEFFICIENTS FOR HEAT CAPACITY EQUATIONS FOR SELECTED ELEMENTS

NAME AND FORMULA	ENTROPY J·mol ⁻¹ ·K ⁻¹	A1	A2 (T)	A3 (T ²)	A4 (T ^{0.5})	A5 (T ²)	T range K	T _{tm} K	Δ _{tm} H° kJ·mol ⁻¹
COPPER Cu (crystal)	33.14 0.03	6.084E+01	-2.875E-02	3.331E+05	-5.671E+02	1.420E-05	298 1357.8	1357.8	13.14
COPPER Cu (liquid)	83.95 0.50	3.280E+01					1357.8 2500		
FLUORINE F ₂ (ideal gas)	202.79 0.02	4.057E+01	1.792E-03	-1.004E+05	-1.489E+02	-4.836E-07	298 2500		
GERMANIUM Ge (crystal)	31.09 0.15	2.4033E+01	3.049E-03	-1.5714E+05	0.84921E+00	-2.5E-08	298 1211.4		
HYDROGEN H ₂ (ideal gas)	130.68 0.02	4.783E+00	1.335E-02	-5.617E+05	4.583E+02	-1.825E-06	298 2500		
MERCURY Hg (liquid)	75.90 0.12	1.6815E+01	3.623E-03	-7.956E+04	1.860E+02	2.168E-06	298 629		59.2
MERCURY Hg (ideal gas)	174.97 0.02	2.079E+01					298 1800	629	
IODINE I ₂ (ideal gas)	116.14 0.30	1.3122E+01	9.111E-03	-1.0131E+06	5.3419E+02	-1.5E-07	457.7 1800		
MAGNESIUM Mg (crystal)	32.67 0.10		4.1345E-02	-2.7217E+05	3.1329E+02	-1.3745E-05	298 923	923	8.48
MAGNESIUM Mg (liquid)	73.23 0.15	3.431E+01					923 1366		
MAGNESIUM Mg (ideal gas)	148.65 0.02	2.079E+01					298 2000		
MANGANESE Mn (α-crystal)	32.01 0.08		4.1345E-02	-2.7217E+05	3.1329E+02	-1.3745E-05	298 980		
MOLYBDENUM Mo (crystal)	28.66 0.21	4.167E+01	-9.165E-03	1.082E+05	-2.882E+02	4.904E-06	298 2500		
NITROGEN N ₂ (ideal gas)	191.61 0.02	2.479E+01	9.648E-03	1.459E+05		-2.003E-06	298 2500		
SODIUM Na (liquid)	64.92 0.20	3.7482E+01	-1.9183E-02			1.0644E-05	371 1170.5		
SODIUM Na (ideal gas)	153.72 0.02	2.079E+01					298 2500		

COEFFICIENTS FOR HEAT CAPACITY EQUATIONS FOR SELECTED ELEMENTS

NAME AND FORMULA	ENTROPY $\text{J}\cdot\text{mol}^{-1}\cdot\text{K}^{-1}$	A1	A2 (T)	A3 (T^2)	A4 ($T^{0.5}$)	A5 (T^2)	T range K	T_{m} K	$\Delta_{\text{m}}H^{\circ}$ $\text{kJ}\cdot\text{mol}^{-1}$
NICKEL Ni (crystal)	29.87 0.08	1.5121E+02	-2.049E-01		-1.3746E+03	1.742E-04	298 600		
OXYGEN O ₂ (ideal gas)	205.15 0.02	5.658E+01	-5.255E-03	6.856E+05	-5.780E+02	1.113E-06	298 2500		
PHOSPHORUS P (liquid)	42.58 0.25	2.632E+01					317.3 1000		
LEAD Pb (crystal)	64.80 0.30	2.266E+01	1.0089E-01	-8.717E+04	4.0666E+01		298 600.6	600.6	4.81
PLATINUM Pt (crystal)	41.63 0.20	2.0046E+01	7.415E-03	-1.298E+05	8.738E+01	-4.798E-07	298 1800		
SULFUR S (ortho-crystal)	32.05 0.05	2.270E+01					298		
SULFUR S ₂ (ideal gas)	228.17 0.02	3.751E+01	2.173E-03	-1.645E+05	-6.575E+01	-7.275E-08	298 2500		
ANTIMONY Sb (crystal)	45.52 0.21	5.2603E+01	-3.2904E-02	1.2617E+05	-3.6512E+02	2.4691E-05	298 904		
SILICON Si (crystal)	18.81 0.08	2.431E+01	3.003E-03	-3.185E+05	-2.831E+01	2.330E-07	298 1685	1685	50.02
SILICON Si (liquid)	91.56 0.5	2.720E+01					1685 2500		
TIN Sn (crystal)	51.18 0.08	-6.8705E+01	7.2961E-02	-1.2938E+06	1.53013E+03		298 505.1		
STRONTIUM Sr (crystal)	55.69 0.03	2.3369E+01	1.066E-02	2.233E+04			298 820		
TELLURIUM Te (crystal)	49.71 0.20	1.9124E+01	2.2061E-02				298 723		
Thorium Th (crystal)	51.83 0.50	2.27467E+01	9.338E-03	-3.00023E+03	1.27357E+01	-9.09E-08	298 1650		
TITANIUM Ti (α -crystal)	30.76 0.10	2.01595E+02	-1.4675E-01	1.97328E+06	-2.7691E+03	6.28E-05	298 1166		
URANIUM U (crystal)	50.20 0.20	3.2944E+01	-7.800E-03		-9.500E+01	2.860E-05	298 942		

COEFFICIENTS FOR HEAT CAPACITY EQUATIONS FOR SELECTED ELEMENTS

NAME AND FORMULA	ENTROPY J·mol ⁻¹ ·K ⁻¹	A1	A2 (T)	A3 (T ²)	A4 (T ^{0.5})	A5 (T ²)	T range K	T _{cm} K	Δ _{cm} H° kJ·mol ⁻¹
VANADIUM V (crystal)	28.94 0.42	3.440E+00	1.334E-02	-6.971E+05	4.369E+02	2.020E-07	298 2200		
TUNGSTEN W (crystal)	32.65 0.10	3.814E+01	-5.430E-03	2.183E+05	-2.568E+02	2.552E-06	298 2500		
ZINC Zn (crystal)	41.63 0.15	2.909E+01	-3.507E-03		-6.366E+01	1.161E-05	298 692.7	692.7	7.30
ZINC Zn (liquid)	75.16 0.30	3.138E+01					692.7 1180.2		
ZINC Zn (ideal gas)	160.99 0.03	2.079E+01					1180.2 2500		
ZIRCONIUM Zr (α-crystal)	38.87 0.20	-2.585E+01	3.6755E-02	-9.032E+05	8.778E+02	-6.585E-06	298 1135	1135	4.02
ZIRCONIUM Zr (β-crystal)	79.48	2.1943E+01	-6.37E-03	-1.1452E+06	2.7991E+02	4.81E-06	1135 2000		
METHANE CH ₄	186.26 0.04	1.194E+02	2.055E-02	2.814E+06	-2.090E+03	-5.000E-06	298 1800		
COHENITE Fe ₃ C	104.40 3.40	1.073E+02	1.253E-02				298 1800		
AMMONIA NH ₃	192.77 0.03	5.139E+01	2.660E-02	7.584E+05	-5.480E+02	-4.900E-06	298 1800		

COEFFICIENTS FOR HEAT CAPACITY EQUATIONS FOR SULFIDE AND SULFOSALT MINERALS

NAME AND FORMULA	ENTROPY J·mol ⁻¹ ·K ⁻¹	A1	A2 (T)	A3 (T ⁻²)	A4 (T ^{-0.5})	A5 (T ²)	T range K	T _{tm} K	Δ _{tm} H° kJ·mol ⁻¹
ACANTHITE (ARGENTITE) Ag ₂ S	142.9 0.3	7.531E+01					298		
REALGAR AsS	63.5 0.6	4.702E+01					298		
GREENOCKITE CdS	72.2 0.3	3.538E+01	1.503E-02	-5.333E+05	2.357E+02	-2.400E-06	298 1100		
CATTIERITE CoS ₂	74.8 0.2	6.582E+01	3.032E-02	-5.870E+05			298 1000		
COVELLITE CuS	67.4 0.2	4.3049E+01	2.023E-02	-1.39938E-05	4.35838E-01		298 780		
CHALCOCITE Cu ₂ S	116.2 0.1	7.684E+01					298		
CHALCOPYRITE CuFeS ₂	124.9 0.2	-5.8753E+02	3.7073E-01	-1.4721E+07	1.275E+04		298 820		
ISS (intermediate ss) CuFeS ₂	250.5	-1.01845E+03	1.358E+00				820 930		
BORNITE Cu ₅ FeS ₄	398.5 0.8	2.429E+02					298		
TROILITE FeS	60.3 0.2	5.049E+01					298		
PYRRHOTITE Fe _{.875} S	60.7 0.2	4.988E+01					298		
PYRRHOTITE Fe _{.89} S		5.084E+01					298		
PYRRHOTITE Fe _{.90} S	63.2 0.1	5.123E+01					298		
PYRRHOTITE Fe _{.98} S		5.095E+01					298		
PYRITE FeS ₂	52.9 0.1	-2.032E+01	5.030E-02	-3.200E+06	1.787E+03		298 1015		
MARCASITE FeS ₂	53.9 0.1	3.832E+02	-3.173E-01	1.676E+06	-4.488E+03	1.676E-04	298 700		

COEFFICIENTS FOR HEAT CAPACITY EQUATIONS FOR SULFIDE AND SULFOSALT MINERALS

NAME AND FORMULA	ENTROPY J·mol ⁻¹ ·K ⁻¹	A1	A2 (T)	A3 (T ²)	A4 (T ^{0.5})	A5 (T ²)	T range K	T _m K	Δ _{tm} H° kJ·mol ⁻¹
HYDROGEN SULFIDE H ₂ S (IDEAL GAS)	205.8 0.2	2.636E+01	2.650E-02	2.660E+05	-4.356E+01	-6.024E-06	298 1800		
ALABANDITE MnS	80.3 0.8	1.353E+02	-5.775E-02	1.169E+06	-1.435E+03	2.087E-05	298 1800		
MOLYBDENITE MoS ₂	62.6 0.2	1.045E+02	-4.812E-03	-6.291E+03	-6.817E+02		298 1200		
MILLERITE NiS	53.0 0.4	4.711E+01					298		
HEAZLEWOODITE Ni ₃ S ₂	133.2 0.3	1.057E+03	-8.988E-01	8.139E+06	-1.388E+04	4.660E-04	298 840		
GALENA PbS	91.7 0.7	4.460E+01	1.640E-02				298 900		
STIBNITE Sb ₂ S ₃	182.0 3.3	1.705E+02	-4.860E-03	7.539E+05	-9.978E+02		298 829		
HERZENBERGITE SnS	77.0 0.8	-1.559E+02	1.219E-01	-3.548E+06	3.604E+03		298 875		
HERZENBERGITE SnS	135.1 1.0	2.672E+01	3.035E-02				875 1153		
BERNDTITE SnS ₂	87.5 0.2	2.004E+01	3.823E-02	-9.602E+05	8.544E+02		298 1000		
TUNGSTENITE WS ₂	67.8 0.3	7.633E+01	5.561E-04	-1.137E+06		1.408E-06	298 1500		
SPHALERITE ZnS	58.7 0.8	6.151E+01	7.631E-04	-7.963E+04	-2.604E+02		298 1300		
WURTZITE ZnS	58.8 0.2	4.191E+01	7.619E-03	-6.603E+05	1.577E+02		298 1300		
BERTHIERITE FeSb ₂ S ₄	245.0 1.0	1.000E+01	7.930E-02	-6.416E+06	3.691E+03		298 836		
CHALCOSTIBITE CuSbS ₂	149.2 3.8	8.810E+01	4.040E-02				298 826		

COEFFICIENTS FOR HEAT CAPACITY EQUATIONS FOR OXIDE AND HYDROXIDE MINERALS

NAME AND FORMULA	ENTROPY J·mol ⁻¹ ·K ⁻¹	A1	A2 (T)	A3 (T ²)	A4 (T ^{0.5})	A5 (T ²)	T range K	T _m K	Δ _{tm} H° kJ·mol ⁻¹
CORUNDUM Al ₂ O ₃	50.9 0.1	1.612E+02	-1.352E-03	-1.815E+06	-1.059E+03	5.381E-07	298 2250	2345	
BOEHMITE AlO(OH)	37.2 0.1	2.057E+02	-3.492E-02	1.027E+06	-2.635E+03		298 600		
DIASPORE AlO(OH)	35.3 0.2	5.333E+01					298		
GIBBSITE Al(OH) ₃	68.4 0.1	9.170E+01					298		
DIBORON TRIOXIDE B ₂ O ₃	54.0 0.3	1.847E+02	7.108E-03	6.441E+05	-2.270E+03		298 723		
DIBORON TRIOXIDE B ₂ O ₃ (liquid)	160.9 0.5	1.297E+02					723 2200		
BARIUM MONOXIDE BaO	72.1 0.4	5.722E+01	5.370E-03	-1.669E+05	-1.668E+02		298 1800		
BROMELLITE BeO	13.8 0.2	8.274E+01	-7.301E-03	-4.158E+05	-8.718E+02	1.845E-06	298 2000		
BISMITE Bi ₂ O ₃	151.5 2.1	1.036E+02	3.336E-02				298 800		
CARBON MONOXIDE CO (ideal gas)	197.3 0.0	3.976E+01	3.188E-03	5.292E+05	-3.013E+02	-8.078E-07	298 2500		
CARBON DIOXIDE CO ₂ (ideal gas)	213.8 0	8.811E+01	-2.698E-03	7.232E+05	-1.007E+03		298 2200		
LIME CaO	38.1 0.4	5.185E+01	2.444E-03	-9.340E+05			298 2500		
PORTLANDITE Ca(OH) ₂	83.4 0.4	1.867E+02	-2.191E-02		-1.600E+03		298 700		
CERIANITE CeO ₂	62.3 0.1	8.029E+01	5.699E-03	-7.294E+05	-2.099E+02		298 1800		
COBALT MONOXIDE CoO	52.8 0.3	-3.047E+01	2.946E-02	-4.166E+06	1.932E+03		298 1800		
TRICOBALT TETROXIDE Co ₃ O ₄	109.3 0.3	1.316E+02	6.602E-02	-2.480E+06			298 1000		

COEFFICIENTS FOR HEAT CAPACITY EQUATIONS FOR OXIDE AND HYDROXIDE MINERALS

NAME AND FORMULA	ENTROPY J·mol ⁻¹ ·K ⁻¹	A1	A2 (T)	A3 (T ²)	A4 (T ^{-0.6})	A5 (T ²)	T range K	T _{tm} K	Δ _{tm} H° kJ·mol ⁻¹
ESKOLAITE Cr ₂ O ₃	81.2 1.2	1.190E+02	9.496E-03	-1.442E+06	-3.405E+00		298 1800		
TENORITE CuO	42.6 0.2	3.097E+01	1.374E-02	-1.258E+06	3.693E+02		298 1400		
CUPRITE Cu ₂ O	92.4 0.3	4.260E+02	-2.508E-01	4.898E+06	-6.078E+03	9.244E-05	298 1500		
WUSTITE Fe ₉₄₇ O	56.6 0.4	-1.930E+01	3.017E-02	-2.533E+06	1.501E+03		298 1652		
FERROUS OXIDE FeO (fictive)	60.6 1.7	3.908E+01	8.574E-03	-7.325E+05	2.466E+02		298 1800		
HEMATITE Fe ₂ O ₃	87.4 0.2	1.50147E+03	-1.2146E+00	1.4123E+07	-2.1493E+04	5.690E-04	298 950	950	1.24
HEMATITE Fe ₂ O ₃	243.8 1.0	-1.0957E+03	2.7267E-01	-1.0239E+08	3.396E+04		950 1800		
MAGNETITE Fe ₃ O ₄	146.1 0.4	2.65911E+03	-2.5215E+00	2.0734E+07	-3.6455E+04	1.3677E-03	298 800		
MAGNETITE Fe ₃ O ₄	369.1 0.6	9.6823E+01	5.2733E-02	5.6413E+07			900 1800		
STEAM H ₂ O (ideal gs)	188.8 0.04	2.7057E+01	1.7584E-02	2.7696E+05	-2.7656E+01	-2.5097E-06	298 2500		
DIPOTASSIUM MONOXIDE K ₂ O	94.1 6.3	7.450E+01	3.965E-02	-2.346E+05			298 2000		
DILITHIUM MONOXIDE Li ₂ O	37.6 0.8	6.133E+01	3.568E-02	-1.168E+06	-7.050E+01	-7.318E-06	298 2000		
PERICLASE MgO	26.9 0.2	6.653E+01	-6.143E-03	-6.093E+05	-3.592E+02	2.451E-06	298 2500		
BRUCITE Mg(OH) ₂	63.2 0.1	1.022E+02	1.511E-02	-2.617E+06			298 900		
MANGANOSITE MnO	59.7 0.1	6.028E+01	3.510E-03		-2.975E+02		298 2000		
PYROLUSITE MnO ₂	52.8 0.1	2.904E+02	-1.442E-01	2.012E+06	-3.787E+03	4.541E-05	298 850		

COEFFICIENTS FOR HEAT CAPACITY EQUATIONS FOR OXIDE AND HYDROXIDE MINERALS

NAME AND FORMULA	ENTROPY J·mol ⁻¹ ·K ⁻¹	A1	A2 (T)	A3 (T ²)	A4 (T ^{0.5})	A5 (T ²)	T range K	T _{cm} K	Δ _{cm} H ⁰ kJ·mol ⁻¹
BIXBYITE Mn ₂ O ₃	113.7 0.2	1.624E+02	1.211E-02	1.046E+06	-1.317E+03	3.462E-06	325 1400		
HAUSMANNITE Mn ₃ O ₄	164.1 0.3	-7.432E+00	9.487E-02	-6.712E+06	3.396E+03		298 1400		
BRAUNITE Mn ₇ SiO ₁₂	416.4 0.8	4.301E+02	1.110E-01	-7.325E+06			298 1500		
MOLYBDITE MoO ₃	77.7 0.4	6.433E+00	6.278E-02	-2.460E+06	1.337E+03		298 1074	1074	
NITROGEN DIOXIDE NO ₂	240.1 0.1	1.018E+02	-1.121E-02	1.218E+06	-1.300E+03	1.461E-06	298 2500		
DISODIUM MONOXIDE Na ₂ O	75.3 0.8	1.1397E+02	7.4857E-03		-8.1335E+02		298 1000		
BUNSENITE NiO	38.0 0.2	4.1107E+03	-5.3024E+00	2.43067E+07	-5.3039E+04	3.5206E-03	298 519		
BUNSENITE NiO	67.7 0.5	-8.776E+00	4.223E-02	3.607E+06	7.873E+02	-7.526E-06	519 1800		
LITHARGE PbO	66.5 0.2	5.102E+01	1.027E-02	-7.387E+05			298 1000		
PLATTNERITE PbO ₂	71.8 0.4	7.312E+01	7.484E-03	-1.261E+06			298 1200		
MINIUM Pb ₃ O ₄	212.0 6.7	1.779E+02	3.326E-02	-2.926E+06			298 1800		
SULFUR DIOXIDE SO ₂ (IDEAL GAS)	248.2 0.1	9.890E+01	-1.161E-02	8.465E+05	-1.127E+03	1.788E-06	298 2500		
SULFUR TRIOXIDE SO ₃ (IDEAL GAS)	256.8 0.8	1.478E+02	-1.898E-02	1.079E+06	-1.794E+03	2.763E-06	298 2500		
SILICON MONOXIDE SiO (IDEAL GAS)	211.6 0.8	5.686E+01	-5.616E-03	4.922E+05	-5.335E+02	8.5943E-07	298 2500		
QUARTZ SiO ₂	41.5 0.1	8.1145E+01	1.828E-02	-1.810E+05	-6.985E+02	5.406E-06	298 844		
QUARTZ SiO ₂	104.6 0.2	5.796E+01	9.330E-03	1.835E+06			844 1700		

COEFFICIENTS FOR HEAT CAPACITY EQUATIONS FOR OXIDE AND HYDROXIDE MINERALS

NAME AND FORMULA	ENTROPY J·mol ⁻¹ ·K ⁻¹	A1	A2 (T)	A3 (T ²)	A4 (T ^{0.5})	A5 (T ²)	T range K	T _m K	Δ _{tm} H° kJ·mol ⁻¹
CRISTOBALITE SiO ₂	43.4 0.1	-4.160E+03	2.548E+00	-6.286E+07	7.168E+04		298 523		
CRISTOBALITE SiO ₂	76.3 1.0	7.275E+01	1.300E-03	-4.132E+06			523 1800		
COESITE SiO ₂	38.5 1.0	2.331E+02	-7.777E-02	2.604E+06	-3.375E+03	1.924E-05	298 1800		
STISHOVITE SiO ₂	27.8 0.4	1.474E+02	-4.027E-02	-2.834E+05	-1.559E+03	1.203E-05	298 1800		
SILICA GLASS SiO ₂	48.5 1.0	7.464E+01	-7.259E-03	-3.114E+06		5.570E-06	298 1700		
CASSITERITE SnO ₂	49.0 0.1	7.604E+01	7.364E-03	-2.224E+06			298 1500		
STRONTIUM MONOXIDE SrO	55.5 0.4	5.365E+01	5.982E-03	-3.666E+05	-1.019E+02		298 2500		
THORIANITE ThO ₂	65.2 0.2	7.138E+01	7.556E-03	-1.053E+06			298 1200		
RUTILE TiO ₂	50.6 0.2	8.462E+01	5.990E-04	-1.101E+06	-2.957E+02		298 2100		
ANATASE TiO ₂	49.9 0.3	4.396E+01	1.374E-02	-2.595E+06	6.294E+02		298 1300		
URANINITE UO ₂	77.0 0.2	5.845E+01	1.606E-02	-1.867E+06	3.689E+02		298 1800		
KARELIANITE V ₂ O ₃	98.1 1.3	5.799E+01	4.120E-02	-3.872E+06	1.351E+03		298 1800		
TUNGSTEN DIOXIDE WO ₂	50.6 0.3	6.638E+01	1.326E-02	-1.294E+06			298 2500		
ZINCITE ZnO	43.2 0.1	4.350E+01	7.658E-03	-7.573E+05	5.456E+01		298 1800		
BADDELEYITE ZrO ₂	50.4 0.3	1.073E+02	-5.011E-03	-2.203E+05	-8.141E+02		298 1478	1478	8.08
BADDELEYITE ZrO ₂	167.1 1.5	7.448E+01					1478 2000		

COEFFICIENTS FOR HEAT CAPACITY EQUATIONS FOR MULTIPLE OXIDE MINERALS

NAME AND FORMULA	ENTROPY J·mol ⁻¹ ·K ⁻¹	A1	A2 (T)	A3 (T ²)	A4 (T ^{0.5})	A5 (T ²)	T range K	T _{tm} K	Δ _{tm} H ⁰ kJ·mol ⁻¹
TIALITE Al ₂ TiO ₅	109.6 0.8	2.111E+02	1.461E-02	-3.625E+06	-6.610E+02		298 1800		
CHRYSOBERYL BeAl ₂ O ₄	66.3 0.1	3.627E+02	-8.353E-02	-6.798E+04	-4.034E+03	2.248E-05	298 1800		
CALCIUM FERRITE CaFe ₂ O ₄	145.4 0.8	9.588E+01	4.666E-02	-3.360E+06	1.410E+03		298 1510		
DICALCIUM FERRITE Ca ₂ Fe ₂ O ₅	188.8 1.3	2.223E+02	9.728E-03	-5.661E+06	5.420E+02		298 1750		
PEROVSKITE CaTiO ₃	93.6 0.4	1.250E+01	4.516E-02	-6.302E+06	2.462E+03		298 1530		
HERCYNITE FeAl ₂ O ₄	116.0 3.0	2.247E+02	4.480E-03	-1.581E+06	-1.370E+03		298 1200		
CHROMITE FeCr ₂ O ₄	146.0 1.7	3.018E+02	-4.157E-02	4.877E+05	-2.803E+03	1.147E-05	298 1800		
ILMENITE FeTiO ₃	108.9 0.3	2.627E+02	-7.999E-02	3.827E+05	-2.538E+03	3.388E-05	298 1000		
ULVOSPINEL Fe ₂ TiO ₄	168.9 2.5	-1.026E+02	1.425E-01	-9.145E+06	5.271E+03		298 1800		
PSEUDOBROOKITE Fe ₂ TiO ₅	156.5 1.3	2.136E+02	1.625E-02	-2.345E+06	-4.795E+02		298 1800		
SPINEL MgAl ₂ O ₄	84.5 0.04	2.229E+02	6.127E-03	-1.686E+06	-1.551E+03		298 1800		
MAGNESIOCHROMITE MgCr ₂ O ₄	106.0 0.8	1.961E+02	5.398E-03	-3.126E+06	-6.169E+02		298 1800		
MAGNESIOFERRITE MgFe ₂ O ₄	123.8 0.8	1.782E+02	1.275E-02				665 1230		
MAGNESIOFERRITE MgFe ₂ O ₄	379.2 3.0	1.066E+02	5.716E-02				1230 1800		
GEIKIELITE MgTiO ₃	74.6 0.2	2.225E+02	-5.274E-02	-6.092E+05	-1.8746E+03	1.878E-05	298 1800		
PYROPHANITE MnTiO ₃	104.9 0.3	1.217E+02	9.288E-03	-2.188E+06			298 1600		

THERMODYNAMIC PROPERTIES OF MINERALS AND RELATED SUBSTANCES

COEFFICIENTS FOR HEAT CAPACITY EQUATIONS FOR MULTIPLE OXIDE MINERALS

NAME AND FORMULA	ENTROPY $\text{J}\cdot\text{mol}^{-1}\cdot\text{K}^{-1}$	A1	A2 (T)	A3 (T^2)	A4 ($T^{0.5}$)	A5 (T^2)	T range K	T_{tm} K	$\Delta_{\text{tm}}H^\circ$ $\text{kJ}\cdot\text{mol}^{-1}$
TREVORITE NiFe_2O_4	165.0 3.0	9.559E+01	1.705E-01	3.9927E+04			298 1000		
FRANKLINITE ZnFe_2O_4	150.7 0.3	1.995E+02	3.045E-02	-1.352E+06			298 600		
ZINC TITANIUM SPINEL Zn_2TiO_4	143.1 0.3	2.613E+02	-5.138E-03	-4.317E+05	-2.095E+03		298 1800		

COEFFICIENTS FOR HEAT CAPACITY EQUATIONS FOR HALIDE MINERALS

NAME AND FORMULA	ENTROPY J·mol ⁻¹ ·K ⁻¹	A1	A2 (T)	A3 (T ²)	A4 (T ^{-0.6})	A5 (T ²)	T range K	T _m K	Δ _m H° kJ·mol ⁻¹
BROMARGYRITE AgBr	107.1 0.4	3.317E+01	6.443E-02				298 703		
POTASSIUM BROMIDE KBr	95.9 0.2	-4.392E+01	5.855E-02	-1.839E+06	1.717E+03		298 1000		
CHLORARGYRITE AgCl	96.2 0.2	5.996E+01	7.620E-03	-1.017E+06			298 728		
HYDROPHILITE CaCl ₂	104.6 1.3	-4.725E+00	4.504E-02	-2.037E+06	1.503E+03		298 1045	1045	28.54
HYDROPHILITE CaCl ₂ (liquid)	230.2 5.0	1.025E+02					1045 1800		
LAWRENCITE FeCl ₂	118.0 0.4	-1.123E+02	8.951E-02	-5.115E+06	3.790E+03		298 950		
MOLYSITE FeCl ₃	142.3 0.4	-2.56E+02	1.1755E+00	7.89E+06		-9.738E-04	298 577		
HYDROGEN CHLORIDE HCl (ideal gas)	186.9 0.03	1.738E+01	1.165E-02	-7.597E+03	1.477E+02	-2.052E-06	298 2500		
SYLVITE KCl	82.6 0.2	-2.452E+01	4.852E-02	-1.605E+06	1.371E+03		298 1043		
CHLOROMAGNESITE MgCl ₂	89.6 0.8	7.690E+01	8.496E-03	-7.463E+05			298 987		
SCACCHITE MnCl ₂	118.2 0.2	7.626E+01	1.191E-02	-6.048E+05			298 923		
SALAMMONIAC NH ₄ Cl	95.0 0.4	8.410E+01					298		
HALITE NaCl	72.1 0.2	4.515E+01	1.797E-02				298 1074		
HALITE NaCl (liquid)	170.3 2.2	7.2008E+01	-3.2228E-03				1074 1791		
NICKELOUS CHLORIDE NiCl ₂	97.7 0.2	-5.078E+01	5.748E-02	-4.064E+06	2.608E+03		298 1303		
COTUNNITE PbCl ₂	136.0 2.1	1.229E+02			-8.585E+02		298 768		

COEFFICIENTS FOR HEAT CAPACITY EQUATIONS FOR HALIDE MINERALS

NAME AND FORMULA	ENTROPY J·mol ⁻¹ ·K ⁻¹	A1	A2 (T)	A3 (T ²)	A4 (T ^{0.5})	A5 (T ²)	T range K	T _{tm} K	Δ _{tm} H° kJ·mol ⁻¹
FLUORITE CaF ₂	68.9 0.3	2.033E+03	-1.436E+00	2.988E+07	-3.312E+04	5.040E-04	298 1400		
HYDROGEN FLUORIDE HF (ideal gas)	173.8 0.04	6.845E+00	1.301E-02	-4.108E+05	4.007E+02	-1.911E-06	298 2500		
SELLAITE MgF ₂	57.3 0.4	9.474E+01	1.595E-04	-7.328E+05	-4.322E+02		298 1536	1536	58.16
VILLIAMITE NaF	51.5 0.1	-2.612E+00	3.347E-02	-1.402E+06	9.542E+02		298 1269	1269	33.14
CRYOLITE Na ₃ AlF ₆	238.5 0.5	4.04227E+03	-3.8582E+00	3.4071E+07	-5.5876E+04	2.004E-03	298 836	836	8.20
CRYOLITE Na ₃ AlF ₆	512.4 2.5	2.3669E+02	4.7986E-02				836 1153	1153	1.8
CRYOLITE Na ₃ AlF ₆	605.5 2.5	3.0041E+02					1153 1290	1290	113.75
CHIOLITE Na ₅ Al ₃ F ₁₄	515.3 0.8	5.099E+02	8.768E-02	-7.301E+06			298 1010	1010	80.83
IODARGYRITE AgI	115.5 1.7	2.4351E+01	1.0083E-02				298 423		
MARSHITE CuI	96.6 0.5	-1.6941E+03	1.0046E+00	-2.8543E+07	3.0558E+04		298 643		

COEFFICIENTS FOR HEAT CAPACITY EQUATIONS FOR CARBONATE AND NITRATE MINERALS

NAME AND FORMULA	ENTROPY J·mol ⁻¹ ·K ⁻¹	A1	A2 (T)	A3 (T ²)	A4 (T ^{0.5})	A5 (T ²)	T range K	T _m K	Δ _m H ⁰ kJ·mol ⁻¹
WITHERITE BaCO ₃	112.1 2.1	-9.936E+01	1.258E-01	-6.274E+06	3.760E+03		298 1079		
ARAGONITE CaCO ₃	88.0 0.2	8.153E+01	4.567E-02	-1.141E+06			298 1000		
CALCITE CaCO ₃	91.7 0.2	9.972E+01	2.692E-02	-2.158E+06			298 1200		
DOLOMITE CaMg(CO ₃) ₂	155.2 0.3	5.479E+02	-1.676E-01	2.840E+06	-6.548E+03	7.708E-05	298 1100		
SIDERITE FeCO ₃	95.5 0.2	2.574E+02	-4.620E-02	1.523E+06	-3.082E+03		298 600		
MAGNESITE MgCO ₃	65.1 0.1	8.112E+01	5.225E-02	-1.832E+06			298 1000		
RHODOCHROSITE MnCO ₃	98.0 0.1	1.497E+02	1.876E-02	1.417E+05	-1.3142E+03		298 600		
THERMONATRITE Na ₂ CO ₃ ·H ₂ O	168.1 0.8	7.240E+01	2.607E-01	-1.258E+05			298 380		
DAWSONITE NaAlCO ₃ (OH) ₂	132.0 0.5	3.441E+01	3.347E-04	7.464E+02			298 500		
STRONTIANITE SrCO ₃	97.1 1.7	-1.618E+02	1.2795E-01	-9.018E+06	5.294E+03		298 1197	1197	18.82
SMITHSONITE ZnCO ₃	81.2 0.2	1.4838E+02	2.835E-02	4.796E+05	-1.419E+03		298 1200		
NITROBARITE Ba(NO ₃) ₂	213.8 0.8	1.255E+02	1.497E-01	-1.670E+06			298 800		
CALCIUM NITRATE Ca(NO ₃) ₂	193.3 0.4	7.815E+01	1.734E-01	-2.778E+06	8.722E+02		298 800		
MAGNESIUM NITRATE Mg(NO ₃) ₂	164.0 0.8	5.8417E+01	2.7292E-01	1.8949E+05			298 600		
SODA NITER NaNO ₃	116.5 0.7	2.570E+01	2.237E-01		1.161E+01		298 549		
STRONTIUM NITRATE Sr(NO ₃) ₂	194.6 0.5	1.3389E+03	-3.79E-01	2.5757E+07	-2.3582E+04		298 900		

COEFFICIENTS FOR HEAT CAPACITY EQUATIONS FOR SULFATE AND PHOSPHATE MINERALS

NAME AND FORMULA	ENTROPY J·mol ⁻¹ ·K ⁻¹	A1	A2 (T)	A3 (T ²)	A4 (T ^{0.5})	A5 (T ²)	T range K	T _{cm} K	Δ _{cm} H° kJ·mol ⁻¹
ALUMINUM SULFATE Al ₂ (SO ₄) ₃	239.3 1.2	7.877E+02	-9.899E-02		-8.615E+03		298 1100		
BARITE BaSO ₄	132.2 0.8	1.412E+02			-3.507E+06		298 1300		
ANHYDRITE CaSO ₄	107.4 0.2	3.728E+02	-1.574E-01	1.695E+06	-4.3308E+03	7.99E-05	298 1000		
CHALCOCYANITE CuSO ₄	109.5 0.6	1.615E+02	4.796E-02	-3.192E+06			298 1200		
FERRIC SULFATE Fe ₂ (SO ₄) ₃	282.8 0.8	2.553E+02	2.269E-01	-4.260E+06			298 800		
ARCANITE α-K ₂ SO ₄	175.6 0.4	1.2037E+02	9.958E-02	-1.782E+06			298 856		
ARCANITE β-K ₂ SO ₄	360.9 1.0	-8.445E+02	6.845E-01	3.499E+08			856 1342		
K-AL SULFATE KAl(SO ₄) ₂	204.6 1.3	2.370E+02	7.828E-02	-5.988E+06			298 1000		
ALUNITE KAl ₃ (OH) ₆ (SO ₄) ₂	321.0 5.0	5.145E+03	1.1375E-01	-1.5635E+07			298 700		
LANGBEINITE K ₂ Mg ₂ (SO ₄) ₃	389.3 0.8	5.359E+02	1.101E-01	-1.020E+06	-4.040E+03	-4.909E-05	298 1000		
MAGNESIUM SULFATE MgSO ₄	91.4 0.8	1.056E+02	4.717E-02	-2.129E+06			298 1400		
MANGANOUS SULFATE MnSO ₄	127.0 2.0	1.203E+02	3.999E-02	-2.818E+06			298 1000		
MASCAGNITE (NH ₄) ₂ SO ₄	220.5 1.3	1.0436E+02	2.788E-01				298 600		
THENARDITE Na ₂ SO ₄ (hexagonal)	239.7 1.0	1.2193E+02	8.141E-02				514 1155		
THENARDITE Na ₂ SO ₄ (liquid)	424.6 2.0	2.011E+02	-3.941E-03				1155 1800		
NICKELOUS SULFATE NiSO ₄	101.3 0.2	1.240E+02	3.062E-02	-3.150E+06			298 1200		

COEFFICIENTS FOR HEAT CAPACITY EQUATIONS FOR SULFATE AND PHOSPHATE MINERALS

NAME AND FORMULA	ENTROPY $\text{J}\cdot\text{mol}^{-1}\cdot\text{K}^{-1}$	A1	A2 (T)	A3 (T^2)	A4 ($T^{0.5}$)	A5 (T^2)	T range K	T_{tm} K	$\Delta_{\text{tm}}H^\circ$ $\text{kJ}\cdot\text{mol}^{-1}$
ANGLESITE PbSO_4	148.5 0.6	4.683E+01	1.278E-01	1.724E+06			298 1100		
ZINKOSITE ZnSO_4	110.5 1.3	4.019E+01	1.243E-01	2.389E+06			298 1100		
BERLINITE AlPO_4	90.8 0.2	1.9833E+03	-1.64948E+00	2.0607E+07	-2.93193E+04	7.72E-04	298 830		
WHITLOCKITE $\text{Ca}_3(\text{PO}_4)_2$	236.0 0.8	1.929E+02	1.742E-01	-1.174E+06			298 1373		
FLUORAPATITE $\text{Ca}_5(\text{PO}_4)_3(\text{F})$	387.9 1.7	7.543E+02	-3.026E-02	-9.084E+05	-6.201E+03		298 1600		
HYDROXYAPATITE $\text{Ca}_5(\text{PO}_4)_3(\text{OH})$	390.4 1.7	3.878E+02	1.186E-01	-1.270E+07	1.811E+03		298 1500		

COEFFICIENTS FOR HEAT CAPACITY EQUATIONS FOR ORTHO AND RING STRUCTURE SILICATE MINERALS

NAME AND FORMULA	ENTROPY J·mol ⁻¹ ·K ⁻¹	A1	A2 (T)	A3 (T ²)	A4 (T ^{0.5})	A5 (T ²)	T range K	T _{tm} K	Δ _{tm} H° kJ·mol ⁻¹
TOPAZ Al ₂ SiO ₄ F ₂	105.4 0.2	4.714E+02	-8.165E-02	1.270E+06	-5.486E+03		298 1000		
KYANITE Al ₂ SiO ₅	82.8 0.5	2.794E+02	-7.124E-03	-2.056E+06	-2.289E+03		298 2000		
ANDALUSITE Al ₂ SiO ₅	91.4 0.1	2.77306E+02	-6.588E-03	-1.9141E+06	-2.2656E+03		298 2000		
SILLIMANITE Al ₂ SiO ₅	95.4 0.6	2.8019E+02	-6.900E-03	-1.376E+06	-2.399E+03		298 2000		
MULLITE Al ₆ Si ₂ O ₁₃	275.0 5.0	7.546E+02	-2.943E-02	-3.454E+06	-6.576E+03		298 1800		
DUMORTIERITE Al _{6.75} □ _{0.25} Si ₃ BO _{17.25} (OH) _{0.75}	334.9 5.0	1.43871E+03	-2.427E-01	3.860E+06	-1.682E+04	4.884E-05	298 1800		
PHENAKITE Be ₂ SiO ₄	63.4 0.3	4.2849E+02	-9.958E-02	2.083E+06	-5.6705E+03	1.989E-05	298 1800		
BERYL Be ₃ Al ₂ (Si ₆ O ₁₈)	346.7 4.7	1.625E+03	-4.252E-01	6.825E+06	-2.018E+04	1.203E-04	298 1800		
BERTRANDITE Be ₄ Si ₂ O ₇ (OH) ₂	172.1 0.8	8.253E+02	-9.965E-02	3.662E+06	-1.057E+04		298 1400		
EUCLASE BeAlSiO ₄ (OH)	89.1 0.4	5.329E+02	-1.507E-01	2.198E+06	-6.726E+03	4.122E-05	298 1800		
EPIDOTE Ca ₂ Al ₂ Fe ₂ Si ₃ O ₁₂ (OH)	328.9 2.5	3.676E+02					298		
LAWSONITE CaAl ₂ Si ₂ O ₇ (OH) ₂ H ₂ O	230.0 0.4	2.7732E+02	2.341E-01	-6.389E+06			298 600		
GEHLENITE Ca ₂ Al ₂ SiO ₇	210.1 0.6	4.057E+02	-7.099E-03	-1.188E+06	-3.174E+03		298 1800		
ZOISITE Ca ₂ Al ₃ Si ₃ O ₁₂ (OH)	295.9 0.3	1.134E+03	-4.523E-01		-1.157E+04	2.391E-04	298 750		
GROSSULAR Ca ₃ Al ₂ Si ₃ O ₁₂	260.1 0.5	1.5293E+03	-6.990E-01	7.443E+06	-1.894E+04	2.530E-04	298 1200		
GLASS Ca ₃ Al ₂ Si ₃ O ₁₂	329.9+ 0.7	3.392E+02					298		

COEFFICIENTS FOR HEAT CAPACITY EQUATIONS FOR ORTHO AND RING STRUCTURE SILICATE MINERALS

NAME AND FORMULA	ENTROPY J·mol ⁻¹ ·K ⁻¹	A1	A2 (T)	A3 (T ²)	A4 (T ^{0.5})	A5 (T ²)	T range K	T _m K	Δ _m H ⁰ kJ·mol ⁻¹
DATOLITE CaB(SiO ₄)(OH)	110.2 0.6	1.9446E+02	1.8447E-01	4.0191E+05	-2.0305E+03	-1.01E-04	298 1000		
ILVAITE CaFe ₃ (Si ₂ O ₇)O(OH)	292.3 0.6	8.569E+03	-5.2407E+00	9.6449E+07	-1.3456E+05		290 376		
ANDRADITE Ca ₃ Fe ₂ Si ₃ O ₁₂	316.4 2.0	8.092E+02	-7.025E-02	-6.789E+05	-7.403E+03		298 1000		
MONTICELLITE CaMgSiO ₄	108.1 0.3	2.314E+02	-8.531E-04	-1.247E+06	-1.623E+03	-1.333E-06	298 1000		
AKERMANITE Ca ₂ MgSi ₂ O ₇	212.5 0.4	7.8146E+01	1.6573E-01	-6.7905E+06	2.8646E+03	-3.3437E-05	298 1731	357.9	0.68
MERWINITE Ca ₃ Mg(SiO ₄) ₂	253.1 2.1	6.508E+02	-1.816E-01		-6.053E+03	7.036E-05	298 1600		
TITANITE (Sphene) CaTiSiO ₅	129.2 0.8	1.767E+02	2.385E-02	-3.991E+06			298 1670		
LARNITE α-Ca ₂ SiO ₄	127.6 0.8	2.487E+02	-8.315E-04	-9.077E+04	-2.052E+03		298 970		
BREDIGITE α'-Ca ₂ SiO ₄	314.2 1.0	1.3456E+02	4.611E-02				970 1710		
CALCIO-OLIVINE γ-Ca ₂ SiO ₄	120.5 0.8	1.327E+02	5.251E-02	-1.905E+06			298 1200		
NATURITE (ALITE) Ca ₃ SiO ₅	168.6 0.3	3.339E+02	-4.651E-03	-6.526E+04	-2.766E+03		298 1800		
RANKINITE Ca ₃ Si ₂ O ₇	210.6 2.9	4.732E+02	-4.207E-02	3.397E+05	-4.319E+03		298 1400		
ROSENHANNITE Ca ₃ Si ₃ O ₈ (OH) ₂	281.8 3.0	3.650E+02	5.419E-02	-8.161E+06			298 1800		
SPURRITE Ca ₅ (SiO ₄) ₂ CO ₃	331.0 2.0	6.141E+02	-3.508E-03	-2.493E+06	-4.168E+03		298 1300		
TILLEYITE Ca ₅ Si ₂ O ₇ (CO ₃) ₂	394.0 4.0	7.417E+02	-5.345E-03	-1.435E+06	-5.879E+03		298 1200		
COBALT-OLIVINE Co ₂ SiO ₄	142.6 0.2	3.0583E+02	-3.195E-02	2.693E+05	-2.865E+03		298 1100		

COEFFICIENTS FOR HEAT CAPACITY EQUATIONS FOR ORTHO AND RING STRUCTURE SILICATE MINERALS

NAME AND FORMULA	ENTROPY J·mol ⁻¹ ·K ⁻¹	A1	A2 (T)	A3 (T ²)	A4 (T ^{0.5})	A5 (T ²)	T range K	T _m K	Δ _m H° kJ·mol ⁻¹
FAYALITE Fe ₂ SiO ₄	151.0 0.2	1.7602E+02	-8.808E-03	-3.889E+06		2.471E-05	298 1490	1490	
ALMANDINE Fe ₃ Al ₂ Si ₃ O ₁₂	342.6 1.4	8.629E+02	-8.288E-02	1.697E+06	-8.875E+03		298 1200		
STAUROLITE Fe ₄ Al ₁₈ Si ₈ O ₄₆ (OH) ₂	985.0 4.0	2.798E+03	7.921E-02	-9.952E+06	-2.474E+04		298 1000		
OSUMILITE KMg ₂ Al ₃ [Si ₁₀ Al ₂ O ₃₀]·H ₂ O		5.842E+02	1.276E+00	-3.967E+06	-1.556E+03	-6.497E-04	298 1000		
CORDIERITE Mg ₂ Al ₃ (AlSi ₅ O ₁₈)	407.2 3.8	8.123E+02	4.334E-02	-8.211E+06	-5.000E+03		298 1700		
FORSTERITE Mg ₂ SiO ₄	94.1 0.1	8.736E+01	8.717E-02	-3.699E+06	8.436E+02	-2.237E-05	298 1800		
PYROPE Mg ₃ Al ₂ Si ₃ O ₁₂	266.3 0.8	8.730E+02	-1.374E-01	4.500E+03	-8.794E+03	3.341E-05	298 1570	1570	241.0
GLASS Mg ₃ Al ₂ Si ₃ O ₁₂	346.3 12.0	5.138E+02	7.119E-02	-5.857E+05	-2.439E+03		298 1020		
GLASS Mg ₃ Al ₂ Si ₃ O ₁₂		6.300E+02	3.50E-02				1083 1863		
PYROPE-GROSSULAR ss (Mg _{1.8} Ca _{1.2})Al ₂ Si ₃ O ₁₂	268.3+ 0.5	3.280E+02					298		
GLASS (Mg _{1.5} Ca _{1.5})Al ₂ Si ₃ O ₁₂	311.8+ 0.6	3.329E+02					298		
TEPHROITE Mn ₂ SiO ₄	155.9 0.5	2.613E+02	-1.378E-02		-2.218E+03		298 1600		
LIEBENBERGITE Ni ₂ SiO ₄	128.1 0.2	2.897E+02	-2.402E-02	1.310E+05	-2.779E+03		298 1300		
Ni ₂ SiO ₄ -SPINEL Ni ₂ SiO ₄	124.1 0.4	1.654E+02	1.412E-02	-4.345E+06			350 800		
WILLEMITE Zn ₂ SiO ₄	131.4 0.8	1.233E+02					298		
ZIRCON ZrSiO ₄	84.0 1.3	2.370E+02	-1.788E-02	-1.496E+05	-2.268E+03		298 1600		

COEFFICIENTS FOR HEAT CAPACITY EQUATIONS FOR CHAIN STRUCTURE SILICATE MINERALS

NAME AND FORMULA	ENTROPY J·mol ⁻¹ ·K ⁻¹	A1	A2 (T)	A3 (T ²)	A4 (T ^{-0.5})	A5 (T ²)	T range K	T _{tm} K	Δ _{tm} H° kJ·mol ⁻¹
WOLLASTONITE CaSiO ₃	81.7 0.1	2.0078E+02	-2.589E-02	-1.579E+05	-1.826E+03	7.434E-06	298 1400	1398	5.93
PSEUDOWOLLASTONITE CaSiO ₃	87.2 0.9	1.578E+02	-1.045E-03	-6.396E+05	-1.077E+03		298 1821	1821	57.30
GLASS CaSiO ₃	94.8 3.0	9.689E+01	3.425E-02	-1.804E+06			298 1821		
Ca-Al PYROXENE CaAl ₂ SiO ₆	141.0 2.0	4.652E+02	-7.838E-02	6.729E+05	-4.941E+03	1.934E-05	298 1000		
GLASS CaAl ₂ SiO ₆	155.3 0.3	1.661E+02					298		
FERROBUSTAMITE CaFeSi ₂ O ₆	180.5 0.3	4.038E+02	-4.444E-02		-3.757E+03	1.597E-05	298 1600		
HEDENBERGITE CaFeSi ₂ O ₆	174.2 0.3	3.1046E+02	1.257E-02	-1.846E+06	-2.040E+03		298 1300		
GLASS CaFeSi ₂ O ₆	185.7+ 0.4	1.732E+02					298		
DIOPSIDE CaMgSi ₂ O ₆	142.7 0.3	4.7025E+02	-9.864E-02	2.454E+05	-4.823E+03	2.813E-05	298 1700	1668	137.70
GLASS CaMgSi ₂ O ₆	166.0 3.0	1.041E+03	-6.358E-01	6.677E+06	-1.351E+04	2.724E-04	298 1400		
FERROSILITE FeSiO ₃	94.6 0.3	1.243E+02	1.454E-02	-3.378E+06			298 800		
α-SPODUMENE LiAlSi ₂ O ₆	129.3 0.8	4.212E+02	-2.401E-02	1.910E+06	-4.776E+03		298 1200		
β-SPODUMENE LiAlSi ₂ O ₆	154.4 1.2	3.628E+02	-3.684E-03		-3.435E+03		298 1700		
ENSTATITE MgSiO ₃	66.3 0.1	3.507E+02	-1.472E-01	1.769E+06	-4.296E+03	5.826E-05	298 1000	1834	73.20
GLASS MgSiO ₃	74.1 0.2	8.205E+01					298		
CLINOENSTATITE MgSiO ₃	67.9 0.4	2.056E+02	-1.280E-02	1.193E+06	-2.298E+03		298 1600		

COEFFICIENTS FOR HEAT CAPACITY EQUATIONS FOR CHAIN STRUCTURE SILICATE MINERALS

NAME AND FORMULA	ENTROPY J·mol ⁻¹ ·K ⁻¹	A1	A2 (T)	A3 (T ²)	A4 (T ^{0.5})	A5 (T ²)	T range K	T _{tm} K	Δ _{tm} H° kJ·mol ⁻¹
MgSiO ₃ -ILMENITE MgSiO ₃	60.4 3.0	6.912E+01	7.330E-02	1.037E+06			298 700		
HYPERSTHENE (Mg _{0.85} Fe _{0.15})SiO ₃	69.0+ 0.2	2.079E+02	-1.489E-02	1.921E+05	-2.135E+03		298 1000		
RHODONITE MnSiO ₃	100.5 1.0	9.904E+01	1.915E-02	-3.041E+06	2.745E+02		298 1500		
JADEITE NaAlSi ₂ O ₆	133.5 1.3	3.011E+02	1.014E-02	-2.239E+06	-2.055E+03		298 1300		
GLASS NaAlSi ₂ O ₆	170.5 0.4	1.663E+02					298		
ACHITE NaFeSi ₂ O ₆	170.6 0.8	1.994E+02	6.197E-02	-4.267E+06			298 1300		
TREMOLITE Ca ₂ Mg ₅ Si ₈ O ₂₂ (OH) ₂	548.9 1.3	6.131E+03	-4.189E+00	5.139E+07	-8.566E+04	1.757E-03	298 1100		
GRUNERITE Fe ₇ Si ₈ O ₂₂ (OH) ₂	725.0 7.0	7.555E+02	3.620E-01	-1.621E+07			298 900		
ANTHOPHILLITE Mg ₇ Si ₈ O ₂₂ (OH) ₂	534.5 3.5	1.260E+03	1.888E-02	-1.164E+07	-8.127E+03		298 1200		
RIEBECKITE Na ₂ Fe ₃ Fe ₂ Si ₈ O ₂₂ (OH) ₂	691.0 6.0	7.721E+02	2.827E-01	-1.598E+07			298 1000		
GLAUCOPHANE Na ₂ Mg ₃ Al ₂ Si ₈ O ₂₂ (OH) ₂	541.2 3.0	1.718E+03	-1.211E-01	7.075E+06	-1.927E+04		298 1200		

COEFFICIENTS FOR HEAT CAPACITY EQUATIONS FOR FRAMEWORK STRUCTURE SILICATE MINERALS

NAME AND FORMULA	ENTROPY J·mol ⁻¹ ·K ⁻¹	A1	A2 (T)	A3 (T ²)	A4 (T ^{-0.6})	A5 (T ²)	T range K	T _{cm} K	Δ _{cm} H° kJ·mol ⁻¹
EDINGTONITE (ordered) BaAl ₂ Si ₃ O ₁₀ ·3H ₂ O	434.8 1.5	4.220E+02					298		
ANORTHITE CaAl ₂ Si ₂ O ₈	199.3 0.3	5.168E+02	-9.249E-02	-1.408E+06	-4.589E+03	4.188E-05	298 1800		
CaAl ₂ Si ₂ O ₈ -glass CaAl ₂ Si ₂ O ₈	237.3 2.5	3.752E+02	3.197E-02	-2.815E+06	-2.459E+03		298 1500	1830	133.0 4.0
BICCHULITE Ca ₂ Al ₂ Si ₆ (OH) ₂	213.1 5.0	2.803E+02	8.204E-02	-5.679E+06			298 1800		
MEIONITE (ordered) Ca ₄ Al ₆ Si ₆ O ₂₄ CO ₃	715.2 1.0	9.103E+02	1.9435E-01	-2.300E+07			298 1000		
DANBURITE CaB ₂ Si ₂ O ₈	155.3 0.4	1.488E+02	2.173E-01	-3.280E+06			298 1000		
POLLUCITE (Cs _{.65} Na _{.19} Rb _{.03})Al ₂ Si ₄ O ₁₂ ·H ₂ O	207.2 0.4	1.128E+02	1.876E-01	4.556E+05			298 700		
MICROCLINE KAlSi ₃ O ₈	214.2 0.4	7.595E+02	-2.171E-01	4.746E+06	-9.527E+03	6.433E-05	298 1400		
SANIDINE KAlSi ₃ O ₈	232.8 0.5	6.934E+02	-1.717E-01	3.462E+06	-8.305E+03	4.919E-05	298 1400	1500	54.0
GLASS KAlSi ₃ O ₈	261.6 1.8	6.295E+02	-1.084E-01	2.496E+06	-7.210E+03	-1.928E-05	298 1300		
KALIOPHILLITE KAlSi ₄ O ₈	133.3 1.2	1.889E+02	5.519E-02		-1.479E+03		298 810	810	0.5
LEUCITE KAlSi ₂ O ₆	200.2 1.7	1.4842E+02	1.343E-01	-2.165E+06			298 955		
LEUCITE KAlSi ₂ O ₆	450.1 2.0	1.9647E+02	2.7666E-02	1.2261E+07			955 1800		
EUCRYPTITE LiAlSi ₄ O ₈	103.8 0.8	2.470E+02		-1.290E+06	-2.058E+03		298 1300		
PETALITE LiAlSi ₄ O ₁₀	233.2 0.6	8.763E+02	-2.079E-01	4.033E+06	-1.069E+04	5.301E-05	298 1300		
ALBITE NaAlSi ₃ O ₈	207.4 0.4	5.839E+02	-9.285E-02	1.678E+06	-6.424E+03	2.272E-05	298 1400		

COEFFICIENTS FOR HEAT CAPACITY EQUATIONS FOR FRAMEWORK STRUCTURE SILICATE MINERALS

NAME AND FORMULA	ENTROPY J·mol ⁻¹ ·K ⁻¹	A1	A2 (T)	A3 (T ²)	A4 (T ^{0.5})	A5 (T ²)	T range K	T _m K	Δ _m H° kJ·mol ⁻¹
ANALBITE NaAlSi ₃ O ₈	225.6 0.4	6.714E+02	-1.467E-01	3.174E+06	-7.974E+03	3.659E-05	298 1400	1393	64.5
GLASS NaAlSi ₃ O ₈	251.9 1.5	9.180E+02	-3.824E-01	5.280E+06	-1.151E+04	1.474E-04	298 1200		
NEPHELINE NaAlSiO ₄	124.4 1.3	2.774E+01	2.954E-01				298 457		
NEPHELINE NaAlSiO ₄		1.1209E+02	6.711E-02				457 1180		
NEPHELINE NaAlSiO ₄	338.3 2.0	1.720E+02	5.520E-03				1180 1525		
CARNEGIEITE NaAlSiO ₄	118.7 0.3	1.1613E+02	8.595E-02	-2.000E+06			273 966	966	8.5
CARNEGIEITE NaAlSiO ₄	311.1 1.5	1.5232E+02	2.883E-02				966 1700		
GLASS NaAlSiO ₄	134.5 0.5	3.171E+02	-4.320E-02	4.163E+05	-3.244E+03		272 1033		
NEPHELINE (Na _{0.78} K _{0.22})AlSiO ₄		1.121E+02	6.711E-02				467 1180		
ANALCIME NaAlSi ₂ O ₆ ·H ₂ O	227.7 0.3	1.3438E+02	2.5415E-01	1.845E+05			298 700		
DEHYDRATED ANALCIME NaAlSi ₂ O ₆	172.5 0.2	1.9211E+02	8.0735E-02	-4.723E+06			298 1000		

COEFFICIENTS FOR HEAT CAPACITY EQUATIONS FOR SHEET STRUCTURE SILICATES

NAME AND FORMULA	ENTROPY J·mol ⁻¹ ·K ⁻¹	A1	A2 (T)	A3 (T ²)	A4 (T ^{0.5})	A5 (T ²)	T range K	T _{cm} K	Δ _{cm} H ⁰ kJ·mol ⁻¹
DICKITE Al ₂ Si ₂ O ₅ (OH) ₄	197.1 1.3	9.084E+02	-2.113E-01	3.804E+06	-1.120E+04		298 1000		
KAOLINITE Al ₂ Si ₂ O ₅ (OH) ₄	200.4 0.5	1.4303E+03	-7.885E-01	8.334E+06	-1.852E+04	3.034E-04	298 800		
HALLOYSITE Al ₂ Si ₂ O ₅ (OH) ₄	203.0 1.3	2.463E+02					298		
PYROPHYLLITE Al ₂ Si ₄ O ₁₀ (OH) ₂	239.4 0.4	7.468E+02	-5.345E-02		-7.578E+03	1.986E-05	298 800		
ILLITE K ₃ (Al ₇ Mg)(Al ₂ Si ₁₄)O ₄₀ (OH) ₈	1104.2 2.5	1.291E+03					298		
MARGARITE CaAl ₂ [Al ₂ Si ₂₀] (OH) ₂	263.6 0.3	8.265E+02	-5.040E-01		-8.7274E+03		298 1200		
PREHNITE Ca ₂ Al [AlSi ₃ O ₁₀] (OH) ₂	292.8 0.7	9.460E+02	-1.1506E-01	2.755E+06	-1.056E+04		298 1200		
MUSCOVITE (disordered) KAl ₂ [AlSi ₃ O ₁₀] (OH) ₂	306.4 0.6	9.177E+02	-8.111E-02	2.834E+06	-1.035E+04		298 1000		
MUSCOVITE (ordered) KAl ₂ [AlSi ₃ O ₁₀] (OH) ₂	287.7 0.6	9.177E+02	-8.111E-02	2.834E+06	-1.035E+04		298 1000		
ANNITE KFe ₃ [AlSi ₃ O ₁₀] (OH) ₂	415.0 10.0	6.366E+02	8.208E-02	-4.860E+06	-3.731E+03		298 1000		
PHLOGOPITE (disordered) KMg ₃ [AlSi ₃ O ₁₀] (OH) ₂	334.6 1.0	8.639E+02	-7.6076E-02	3.5206E+05	-8.470E+03		298 1000		
PHLOGOPITE (ordered) KMg ₃ [AlSi ₃ O ₁₀] (OH) ₂	315.9 1.0	8.639E+02	-7.6076E-02	3.5206E+05	-8.470E+03		298 1000		
FLUORPHLOGOPITE (disordered) KMg ₃ [AlSi ₃ O ₁₀]F ₂	336.3 2.1	4.9288E+02	4.910E-02	-6.599E+06	-1.569E+03		298 1670		
FLUORPHLOGOPITE (ordered) KMg ₃ [AlSi ₃ O ₁₀]F ₂	317.6 2.1	4.9288E+02	4.910E-02	-6.599E+06	-1.569E+03		298 1670		
TALC Mg ₃ Si ₄ O ₁₀ (OH) ₂	260.8 0.6	5.654E+03	-5.272E+00	4.021E+07	-7.693E+04	2.729E-03	298 800		
CHRYSOTILE Mg ₃ Si ₂ O ₅ (OH) ₄	221.3 0.8	8.996E+02	-1.448E-01	4.500E+06	-1.093E+04		298 900		

COEFFICIENTS FOR HEAT CAPACITY EQUATIONS FOR SHEET STRUCTURE SILICATES

NAME AND FORMULA	ENTROPY J·mol ⁻¹ ·K ⁻¹	A1	A2 (T)	A3 (T ²)	A4 (T ^{-0.5})	A5 (T ²)	T range K	T _m K	Δ _m H° kJ·mol ⁻¹
CLINOCHLORE Mg ₅ Al(AlSi ₃ O ₁₀)(OH) ₈	421.0 15.0	9.47951E+03	-7.8834E+00	8.31194E+07	-1.3594E+05	3.6206E-03	298 800		
PARAGONITE (disordered) NaAl ₂ [AlSi ₃ O ₁₀](OH) ₂	295.8 0.9	6.6844E+02	3.627E-02	-1.860E+06	-5.816E+03		298 800		
PARAGONITE (ordered) NaAl ₂ [AlSi ₃ O ₁₀](OH) ₂	277.1 0.9	6.6844E+02	3.627E-02	-1.860E+06	-5.816E+03		298 800		

Thermodynamic Properties at High Temperature of Individual Phases

SILVER (REFERENCE STATE)

Formula wt 107.868

Ag: Face-centered cubic crystals 298.15 to melting point 1234.9 K; liquid 1234.9 to 1800 K.

Temp. K	C_p°	S_T°	$(H_T^\circ - H_{298}^\circ)/T$ J·mol ⁻¹ ·K ⁻¹	$-(G_T^\circ - H_{298}^\circ)/T$	FORMATION FROM THE ELEMENTS		
					$\Delta_f H^\circ$ kJ·mol ⁻¹	$\Delta_f G^\circ$	Log K_f
298.15	25.40	42.55	0.00	42.55	0.0	0.0	0.0
300	25.41	42.71	0.16	42.55	0.0	0.0	0.0
400	25.87	50.08	6.53	43.55	0.0	0.0	0.0
500	26.33	55.90	10.44	45.46	0.0	0.0	0.0
600	26.88	60.75	13.14	47.62	0.0	0.0	0.0
700	27.52	64.94	15.14	49.80	0.0	0.0	0.0
800	28.24	68.66	16.73	51.93	0.0	0.0	0.0
900	29.03	72.03	18.06	53.98	0.0	0.0	0.0
1000	29.86	75.14	19.19	55.94	0.0	0.0	0.0
1100	30.73	78.02	20.20	57.82	0.0	0.0	0.0
1200	31.64	80.73	21.12	59.62	0.0	0.0	0.0
1234.9	31.96	81.73	21.41	60.32	0.0	0.0	0.0
1234.9	33.47	90.88	30.57	60.31	0.0	0.0	0.0
1300	33.47	92.52	30.71	61.81	0.0	0.0	0.0
1400	33.47	95.00	30.91	64.09	0.0	0.0	0.0
1500	33.47	97.31	31.08	66.23	0.0	0.0	0.0
1600	33.47	99.47	31.23	68.24	0.0	0.0	0.0
1700	33.47	101.50	31.36	70.14	0.0	0.0	0.0
1800	33.47	103.41	31.48	71.93	0.0	0.0	0.0

Melting T 1234.9 K

Boiling T K

 $\Delta_{\text{fus}} H^\circ$ 11.94 kJ $\Delta_{\text{vap}} H^\circ$ kJ $H_{298}^\circ - H_0^\circ$ 5.745 kJMolar Vol. 1.0272 J·bar⁻¹
10.272 cm³

ALUMINUM (REFERENCE STATE)

Formula wt 26.982

Al: Face-centered cubic crystals 298.15 to melting point 933.5 K. Liquid 933.5 to 1800 K.

FORMATION FROM THE ELEMENTS

Temp.	C_p°	S_T°	$(H_T^\circ - H_{298}^\circ)/T$	$-(G_T^\circ - H_{298}^\circ)/T$	$\Delta_f H^\circ$	$\Delta_f G^\circ$	Log K_f
			-1	-1		-1	

ARSENIC (REFERENCE STATE)

Formula wt 74.922

As: Rhombohedral crystals 298.15 to sublimation point 875 K. Ideal tetratomic gas 875 to 1800 K.

Temp. K	C_p°	S_T°	$(H_T^\circ - H_{298}^\circ)/T$	$-(G_T^\circ - H_{298}^\circ)/T$	FORMATION FROM THE ELEMENTS		
					$\Delta_f H^\circ$	$\Delta_f G^\circ$	Log K_f
			$J \cdot mol^{-1} \cdot K^{-1}$		$kJ \cdot mol^{-1}$		
298.15	24.65	35.69	0.00	35.69	0.0	0.0	0.0
300	24.67	35.84	0.15	35.69	0.0	0.0	0.0
400	25.38	43.04	6.37	36.66	0.0	0.0	0.0
500	25.96	48.77	10.23	38.54	0.0	0.0	0.0
600	26.51	53.55	12.90	40.65	0.0	0.0	0.0
700	27.05	57.68	14.88	42.80	0.0	0.0	0.0
800	27.60	61.33	16.43	44.89	0.0	0.0	0.0
875	28.03	63.82	17.31	46.51	0.0	0.0	0.0
875	20.60	103.62	57.11	46.51	0.0	0.0	0.0
900	20.61	104.14	56.14	48.00	0.0	0.0	0.0
1000	20.64	106.31	52.59	53.72	0.0	0.0	0.0
1100	20.67	108.28	49.68	58.59	0.0	0.0	0.0
1200	20.69	110.08	47.26	62.81	0.0	0.0	0.0

Melting T	K	Boiling T	875	K
$\Delta_{fus} H^\circ$	kJ	$\Delta_{vap} H^\circ$	34.828	kJ
$H_{298}^\circ - H_0^\circ$	5.130 kJ	Molar Vol.	1.2963	$J \cdot bar^{-1}$
			12.963	cm^3

GOLD (REFERENCE STATE)

Formula wt 196.967

Au: Face-centered cubic crystals 298.15 to melting point 1336.15 K.

Temp. K	C_p°	S_T°	$(H_T^\circ - H_{298}^\circ)/T$ J·mol ⁻¹ ·K ⁻¹	$-(G_T^\circ - H_{298}^\circ)/T$	FORMATION FROM THE ELEMENTS		
					$\Delta_f H^\circ$ kJ·mol ⁻¹	$\Delta_f G^\circ$	Log K_f
298.15	25.18	47.49	0.00	47.49	0.0	0.0	0.0
300	25.19	47.65	0.16	47.49	0.0	0.0	0.0
400	25.88	55.00	6.51	48.49	0.0	0.0	0.0
500	26.26	60.82	10.43	50.39	0.0	0.0	0.0
600	26.57	65.63	13.09	52.54	0.0	0.0	0.0
700	26.91	69.76	15.04	54.71	0.0	0.0	0.0
800	27.36	73.38	16.55	56.83	0.0	0.0	0.0
900	27.93	76.63	17.78	58.85	0.0	0.0	0.0
1000	28.67	79.61	18.83	60.78	0.0	0.0	0.0
1100	29.57	82.38	19.77	62.62	0.0	0.0	0.0
1200	30.66	85.00	20.63	64.37	0.0	0.0	0.0
1300	31.95	87.51	21.45	66.06	0.0	0.0	0.0
1336.15	32.47	88.55	21.80	66.74	0.0	0.0	0.0
1336.15	33.54	97.94	31.20	66.74	0.0	0.0	0.0
1400	32.75	99.34	31.23	68.11	0.0	0.0	0.0
1500	31.49	101.54	31.28	70.26	0.0	0.0	0.0
1600	30.81	103.54	31.25	72.29	0.0	0.0	0.0
1700	30.81	105.39	31.21	74.18	0.0	0.0	0.0
1800	30.81	107.15	31.19	75.96	0.0	0.0	0.0

Melting T	1336.15 K	Boiling T	K
$\Delta_{fus} H^\circ$	12.55 kJ	$\Delta_{vap} H^\circ$	kJ
$H_{298}^\circ - H_0^\circ$	6.017 kJ	Molar Vol.	1.0215 J·bar ⁻¹ 10.215 cm ³

BORON (REFERENCE STATE)

Formula wt 10.811

B: Rhombohedral crystals 298.15 to melting point 2350 K.

Temp. K	C_p°	S_T°	$(H_T^\circ - H_{298}^\circ)/T$ J·mol ⁻¹ ·K ⁻¹	$-(G_T^\circ - H_{298}^\circ)/T$	FORMATION FROM THE ELEMENTS		
					$\Delta_f H^\circ$ kJ·mol ⁻¹	$\Delta_f G^\circ$	Log K_f
298.15	11.32	5.83	0.00	5.83	0.0	0.0	0.0
300	11.42	5.90	0.07	5.83	0.0	0.0	0.0
400	15.84	9.84	3.51	6.34	0.0	0.0	0.0
500	18.69	13.71	6.28	7.43	0.0	0.0	0.0
600	20.69	17.30	8.52	8.78	0.0	0.0	0.0
700	22.18	20.61	10.37	10.24	0.0	0.0	0.0
800	23.33	23.65	11.92	11.72	0.0	0.0	0.0
900	24.25	26.45	13.24	13.21	0.0	0.0	0.0
1000	25.01	29.05	14.38	14.66	0.0	0.0	0.0
1100	25.66	31.46	15.38	16.08	0.0	0.0	0.0
1200	26.21	33.72	16.26	17.46	0.0	0.0	0.0
1300	26.71	35.83	17.04	18.79	0.0	0.0	0.0
1400	27.16	37.83	17.75	20.08	0.0	0.0	0.0
1500	27.57	39.72	18.39	21.33	0.0	0.0	0.0
1600	27.96	41.51	18.98	22.53	0.0	0.0	0.0
1700	28.33	43.22	19.52	23.70	0.0	0.0	0.0
1800	28.69	44.85	20.02	24.83	0.0	0.0	0.0

Melting T 2350 K

Boiling T K

 $\Delta_{fus} H^\circ$ 22.55 kJ $\Delta_{vap} H^\circ$ kJ $H_{298}^\circ - H_0^\circ$ 1.22 kJMolar Vol. 0.4386 J·bar⁻¹
4.386 cm³

BARIUM (REFERENCE STATE)

Formula wt 137.327

Ba: α -crystals (body-centered cubic) 298.15 to lambda-anomaly in heat capacity at 582 K. β -crystals 582 to second-order lambda-anomaly in heat capacity at 768.13 K. γ -crystals 768.13 to melting point 1002 K. Liquid 1002 to boiling point 2169 K.

Temp. K	C_p°	S_T°	FORMATION FROM THE ELEMENTS				
			$(H_T^\circ - H_{298}^\circ)/T$ J·mol ⁻¹ ·K ⁻¹	$-(G_T^\circ - H_{298}^\circ)/T$	$\Delta_f H^\circ$ kJ·mol ⁻¹	$\Delta_f G^\circ$	Log K_f
298.15	28.09	62.42	0.00	62.42	0.0	0.0	0.0
300	28.14	62.59	0.17	62.42	0.0	0.0	0.0
400	33.23	71.24	7.68	63.56	0.0	0.0	0.0
500	43.74	79.72	13.78	65.94	0.0	0.0	0.0
582	54.43	86.71	18.19	68.52	0.0	0.0	0.0
582	32.47	87.13	18.61	68.52	0.0	0.0	0.0
600	33.94	88.16	19.18	68.97	0.0	0.0	0.0
700	42.36	94.02	21.89	72.13	0.0	0.0	0.0
768	48.10	98.02	23.64	74.38	0.0	0.0	0.0
768	39.07	98.34	23.96	74.38	0.0	0.0	0.0
800	39.07	99.81	24.56	75.24	0.0	0.0	0.0
900	39.07	104.41	26.17	78.24	0.0	0.0	0.0
1000	39.07	108.52	27.46	81.06	0.0	0.0	0.0
1002	39.07	109.34	27.87	81.46	0.0	0.0	0.0
1002	40.62	117.07	35.61	81.46	0.0	0.0	0.0
1100	40.37	120.60	36.13	84.48	0.0	0.0	0.0
1200	40.12	124.20	36.57	87.64	0.0	0.0	0.0
1300	39.86	127.44	36.86	90.58	0.0	0.0	0.0
1400	39.61	130.38	37.08	93.30	0.0	0.0	0.0
1500	39.36	133.08	37.20	95.88	0.0	0.0	0.0
1600	39.10	135.58	37.30	98.28	0.0	0.0	0.0
1700	38.85	137.92	37.37	100.55	0.0	0.0	0.0
1800	38.60	140.13	37.44	102.69	0.0	0.0	0.0
Melting T	1002 K				Boiling T		K
$\Delta_{\text{m}} H^\circ$	7.749 kJ				$\Delta_{\text{vp}} H^\circ$		kJ
$H_{298}^\circ - H_0^\circ$	6.912 kJ				Molar Vol.	3.821 J·bar ⁻¹	38.21 cm ³

BERYLLIUM (REFERENCE STATE)

Formula wt 9.012

Be: Hexagonal close-packed crystals 298.15 to 1550 K; beta crystals 1550 to melting point 1560 K; liquid 1560 to 1800 K.

Temp. K	C_p°	S_T°	FORMATION FROM THE ELEMENTS				
			$(H_T^\circ - H_{298}^\circ)/T$ J·mol ⁻¹ ·K ⁻¹	$-(G_T^\circ - H_{298}^\circ)/T$	$\Delta_f H^\circ$ kJ·mol ⁻¹	$\Delta_f G^\circ$	Log K_f
298.15	16.44	9.50	0.00	9.50	0.0	0.0	0.0
300	16.52	9.60	0.10	9.50	0.0	0.0	0.0
400	19.64	14.83	4.64	10.19	0.0	0.0	0.0
500	21.58	19.43	7.84	11.59	0.0	0.0	0.0
600	23.06	23.50	10.26	13.24	0.0	0.0	0.0
700	24.32	27.15	12.18	14.97	0.0	0.0	0.0
800	25.47	30.47	13.77	16.71	0.0	0.0	0.0
900	26.54	33.54	15.13	18.41	0.0	0.0	0.0
1000	27.58	36.39	16.32	20.07	0.0	0.0	0.0
1100	28.59	39.06	17.39	21.67	0.0	0.0	0.0
1200	29.57	41.59	18.37	23.23	0.0	0.0	0.0
1300	30.55	44.00	19.27	24.73	0.0	0.0	0.0
1400	31.52	46.30	20.11	26.19	0.0	0.0	0.0
1500	32.47	48.51	20.90	27.61	0.0	0.0	0.0
1550	32.95	49.58	21.28	28.30	0.0	0.0	0.0
1550	30.00	50.94	22.64	28.30	0.0	0.0	0.0
1560	30.00	51.13	22.68	28.45	0.0	0.0	0.0
1560	30.00	59.20	30.76	28.44	0.0	0.0	0.0
1600	30.00	59.96	30.74	29.22	0.0	0.0	0.0
1700	30.00	61.78	30.70	31.08	0.0	0.0	0.0
1800	30.00	63.50	30.66	32.84	0.0	0.0	0.0
Melting T	1560 K				Boiling T	K	
$\Delta_{\text{m}} H^\circ$	12.21 kJ				$\Delta_{\text{vap}} H^\circ$	kJ	
$H_{298}^\circ - H_0^\circ$	1.95 kJ				Molar Vol.	0.488 J·bar ⁻¹ 4.88 cm ³	

6/18/92

BISMUTH (REFERENCE STATE)

Formula wt 208.980

Bi: Rhombohedral crystals 298.15 to melting point 544.5 K. Liquid 544.5 to 1800 K.

Temp. K	C_p°	S_T°	$(H_T^\circ - H_{298}^\circ)/T$ J·mol ⁻¹ ·K ⁻¹	$-(G_T^\circ - H_{298}^\circ)/T$	FORMATION FROM THE ELEMENTS		
					$\Delta_f H^\circ$ kJ·mol ⁻¹	$\Delta_f G^\circ$	Log K_f
298.15	25.41	56.74	0.00	56.74	0.0	0.0	0.0
300	25.43	56.90	0.16	56.74	0.0	0.0	0.0
400	26.62	64.36	6.61	57.75	0.0	0.0	0.0
500	28.66	70.50	10.80	59.70	0.0	0.0	0.0
544.52	29.83	73.40	12.39	61.01	0.0	0.0	0.0
544.52	30.48	94.15	33.14	61.01	0.0	0.0	0.0
600	29.61	96.64	32.76	63.88	0.0	0.0	0.0
700	28.61	101.13	32.24	68.89	0.0	0.0	0.0
800	28.02	104.90	31.74	73.16	0.0	0.0	0.0
900	27.67	108.18	31.31	76.87	0.0	0.0	0.0
1000	27.45	111.08	30.93	80.15	0.0	0.0	0.0
1100	27.31	113.69	30.61	83.08	0.0	0.0	0.0
1200	27.24	116.07	30.33	85.74	0.0	0.0	0.0
1300	27.19	118.25	30.09	88.16	0.0	0.0	0.0
1400	27.17	120.26	29.88	90.38	0.0	0.0	0.0
1500	27.17	122.13	29.70	92.43	0.0	0.0	0.0
1600	27.18	123.89	29.54	94.35	0.0	0.0	0.0
1700	27.19	125.54	29.41	96.14	0.0	0.0	0.0
1800	27.21	127.09	29.28	97.81	0.0	0.0	0.0

Melting T	544.52 K	Boiling T	1835 K
$\Delta_{\text{sub}} H^\circ$	11.299 kJ	$\Delta_{\text{vap}} H^\circ$	kJ
$H_{298}^\circ - H_0^\circ$	6.43 kJ	Molar Vol.	2.131 J·bar ⁻¹ 21.31 cm ³

BROMINE (REFERENCE STATE)

Formula wt 159.808

Br₂: Liquid 298.15 to boiling point 332.5 K; ideal diatomic gas, P = 1 bar, 332.5 to 2200 K.

Temp. K	C _p ^o	S _T ^o	(H _T ^o -H ₂₉₈ ^o)/T J·mol ⁻¹ ·K ⁻¹	-(G _T ^o -H ₂₉₈ ^o)/T	FORMATION FROM THE ELEMENTS		
					Δ _f H ^o kJ·mol ⁻¹	Δ _f G ^o	Log K _f
298.15	75.67	152.20	0.00	152.20	0.0	0.0	0.0
300	75.60	152.67	0.47	152.20	0.0	0.0	0.0
332.5	75.30	160.43	7.79	152.64	0.0	0.0	0.0
332.5	36.33	249.34	96.70	152.64	0.0	0.0	0.0
400	36.71	256.09	86.55	169.54	0.0	0.0	0.0
500	37.08	264.33	76.62	187.71	0.0	0.0	0.0
600	37.31	271.11	70.05	201.06	0.0	0.0	0.0
700	37.48	276.87	65.39	211.49	0.0	0.0	0.0
800	37.60	281.89	61.91	219.98	0.0	0.0	0.0
900	37.70	286.32	59.21	227.11	0.0	0.0	0.0
1000	37.78	290.30	57.06	233.23	0.0	0.0	0.0
1100	37.87	293.90	55.31	238.59	0.0	0.0	0.0
1200	37.95	297.20	53.86	243.34	0.0	0.0	0.0
1300	38.04	300.24	52.64	247.60	0.0	0.0	0.0
1400	38.14	303.06	51.60	251.46	0.0	0.0	0.0
1500	38.24	305.70	50.71	254.99	0.0	0.0	0.0
1600	38.36	308.17	49.93	258.24	0.0	0.0	0.0
1700	38.49	310.50	49.26	261.24	0.0	0.0	0.0
1800	38.63	312.70	48.66	264.04	0.0	0.0	0.0
Melting T	265.9 K				Boiling T	332.5 K	
Δ _{fus} H ^o	10.57 kJ				Δ _{vap} H ^o	29.56 kJ	
H ₂₉₈ ^o -H ₀ ^o	24.51 kJ				Molar Vol.	5.458 J·bar ⁻¹ 54.58 cm ³	

GRAPHITE (REFERENCE STATE)

Formula wt 12.011

C: Hexagonal crystals 298.15 to 2500 K.

Temp. K	C_p°	S_T°	$(H_T^\circ - H_{298}^\circ)/T$ J·mol ⁻¹ ·K ⁻¹	$-(G_T^\circ - H_{298}^\circ)/T$	FORMATION FROM THE ELEMENTS		
					$\Delta_f H^\circ$ kJ·mol ⁻¹	$\Delta_f G^\circ$	Log K_f
298.15	8.52	5.74	0.00	5.74	0.0	0.0	0.0
300	8.59	5.79	0.05	5.74	0.0	0.0	0.0
400	11.88	8.72	2.60	6.12	0.0	0.0	0.0
500	14.64	11.68	4.75	6.93	0.0	0.0	0.0
600	16.79	14.55	6.58	7.97	0.0	0.0	0.0
700	18.47	17.27	8.17	9.10	0.0	0.0	0.0
800	19.77	19.82	9.54	10.29	0.0	0.0	0.0
900	20.80	22.21	10.73	11.48	0.0	0.0	0.0
1000	21.63	24.45	11.78	12.67	0.0	0.0	0.0
1100	22.29	26.54	12.71	13.83	0.0	0.0	0.0
1200	22.83	28.51	13.53	14.98	0.0	0.0	0.0
1300	23.27	30.35	14.26	16.09	0.0	0.0	0.0
1400	23.64	32.09	14.92	17.17	0.0	0.0	0.0
1500	23.95	33.73	15.51	18.22	0.0	0.0	0.0
1600	24.22	35.29	16.05	19.24	0.0	0.0	0.0
1700	24.46	36.76	16.54	20.23	0.0	0.0	0.0
1800	24.67	38.17	16.98	21.18	0.0	0.0	0.0

Melting T

K

Boiling T

K

 $\Delta_{fus} H^\circ$

kJ

 $\Delta_{vap} H^\circ$

kJ

 $H_{298}^\circ - H_0^\circ$

1.05 kJ

Molar Vol. 0.5298 J·bar⁻¹
5.298 cm³

DIAMOND

Formula wt 12.011

C: Cubic crystals 298.15 to 1600 K.

Temp. K	C_p°	S_T°	FORMATION FROM THE ELEMENTS				
			$(H_T^\circ - H_{298}^\circ)/T$ J·mol ⁻¹ ·K ⁻¹	$-(G_T^\circ - H_{298}^\circ)/T$	$\Delta_f H^\circ$ kJ·mol ⁻¹	$\Delta_f G^\circ$	Log K_f
298.15	6.14	2.38	0.00	2.38	1.9	2.9	-0.51
300	6.21	2.42	0.04	2.38	1.9	2.9	-0.51
400	10.24	4.76	2.09	2.67	1.7	3.3	-0.43
500	13.60	7.43	4.07	3.35	1.6	3.7	-0.38
600	16.12	10.14	5.88	4.26	1.5	4.1	-0.36
700	18.02	12.77	7.48	5.29	1.4	4.6	-0.34
800	19.48	15.28	8.90	6.38	1.4	5.0	-0.33
900	20.65	17.64	10.14	7.50	1.3	5.5	-0.32
1000	21.63	19.87	11.24	8.63	1.3	5.9	-0.31
1100	22.52	21.98	12.23	9.75	1.4	6.4	-0.30
1200	23.36	23.97	13.12	10.85	1.4	6.8	-0.30
1300	24.20	25.87	13.94	11.93	1.5	7.3	-0.29
1400	25.08	27.70	14.70	13.00	1.6	7.7	-0.29
1500	26.04	29.46	15.43	14.04	1.8	8.2	-0.28
1600	27.08	31.18	16.12	15.05	2.0	8.6	-0.28

Melting T	K	Boiling T	K
$\Delta_{\text{fus}} H^\circ$	kJ	$\Delta_{\text{vap}} H^\circ$	kJ
$H_{298}^\circ - H_0^\circ$	0.523 kJ	Molar Vol.	0.3417 J·bar ⁻¹ 3.417 cm ³

A= 1.37E+00

B= 0.453E-02

C= 1.547E+04

11/18/92

CALCIUM (REFERENCE STATE)

Formula wt 40.078

Ca: α -crystals (face-centered cubic) 298.15 to 716 K. β -crystals (body-centered cubic) 716 to melting point 1115 K. Liquid 1115 to boiling point 1774 K. Ideal monatomic gas, $P = 1$ bar, 1774 to 1800 K.

Temp. K	C_p°	S_T°	$(H_T^\circ - H_{298}^\circ)/T$ J·mol ⁻¹ ·K ⁻¹	$-(G_T^\circ - H_{298}^\circ)/T$	FORMATION FROM THE ELEMENTS		
					$\Delta_f H^\circ$ kJ·mol ⁻¹	$\Delta_f G^\circ$	Log K_f
298.15	25.77	42.90	0.00	42.90	0.0	0.0	0.0
300	25.79	43.06	0.16	42.90	0.0	0.0	0.0
400	26.95	50.63	6.71	43.93	0.0	0.0	0.0
500	28.48	56.80	10.90	45.90	0.0	0.0	0.0
600	30.34	62.16	13.98	48.17	0.0	0.0	0.0
700	32.41	66.98	16.46	50.52	0.0	0.0	0.0
716	32.74	67.73	16.83	50.90	0.0	0.0	0.0
716	31.50	69.03	18.13	50.90	0.0	0.0	0.0
800	33.82	72.65	19.65	52.99	0.0	0.0	0.0
900	36.71	76.80	21.39	55.41	0.0	0.0	0.0
1000	39.71	80.82	23.07	57.75	0.0	0.0	0.0
1100	42.76	84.75	24.72	60.03	0.0	0.0	0.0
1115	43.23	85.33	24.96	60.37	0.0	0.0	0.0
1115	35.00	92.99	32.62	60.32	0.0	0.0	0.0
1200	35.00	95.55	32.79	62.76	0.0	0.0	0.0
1300	35.00	98.36	32.96	65.40	0.0	0.0	0.0
1400	35.00	100.95	33.11	67.84	0.0	0.0	0.0
1500	35.00	103.37	33.24	70.13	0.0	0.0	0.0
1600	35.00	105.63	33.35	72.28	0.0	0.0	0.0
1700	35.00	107.75	33.44	74.31	0.0	0.0	0.0
1774	35.00	109.23	33.50	75.73	0.0	0.0	0.0
1774	20.84	193.25	117.52	75.73	0.0	0.0	0.0
1800	20.84	193.55	116.12	77.43	0.0	0.0	0.0

Melting T	1115 K	Boiling T	1774 K
$\Delta_{\text{sub}} H^\circ$	8.54 kJ	$\Delta_{\text{vap}} H^\circ$	330.915 kJ
$H_{298}^\circ - H_0^\circ$	5.707 kJ	Molar Vol.	2.619 J·bar ⁻¹ 26.19 cm ³

CADMIUM (REFERENCE STATE)

Formula wt 112.411

Cd: Hexagonal close packed crystals 298.15 to melting point 594.18 K. Liquid 594.18 to boiling point 1039 K. Ideal monatomic gas 1039 to 1800 K.

Temp. K	C_p°	S_T°	FORMATION FROM THE ELEMENTS				
			$(H_T^\circ - H_{298}^\circ)/T$ J·mol ⁻¹ ·K ⁻¹	$-(G_T^\circ - H_{298}^\circ)/T$	$\Delta_f H^\circ$ kJ·mol ⁻¹	$\Delta_f G^\circ$	Log K_f
298.15	25.98	51.80	0.00	51.80	0.0	0.0	0.0
300	26.00	51.96	0.16	51.80	0.0	0.0	0.0
400	27.14	59.59	6.76	52.83	0.0	0.0	0.0
500	28.37	65.78	10.95	54.82	0.0	0.0	0.0
594.18	29.53	70.79	13.81	56.98	0.0	0.0	0.0
594.18	29.71	81.21	24.23	56.98	0.0	0.0	0.0
600	29.71	81.48	24.28	57.19	0.0	0.0	0.0
700	29.71	86.06	25.05	61.00	0.0	0.0	0.0
800	29.71	90.03	25.64	64.39	0.0	0.0	0.0
900	29.71	93.53	26.09	67.44	0.0	0.0	0.0
1000	29.71	96.66	26.45	70.21	0.0	0.0	0.0
1039	29.71	97.97	26.52	71.44	0.0	0.0	0.0
1039	20.79	193.90	122.45	71.44	0.0	0.0	0.0
1100	20.79	194.88	116.81	78.06	0.0	0.0	0.0
1200	20.79	196.69	108.81	87.88	0.0	0.0	0.0
1300	20.79	198.35	102.04	96.31	0.0	0.0	0.0
1400	20.79	199.89	96.23	103.65	0.0	0.0	0.0
1500	20.79	201.33	91.20	110.12	0.0	0.0	0.0
1600	20.79	202.67	86.80	115.86	0.0	0.0	0.0
1700	20.79	203.93	82.92	121.01	0.0	0.0	0.0
1800	20.79	205.12	79.47	125.65	0.0	0.0	0.0

Melting T 594.18 K

Boiling T 1039 K

 $\Delta_{\text{fus}} H^\circ$ 6.19 kJ $\Delta_{\text{vap}} H^\circ$ 99.667 kJ $H_{298}^\circ - H_0^\circ$ 6.25 kJMolar Vol. 1.3005 J·bar⁻¹
13.005 cm³

CERIUM (REFERENCE STATE)

Formula wt 140.115

Ce: α -crystals (face-centered cubic) 298.15 to 999 K. β -crystals 999 to melting point 1071 K. Liquid 1071 to 1800 K.

Temp. K	C_p°	S_T°	$(H_T^\circ - H_{298}^\circ)/T$ J·mol ⁻¹ ·K ⁻¹	$-(G_T^\circ - H_{298}^\circ)/T$	FORMATION FROM THE ELEMENTS		
					$\Delta_f H^\circ$ kJ·mol ⁻¹	$\Delta_f G^\circ$	Log K_f
298.15	26.93	72.00	0.00	72.00	0.0	0.0	0.0
300	26.96	72.17	0.17	72.00	0.0	0.0	0.0
400	28.29	80.10	7.03	73.07	0.0	0.0	0.0
500	29.70	86.57	11.42	75.14	0.0	0.0	0.0
600	31.20	92.11	14.59	77.52	0.0	0.0	0.0
700	32.77	97.04	17.07	79.96	0.0	0.0	0.0
800	34.40	101.52	19.14	82.38	0.0	0.0	0.0
900	36.07	105.67	20.93	84.74	0.0	0.0	0.0
999	37.76	109.35	22.34	87.01	0.0	0.0	0.0
999	37.61	112.46	25.45	87.01	0.0	0.0	0.0
1000	37.61	112.55	25.52	87.03	0.0	0.0	0.0
1071	37.61	115.19	26.32	88.88	0.0	0.0	0.0
1071	37.70	120.29	31.41	88.88	0.0	0.0	0.0
1100	37.70	121.24	31.58	89.66	0.0	0.0	0.0
1200	37.70	124.52	32.09	92.43	0.0	0.0	0.0
1300	37.70	127.53	32.53	95.00	0.0	0.0	0.0
1400	37.70	130.33	32.89	97.44	0.0	0.0	0.0
1500	37.70	132.93	33.21	99.72	0.0	0.0	0.0
1600	37.70	135.36	33.49	101.87	0.0	0.0	0.0
1700	37.70	137.65	33.74	103.91	0.0	0.0	0.0
1800	37.70	139.80	33.96	105.84	0.0	0.0	0.0
Melting T		1071 K			Boiling T		K
$\Delta_{\text{m}} H^\circ$		5.46 kJ			$\Delta_{\text{vp}} H^\circ$		kJ
$H_{298}^\circ - H_0^\circ$		7.28 kJ			Molar Vol.	2.077 J·bar ⁻¹	20.77 cm ³

CHLORINE (REFERENCE STATE)

Formula wt 70.905

Cl₂: Ideal diatomic gas 298.15 to 2500 K.

Temp. K	C _p ^o	S _T ^o	(H _T ^o -H ₂₉₈ ^o)/T	-(G _T ^o -H ₂₉₈ ^o)/T	FORMATION FROM THE ELEMENTS		
					Δ _f H ^o	Δ _f G ^o	Log K _f
			J·mol ⁻¹ ·K ⁻¹		kJ·mol ⁻¹		
298.15	33.95	223.08	0.00	223.08	0.0	0.0	0.0
300	33.98	223.29	0.21	223.08	0.0	0.0	0.0
400	35.28	233.26	8.83	224.43	0.0	0.0	0.0
500	36.05	241.22	14.20	227.02	0.0	0.0	0.0
600	36.55	247.84	17.89	229.95	0.0	0.0	0.0
700	36.89	253.50	20.58	232.92	0.0	0.0	0.0
800	37.13	258.45	22.63	235.81	0.0	0.0	0.0
900	37.31	262.83	24.26	238.58	0.0	0.0	0.0
1000	37.45	266.77	25.57	241.20	0.0	0.0	0.0
1100	37.57	270.34	26.65	243.69	0.0	0.0	0.0
1200	37.67	273.62	27.57	246.05	0.0	0.0	0.0
1300	37.76	276.64	28.35	248.29	0.0	0.0	0.0
1400	37.85	279.44	29.02	250.41	0.0	0.0	0.0
1500	37.94	282.05	29.61	252.44	0.0	0.0	0.0
1600	38.03	284.50	30.14	254.37	0.0	0.0	0.0
1700	38.13	286.81	30.61	256.21	0.0	0.0	0.0
1800	38.24	288.99	31.03	257.97	0.0	0.0	0.0

Melting T 172.16 K

Boiling T 239.1 K

Δ_{sub}H^o 6.406 kJΔ_{sub}H^o 20.41 kJH₂₉₈^o-H₀^o 9.18 kJMolar Vol. 2478.97 J·bar⁻¹
24789.7 cm³

COBALT (REFERENCE STATE)

Formula wt 58.933

Co: α -crystals (hexagonal close packed) 298.15 to 700 K. β -crystals (face-centered cubic) 700 to melting point 1768 K. Liquid 1768 to 1800 K. Curie point at 1394 K.

Temp. K	C_p°	S_T°	$(H_T^\circ - H_{298}^\circ)/T$ J·mol ⁻¹ ·K ⁻¹	$-(G_T^\circ - H_{298}^\circ)/T$	FORMATION FROM THE ELEMENTS		
					$\Delta_f H^\circ$ kJ·mol ⁻¹	$\Delta_f G^\circ$	Log K_f
298.15	24.81	30.04	0.00	30.04	0.0	0.0	0.0
300	24.85	30.19	0.15	30.04	0.0	0.0	0.0
400	26.56	37.58	6.54	31.04	0.0	0.0	0.0
500	28.19	43.68	10.71	32.97	0.0	0.0	0.0
600	29.70	48.96	13.75	35.21	0.0	0.0	0.0
700	31.05	53.64	16.13	37.51	0.0	0.0	0.0
700	30.51	54.27	16.78	37.49	0.0	0.0	0.0
800	32.58	58.50	18.63	39.88	0.0	0.0	0.0
900	34.55	62.45	20.28	42.17	0.0	0.0	0.0
1000	36.85	66.20	21.82	44.38	0.0	0.0	0.0
1100	39.77	69.84	23.31	46.53	0.0	0.0	0.0
1200	43.52	73.46	24.83	48.63	0.0	0.0	0.0
1300	48.26	77.12	26.45	50.67	0.0	0.0	0.0
1394	53.70	80.67	28.15	52.52	0.0	0.0	0.0
1400	44.22	80.88	28.24	52.64	0.0	0.0	0.0
1500	39.75	83.72	29.12	54.61	0.0	0.0	0.0
1600	38.28	86.23	29.73	56.50	0.0	0.0	0.0
1700	37.78	88.53	30.21	58.32	0.0	0.0	0.0
1768	37.74	90.00	30.50	59.50	0.0	0.0	0.0
1768	40.50	99.16	39.66	59.50	0.0	0.0	0.0
1800	40.50	99.98	39.68	60.30	0.0	0.0	0.0

Melting T	1768 K	Boiling T	K
$\Delta_{\text{sub}} H^\circ$	16.19 kJ	$\Delta_{\text{vap}} H^\circ$	kJ
$H_{298}^\circ - H_0^\circ$	4.766 kJ	Molar Vol.	0.667 J·bar ⁻¹ 6.67 cm ³

CHROMIUM (REFERENCE STATE)

Formula wt 51.996

Cr: Body-centered cubic crystals 298.15 to melting point 2130 K. Néel temperature 311.5 K.

Temp. K	C_p°	S_T°	$(H_T^\circ - H_{298}^\circ)/T$ J·mol ⁻¹ ·K ⁻¹	$-(G_T^\circ - H_{298}^\circ)/T$	FORMATION FROM THE ELEMENTS		
					$\Delta_f H^\circ$ kJ·mol ⁻¹	$\Delta_f G^\circ$	Log K_f
298.15	23.47	23.62	0.00	23.62	0.0	0.0	0.0
300	23.53	23.77	0.14	23.62	0.0	0.0	0.0
311.50	23.81	24.66	0.98	23.64	0.0	0.0	0.0
400	25.64	30.88	6.31	24.58	0.0	0.0	0.0
500	26.56	36.71	10.27	26.44	0.0	0.0	0.0
600	27.35	41.62	13.05	28.57	0.0	0.0	0.0
700	28.27	45.90	15.16	30.75	0.0	0.0	0.0
800	29.37	49.75	16.86	32.89	0.0	0.0	0.0
900	30.65	53.28	18.32	34.96	0.0	0.0	0.0
1000	32.09	56.58	19.63	36.96	0.0	0.0	0.0
1100	33.67	59.71	20.83	38.88	0.0	0.0	0.0
1200	35.38	62.71	21.97	40.75	0.0	0.0	0.0
1300	37.19	65.62	23.07	42.55	0.0	0.0	0.0
1400	39.11	68.44	24.15	44.30	0.0	0.0	0.0
1500	41.11	71.21	25.21	46.00	0.0	0.0	0.0
1600	43.19	73.93	26.27	47.66	0.0	0.0	0.0
1700	45.35	76.61	27.33	49.28	0.0	0.0	0.0
1800	47.57	79.27	28.39	50.88	0.0	0.0	0.0

Melting T 2130 K

Boiling T 2945 K

 $\Delta_{\text{m}} H^\circ$ 16.933 kJ $\Delta_{\text{v}} H^\circ$ 344.31 kJ $H_{298}^\circ - H_0^\circ$ 4.058 kJMolar Vol. 0.7231 J·bar⁻¹
7.231 cm³

CESIUM (REFERENCE STATE)

Formula wt 132.905

Cs: Body-centered cubic crystals 298.15 to melting point 301.55 K. Liquid 301.55 to boiling point 947.96 K. Ideal monatomic gas, P = 1 bar, 942 to 1800 K.

Temp. K	C_p°	S_T°	$(H_T^\circ - H_{298}^\circ)/T$	$-(G_T^\circ - H_{298}^\circ)/T$	FORMATION FROM THE ELEMENTS		
					$\Delta_f H^\circ$	$\Delta_f G^\circ$	Log K_f
			$J \cdot mol^{-1} \cdot K^{-1}$		$kJ \cdot mol^{-1}$		
298.15	32.19	85.23	0.00	85.23	0.0	0.0	0.0
300	32.35	85.43	0.16	85.27	0.0	0.0	0.0
301.55	32.50	85.60	0.33	85.27	0.0	0.0	0.0
301.55	32.39	92.52	7.25	85.27	0.0	0.0	0.0
400	31.51	101.54	13.34	88.20	0.0	0.0	0.0
500	31.15	108.53	16.94	91.59	0.0	0.0	0.0
600	30.99	114.20	19.29	94.90	0.0	0.0	0.0
700	30.94	118.97	20.96	98.01	0.0	0.0	0.0
800	30.93	123.10	22.21	100.89	0.0	0.0	0.0
900	30.95	126.75	23.18	103.57	0.0	0.0	0.0
947.96	30.97	128.36	23.57	104.78	0.0	0.0	0.0
947.96	20.78	199.73	94.95	104.78	0.0	0.0	0.0
1000	20.78	200.84	91.09	109.75	0.0	0.0	0.0
1100	20.78	202.82	84.70	118.12	0.0	0.0	0.0
1200	20.79	204.63	79.37	125.26	0.0	0.0	0.0
1300	20.79	206.29	74.86	131.43	0.0	0.0	0.0
1400	20.81	207.84	71.00	136.83	0.0	0.0	0.0
1500	20.84	209.27	67.66	141.61	0.0	0.0	0.0
1600	20.88	210.62	64.73	145.88	0.0	0.0	0.0
1700	20.95	211.89	62.16	149.73	0.0	0.0	0.0
1800	21.04	213.09	59.87	153.22	0.0	0.0	0.0

Melting T 301.55 K

Boiling T 942 K

 $\Delta_{fus} H^\circ$ 2.09 kJ $\Delta_{vap} H^\circ$ 67.71 kJ $H_{298}^\circ - H_0^\circ$ 7.71 kJMolar Vol. 6.973 $J \cdot bar^{-1}$
69.73 cm^3

COPPER (REFERENCE STATE)

Formula wt 63.546

Cu: Face-centered cubic crystals 298.15 to melting point 1357.8 K. Liquid 1357.8 to 1800 K.

Temp. K	C_p°	S_T°	$(H_T^\circ - H_{298}^\circ)/T$ J·mol ⁻¹ ·K ⁻¹	$-(G_T^\circ - H_{298}^\circ)/T$	FORMATION FROM THE ELEMENTS		
					$\Delta_f H^\circ$ kJ·mol ⁻¹	$\Delta_f G^\circ$	Log K_f
298.15	24.43	33.14	0.00	33.14	0.0	0.0	0.0
300	24.45	33.29	0.15	33.14	0.0	0.0	0.0
400	25.34	40.45	6.34	34.11	0.0	0.0	0.0
500	25.99	46.18	10.21	35.97	0.0	0.0	0.0
600	26.48	50.96	12.88	38.08	0.0	0.0	0.0
700	26.92	55.08	14.85	40.22	0.0	0.0	0.0
800	27.40	58.70	16.39	42.31	0.0	0.0	0.0
900	27.97	61.96	17.65	44.31	0.0	0.0	0.0
1000	28.69	64.94	18.71	46.23	0.0	0.0	0.0
1100	29.57	67.72	19.66	48.06	0.0	0.0	0.0
1200	30.65	70.34	20.53	49.81	0.0	0.0	0.0
1300	31.93	72.84	21.35	51.48	0.0	0.0	0.0
1357.8	32.77	74.25	21.82	52.43	0.0	0.0	0.0
1357.8	32.80	83.94	31.51	52.43	0.0	0.0	0.0
1400	32.80	84.95	31.55	53.40	0.0	0.0	0.0
1500	32.80	87.21	31.63	55.58	0.0	0.0	0.0
1600	32.80	89.32	31.70	57.62	0.0	0.0	0.0
1700	32.80	91.32	31.77	59.55	0.0	0.0	0.0
1800	32.80	93.19	31.82	61.37	0.0	0.0	0.0

Melting T	1357.8 K	Boiling T	K
$\Delta_{\text{fus}} H^\circ$	13.14 kJ	$\Delta_{\text{vap}} H^\circ$	kJ
$H_{298}^\circ - H_0^\circ$	5.00 kJ	Molar Vol.	0.7113 J·bar ⁻¹ 7.113 cm ³

FLUORINE (REFERENCE STATE)

Formula wt 37.997

F₂: Ideal diatomic gas at P = 1 bar 298.15 to 2500 K.

Temp. K	C _p ^o	S _T ^o	(H _T ^o -H ₂₉₈ ^o)/T	-(G _T ^o -H ₂₉₈ ^o)/T	FORMATION FROM THE ELEMENTS		
					Δ _f H ^o	Δ _f G ^o	Log K _f
			J·mol ⁻¹ ·K ⁻¹		kJ·mol ⁻¹		
298.15	31.31	202.79	0.00	202.79	0.0	0.0	0.0
300	31.35	202.98	0.19	202.79	0.0	0.0	0.0
400	33.14	212.27	8.23	204.04	0.0	0.0	0.0
500	34.28	219.80	13.33	206.47	0.0	0.0	0.0
600	35.11	226.12	16.89	209.23	0.0	0.0	0.0
700	35.75	231.59	19.54	212.04	0.0	0.0	0.0
800	36.27	236.40	21.60	214.79	0.0	0.0	0.0
900	36.70	240.69	23.26	217.43	0.0	0.0	0.0
1000	37.07	244.58	24.62	219.96	0.0	0.0	0.0
1100	37.38	248.13	25.77	222.36	0.0	0.0	0.0
1200	37.66	251.39	26.75	224.64	0.0	0.0	0.0
1300	37.89	254.42	27.60	226.82	0.0	0.0	0.0
1400	38.10	257.23	28.34	228.89	0.0	0.0	0.0
1500	38.28	259.87	29.00	230.87	0.0	0.0	0.0
1600	38.44	262.34	29.58	232.76	0.0	0.0	0.0
1700	38.57	264.68	30.11	234.57	0.0	0.0	0.0
1800	38.69	266.89	30.58	236.31	0.0	0.0	0.0

Melting T	53.48 K	Boiling T	84.95 K
Δ _{sub} H ^o	0.51 kJ	Δ _{sub} H ^o	6.54 kJ
H ₂₉₈ ^o -H ₀ ^o	8.82 kJ	Molar Vol.	2478.97 J·bar ⁻¹ 24789.7 cm ³

IRON (REFERENCE STATE)

Formula wt 55.847

Fe: Body-centered cubic crystals 298.15 to 1185 K. Curie point 1043 K; face-centered cubic crystals 1185 to 1667 K; body-centered cubic crystals 1667 to melting point 1809 K.

Temp. K	C_p°	S_T°	$(H_T^\circ - H_{298}^\circ)/T$	$-(G_T^\circ - H_{298}^\circ)/T$	FORMATION FROM THE ELEMENTS		
					$\Delta_f H^\circ$	$\Delta_f G^\circ$	Log K_f
			$J \cdot mol^{-1} \cdot K^{-1}$		$kJ \cdot mol^{-1}$		
298.15	25.08	27.09	0.00	27.08	0.0	0.0	0.0
300	25.13	27.24	0.16	27.08	0.0	0.0	0.0
400	27.43	34.80	6.69	28.10	0.0	0.0	0.0
500	29.64	41.15	11.06	30.09	0.0	0.0	0.0
600	32.01	46.76	14.35	32.41	0.0	0.0	0.0
700	34.62	51.89	17.06	34.83	0.0	0.0	0.0
800	37.92	56.72	19.45	37.27	0.0	0.0	0.0
900	43.16	61.46	21.76	39.70	0.0	0.0	0.0
1000	54.46	66.50	24.39	42.11	0.0	0.0	0.0
1043	83.77	69.14	25.97	43.18	0.0	0.0	0.0
1100	44.35	71.91	27.31	44.60	0.0	0.0	0.0
1185	40.00	75.01	28.33	46.67	0.0	0.0	0.0
1185	33.78	75.77	29.10	46.67	0.0	0.0	0.0
1200	33.90	76.19	29.16	47.04	0.0	0.0	0.0
1300	34.81	78.94	29.56	49.38	0.0	0.0	0.0
1400	35.75	81.56	29.97	51.59	0.0	0.0	0.0
1500	36.69	84.06	30.38	53.67	0.0	0.0	0.0
1600	37.63	86.45	30.81	55.65	0.0	0.0	0.0
1667	38.26	88.01	31.09	56.92	0.0	0.0	0.0
1667	40.40	88.52	31.60	56.92	0.0	0.0	0.0
1700	41.45	89.32	31.78	57.54	0.0	0.0	0.0
1800	44.65	91.78	32.41	59.37	0.0	0.0	0.0

Melting T	1809 K	Boiling T	K
$\Delta_{fus} H^\circ$	13.81 kJ	$\Delta_{vap} H^\circ$	kJ
$H_{298}^\circ - H_0^\circ$	4.51 kJ	Molar Vol.	0.7092 $J \cdot bar^{-1}$ 7.092 cm^3

GERMANIUM (REFERENCE STATE)

Formula wt 72.61

Ge: Face-centered cubic crystals (diamond structure) 298.15 to 1211.4 K. Liquid 1211.4 to boiling point 3107 K.

Temp. K	C_p°	S_T°	$(H_T^\circ - H_{298}^\circ)/T$ J·mol ⁻¹ ·K ⁻¹	$-(G_T^\circ - H_{298}^\circ)/T$	FORMATION FROM THE ELEMENTS		
					$\Delta_f H^\circ$ kJ·mol ⁻¹	$\Delta_f G^\circ$	Log K_f
298.15	23.22	31.09	0.00	31.09	0.0	0.0	0.0
300	23.25	31.23	0.14	31.09	0.0	0.0	0.0
400	24.31	38.08	6.06	32.02	0.0	0.0	0.0
500	24.96	43.58	9.78	33.80	0.0	0.0	0.0
600	25.45	48.18	12.36	35.82	0.0	0.0	0.0
700	25.87	52.13	14.26	37.88	0.0	0.0	0.0
800	26.24	55.61	15.73	39.88	0.0	0.0	0.0
900	26.59	58.72	16.92	41.80	0.0	0.0	0.0
1000	26.93	61.54	17.90	43.64	0.0	0.0	0.0
1100	27.25	64.12	18.74	45.39	0.0	0.0	0.0
1200	27.57	66.51	19.46	47.05	0.0	0.0	0.0
1211.4	27.61	66.77	19.54	47.23	0.0	0.0	0.0
1211.4	27.60	97.34	50.11	47.23	0.0	0.0	0.0
1300	27.60	99.29	48.57	50.72	0.0	0.0	0.0
1400	27.60	101.33	47.07	54.26	0.0	0.0	0.0
1500	27.60	103.24	45.78	57.46	0.0	0.0	0.0
1600	27.60	105.02	44.64	60.38	0.0	0.0	0.0
1700	27.60	106.69	43.64	63.05	0.0	0.0	0.0
1800	27.60	108.27	42.75	65.52	0.0	0.0	0.0

Melting T	1211.4 K	Boiling T	3107 K
$\Delta_{\text{fus}} H^\circ$	37.03 kJ	$\Delta_{\text{vap}} H^\circ$	330.92 kJ
$H_{298}^\circ - H_0^\circ$	4.64 kJ	Molar Vol.	1.363 J·bar ⁻¹ 13.63 cm ³

HYDROGEN (REFERENCE STATE)

Formula wt 2.016

 H_2 : Ideal diatomic gas at $P = 1$ bar 298.15 to 2500 K.

Temp. K	C_p°	S_T°	$(H_T^\circ - H_{298}^\circ)/T$ J·mol ⁻¹ ·K ⁻¹	$-(G_T^\circ - H_{298}^\circ)/T$	FORMATION FROM THE ELEMENTS		
					$\Delta_f H^\circ$ kJ·mol ⁻¹	$\Delta_f G^\circ$	Log K_f
298.15	28.82	130.68	0.00	130.68	0.0	0.0	0.0
300	28.84	130.86	0.18	130.68	0.0	0.0	0.0
400	29.24	139.23	7.41	131.82	0.0	0.0	0.0
500	29.25	145.76	11.78	133.98	0.0	0.0	0.0
600	29.29	151.09	14.69	136.40	0.0	0.0	0.0
700	29.41	155.61	16.78	138.83	0.0	0.0	0.0
800	29.62	159.55	18.38	141.18	0.0	0.0	0.0
900	29.90	163.06	19.64	143.42	0.0	0.0	0.0
1000	30.24	166.23	20.68	145.54	0.0	0.0	0.0
1100	30.61	169.13	21.57	147.56	0.0	0.0	0.0
1200	31.01	171.81	22.34	149.47	0.0	0.0	0.0
1300	31.43	174.31	23.02	151.28	0.0	0.0	0.0
1400	31.86	176.65	23.64	153.01	0.0	0.0	0.0
1500	32.29	178.86	24.20	154.66	0.0	0.0	0.0
1600	32.71	180.96	24.72	156.24	0.0	0.0	0.0
17	33.12	182.96	25.20	157.75	0.0	0.0	0.0
1800	33.53	184.86	25.65	159.21	0.0	0.0	0.0

Melting T 13.80 K

Boiling T 20.27 K

 $\Delta_{\text{sub}} H^\circ$ 0.117 kJ $\Delta_{\text{vap}} H^\circ$ 0.904 kJ $H_{298}^\circ - H_0^\circ$ 8.468 kJMolar Vol. 2478.97 J·bar⁻¹
24789.7 cm³

MERCURY (REFERENCE STATE)

Formula wt 200.59

Hg: Liquid 298.15 to boiling point 629.0 K. Ideal monatomic gas at P = 1 bar, 629.0 K.

Temp. K	C_p°	S_T°	$(H_T^\circ - H_{298}^\circ)/T$	$-(G_T^\circ - H_{298}^\circ)/T$	FORMATION FROM THE ELEMENTS		
					$\Delta_f H^\circ$	$\Delta_f G^\circ$	Log K_f
			$J \cdot mol^{-1} \cdot K^{-1}$		$kJ \cdot mol^{-1}$		
298.15	27.96	75.90	0.00	75.90	0.0	0.0	0.0
300	27.95	76.07	0.17	75.90	0.0	0.0	0.0
400	27.41	84.03	7.04	76.99	0.0	0.0	0.0
500	27.17	90.12	11.09	79.03	0.0	0.0	0.0
600	27.14	95.07	13.76	81.31	0.0	0.0	0.0
629.0	27.17	96.35	14.38	81.97	0.0	0.0	0.0
629.0	20.79	190.49	108.52	81.97	0.0	0.0	0.0
700	20.79	192.71	99.62	93.09	0.0	0.0	0.0
800	20.79	195.48	89.77	105.71	0.0	0.0	0.0
900	20.79	197.93	82.10	115.83	0.0	0.0	0.0
1000	20.79	200.12	75.97	124.15	0.0	0.0	0.0
1100	20.79	202.10	70.96	131.14	0.0	0.0	0.0
1200	20.79	203.91	66.78	137.14	0.0	0.0	0.0
1300	20.79	205.58	63.24	142.34	0.0	0.0	0.0
1400	20.79	207.12	60.21	146.91	0.0	0.0	0.0
1500	20.79	208.55	57.58	150.97	0.0	0.0	0.0
1600	20.79	209.89	55.28	154.61	0.0	0.0	0.0
1700	20.79	211.15	53.25	157.90	0.0	0.0	0.0
1800	20.79	212.34	51.45	160.89	0.0	0.0	0.0

Melting T 234.32 K

Boiling T 629.0 K

 $\Delta_{\text{m}} H^\circ$ 2.297 kJ $\Delta_{\text{vap}} H^\circ$ 59.214 kJ $H_{298}^\circ - H_0^\circ$ 9.343 kJMolar Vol. 1.4822 $J \cdot \text{bar}^{-1}$
14.822 cm^3

IODINE (REFERENCE STATE)

Formula wt 253.809

I_2 : Crystals 298.15 to melting point 386.8 K; liquid 386.8 to boiling point 457.7 K; ideal diatomic gas, P=1 bar, 457.7 to 2200 K.

Temp. K	C_p°	S_T°	$(H_T^\circ - H_{298}^\circ)/T$	$-(G_T^\circ - H_{298}^\circ)/T$	FORMATION FROM THE ELEMENTS		
					$\Delta_f H^\circ$	$\Delta_f G^\circ$	Log K_f
			$J \cdot mol^{-1} \cdot K^{-1}$		$kJ \cdot mol^{-1}$		
298.15	54.44	116.14	0.00	116.14	0.0	0.0	0.0
300	54.51	116.48	0.34	116.14	0.0	0.0	0.0
386.8	63.54	131.22	13.32	117.90	0.0	0.0	0.0
386.8	80.67	171.34	53.44	117.90	0.0	0.0	0.0
400	80.67	174.06	54.35	119.71	0.0	0.0	0.0
457.7	80.67	184.93	57.67	127.26	0.0	0.0	0.0
457.7	37.39	276.61	149.35	127.26	0.0	0.0	0.0
500	37.48	279.93	139.88	140.06	0.0	0.0	0.0
600	37.53	286.77	122.82	163.96	0.0	0.0	0.0
700	37.55	292.56	110.63	181.93	0.0	0.0	0.0
800	37.62	297.58	101.50	196.08	0.0	0.0	0.0
900	37.76	302.01	94.41	207.61	0.0	0.0	0.0
1000	37.96	306.00	88.75	217.25	0.0	0.0	0.0
1100	38.23	309.63	84.15	225.48	0.0	0.0	0.0
1200	38.56	312.97	80.34	232.64	0.0	0.0	0.0
1300	38.93	316.07	77.14	238.94	0.0	0.0	0.0
1400	39.34	318.97	74.42	244.55	0.0	0.0	0.0
1500	39.79	321.70	72.10	249.61	0.0	0.0	0.0
1600	40.27	324.29	70.09	254.19	0.0	0.0	0.0
1700	40.78	326.74	68.35	258.39	0.0	0.0	0.0
1800	41.31	329.09	66.84	262.25	0.0	0.0	0.0

Melting T 386.8 K

Boiling T 457.7 K

 $\Delta_{\text{sub}} H^\circ$ 15.52 kJ $\Delta_{\text{vap}} H^\circ$ 41.96 kJ $H_{298}^\circ - H_0^\circ$ 13.20 kJMolar Vol. 5.129 $J \cdot \text{bar}^{-1}$
51.29 cm^3

POTASSIUM (REFERENCE STATE)

Formula wt 39.098

K: Crystals 298.15 to melting point 336.4 K; liquid 336.4 to boiling point 1039.5 K; ideal monatomic gas, P=1 bar, 1039.5 to 1800 K.

Temp. K	C_p°	S_T°	$(H_T^\circ - H_{298}^\circ)/T$ J·mol ⁻¹ ·K ⁻¹	$-(G_T^\circ - H_{298}^\circ)/T$	FORMATION FROM THE ELEMENTS		
					$\Delta_f H^\circ$ kJ·mol ⁻¹	$\Delta_f G^\circ$	Log K_f
298.15	29.50	64.67	0.00	64.67	0.0	0.0	0.0
300	29.57	64.85	0.18	64.67	0.0	0.0	0.0
336.4	34.57	68.37	3.49	64.88	0.0	0.0	0.0
336.4	32.14	75.31	10.43	64.88	0.0	0.0	0.0
400	31.50	80.82	13.83	66.99	0.0	0.0	0.0
500	30.70	87.76	17.28	70.48	0.0	0.0	0.0
600	30.14	93.31	19.47	73.84	0.0	0.0	0.0
700	29.82	97.92	20.97	76.95	0.0	0.0	0.0
800	29.76	101.90	22.07	79.83	0.0	0.0	0.0
900	29.94	105.41	22.93	82.48	0.0	0.0	0.0
1000	30.36	108.59	23.65	84.94	0.0	0.0	0.0
1039.5	30.60	109.77	23.91	85.86	0.0	0.0	0.0
1039.5	20.79	186.30	100.44	85.86	0.0	0.0	0.0
1100	20.79	187.48	96.07	91.41	0.0	0.0	0.0
1200	20.79	189.28	89.78	99.50	0.0	0.0	0.0
1300	20.79	190.95	84.48	106.47	0.0	0.0	0.0
1400	20.79	192.49	79.93	112.56	0.0	0.0	0.0
1500	20.80	193.92	75.99	117.93	0.0	0.0	0.0
1600	20.81	195.27	72.54	122.73	0.0	0.0	0.0
1700	20.84	196.53	69.50	127.03	0.0	0.0	0.0
1800	20.87	197.72	66.80	130.92	0.0	0.0	0.0

Melting T	336.4 K	Boiling T	1039.5 K
$\Delta_{\text{fus}} H^\circ$	2.33 kJ	$\Delta_{\text{vap}} H^\circ$	79.92 kJ
$H_{298}^\circ - H_0^\circ$	7.09 kJ	Molar Vol.	4.536 J·bar ⁻¹ 45.36 cm ³

LITHIUM (REFERENCE STATE)

Formula wt 6.941

Li: Crystals 298.15 to melting point 453.2 K; liquid 453.7 K to boiling point 1620 K; ideal monatomic gas, P=1 bar, 1620 to 1800 K.

Temp. K	C_p°	S_T°	FORMATION FROM THE ELEMENTS				
			$(H_T^\circ - H_{298}^\circ)/T$ J·mol ⁻¹ ·K ⁻¹	$-(G_T^\circ - H_{298}^\circ)/T$	$\Delta_f H^\circ$ kJ·mol ⁻¹	$\Delta_f G^\circ$	Log K_f
298.15	24.62	29.09	0.00	29.09	0.0	0.0	0.0
300	24.67	29.24	0.15	29.08	0.0	0.0	0.0
400	27.61	36.70	6.62	30.08	0.0	0.0	0.0
453.7	29.39	40.29	9.21	31.08	0.0	0.0	0.0
453.7	30.39	46.90	15.82	31.08	0.0	0.0	0.0
500	30.13	49.84	17.16	32.69	0.0	0.0	0.0
600	29.54	55.28	19.27	36.01	0.0	0.0	0.0
700	28.99	59.79	20.70	39.10	0.0	0.0	0.0
800	28.94	63.66	21.73	41.93	0.0	0.0	0.0
900	28.89	67.07	22.53	44.54	0.0	0.0	0.0
1000	28.84	70.11	23.16	46.95	0.0	0.0	0.0
1100	28.79	72.85	23.67	49.18	0.0	0.0	0.0
1200	28.74	75.36	24.10	51.26	0.0	0.0	0.0
1300	28.70	77.66	24.45	53.20	0.0	0.0	0.0
1400	28.62	79.78	24.75	55.02	0.0	0.0	0.0
1500	28.54	81.75	25.01	56.74	0.0	0.0	0.0
1600	28.45	83.59	25.23	58.36	0.0	0.0	0.0
1620	28.43	83.95	25.27	58.68	0.0	0.0	0.0
1620	20.79	173.97	115.30	58.67	0.0	0.0	0.0
1700	20.80	174.97	110.85	64.12	0.0	0.0	0.0
1800	20.81	176.16	105.85	70.31	0.0	0.0	0.0

Melting T 453.2 K

Boiling T 1620 K

 $\Delta_{\text{sub}} H^\circ$ 3.00 kJ $\Delta_{\text{vap}} H^\circ$ 145.84 kJ $H_{298}^\circ - H_0^\circ$ 4.62 kJMolar Vol. 1.3017 J·bar⁻¹
13.017 cm³

MAGNESIUM (REFERENCE STATE)

Formula wt 24.305

Mg: Hexagonal close-packed crystals 298.15 to melting point 923 K. Liquid 923 to boiling point 1366.1 K. Ideal monotomic gas, P = 1 bar, 1366.1 to 1800 K.

Temp. K	C_p°	S_T°	$(H_T^\circ - H_{298}^\circ)/T$ J·mol ⁻¹ ·K ⁻¹	$-(G_T^\circ - H_{298}^\circ)/T$	FORMATION FROM THE ELEMENTS		
					$\Delta_f H^\circ$ kJ·mol ⁻¹	$\Delta_f G^\circ$	Log K_f
298.15	24.87	32.67	0.00	32.67	0.0	0.0	0.0
300	24.90	32.82	0.15	32.67	0.0	0.0	0.0
400	26.14	40.17	6.50	33.66	0.0	0.0	0.0
500	27.18	46.11	10.54	35.58	0.0	0.0	0.0
600	28.20	51.16	13.39	37.76	0.0	0.0	0.0
700	29.29	55.58	15.59	40.00	0.0	0.0	0.0
800	30.51	59.57	17.37	42.20	0.0	0.0	0.0
900	31.90	63.25	18.91	44.34	0.0	0.0	0.0
923	32.24	64.05	19.23	44.82	0.0	0.0	0.0
923	34.31	73.23	28.42	44.82	0.0	0.0	0.0
1000	34.31	75.98	28.87	47.11	0.0	0.0	0.0
1100	34.31	79.25	29.36	49.89	0.0	0.0	0.0
1200	34.91	82.24	29.78	52.46	0.0	0.0	0.0
1300	34.31	84.98	30.12	54.86	0.0	0.0	0.0
1366.1	34.31	86.69	30.33	56.36	0.0	0.0	0.0
1366.1	20.79	180.29	123.93	56.36	0.0	0.0	0.0
1400	20.79	180.80	121.43	59.34	0.0	0.0	0.0
1500	20.79	182.23	114.72	67.49	0.0	0.0	0.0
1600	20.79	183.57	108.85	74.72	0.0	0.0	0.0
1700	20.79	184.83	103.67	81.16	0.0	0.0	0.0
1800	20.79	186.02	99.07	86.95	0.0	0.0	0.0

Melting T	923 K	Boiling T	1361.1 K
$\Delta_{\text{sub}} H^\circ$	8.477 kJ	$\Delta_{\text{vap}} H^\circ$	127.87 kJ
$H_{298}^\circ - H_0^\circ$	5.00 kJ	Molar Vol.	1.3996 J·bar ⁻¹ 13.996 cm ³

MANGANESE (REFERENCE STATE)

Formula wt 54.938

Mn: α -crystals 298.15 to 980 K. β -crystals 980 to 1360 K. γ -crystals 1360 to 1410 K. Δ -crystals 1410 to melting point 1517 K. Liquid 1517 to boiling point 2335 K.

Temp. K	C_p°	S_T°	$(H_T^\circ - H_{298}^\circ)/T$ J·mol ⁻¹ ·K ⁻¹	$-(G_T^\circ - H_{298}^\circ)/T$	FORMATION FROM THE ELEMENTS		
					$\Delta_f H^\circ$ kJ·mol ⁻¹	$\Delta_f G^\circ$	Log K_f
298.15	26.19	32.01	0.00	32.01	0.0	0.0	0.0
300	26.23	32.17	0.16	32.01	0.0	0.0	0.0
400	28.30	40.01	6.95	33.07	0.0	0.0	0.0
500	30.16	46.53	11.40	35.13	0.0	0.0	0.0
600	31.89	52.18	14.68	37.50	0.0	0.0	0.0
700	33.49	57.22	17.25	39.97	0.0	0.0	0.0
800	34.93	61.79	19.37	42.42	0.0	0.0	0.0
900	36.18	65.98	21.17	44.81	0.0	0.0	0.0
980	37.04	69.05	22.35	46.70	0.0	0.0	0.0
980	37.59	71.40	24.70	46.70	0.0	0.0	0.0
1000	37.68	72.12	24.96	47.16	0.0	0.0	0.0
1100	38.11	75.73	26.14	49.59	0.0	0.0	0.0
1200	38.54	79.07	27.15	51.92	0.0	0.0	0.0
1300	38.97	82.17	28.04	54.13	0.0	0.0	0.0
1360	39.15	84.01	28.52	55.49	0.0	0.0	0.0
1360	42.41	84.97	29.48	55.49	0.0	0.0	0.0
1400	43.43	86.75	30.47	56.28	0.0	0.0	0.0
1410	43.51	87.07	30.56	56.51	0.0	0.0	0.0
1410	45.23	88.41	31.89	56.52	0.0	0.0	0.0
1500	45.97	91.21	32.72	58.49	0.0	0.0	0.0
1517	46.11	91.86	32.87	59.00	0.0	0.0	0.0
1517	46.02	99.81	40.81	59.00	0.0	0.0	0.0
1600	46.02	102.13	41.08	61.05	0.0	0.0	0.0
1700	46.02	104.92	41.38	63.55	0.0	0.0	0.0
1800	46.02	107.55	41.63	65.92	0.0	0.0	0.0

Melting T 1517 K

Boiling T 2335 K

 $\Delta_{fus} H^\circ$ 12.06 kJ $\Delta_{vap} H^\circ$ kJ $H_{298}^\circ - H_0^\circ$ 4.996 kJMolar Vol. 0.7354 J·bar⁻¹
7.354 cm³

MOLYBDENUM (REFERENCE STATE)

Formula wt 95.94

Mo: Body-centered cubic crystals 298.15 to 2500 K.

Temp. K	C_p°	S_T°	$(H_T^\circ - H_{298}^\circ)/T$ J·mol ⁻¹ ·K ⁻¹	$-(G_T^\circ - H_{298}^\circ)/T$	FORMATION FROM THE ELEMENTS		
					$\Delta_f H^\circ$ kJ·mol ⁻¹	$\Delta_f G^\circ$	Log K_f
298.15	23.90	28.66	0.00	28.66	0.0	0.0	0.0
300	23.92	28.81	0.15	28.66	0.0	0.0	0.0
400	25.05	35.86	6.24	29.61	0.0	0.0	0.0
500	25.86	41.54	10.09	31.45	0.0	0.0	0.0
600	26.47	46.31	12.77	33.54	0.0	0.0	0.0
700	26.99	50.43	14.76	35.66	0.0	0.0	0.0
800	27.46	54.06	16.32	37.74	0.0	0.0	0.0
900	27.92	57.32	17.58	39.74	0.0	0.0	0.0
1000	28.40	60.29	18.64	41.65	0.0	0.0	0.0
1100	28.92	63.02	19.55	43.47	0.0	0.0	0.0
1200	29.49	65.56	20.36	45.20	0.0	0.0	0.0
1300	30.11	67.95	21.08	46.86	0.0	0.0	0.0
1400	30.80	70.20	21.75	48.45	0.0	0.0	0.0
1500	31.56	72.35	22.38	49.97	0.0	0.0	0.0
1600	32.40	74.42	22.98	51.44	0.0	0.0	0.0
1700	33.31	76.41	23.56	52.85	0.0	0.0	0.0
1800	34.30	78.34	24.13	54.21	0.0	0.0	0.0

Melting T	2890 K	Boiling T	4912 K
$\Delta_{\text{fus}} H^\circ$	32.54 kJ	$\Delta_{\text{vap}} H^\circ$	598.07 kJ
$H_{298}^\circ - H_0^\circ$	4.594 kJ	Molar Vol.	0.9387 J·bar ⁻¹ 9.387 cm ³

NITROGEN (REFERENCE STATE)

Formula wt 28.013

N₂: Ideal diatomic gas at P = 1 bar 298.15 to 2500 K.

Temp. K	C _p ^o	S _T ^o	(H _T ^o -H ₂₉₈ ^o)/T	-(G _T ^o -H ₂₉₈ ^o)/T	FORMATION FROM THE ELEMENTS		
					Δ _f H ^o	Δ _f G ^o	Log K _f
			J·mol ⁻¹ ·K ⁻¹		kJ·mol ⁻¹		
298.15	29.13	191.61	0.00	191.61	0.0	0.0	0.0
300	29.13	191.79	0.18	191.61	0.0	0.0	0.0
400	29.24	200.17	7.42	192.75	0.0	0.0	0.0
500	29.70	206.74	11.83	194.92	0.0	0.0	0.0
600	30.26	212.21	14.85	197.35	0.0	0.0	0.0
700	30.86	216.91	17.09	199.82	0.0	0.0	0.0
800	31.45	221.07	18.85	202.22	0.0	0.0	0.0
900	32.03	224.81	20.29	204.53	0.0	0.0	0.0
1000	32.58	228.22	21.49	206.73	0.0	0.0	0.0
1100	33.10	231.35	22.52	208.83	0.0	0.0	0.0
1200	33.58	234.25	23.42	210.83	0.0	0.0	0.0
1300	34.03	236.95	24.22	212.73	0.0	0.0	0.0
1400	34.45	239.49	24.94	214.55	0.0	0.0	0.0
1500	34.82	241.88	25.58	216.30	0.0	0.0	0.0
1600	35.16	244.14	26.17	217.97	0.0	0.0	0.0
1700	35.45	246.28	26.71	219.57	0.0	0.0	0.0
1800	35.71	248.31	27.20	221.11	0.0	0.0	0.0

Melting T 63.14 K

Boiling T 77.35 K

Δ_{at}H^o 0.720 kJΔ_{vap}H^o 5.586 kJH₂₉₈^o-H₀^o 8.669 kJMolar Vol. 2478.97 J·bar⁻¹
24789.7 cm³

SODIUM (REFERENCE STATE)

Formula wt 22.990

Na: Body-centered cubic crystals 298.15 to melting point 371 K; liquid 371 to fictive boiling point 1170.5 K. Ideal monotomic gas, P=1 bar, 1170.5 to 1800 K.

Temp. K	C_p°	S_T°	FORMATION FROM THE ELEMENTS				
			$(H_T^\circ - H_{298}^\circ)/T$ J·mol ⁻¹ ·K ⁻¹	$-(G_T^\circ - H_{298}^\circ)/T$	$\Delta_f H^\circ$ kJ·mol ⁻¹	$\Delta_f G^\circ$	Log K_f
298.15	28.15	51.46	0.00	51.46	0.0	0.0	0.0
300	28.20	51.63	0.17	51.46	0.0	0.0	0.0
371	31.83	57.90	5.80	52.10	0.0	0.0	0.0
371	31.83	64.92	12.82	52.10	0.0	0.0	0.0
400	31.51	67.30	14.18	53.12	0.0	0.0	0.0
500	30.55	74.22	17.54	56.68	0.0	0.0	0.0
600	29.81	79.73	19.66	60.07	0.0	0.0	0.0
700	29.27	84.28	21.06	63.22	0.0	0.0	0.0
800	28.94	88.16	22.06	66.10	0.0	0.0	0.0
900	28.84	91.56	22.82	68.74	0.0	0.0	0.0
1000	28.94	94.61	23.43	71.18	0.0	0.0	0.0
1100	29.26	97.38	23.94	73.44	0.0	0.0	0.0
1170.5	29.61	99.21	24.28	74.93	0.0	0.0	0.0
1170.5	20.79	182.09	107.16	74.93	0.0	0.0	0.0
1200	20.79	182.61	105.04	77.57	0.0	0.0	0.0
1300	20.79	184.28	98.56	85.72	0.0	0.0	0.0
1400	20.79	185.82	93.01	92.81	0.0	0.0	0.0
1500	20.79	187.25	88.19	99.06	0.0	0.0	0.0
1600	20.79	188.59	83.97	104.62	0.0	0.0	0.0
1700	20.79	189.85	80.26	109.59	0.0	0.0	0.0
1800	20.79	191.04	76.96	114.08	0.0	0.0	0.0

Melting T	371 K	Boiling T	1170.5 K
$\Delta_{fm} H^\circ$	2.598 kJ	$\Delta_{vap} H^\circ$	97.610 kJ
$H_{298}^\circ - H_0^\circ$	6.460 kJ	Molar Vol.	2.381 J·bar ⁻¹ 23.81 cm ³

NICKEL (REFERENCE STATE)

Formula wt 58.69

Ni: Face-centered cubic crystals (magnetic) to Curie point 631 K; nonmagnetic 631 to melting point 1728 K; liquid 1728 to 1800 K.

FORMATION FROM THE ELEMENTS

Temp. K	C_p°	S_T°	$(H_T^\circ - H_{298}^\circ)/T$ J·mol ⁻¹ ·K ⁻¹	$-(G_T^\circ - H_{298}^\circ)/T$	$\Delta_f H^\circ$ kJ·mol ⁻¹	$\Delta_f G^\circ$	Log K_f
298.15	25.99	29.87	0.00	29.87	0.0	0.0	0.0
300	26.05	30.03	0.16	29.87	0.0	0.0	0.0
400	28.38	37.87	6.95	30.92	0.0	0.0	0.0
500	30.82	44.45	11.46	32.99	0.0	0.0	0.0
600	34.85	50.39	15.00	35.40	0.0	0.0	0.0
631	39.83	52.26	16.08	36.19	0.0	0.0	0.0
700	30.79	55.58	17.63	37.94	0.0	0.0	0.0
800	31.00	59.10	19.29	39.81	0.0	0.0	0.0
900	31.59	63.38	20.62	42.76	0.0	0.0	0.0
1000	32.22	66.74	21.75	44.99	0.0	0.0	0.0
1100	32.93	69.85	22.73	47.11	0.0	0.0	0.0
1200	33.68	72.74	23.61	49.13	0.0	0.0	0.0
1300	34.52	75.47	24.42	51.05	0.0	0.0	0.0
1400	35.40	78.06	25.17	52.89	0.0	0.0	0.0
1500	36.32	80.53	25.88	54.65	0.0	0.0	0.0
1600	37.28	82.91	26.57	56.34	0.0	0.0	0.0
1700	38.28	85.20	27.23	57.97	0.0	0.0	0.0
1728	38.54	85.83	27.41	58.42	0.0	0.0	0.0
1728	38.91	95.75	37.34	58.42	0.0	0.0	0.0
1800	38.91	97.34	37.40	59.94	0.0	0.0	0.0

Melting T 1728 K

Boiling T K

 $\Delta_{\text{fus}} H^\circ$ 17.16 kJ $\Delta_{\text{vap}} H^\circ$ kJ $H_{298}^\circ - H_0^\circ$ 4.79 kJMolar Vol. 0.6588 J·bar⁻¹
6.588 cm³

OXYGEN (REFERENCE STATE)

Formula wt 31.999

O₂: Ideal diatomic gas at P = 1 bar 298.15 to 2500 K.

Temp. K	C _p ^o	S _T ^o	(H _T ^o -H ₂₉₈ ^o)/T	-(G _T ^o -H ₂₉₈ ^o)/T	FORMATION FROM THE ELEMENTS		
					Δ _f H ^o	Δ _f G ^o	Log K _f
			J·mol ⁻¹ ·K ⁻¹	kJ·mol ⁻¹			
298.15	29.35	205.15	0.00	205.15	0.0	0.0	0.0
300	29.35	205.33	0.18	205.15	0.0	0.0	0.0
400	30.04	213.85	7.54	206.31	0.0	0.0	0.0
500	31.12	220.67	12.15	208.52	0.0	0.0	0.0
600	32.14	226.43	15.40	211.04	0.0	0.0	0.0
700	33.00	231.45	17.85	213.60	0.0	0.0	0.0
800	33.72	235.91	19.79	216.12	0.0	0.0	0.0
900	34.33	239.92	21.37	218.54	0.0	0.0	0.0
1000	34.85	243.56	22.70	220.86	0.0	0.0	0.0
1100	35.29	246.90	23.82	223.08	0.0	0.0	0.0
1200	35.67	249.99	24.79	225.20	0.0	0.0	0.0
1300	36.00	252.86	25.64	227.22	0.0	0.0	0.0
1400	36.31	255.54	26.39	229.14	0.0	0.0	0.0
1500	36.58	258.05	27.06	230.99	0.0	0.0	0.0
1600	36.84	260.42	27.67	232.75	0.0	0.0	0.0
1700	37.08	262.66	28.21	234.45	0.0	0.0	0.0
1800	37.32	264.79	28.71	236.08	0.0	0.0	0.0
Melting T	54.35 K				Boiling T	90.18 K	
Δ _{fus} H ^o	0.444 kJ				Δ _{vap} H ^o	6.816 kJ	
H ₂₉₈ ^o -H ₀ ^o	8.682 kJ				Molar Vol.	2478.97 J·bar ⁻¹ 24789.7 cm ³	

PHOSPHORUS (REFERENCE STATE)

Formula wt 30.974

P: Crystals (white, α) 298.15 to melting point 317.3 K. Liquid 317.3 to sublimation point 1180 K. Ideal diatomic gas 1180 to 1800 K.

Temp. K	C_p°	S_T°	$(H_T^\circ - H_{298}^\circ)/T$ J·mol ⁻¹ ·K ⁻¹	$-(G_T^\circ - H_{298}^\circ)/T$	FORMATION FROM THE ELEMENTS		
					$\Delta_f H^\circ$ kJ·mol ⁻¹	$\Delta_f G^\circ$	Log K_f
298.15	23.82	41.09	0.00	41.08	0.0	0.0	0.0
300	23.87	41.22	0.14	41.08	0.0	0.0	0.0
317.3	24.35	42.57	1.45	41.12	0.0	0.0	0.0
317.3	26.32	44.65	3.53	41.12	0.0	0.0	0.0
400	26.32	50.75	8.24	42.51	0.0	0.0	0.0
500	26.32	56.62	11.86	44.76	0.0	0.0	0.0
600	26.32	61.42	14.27	47.15	0.0	0.0	0.0
700	26.32	65.48	15.99	49.49	0.0	0.0	0.0
800	26.32	68.99	17.28	51.71	0.0	0.0	0.0
900	26.32	72.09	18.29	53.80	0.0	0.0	0.0
1000	26.32	74.87	19.09	55.78	0.0	0.0	0.0
1100	26.32	77.38	19.75	57.63	0.0	0.0	0.0
1180	26.32	79.22	20.19	59.03	0.0	0.0	0.0
1180	18.54	133.23	74.20	59.03	0.0	0.0	0.0
1200	18.55	133.54	73.27	60.27	0.0	0.0	0.0
1300	18.60	135.03	69.07	65.96	0.0	0.0	0.0
1400	18.64	136.41	65.46	70.95	0.0	0.0	0.0
1500	18.68	137.70	62.34	75.36	0.0	0.0	0.0
1600	18.72	138.91	59.62	79.29	0.0	0.0	0.0
1700	18.75	140.04	57.21	82.83	0.0	0.0	0.0
1800	18.77	141.11	55.08	86.03	0.0	0.0	0.0

Melting T 317.3 K

Boiling T 1180 K

 $\Delta_{\text{fus}} H^\circ$ 0.659 kJ $\Delta_{\text{vap}} H^\circ$ 63.84 kJ $H_{298}^\circ - H^\circ$ 5.36 kJMolar Vol. 1.73 J·bar⁻¹
17.3 cm³

LEAD (REFERENCE STATE)

Formula wt 207.2

Pb: Face-centered cubic crystals 298.15 to melting point 600.6 K. Liquid 600.6 to boiling point 2021 K.

Temp. K	C_p°	S_T°	$(H_T^\circ - H_{298}^\circ)/T$ J·mol ⁻¹ ·K ⁻¹	$-(G_T^\circ - H_{298}^\circ)/T$	FORMATION FROM THE ELEMENTS		
					$\Delta_f H^\circ$ kJ·mol ⁻¹	$\Delta_f G^\circ$	Log K_f
298.15	26.65	64.80	0.00	64.80	0.0	0.0	0.0
300	26.67	64.96	0.16	64.80	0.0	0.0	0.0
400	27.79	72.80	6.94	65.86	0.0	0.0	0.0
500	28.78	79.10	11.21	67.89	0.0	0.0	0.0
600	29.74	84.44	14.22	70.22	0.0	0.0	0.0
600.6	29.74	84.47	14.23	70.24	0.0	0.0	0.0
600.6	30.63	92.48	22.24	70.24	0.0	0.0	0.0
700	30.31	97.15	23.41	73.74	0.0	0.0	0.0
800	29.98	101.17	24.25	76.92	0.0	0.0	0.0
900	29.66	104.68	24.87	79.81	0.0	0.0	0.0
1000	29.37	107.79	25.34	82.45	0.0	0.0	0.0
1100	29.17	110.58	25.69	84.89	0.0	0.0	0.0
1200	28.90	113.10	25.97	87.13	0.0	0.0	0.0
1300	28.73	115.41	26.19	89.22	0.0	0.0	0.0
1400	28.60	117.54	26.36	91.18	0.0	0.0	0.0
1500	28.51	119.50	26.51	92.99	0.0	0.0	0.0
1600	28.46	121.34	26.63	94.71	0.0	0.0	0.0
1700	28.45	123.07	26.74	96.33	0.0	0.0	0.0
1800	28.48	124.70	26.84	97.86	0.0	0.0	0.0

Melting T	600.65 K	Boiling T	2021 K
$\Delta_{\text{fus}} H^\circ$	4.81 kJ	$\Delta_{\text{vap}} H^\circ$	177.7 kJ
$H_{298}^\circ - H_0^\circ$	6.870 kJ	Molar Vol.	1.8267 J·bar ⁻¹ 18.267 cm ³

PLATINUM (REFERENCE STATE)

Formula wt 195.08

Pt: Face-centered cubic crystals 298.15 to melting point 2042 K.

Temp. K	C_p°	S_T°	$(H_T^\circ - H_{298}^\circ)/T$ J·mol ⁻¹ ·K ⁻¹	$-(G_T^\circ - H_{298}^\circ)/T$	FORMATION FROM THE ELEMENTS		
					$\Delta_f H^\circ$ kJ·mol ⁻¹	$\Delta_f G^\circ$	Log K_f
298.15	25.81	41.63	0.00	41.63	0.0	0.0	0.0
300	25.83	41.79	0.16	41.63	0.0	0.0	0.0
400	26.49	49.32	6.67	42.65	0.0	0.0	0.0
500	27.02	55.29	10.68	44.60	0.0	0.0	0.0
600	27.53	60.26	13.45	46.81	0.0	0.0	0.0
700	28.04	64.54	15.50	49.04	0.0	0.0	0.0
800	28.56	68.32	17.10	51.22	0.0	0.0	0.0
900	29.08	71.71	18.40	53.31	0.0	0.0	0.0
1000	29.61	74.80	19.49	55.31	0.0	0.0	0.0
1100	30.15	77.65	20.44	57.21	0.0	0.0	0.0
1200	30.69	80.30	21.27	59.03	0.0	0.0	0.0
1300	31.22	82.78	22.02	60.76	0.0	0.0	0.0
1400	31.76	85.11	22.69	62.42	0.0	0.0	0.0
1500	32.29	87.32	23.31	64.00	0.0	0.0	0.0
1600	32.82	89.42	23.89	65.53	0.0	0.0	0.0
1700	33.34	91.42	24.43	66.99	0.0	0.0	0.0
1800	33.86	93.34	24.94	68.40	0.0	0.0	0.0

Melting T 2042 K

Boiling T K

 $\Delta_{\text{fus}} H^\circ$ 19.648 kJ $\Delta_{\text{vap}} H^\circ$ kJ $H_{298}^\circ - H_0^\circ$ 5.724 kJMolar Vol. 0.9091 J·bar⁻¹
9.091 cm³

01/07/93

SULFUR (REFERENCE STATE)

Formula wt 32.066

S: Orthorhombic crystals 298.15 to 368.3 K; monoclinic crystals 368.3 to melting point 388.36 K; liquid 388.36 K to fictive boiling point 882.1 K. Ideal diatomic gas, P=1 bar, 882.1 to 1800 K.

Temp. K	C_p°	S_T°	FORMATION FROM THE ELEMENTS				
			$(H_T^\circ - H_{298}^\circ)/T$	$-(G_T^\circ - H_{298}^\circ)/T$	$\Delta_f H^\circ$	$\Delta_f G^\circ$	Log K_f
			$J \cdot mol^{-1} \cdot K^{-1}$		$kJ \cdot mol^{-1}$		
298.15	22.70	32.05	0.00	32.05	0.0	0.0	0.0
300	22.74	32.19	0.14	32.05	0.0	0.0	0.0
368.3	24.24	37.01	4.47	32.54	0.0	0.0	0.0
368.3	24.77	38.10	5.56	32.54	0.0	0.0	0.0
388.36	25.17	39.43	6.57	32.86	0.0	0.0	0.0
388.36	31.06	43.86	11.00	32.86	0.0	0.0	0.0
400	32.16	44.79	11.60	33.19	0.0	0.0	0.0
500	37.98	53.53	17.13	36.40	0.0	0.0	0.0
600	34.31	60.08	20.25	39.82	0.0	0.0	0.0
700	32.68	65.24	22.14	43.10	0.0	0.0	0.0
800	31.70	69.53	23.39	46.14	0.0	0.0	0.0
882.1	31.66	72.62	24.16	48.47	0.0	0.0	0.0
882.1	18.47	133.08	84.61	48.47	0.0	0.0	0.0
900	18.51	133.45	83.29	50.16	0.0	0.0	0.0
1000	18.68	135.41	76.82	58.59	0.0	0.0	0.0
1100	18.85	137.20	71.55	65.65	0.0	0.0	0.0
1200	19.00	138.85	67.16	71.69	0.0	0.0	0.0
1300	19.15	140.37	63.46	76.91	0.0	0.0	0.0
1400	19.28	141.80	60.30	81.50	0.0	0.0	0.0
1500	19.42	143.13	57.57	85.56	0.0	0.0	0.0
1600	19.55	144.39	55.19	89.20	0.0	0.0	0.0
1700	19.67	145.58	53.10	92.48	0.0	0.0	0.0
1800	19.79	146.71	51.24	95.46	0.0	0.0	0.0
Melting T	388.36 K				Boiling T	882.1 K	
$\Delta_{\text{sub}} H^\circ$	1.72 kJ				$\Delta_{\text{vap}} H^\circ$	53.32 kJ	
$H_{298}^\circ - H_0^\circ$	4.412 kJ				Molar Vol.	1.5511 J·bar ⁻¹ 15.511 cm ³	

S_2 (gas)

Formula wt 64.132

 S_2 : Ideal diatomic gas, P = 1 bar, 298.15 to 2500 K.

Temp. K	C_p°	S_T°	$(H_T^\circ - H_{298}^\circ)/T$	$-(G_T^\circ - H_{298}^\circ)/T$	FORMATION FROM THE ELEMENTS		
					$\Delta_f H^\circ$	$\Delta_f G^\circ$	Log K_f
			J·mol ⁻¹ ·K ⁻¹		kJ·mol ⁻¹		
298.15	32.49	228.17	0.00	228.17	128.6	79.7	-13.96
300	32.53	228.37	0.20	228.17	128.6	79.4	-13.82
400	34.05	237.96	8.49	229.47	122.7	63.4	-8.27
500	34.98	245.66	13.70	231.96	118.3	49.0	-5.12
600	35.65	252.10	17.31	234.80	114.7	35.5	-3.09
700	36.17	257.64	19.97	237.67	111.6	22.6	-1.68
800	36.62	262.50	22.02	240.48	108.8	10.0	-0.66
900	37.01	266.84	23.66	243.17	0.0	0.0	0.0
1000	37.37	270.75	25.02	245.74	0.0	0.0	0.0
1100	37.69	274.33	26.16	248.18	0.0	0.0	0.0
1200	38.00	277.62	27.13	250.49	0.0	0.0	0.0
1300	38.29	280.68	27.98	252.70	0.0	0.0	0.0
1400	38.57	283.53	28.72	254.80	0.0	0.0	0.0
1500	38.84	286.20	29.39	256.81	0.0	0.0	0.0
1600	39.09	288.71	29.99	258.72	0.0	0.0	0.0
1700	39.34	291.09	30.53	260.56	0.0	0.0	0.0
1800	39.59	293.34	31.03	262.32	0.0	0.0	0.0

Melting T

K

Boiling T

K

 $\Delta_{\text{fus}} H^\circ$

kJ

 $\Delta_{\text{vap}} H^\circ$

kJ

 $H_{298}^\circ - H_0^\circ$

9.124 kJ

Molar Vol. 2478.97 J·bar⁻¹
24789.7 cm³

11/18/92

ANTIMONY (REFERENCE STATE)

Formula wt 121.75

Sb: Rhombohedral crystals 298.15 to melting point 904 K. Liquid 904 to 1800 K.

Temp. K	C_p°	S_T°	$(H_T^\circ - H_{298}^\circ)/T$ J·mol ⁻¹ ·K ⁻¹	$-(G_T^\circ - H_{298}^\circ)/T$	FORMATION FROM THE ELEMENTS		
					$\Delta_f H^\circ$ kJ·mol ⁻¹	$\Delta_f G^\circ$	Log K_f
298.15	25.25	45.52	0.00	45.52	0.0	0.0	0.0
300	25.27	45.69	0.16	45.52	0.0	0.0	0.0
400	25.91	53.04	6.52	46.52	0.0	0.0	0.0
500	26.48	58.88	10.45	48.43	0.0	0.0	0.0
600	27.17	63.77	13.18	50.59	0.0	0.0	0.0
700	28.09	68.02	15.24	52.78	0.0	0.0	0.0
800	29.32	71.85	16.92	54.93	0.0	0.0	0.0
900	30.92	75.39	18.38	57.01	0.0	0.0	0.0
904	30.99	75.54	18.41	57.11	0.0	0.0	0.0
904	31.38	97.53	40.42	57.11	0.0	0.0	0.0
1000	31.38	100.68	39.55	61.12	0.0	0.0	0.0
1100	31.38	103.67	38.81	64.86	0.0	0.0	0.0
1200	31.38	106.40	38.19	68.21	0.0	0.0	0.0
1300	31.38	108.91	37.66	71.24	0.0	0.0	0.0
1400	31.38	111.24	37.22	74.02	0.0	0.0	0.0
1500	31.38	113.40	36.83	76.57	0.0	0.0	0.0
1600	31.38	115.41	36.49	78.94	0.0	0.0	0.0
1700	31.38	117.33	36.18	81.14	0.0	0.0	0.0
1800	31.38	119.12	35.92	83.20	0.0	0.0	0.0
Melting T	904 K				Boiling T	1860 K	
$\Delta_{fus} H^\circ$	19.874 kJ				$\Delta_{vap} H^\circ$	86.525 kJ	
$H_{298}^\circ - H_0^\circ$	5.870 kJ				Molar Vol.	1.8178 J·bar ⁻¹ 18.178 cm ³	

SELENIUM (REFERENCE STATE)

Formula wt 78.96

Se: Crystals 298.15 to melting point 494 K. Liquid 494 to boiling point 957 K. Ideal diatomic gas 957 to 1800 K.

Temp. K	C_p^0	S_T^0	FORMATION FROM THE ELEMENTS				
			$(H_T^0 - H_{298}^0)/T$ J·mol ⁻¹ ·K ⁻¹	$-(G_T^0 - H_{298}^0)/T$	$\Delta_f H^0$ kJ·mol ⁻¹	$\Delta_f G^0$	Log K_f
298.15	25.06	42.27	0.00	42.27	0.0	0.0	0.0
300	25.06	42.42	0.15	42.27	0.0	0.0	0.0
400	26.44	49.83	6.56	43.27	0.0	0.0	0.0
494	27.30	55.51	10.45	45.06	0.0	0.0	0.0
494	35.95	67.97	22.91	45.06	0.0	0.0	0.0
500	35.85	68.38	23.06	45.32	0.0	0.0	0.0
600	34.37	74.79	25.07	49.72	0.0	0.0	0.0
700	33.54	80.03	26.34	53.69	0.0	0.0	0.0
800	33.29	84.48	27.21	57.27	0.0	0.0	0.0
900	33.93	88.43	27.92	60.51	0.0	0.0	0.0
957	34.78	90.50	28.30	62.19	0.0	0.0	0.0
957	19.27	146.44	84.28	62.19	0.0	0.0	0.0
1000	19.31	147.29	81.48	65.81	0.0	0.0	0.0
1100	19.41	149.13	75.83	73.30	0.0	0.0	0.0
1200	19.52	150.82	71.14	79.68	0.0	0.0	0.0
1300	19.62	162.39	67.17	85.22	0.0	0.0	0.0
1400	19.73	153.84	63.78	90.06	0.0	0.0	0.0
1500	19.83	155.21	60.84	94.37	0.0	0.0	0.0
1600	19.94	156.49	58.28	98.21	0.0	0.0	0.0
1700	20.04	157.70	56.03	101.67	0.0	0.0	0.0
1800	20.15	158.85	54.03	104.82	0.0	0.0	0.0

Melting T 494 K

Boiling T 957 K

 $\Delta_{\text{m}} H^0$ 6.16 kJ $\Delta_{\text{v}} H^0$ 53.57 kJ $H_{298}^0 - H_0^0$ 5.52 kJMolar Vol. 1.642 J·bar⁻¹
16.42 cm³

SILICON (REFERENCE STATE)

Formula wt 28.086

Si: Cubic crystals 298.15 to melting point 1685 K; liquid 1685 to 1800 K.

Temp. K	C_p°	S_T°	FORMATION FROM THE ELEMENTS				
			$(H_T^\circ - H_{298}^\circ)/T$ J·mol ⁻¹ ·K ⁻¹	$-(G_T^\circ - H_{298}^\circ)/T$	$\Delta_f H^\circ$ kJ·mol ⁻¹	$\Delta_f G^\circ$	Log K_f
298.15	20.00	18.81	0.00	18.81	0.0	0.0	0.0
300	20.06	18.93	0.12	18.81	0.0	0.0	0.0
400	22.14	25.02	5.40	19.63	0.0	0.0	0.0
500	23.33	30.10	8.87	21.23	0.0	0.0	0.0
600	24.16	34.43	11.36	23.08	0.0	0.0	0.0
700	24.81	38.21	13.23	24.97	0.0	0.0	0.0
800	25.36	41.56	14.71	26.84	0.0	0.0	0.0
900	25.86	44.57	15.93	28.65	0.0	0.0	0.0
1000	26.33	47.32	16.94	30.38	0.0	0.0	0.0
1100	26.78	49.85	17.82	32.04	0.0	0.0	0.0
1200	27.21	52.20	18.58	33.62	0.0	0.0	0.0
1300	27.63	54.40	19.26	35.13	0.0	0.0	0.0
1400	28.05	56.46	19.87	36.58	0.0	0.0	0.0
1500	28.47	58.41	20.43	37.98	0.0	0.0	0.0
1600	28.88	60.26	20.95	39.31	0.0	0.0	0.0
1685	29.22	61.75	21.35	40.40	0.0	0.0	0.0
1685	27.20	91.55	51.15	40.40	0.0	0.0	0.0
1700	27.20	91.79	50.94	40.85	0.0	0.0	0.0
1800	27.20	93.35	49.62	43.73	0.0	0.0	0.0

Melting T	1685 K	Boiling T	K
$\Delta_{\text{fus}} H^\circ$	50.2 kJ	$\Delta_{\text{vap}} H^\circ$	kJ
$H_{298}^\circ - H_0^\circ$	3.218 kJ	Molar Vol.	1.2056 J·bar ⁻¹ 12.056 cm ³

TIN (REFERENCE STATE)

Formula wt 118.710

Sn: Crystals 298.15 to melting point 505.1 K. Liquid 501 to 1800 K.

Temp. K	C_p°	S_T°	$(H_T^\circ - H_{298}^\circ)/T$	$-(G_T^\circ - H_{298}^\circ)/T$	FORMATION FROM THE ELEMENTS		
					$\Delta_f H^\circ$	$\Delta_f G^\circ$	Log K_f
			$J \cdot mol^{-1} \cdot K^{-1}$		$kJ \cdot mol^{-1}$		
298.15	27.11	51.18	0.00	51.18	0.0	0.0	0.0
300	27.15	51.35	0.17	51.18	0.0	0.0	0.0
400	28.90	59.40	7.13	52.27	0.0	0.0	0.0
500	31.03	66.06	11.69	54.37	0.0	0.0	0.0
505.1	31.16	66.38	11.88	54.50	0.0	0.0	0.0
505.1	29.42	80.63	26.13	54.50	0.0	0.0	0.0
600	28.66	85.62	26.58	59.04	0.0	0.0	0.0
700	28.25	90.00	26.85	63.15	0.0	0.0	0.0
800	28.04	93.76	27.01	66.75	0.0	0.0	0.0
900	27.96	97.06	27.12	69.94	0.0	0.0	0.0
1000	27.95	100.00	27.20	72.80	0.0	0.0	0.0
1100	27.98	102.67	27.27	75.40	0.0	0.0	0.0
1200	28.04	105.10	27.33	77.77	0.0	0.0	0.0
1300	28.13	107.35	27.39	79.96	0.0	0.0	0.0
1400	28.23	109.44	27.44	82.00	0.0	0.0	0.0
1500	28.34	111.39	27.50	83.89	0.0	0.0	0.0
1600	28.46	113.22	27.56	85.66	0.0	0.0	0.0
1700	28.58	114.95	27.61	87.34	0.0	0.0	0.0
1800	28.70	116.59	27.67	88.92	0.0	0.0	0.0

Melting T 505.1 K

Boiling T 2876 K

 $\Delta_{fus} H^\circ$ 7.195 kJ $\Delta_{vap} H^\circ$ 295.77 kJ $H_{298}^\circ - H_0^\circ$ 6.323 kJMolar Vol. 1.629 $J \cdot bar^{-1}$
16.29 cm^3

STRONTIUM (REFERENCE STATE)

Formula wt 87.62

Sr: α -crystals (face-centered cubic) 298.15 to 820 K; γ -crystals (body-centered cubic) 820 to melting point 1050 K; liquid 1050 to boiling point 1685.5 K; ideal monatomic gas, $P=1$ bar, 1685.5 to 1800 K.

Temp. K	C_p°	S_T°	FORMATION FROM THE ELEMENTS				
			$(H_T^\circ - H_{298}^\circ)/T$ J·mol ⁻¹ ·K ⁻¹	$-(G_T^\circ - H_{298}^\circ)/T$	$\Delta_f H^\circ$ kJ·mol ⁻¹	$\Delta_f G^\circ$	Log K_f
298.15	26.79	55.69	0.00	55.69	0.0	0.0	0.0
300	26.81	55.86	0.17	55.69	0.0	0.0	0.0
400	27.77	63.70	6.94	56.75	0.0	0.0	0.0
500	28.78	70.00	11.21	58.79	0.0	0.0	0.0
600	29.82	75.34	14.23	61.12	0.0	0.0	0.0
700	30.87	80.02	16.53	63.49	0.0	0.0	0.0
800	31.93	84.21	18.39	65.82	0.0	0.0	0.0
820	32.15	85.01	18.72	66.28	0.0	0.0	0.0
820	29.79	86.03	19.74	66.29	0.0	0.0	0.0
900	30.13	88.81	20.65	68.17	0.0	0.0	0.0
1000	30.45	92.01	21.62	70.39	0.0	0.0	0.0
1050	30.75	93.51	22.05	71.46	0.0	0.0	0.0
1050	39.46	100.58	29.12	71.46	0.0	0.0	0.0
1100	39.46	102.42	29.59	72.82	0.0	0.0	0.0
1200	39.46	105.85	30.42	75.44	0.0	0.0	0.0
1300	39.46	109.01	31.11	77.90	0.0	0.0	0.0
1400	39.46	111.94	31.71	80.23	0.0	0.0	0.0
1500	39.46	114.66	32.23	82.43	0.0	0.0	0.0
1600	39.46	117.20	32.68	84.53	0.0	0.0	0.0
1685.5	39.46	119.26	33.02	86.24	0.0	0.0	0.0
1685.5	20.84	200.65	114.41	86.24	0.0	0.0	0.0
1700	20.84	200.83	113.62	87.21	0.0	0.0	0.0
1800	20.88	202.02	108.46	93.56	0.0	0.0	0.0

Melting T	1050 K	Boiling T	1685 K
$\Delta_{\text{fus}} H^\circ$	7.42 kJ	$\Delta_{\text{vap}} H^\circ$	137.18 kJ
$H_{298}^\circ - H_0^\circ$	6.36 kJ	Molar Vol.	3.392 J·bar ⁻¹ 33.92 cm ³

TELLURIUM (REFERENCE STATE)

Formula wt 127.600

Te: Crystals 298.15 to melting point 723 K. Liquid 723 to boiling point 1261 K. Ideal diatomic gas 1261 to 1800 K.

FORMATION FROM THE ELEMENTS

Temp. K	C_p°	S_T°	$(H_T^\circ - H_{298}^\circ)/T$ J·mol ⁻¹ ·K ⁻¹	$-(G_T^\circ - H_{298}^\circ)/T$	$\Delta_f H^\circ$ kJ·mol ⁻¹	$\Delta_f G^\circ$	Log K_f
298.15	25.70	49.71	0.00	49.71	0.0	0.0	0.0
300	25.74	49.87	0.16	49.71	0.0	0.0	0.0
400	27.95	57.58	6.83	50.75	0.0	0.0	0.0
500	30.15	64.05	11.27	52.78	0.0	0.0	0.0
600	32.36	69.74	14.60	55.14	0.0	0.0	0.0
700	34.57	74.90	17.30	57.60	0.0	0.0	0.0
723	35.07	76.43	17.86	58.57	0.0	0.0	0.0
723	37.66	100.62	42.05	58.57	0.0	0.0	0.0
800	37.66	104.04	41.63	62.41	0.0	0.0	0.0
900	37.66	108.48	41.19	67.29	0.0	0.0	0.0
1000	37.66	112.44	40.83	71.60	0.0	0.0	0.0
1100	37.66	116.03	40.54	75.48	0.0	0.0	0.0
1200	37.66	119.31	40.30	79.01	0.0	0.0	0.0
1261	37.66	121.18	40.18	81.00	0.0	0.0	0.0
1261	18.66	161.10	80.10	81.00	0.0	0.0	0.0
1300	18.66	161.67	78.25	83.41	0.0	0.0	0.0

Melting T 723 K

Boiling T 1261 K

 $\Delta_{\text{m}} H^\circ$ 17.489 kJ $\Delta_{\text{vap}} H^\circ$ 50.341 kJ $H_{298}^\circ - H_0^\circ$ 6.121 kJMolar Vol. 2.048 J·bar⁻¹
20.48 cm³

THORIUM (REFERENCE STATE)

Formula wt 232.038

Th: α -crystals (face-centered cubic) 298.15 to 1650 K. β -crystals (body-centered cubic) 1650 to melting point 2023 K.

Temp. K	C_p°	S_T°	FORMATION FROM THE ELEMENTS				
			$(H_T^\circ - H_{298}^\circ)/T$ J·mol ⁻¹ ·K ⁻¹	$-(G_T^\circ - H_{298}^\circ)/T$	$\Delta_f H^\circ$ kJ·mol ⁻¹	$\Delta_f G^\circ$	Log K_f
298.15	26.23	51.80	0.00	51.83	0.0	0.0	0.0
300	26.24	51.99	0.16	51.83	0.0	0.0	0.0
400	27.09	59.66	6.79	52.87	0.0	0.0	0.0
500	27.95	65.79	10.93	54.86	0.0	0.0	0.0
600	28.83	70.97	13.84	57.12	0.0	0.0	0.0
700	29.71	75.48	16.05	59.43	0.0	0.0	0.0
800	30.60	79.50	17.81	61.69	0.0	0.0	0.0
900	31.50	83.16	19.28	63.88	0.0	0.0	0.0
1000	32.39	86.52	20.55	65.98	0.0	0.0	0.0
1100	33.29	89.65	21.67	67.99	0.0	0.0	0.0
1200	34.19	92.59	22.67	69.92	0.0	0.0	0.0
1300	35.08	95.36	23.59	71.77	0.0	0.0	0.0
1400	35.98	97.99	24.44	73.55	0.0	0.0	0.0
1500	36.88	100.51	25.24	75.26	0.0	0.0	0.0
1600	37.77	102.91	25.99	76.92	0.0	0.0	0.0
1650	38.20	104.08	26.35	77.73	0.0	0.0	0.0
1650	35.42	106.21	28.48	77.73	0.0	0.0	0.0
1700	36.02	107.27	28.69	78.58	0.0	0.0	0.0
1800	37.21	109.36	29.13	80.23	0.0	0.0	0.0

Melting T 2023 K

Boiling T K

 $\Delta_{fus} H^\circ$ kJ $\Delta_{vap} H^\circ$ kJ $H_{298}^\circ - H_0^\circ$ 6.350 kJMolar Vol. 1.979 J·bar⁻¹
19.79 cm³

TITANIUM (REFERENCE STATE)

Formula wt 47.88

Ti: α -crystals (hexagonal close packed) 298.15 to 1166 K. β -crystals (body-centered cubic) 1166 to melting point 1939.

Temp. K	C_p°	S_T°	$(H_T^\circ - H_{298}^\circ)/T$	$-(G_T^\circ - H_{298}^\circ)/T$	FORMATION FROM THE ELEMENTS		
					$\Delta_f H^\circ$	$\Delta_f G^\circ$	Log K_f
			$J \cdot mol^{-1} \cdot K^{-1}$		$kJ \cdot mol^{-1}$		
298.15	25.25	30.76	0.00	30.76	0.0	0.0	0.0
300	25.27	30.92	0.16	30.76	0.0	0.0	0.0
400	26.82	38.39	6.62	31.77	0.0	0.0	0.0
500	27.98	44.51	10.79	33.72	0.0	0.0	0.0
600	28.59	49.67	13.71	35.96	0.0	0.0	0.0
700	29.01	54.11	15.87	38.25	0.0	0.0	0.0
800	29.57	58.02	17.54	40.48	0.0	0.0	0.0
900	30.52	61.55	18.92	42.63	0.0	0.0	0.0
1000	32.05	64.84	20.16	44.69	0.0	0.0	0.0
1100	34.30	68.00	21.33	46.66	0.0	0.0	0.0
1166	36.22	70.06	22.12	47.94	0.0	0.0	0.0
1166	29.24	73.64	25.70	47.94	0.0	0.0	0.0
1200	29.46	74.48	25.80	48.68	0.0	0.0	0.0
1300	30.18	76.86	26.10	50.76	0.0	0.0	0.0
1400	31.02	79.13	26.43	52.70	0.0	0.0	0.0
1500	32.00	81.30	26.76	54.54	0.0	0.0	0.0
1600	33.12	83.40	27.12	56.28	0.0	0.0	0.0
1700	34.36	85.45	27.52	57.93	0.0	0.0	0.0
1800	35.74	87.45	27.93	59.52	0.0	0.0	0.0

Melting T 1939 K

Boiling T K

 $\Delta_{\text{sub}} H^\circ$ 14.15 kJ $\Delta_{\text{vap}} H^\circ$ kJ $H_{298}^\circ - H_0^\circ$ 4.83 kJMolar Vol. 1.063 $J \cdot \text{bar}^{-1}$
10.63 cm^3

URANIUM (REFERENCE STATE)

Formula wt 238.029

U: α -crystals (orthorhombic) 298.15 to 942 K. β -crystals (tetragonal) 942 to 1049 K. γ -crystals (body-centered cubic) 1049 to melting point 1408 K. Liquid 1408 to 1800 K.

Temp. K	C_p°	S_T°	$(H_T^\circ - H_{298}^\circ)/T$ J·mol ⁻¹ ·K ⁻¹	$-(G_T^\circ - H_{298}^\circ)/T$	FORMATION FROM THE ELEMENTS		
					$\Delta_f H^\circ$ kJ·mol ⁻¹	$\Delta_f G^\circ$	Log K_f
298.15	27.66	50.20	0.00	50.20	0.0	0.0	0.0
300	27.69	50.37	0.17	50.20	0.0	0.0	0.0
400	29.65	58.60	7.29	51.31	0.0	0.0	0.0
500	31.95	65.46	11.99	53.47	0.0	0.0	0.0
600	34.68	71.51	15.53	55.98	0.0	0.0	0.0
700	37.91	77.10	18.49	58.60	0.0	0.0	0.0
800	41.65	82.40	21.15	61.25	0.0	0.0	0.0
900	45.92	87.54	23.66	63.88	0.0	0.0	0.0
942	47.88	89.69	24.69	65.00	0.0	0.0	0.0
942	42.40	92.64	27.64	65.00	0.0	0.0	0.0
1000	42.40	95.17	28.50	66.67	0.0	0.0	0.0
1049	42.40	97.20	29.15	68.05	0.0	0.0	0.0
1049	38.30	101.71	33.66	68.05	0.0	0.0	0.0
1100	38.30	103.52	33.87	69.65	0.0	0.0	0.0
1200	38.30	106.86	34.24	72.62	0.0	0.0	0.0
1300	38.30	109.92	34.55	75.37	0.0	0.0	0.0
1400	38.30	112.76	34.82	77.94	0.0	0.0	0.0
1408	38.30	112.98	34.84	78.14	0.0	0.0	0.0
1408	47.74	119.17	41.03	78.14	0.0	0.0	0.0
1500	47.91	122.20	41.45	80.75	0.0	0.0	0.0
1600	48.12	125.30	41.86	83.44	0.0	0.0	0.0
1700	48.36	128.22	42.23	85.99	0.0	0.0	0.0
1800	48.60	130.99	42.58	88.41	0.0	0.0	0.0

Melting T	1408 K	Boiling T	K
$\Delta_{fm} H^\circ$	8.720 kJ	$\Delta_{vap} H^\circ$	kJ
$H_{298}^\circ - H_0^\circ$	6.364 kJ	Molar Vol.	1.250 J·bar ⁻¹ 12.50 cm ³

VANADIUM (REFERENCE STATE)

Formula wt 50.942

V: Body-centered cubic crystals 298.15 to 2175 K.

Temp. K	C_p°	S_T°	$(H_T^\circ - H_{298}^\circ)/T$ J·mol ⁻¹ ·K ⁻¹	$-(G_T^\circ - H_{298}^\circ)/T$	FORMATION FROM THE ELEMENTS		
					$\Delta_f H^\circ$ kJ·mol ⁻¹	$\Delta_f G^\circ$	Log K_f
298.15	24.90	28.94	0.00	28.94	0.0	0.0	0.0
300	24.94	29.09	0.15	28.94	0.0	0.0	0.0
400	26.30	36.49	6.55	29.94	0.0	0.0	0.0
500	26.91	42.43	10.57	31.86	0.0	0.0	0.0
600	27.42	47.38	13.33	34.05	0.0	0.0	0.0
700	27.97	51.65	15.38	36.26	0.0	0.0	0.0
800	28.60	55.42	16.99	38.43	0.0	0.0	0.0
900	29.31	58.83	18.32	40.51	0.0	0.0	0.0
1000	30.10	61.96	19.46	42.50	0.0	0.0	0.0
1100	30.96	64.87	20.47	44.40	0.0	0.0	0.0
1200	31.87	67.60	21.38	46.22	0.0	0.0	0.0
1300	32.83	70.19	22.22	47.97	0.0	0.0	0.0
1400	33.83	72.66	23.01	49.64	0.0	0.0	0.0
1500	34.88	75.03	23.77	51.26	0.0	0.0	0.0
1600	35.95	77.31	24.50	52.81	0.0	0.0	0.0
1700	37.06	79.52	25.20	54.32	0.0	0.0	0.0
1800	38.19	81.67	25.89	55.78	0.0	0.0	0.0

Melting T	2175 K	Boiling T	K
$\Delta_{\text{vap}} H^\circ$	20.928 kJ	$\Delta_{\text{vap}} H^\circ$	kJ
$H_{298}^\circ - H_0^\circ$	4.64 kJ	Molar Vol.	0.835 J·bar ⁻¹ 8.35 cm ³

TUNGSTEN (REFERENCE STATE)

Formula wt 183.85

W: Body-centered cubic crystals 298.15 to 2500 K.

Temp. K	C_p°	S_T°	$(H_T^\circ - H_{298}^\circ)/T$ J·mol ⁻¹ ·K ⁻¹	$-(G_T^\circ - H_{298}^\circ)/T$	FORMATION FROM THE ELEMENTS		
					$\Delta_f H^\circ$ kJ·mol ⁻¹	$\Delta_f G^\circ$	Log K_f
298.15	24.33	32.65	0.00	32.65	0.0	0.0	0.0
300	24.34	32.80	0.15	32.65	0.0	0.0	0.0
400	24.90	39.88	6.27	33.61	0.0	0.0	0.0
500	25.45	45.49	10.05	35.45	0.0	0.0	0.0
600	25.92	50.18	12.66	37.52	0.0	0.0	0.0
700	26.33	54.20	14.58	39.62	0.0	0.0	0.0
800	26.69	57.74	16.07	41.67	0.0	0.0	0.0
900	27.03	60.91	17.27	43.64	0.0	0.0	0.0
1000	27.36	63.77	18.26	45.51	0.0	0.0	0.0
1100	27.69	66.39	19.11	47.29	0.0	0.0	0.0
1200	28.04	68.82	19.84	48.98	0.0	0.0	0.0
1300	28.40	71.08	20.48	50.60	0.0	0.0	0.0
1400	28.79	73.20	21.06	52.14	0.0	0.0	0.0
1500	29.20	75.20	21.59	53.61	0.0	0.0	0.0
1600	29.65	77.10	22.08	55.02	0.0	0.0	0.0
1700	30.13	78.91	22.54	56.37	0.0	0.0	0.0
1800	30.65	80.64	22.97	57.67	0.0	0.0	0.0

Melting T 3680 K

Boiling T K

 $\Delta_{\text{m}} H^\circ$ 35.397 kJ $\Delta_{\text{vap}} H^\circ$ kJ $H_{298}^\circ - H_0^\circ$ 4.979 kJMolar Vol. 0.9545 J·bar⁻¹
9.545 cm³

ZINC (REFERENCE STATE)

Formula wt 65.390

Zn: Hexagonal close-packed crystals 298.15 to melting point 692.7 K. Liquid 692.7 to boiling point 1180.2 K. Ideal monatomic gas 1180.2 to 2000 K.

Temp. K	C_p°	S_T°	$(H_T^\circ - H_{298}^\circ)/T$ J·mol ⁻¹ ·K ⁻¹	$-(G_T^\circ - H_{298}^\circ)/T$	FORMATION FROM THE ELEMENTS		
					$\Delta_f H^\circ$ kJ·mol ⁻¹	$\Delta_f G^\circ$	Log K_f
298.15	25.39	41.63	0.00	41.63	0.0	0.0	0.0
300	25.41	41.79	0.16	41.63	0.0	0.0	0.0
400	26.36	49.23	6.59	42.64	0.0	0.0	0.0
500	27.39	55.22	10.64	44.57	0.0	0.0	0.0
600	28.57	60.31	13.53	46.78	0.0	0.0	0.0
692.7	29.81	64.50	15.62	48.88	0.0	0.0	0.0
692.7	31.38	75.07	26.19	48.88	0.0	0.0	0.0
700	31.38	75.40	26.24	49.16	0.0	0.0	0.0
800	31.38	79.59	26.89	52.70	0.0	0.0	0.0
900	31.38	83.29	27.39	55.90	0.0	0.0	0.0
1000	31.38	86.59	27.78	58.81	0.0	0.0	0.0
1100	31.38	89.58	28.11	61.47	0.0	0.0	0.0
1180.2	31.38	91.79	28.33	63.46	0.0	0.0	0.0
1180.2	20.79	189.50	126.04	63.46	0.0	0.0	0.0
1200	20.79	189.84	124.29	65.55	0.0	0.0	0.0
1300	20.79	191.51	116.33	75.18	0.0	0.0	0.0
1400	20.79	193.05	109.51	83.54	0.0	0.0	0.0
1500	20.79	194.48	103.59	90.89	0.0	0.0	0.0
1600	20.79	195.82	98.41	97.41	0.0	0.0	0.0
1700	20.79	197.08	93.85	103.23	0.0	0.0	0.0
1800	20.79	198.27	89.79	108.48	0.0	0.0	0.0

Melting T

K

Boiling T 1080.2 K

 $\Delta_{fm} H^\circ$ 7.32 kJ $\Delta_{vap} H^\circ$ 115.30 kJ $H_{298}^\circ - H_0^\circ$ 5.648 kJMolar Vol. 0.9162 J·bar⁻¹
9.162 cm³

ZIRCONIUM (REFERENCE STATE)

Formula wt 91.224

Zr: α -crystals (hexagonal close packed) 298.15 to 1135 K. β -crystals (body-centered cubic) 1135 to melting point 2125 K.

Temp. K	C_p°	S_T°	$(H_T^\circ - H_{298}^\circ)/T$ J·mol ⁻¹ ·K ⁻¹	$-(G_T^\circ - H_{298}^\circ)/T$	FORMATION FROM THE ELEMENTS		
					$\Delta_f H^\circ$ kJ·mol ⁻¹	$\Delta_f G^\circ$	Log K_f
298.15	25.20	38.87	0.00	38.87	0.0	0.0	0.0
300	25.23	39.03	0.16	38.87	0.0	0.0	0.0
400	26.04	46.42	6.55	39.87	0.0	0.0	0.0
500	26.52	52.28	10.49	41.79	0.0	0.0	0.0
600	27.16	57.17	13.21	43.96	0.0	0.0	0.0
700	27.99	61.42	15.26	46.15	0.0	0.0	0.0
800	28.96	65.22	16.91	48.30	0.0	0.0	0.0
900	30.04	68.69	18.31	50.38	0.0	0.0	0.0
1000	31.18	71.91	19.54	52.37	0.0	0.0	0.0
1100	32.33	74.93	20.65	54.29	0.0	0.0	0.0
1135	32.74	75.94	21.02	54.92	0.0	0.0	0.0
1135	28.33	79.48	24.56	54.92	0.0	0.0	0.0
1200	28.51	81.06	24.76	56.30	0.0	0.0	0.0
1300	28.88	83.36	25.07	58.29	0.0	0.0	0.0
1400	29.35	85.51	25.35	60.16	0.0	0.0	0.0
1500	29.93	87.56	25.64	61.92	0.0	0.0	0.0
1600	30.62	89.51	25.93	63.58	0.0	0.0	0.0
1700	31.41	91.39	26.23	65.16	0.0	0.0	0.0
1800	32.31	93.21	26.54	66.67	0.0	0.0	0.0

Melting T	2125 K	Boiling T	K
$\Delta_{fus} H^\circ$	kJ	$\Delta_{vap} H^\circ$	kJ
$H_{298}^\circ - H_0^\circ$	5.497 kJ	Molar Vol.	1.4016 J·bar ⁻¹ 14.016 cm ³

METHANE

Formula wt 16.043

CH₄: Ideal gas, P = 1 bar, 298.15 to 1800 K

Temp. K	C _p ^o	S _T ^o	(H _T ^o -H ₂₉₈ ^o)/T J·mol ⁻¹ ·K ⁻¹	-(G _T ^o -H ₂₉₈ ^o)/T	FORMATION FROM THE ELEMENTS		
					Δ _f H ^o kJ·mol ⁻¹	Δ _f G ^o	Log K _f
298.15	35.70	186.26	0.00	186.26	-74.8	-50.7	8.88
300	35.72	186.48	0.22	186.26	-74.9	-50.6	8.80
400	39.91	197.22	9.52	187.70	-78.0	-42.0	5.48
500	46.21	206.79	16.22	190.57	-80.8	-32.7	3.41
600	52.42	215.77	21.74	194.03	-83.3	-22.8	1.98
700	58.08	224.29	26.54	197.75	-85.4	-12.5	0.93
800	63.14	232.38	30.80	201.58	-87.2	-2.0	0.13
900	67.65	240.08	34.65	205.43	-88.6	8.8	-0.51
1000	71.67	247.42	38.16	209.27	-89.8	19.7	-1.03
1100	75.26	254.43	41.37	213.05	-90.7	30.7	-1.45
1200	78.48	261.11	44.33	216.78	-91.5	41.7	-1.82
1300	81.36	267.51	47.07	220.44	-92.0	52.9	-2.12
1400	83.95	273.64	49.61	224.02	-92.4	64.0	-2.39
1500	86.26	279.51	51.98	227.53	-92.7	75.2	-2.62
1600	88.33	285.14	54.19	230.95	-92.9	86.4	-2.82
1700	90.17	290.56	56.25	234.30	-92.9	97.6	-3.00
1800	91.80	295.76	58.18	237.57	-93.0	108.8	-3.16

Melting T	K	Boiling T	K
Δ _{sub} H ^o	kJ	Δ _{sub} H ^o	kJ
H ₂₉₈ ^o -H ₀ ^o	10.025 kJ	Molar Vol.	2478.97 J·bar ⁻¹ 24789.7 cm ³

COHENITE

Formula wt 179.552

Fe₃C: Orthorhombic crystals 298.15 to 1800 K.

Temp. K	C _p ^o	S _T ^o	(H _T ^o -H ₂₉₈ ^o)/T	-(G _T ^o -H ₂₉₈ ^o)/T	FORMATION FROM THE ELEMENTS		
					Δ _f H ^o	Δ _f G ^o	Log K _f
			J·mol ⁻¹ ·K ⁻¹		kJ·mol ⁻¹		
298.15	111.04	104.40	0.00	104.40	24.9	19.7	-3.45
300	111.06	105.09	0.68	104.40	24.9	19.7	-3.43
400	112.31	137.21	28.43	108.77	27.2	17.6	-2.29
500	113.57	162.40	45.34	117.07	28.6	15.0	-1.56
600	114.82	183.22	56.81	126.41	29.2	12.2	-1.06
700	116.07	201.01	65.19	135.83	29.0	9.3	-0.70
800	117.32	216.59	71.63	144.97	27.9	6.6	-0.43
900	118.58	230.49	76.77	153.71	25.6	4.1	-0.24
1000	119.83	243.04	81.02	162.03	21.0	1.9	-0.10
1100	121.08	254.52	84.60	169.92	13.8	0.4	-0.02
1200	122.34	265.11	87.69	177.42	8.9	-0.7	0.03
1300	123.59	274.95	90.41	184.55	8.6	-1.5	0.06
1400	124.84	284.16	92.82	191.34	8.1	-2.3	0.08
1500	126.10	292.82	95.00	197.82	7.4	-3.0	0.10
1600	127.35	300.99	96.98	204.01	6.5	-3.6	0.12
1700	128.60	308.75	98.80	209.95	2.7	-4.2	0.13
1800	129.85	316.14	100.49	215.64	0.2	-4.5	0.13

Melting T	K	Boiling T	K
Δ _m H ^o	kJ	Δ _{vap} H ^o	kJ
H ₂₉₈ ^o -H ₀ ^o	kJ	Molar Vol.	2.323 J·bar ⁻¹ 23.23 cm ³

AMMONIA

Formula wt 17.031

NH₃: Ideal gas, P = 1 bar, 298.15 to 1800 K.

Temp. K	C _p ^o	S _T ^o	(H _T ^o -H ₂₉₈ ^o)/T J·mol ⁻¹ ·K ⁻¹	-(G _T ^o -H ₂₉₈ ^o)/T	FORMATION FROM THE ELEMENTS		
					Δ _f H ^o kJ·mol ⁻¹	Δ _f G ^o	Log K _f
298.15	35.68	192.77	0.00	192.77	-45.9	-16.4	2.87
300	35.72	192.99	0.22	192.77	-45.9	-16.2	2.82
400	38.59	203.63	9.43	194.20	-48.1	-5.9	0.78
500	41.99	212.60	15.60	197.01	-49.9	4.8	-0.50
600	45.32	220.56	20.28	200.28	-51.4	15.9	-1.38
700	48.44	227.78	24.08	203.70	-52.6	27.2	-2.03
800	51.34	234.44	27.31	207.13	-53.6	38.7	-2.53
900	54.03	240.65	30.13	210.51	-54.4	50.3	-2.92
1000	56.52	246.47	32.65	213.82	-55.0	61.9	-3.24
1100	58.82	251.96	34.92	217.04	-55.4	73.7	-3.50
1200	60.96	257.18	37.01	220.17	-55.8	85.4	-3.72
1300	62.94	262.13	38.93	223.21	-55.9	97.2	-3.91
1400	64.77	266.87	40.71	226.16	-56.0	109.0	-4.07
1500	66.45	271.39	42.37	229.03	-56.0	120.8	-4.21
1600	68.00	275.73	43.92	231.81	-55.9	132.5	-4.33
1700	69.42	279.90	45.38	234.52	-55.7	144.3	-4.43
1800	70.71	283.90	46.75	237.15	-55.5	156.1	-4.53

Melting T	K	Boiling T	K
Δ _m H ^o	kJ	Δ _{vp} H ^o	kJ
H ₂₉₈ ^o -H ₀ ^o	10.045 kJ	Molar Vol.	2478.97 J·bar ⁻¹ 24789.7 cm ³

ACANTHITE (ARGENTITE)

Formula wt 247.802

Ag₂S: Monoclinic crystals 298.15 to 451.3 K; cubic crystals (argentite) 451.3 to 865 K.
 γ phase 865 to 1000 K. Reference state for sulfur is orthorhombic sulfur.

Temp. K	C _p ^o	S _T ^o	(H _T ^o -H ₂₉₈ ^o)/T	-(G _T ^o -H ₂₉₈ ^o)/T	FORMATION FROM THE ELEMENTS		
					Δ _f H ^o	Δ _f G ^o	Log K _f
			J·mol ⁻¹ ·K ⁻¹		kJ·mol ⁻¹		
298.15	75.31	142.89	0.00	142.89	-32.0	-39.7	6.95
300	75.39	143.35	0.46	142.89	-32.0	-39.7	6.92
400	80.47	165.67	19.78	145.89	-34.0	-42.2	5.52
500	87.26	193.79	41.08	152.71	-30.5	-44.7	4.67
600	86.03	209.59	48.67	160.92	-30.7	-47.5	4.14
700	84.80	222.75	53.91	168.84	-31.0	-50.3	3.75
800	84.69	234.05	57.75	176.30	-31.3	-53.0	3.46
900	80.38	244.84	61.53	183.31	-84.1	-54.7	3.17
1000	80.57	253.28	63.38	189.90	-83.8	-51.5	2.69

Melting T	K	Boiling T	K
Δ _m H ^o	kJ	Δ _{vap} H ^o	kJ
H ₂₉₈ ^o -H ₀ ^o	17.132 kJ	Molar Vol.	3.419 J·bar ⁻¹ 34.19 cm ³

REALGAR

Formula wt 106.988

AsS: Monoclinic crystals 298.15 to melting point 580 K; liquid 580 to 800 K.
Reference state for sulfur is orthorhombic sulfur.

Temp. K	C_p°	S_T°	$(H_T^\circ - H_{298}^\circ)/T$	$-(G_T^\circ - H_{298}^\circ)/T$	FORMATION FROM THE ELEMENTS		
					$\Delta_f H^\circ$	$\Delta_f G^\circ$	Log K_f
	J·mol ⁻¹ ·K ⁻¹		kJ·mol ⁻¹				
298.15	47.02	63.50	0.00	63.50	-30.9	-29.6	5.19
300	47.08	63.80	0.29	63.51	-30.9	-29.6	5.16
400	49.32	77.68	12.29	65.39	-33.2	-29.1	3.80
500	51.18	88.88	19.88	69.00	-34.6	-27.9	2.92
600	67.12	110.35	36.84	73.51	-28.7	-26.7	2.33
700	71.48	121.00	41.46	79.54	-27.8	-26.4	1.97
800	77.50	130.90	45.57	85.33	-26.3	-26.3	1.72

Melting T	580 K	Boiling T	K
$\Delta_{\text{fus}} H^\circ$	6.668 kJ	$\Delta_{\text{vap}} H^\circ$	kJ
$H_{298}^\circ - H_0^\circ$	kJ	Molar Vol.	2.980 J·bar ⁻¹ 29.80 cm ³

9/30/92

GREENOCKITE

Formula wt 144.477

CdS: Cubic crystals 298.15 to 1100 K. Reference state for sulfur is orthorhombic sulfur.

Temp. K	C_p°	S_T°	FORMATION FROM THE ELEMENTS				
			$(H_T^\circ - H_{298}^\circ)/T$ J·mol ⁻¹ ·K ⁻¹	$-(G_T^\circ - H_{298}^\circ)/T$	$\Delta_f H^\circ$ kJ·mol ⁻¹	$\Delta_f G^\circ$ kJ·mol ⁻¹	Log K_f
298.15	47.30	72.18	0.00	72.18	-149.6	-146.1	25.60
300	47.36	72.47	0.29	72.18	-149.6	-146.1	25.44
400	49.46	86.42	12.35	74.07	-152.0	-144.8	18.91
500	50.70	97.60	19.90	77.69	-153.7	-142.8	14.92
600	51.68	106.93	25.12	81.81	-161.2	-140.5	12.23
700	52.55	114.96	28.98	85.99	-162.3	-136.9	10.22
800	53.37	122.03	31.98	90.06	-163.2	-133.2	8.70
900	54.16	128.37	34.40	93.97	-217.1	-128.4	7.45
1000	54.93	134.11	36.41	97.70	-216.5	-118.5	6.19
1100	55.67	139.38	38.13	101.25	-314.8	-102.9	4.89

Melting T	K	Boiling T	K
$\Delta_{fus} H^\circ$	kJ	$\Delta_{vap} H^\circ$	kJ
$H_{298}^\circ - H_0^\circ$	8.818 kJ	Molar Vol.	2.993 J·bar ⁻¹ 29.93 cm ³

CATTIERITE

Formula wt 123.065

CoS₂: Cubic crystals 298.15 to 1000 K. Reference state for sulfur is orthorhombic sulfur.

Temp. K	C _p ^o	S _T ^o	(H _T ^o -H ₂₉₈ ^o)/T	-(G _T ^o -H ₂₉₈ ^o)/T	FORMATION FROM THE ELEMENTS		
					Δ _f H ^o	Δ _f G ^o	Log K _f
			J·mol ⁻¹ ·K ⁻¹		kJ·mol ⁻¹		
298.15	68.26	74.80	0.00	74.80	-150.9	-145.1	25.42
300	68.39	75.22	0.42	74.80	-150.9	-145.1	25.26
400	74.28	95.76	18.20	77.56	-155.5	-143.0	18.67
500	78.63	112.82	29.87	82.96	-158.5	-139.5	14.57
600	82.38	127.50	38.31	89.18	-160.5	-135.5	11.80
700	85.85	140.46	44.86	95.60	-161.8	-131.2	9.79
800	89.16	152.14	50.19	101.95	-163.1	-126.7	8.27
900	92.38	162.83	54.70	108.13	-269.8	-120.0	6.97
1000	95.55	172.72	58.63	114.10	-267.7	-103.5	5.41

Melting T	K	Boiling T	K
Δ _{fus} H ^o	kJ	Δ _{vap} H ^o	kJ
H ₂₉₈ ^o -H ₀ ^o	12.301 kJ	Molar Vol.	2.552 J·bar ⁻¹ 25.52 cm ³

COVELLITE

Formula wt 95.612

CuS: Hexagonal crystals 298.15 to 800 K. Reference state for sulfur is orthorhombic sulfur.

Temp. K	C_p°	S_T°	FORMATION FROM THE ELEMENTS				
			$(H_T^\circ - H_{298}^\circ)/T$	$-(G_T^\circ - H_{298}^\circ)/T$	$\Delta_f H^\circ$	$\Delta_f G^\circ$	Log K_f
	J·mol ⁻¹ ·K ⁻¹		kJ·mol ⁻¹				
298.15	47.53	67.40	0.00	67.40	-54.6	-55.3	9.68
300	47.59	67.69	0.29	67.40	-54.6	-55.3	9.62
400	50.29	81.77	12.47	69.30	-56.8	-55.4	7.23
500	52.62	93.24	20.27	72.98	-58.1	-54.9	5.74
600	54.82	103.03	25.84	77.19	-59.0	-54.2	4.72
700	56.94	111.64	30.14	81.51	-59.4	-53.3	3.98
800	59.03	119.38	33.62	85.77	-59.5	-52.4	3.42

Melting T	780i K	Boiling T	K
$\Delta_{\text{sub}} H^\circ$	kJ	$\Delta_{\text{vap}} H^\circ$	kJ
$H_{298}^\circ - H_0^\circ$	9.45 kJ	Molar Vol.	2.042 J·bar ⁻¹ 20.42 cm ³

CHALCOCITE

Formula wt 159.158

Cu_2S : Orthorhombic crystals 298.15 to 376 K; hexagonal crystals 376 to 710 K; cubic crystals 710 to melting point 1403 K. Reference state for sulfur is orthorhombic sulfur.

Temp. K	C_p°	S_T°	$(H_T^\circ - H_{298}^\circ)/T$ J·mol ⁻¹ ·K ⁻¹	$-(G_T^\circ - H_{298}^\circ)/T$	FORMATION FROM THE ELEMENTS		
					$\Delta_f H^\circ$ kJ·mol ⁻¹	$\Delta_f G^\circ$	Log K_f
298.15	76.84	116.20	0.00	116.20	-83.9	-89.2	15.62
300	77.01	116.67	0.47	116.20	-83.9	-89.2	15.53
400	98.83	151.07	31.14	119.93	-81.1	-91.3	11.92
500	95.31	172.84	44.33	128.51	-80.5	-93.9	9.81
600	92.30	189.93	52.56	137.37	-79.9	-96.7	8.42
700	89.79	203.97	58.06	145.91	-79.5	-99.5	7.43
800	82.76	216.94	62.85	154.09	-78.5	-102.5	6.69
900	82.50	226.66	65.04	161.62	-132.1	-104.5	6.06
1000	85.02	235.65	67.02	168.63	-131.1	-101.5	5.30
1100	85.02	243.77	68.68	175.09	-130.3	-98.6	4.68
1200	85.02	251.17	70.03	181.14	-129.7	-95.7	4.17
1300	85.02	257.95	71.71	186.24	-128.7	-92.2	3.71
1400	85.02	264.23	72.15	192.08	-155.6	-89.2	3.33

Melting T	1403 K	Boiling T	K
$\Delta_{\text{fus}} H^\circ$	kJ	$\Delta_{\text{vap}} H^\circ$	kJ
$H_{298}^\circ - H_0^\circ$	15.80 kJ	Molar Vol.	2.748 J·bar ⁻¹ 27.48 cm ³

CHALCOPYRITE

Formula wt 183.525

CuFeS_2 : Tetragonal crystals 298.15 to 820 K; tetragonal crystals 820 to 930 K; cubic crystals 930 to 1200 K. Reference state for sulfur is orthorhombic sulfur. Above 820 K, the phase is called ISS (intermediate solid solution).

Temp. K	C_p°	S_T°	$(H_T^\circ - H_{298}^\circ)/T$ J·mol ⁻¹ ·K ⁻¹	$-(G_T^\circ - H_{298}^\circ)/T$	FORMATION FROM THE ELEMENTS		
					$\Delta_f H^\circ$ kJ·mol ⁻¹	$\Delta_f G^\circ$	Log K_f
298.15	95.80	124.90	0.00	124.90	-194.9	-195.1	34.18
300	96.24	125.49	0.59	124.90	-194.9	-195.1	33.97
400	106.26	155.01	26.15	128.86	-199.0	-195.0	25.47
500	109.15	179.02	42.45	136.57	-201.5	-193.8	20.24
600	114.53	199.34	53.97	145.38	-203.2	-192.1	16.72
700	123.84	217.64	63.24	154.41	-204.0	-190.1	14.19
800	136.83	234.99	71.59	163.40	-203.8	-188.2	12.29
900	203.75	264.70	91.48	173.22	-298.0	-185.0	10.74
1000	172.49	285.00	101.42	183.58	-290.2	-173.0	9.04
1100	172.49	301.44	107.88	193.56	-285.3	-161.5	7.67
1200	172.49	316.45	113.27	203.18	-279.8	-150.6	6.55

Melting T	K	Boiling T	K
$\Delta_{\text{fus}} H^\circ$	kJ	$\Delta_{\text{vap}} H^\circ$	kJ
$H_{298}^\circ - H_0^\circ$	18.34 kJ	Molar Vol.	4.392 J·bar ⁻¹ 43.92 cm ³

BORNITE

Formula wt 501.841

Cu_5FeS_4 : Orthorhombic crystals 298.15 to 470 K; cubic crystals 470 to 535 K; cubic crystals 535 to 1200 K. Reference state for sulfur is orthorhombic sulfur.

Temp. K	C_p°	S_T°	FORMATION FROM THE ELEMENTS				
			$(H_T^\circ - H_{298}^\circ)/T$ J·mol ⁻¹ ·K ⁻¹	$-(G_T^\circ - H_{298}^\circ)/T$	$\Delta_f H^\circ$ kJ·mol ⁻¹	$\Delta_f G^\circ$ kJ·mol ⁻¹	Log K_f
298.15	242.90	398.50	0.00	398.50	-371.6	-394.7	69.15
300	243.20	400.00	1.50	398.50	-371.6	-394.8	68.75
400	260.60	472.40	64.09	408.31	-379.9	-402.3	52.54
500	369.45	549.41	121.22	428.19	-376.3	-407.9	42.62
600	327.89	615.63	161.33	454.30	-370.6	-414.9	36.12
700	323.50	665.90	184.73	481.17	-368.2	-422.6	31.53
800	325.20	709.20	202.19	507.01	-365.8	-430.5	28.11
900	327.30	747.53	215.89	531.64	-576.1	-434.4	25.21
1000	332.90	782.29	227.29	555.00	-569.5	-419.1	21.89
1100	340.00	814.34	237.21	577.13	-563.5	-404.3	19.20
1200	348.30	844.27	246.12	598.15	-556.7	-390.1	16.98

Melting T	K	Boiling T	K
$\Delta_{\text{m}} H^\circ$	kJ	$\Delta_{\text{vp}} H^\circ$	kJ
$H_{298}^\circ - H_0^\circ$	53.011 kJ	Molar Vol.	9.873 J·bar ⁻¹ 98.73 cm ³

TROILITE

Formula wt 87.913

FeS: Hexagonal crystals (NiAs structure) 298.15 to a complex transition at 411 K and a Néel temperature at 590 K; paramagnetic 590 to melting point at 1468 K; liquid 1468 to 1800 K. Reference state for sulfur is orthorhombic sulfur.

Temp. K	C_p°	S_T°	$(H_T^\circ - H_{298}^\circ)/T$ J·mol ⁻¹ ·K ⁻¹	$-(G_T^\circ - H_{298}^\circ)/T$	FORMATION FROM THE ELEMENTS		
					$\Delta_f H^\circ$ kJ·mol ⁻¹	$\Delta_f G^\circ$	Log K_f
298.15	50.49	60.30	0.00	60.30	-102.6	-102.9	18.03
300	50.64	60.62	0.31	60.31	-102.6	-102.9	17.92
400	70.02	76.87	14.44	62.43	-104.1	-103.0	13.46
500	72.06	102.86	34.29	68.57	-99.5	-103.6	10.83
600	67.33	116.98	41.52	75.46	-98.4	-104.5	9.10
700	58.13	126.32	44.23	82.09	-99.1	-105.5	7.87
800	57.73	134.00	45.90	88.10	-100.1	-106.3	6.94
900	58.65	140.86	47.27	93.59	-154.6	-106.0	6.15
1000	60.64	147.13	48.49	98.64	-155.3	-100.6	5.25
1100	62.00	152.82	49.52	103.30	-156.8	-95.0	4.51
1200	62.99	158.17	50.52	107.65	-157.5	-89.3	3.89
1300	63.99	163.32	51.56	111.76	-156.5	-83.7	3.36
1400	64.99	168.22	52.60	115.62	-155.3	-78.2	2.92
1500	71.13	194.95	75.20	119.75	-121.7	-73.4	2.56
1600	71.13	199.51	74.94	124.57	-120.3	-70.2	2.29
1700	71.13	203.82	74.72	129.10	-119.8	-67.1	2.06
1800	71.13	207.88	74.52	133.36	-119.0	-64.0	1.86

Melting T	1468 K	Boiling T	K
$\Delta_{\text{m}} H^\circ$	32.34 kJ	$\Delta_{\text{vap}} H^\circ$	kJ
$H_{298}^\circ - H_0^\circ$	9.351 kJ	Molar Vol.	1.820 J·bar ⁻¹ 18.20 cm ³

PYRRHOTITE

Formula wt 80.932

Fe_{0.875}S: Monoclinic crystals 298.15 to combined structural and magnetic transition at 590 K; hexagonal crystals (Ni-As-type) 590 to 1000 K. Reference state for sulfur is orthorhombic sulfur.

Temp. K	C _p ^o	S _T ^o	(H _T ^o -H ₂₉₈ ^o)/T	-(G _T ^o -H ₂₉₈ ^o)/T	FORMATION FROM THE ELEMENTS		
					Δ _f H ^o	Δ _f G ^o	Log K _f
			J·mol ⁻¹ ·K ⁻¹	kJ·mol ⁻¹			
298.15	49.88	60.70	0.00	60.70	-97.5	-98.9	17.33
300	50.01	60.70	0.31	60.39	-97.4	-98.8	17.21
400	56.24	76.28	13.53	62.75	-99.0	-99.4	12.98
500	63.56	89.57	22.76	66.81	-99.5	-99.5	10.39
600	67.35	104.51	32.47	72.04	-97.7	-99.8	8.69
700	65.30	114.53	37.37	77.16	-97.2	-100.0	7.46
800	57.42	122.64	40.28	82.36	-97.6	-100.3	6.55
900	57.19	129.39	42.17	87.22	-151.6	-99.6	5.78
1000	58.38	135.46	43.71	91.75	-151.9	-93.8	4.90

Melting T	K	Boiling T	K
Δ _m H ^o	kJ	Δ _{vap} H ^o	kJ
H ₂₉₈ ^o -H ₀ ^o	9.21 kJ	Molar Vol.	1.749 J·bar ⁻¹ 17.49 cm ³

PYRITE

Formula wt 119.979

FeS_2 : Cubic crystals 298.15 to 1000 K. Reference state for sulfur is orthorhombic sulfur.

Temp. K	C_p°	S_T°	$(H_T^\circ - H_{298}^\circ)/T$ J·mol ⁻¹ ·K ⁻¹	$-(G_T^\circ - H_{298}^\circ)/T$	FORMATION FROM THE ELEMENTS		
					$\Delta_f H^\circ$ kJ·mol ⁻¹	$\Delta_f G^\circ$	Log K_f
298.15	62.17	52.90	0.00	52.90	-171.5	-160.1	28.05
300	62.39	53.29	0.38	52.90	-171.6	-160.1	27.87
400	69.15	72.34	16.88	55.45	-176.7	-155.9	20.36
500	71.95	88.10	27.64	60.45	-180.4	-150.3	15.70
600	73.93	101.39	35.20	66.20	-183.3	-144.0	12.54
700	75.90	112.94	40.87	72.07	-185.9	-137.3	10.24
800	78.10	123.21	45.38	77.83	-188.2	-130.2	8.50
900	80.57	132.55	49.15	83.40	-296.8	-120.6	7.00
1000	83.29	141.18	52.43	88.75	-297.1	-101.1	5.28

Melting T	1015i K	Boiling T	K
$\Delta_{fus} H^\circ$	kJ	$\Delta_{vap} H^\circ$	kJ
$H_{298}^\circ - H_0^\circ$	9.63 kJ	Molar Vol.	2.394 J·bar ⁻¹ 23.94 cm ³

MARCASITE

Formula wt 119.979

FeS₂: Orthorhombic crystals 298.15 to 700 K. Reference state for sulfur is orthorhombic sulfur.

Temp. K	C _p ^o	S _T ^o	(H _T ^o -H ₂₉₈ ^o)/T J·mol ⁻¹ ·K ⁻¹	-(G _T ^o -H ₂₉₈ ^o)/T	FORMATION FROM THE ELEMENTS		
					Δ _f H ^o kJ·mol ⁻¹	Δ _f G ^o	Log K _f
298.15	62.43	53.90	0.00	53.90	-169.5	-158.4	27.75
300	62.60	54.29	0.39	53.90	-169.5	-158.3	27.56
400	69.17	73.31	16.86	56.45	-174.7	-154.3	20.15
500	72.44	89.13	27.68	61.45	-178.3	-148.8	15.54
600	74.59	102.53	35.32	67.21	-181.2	-142.6	12.41
700	77.00	114.20	41.10	73.11	-183.7	-136.0	10.14

Melting T	K	Boiling T	K
Δ _{fus} H ^o	kJ	Δ _{vap} H ^o	kJ
H ₂₉₈ ^o -H ₀ ^o	9.74 kJ	Molar Vol.	2.458 J·bar ⁻¹ 24.58 cm ³

HYDROGEN SULFIDE

Formula wt 34.082

H₂S: Ideal gas at p = 1 bar, 298.15 to 1800 K. Reference state for sulfur is orthorhombic sulfur.

Temp. K	C _p ^o	S _T ^o	FORMATION FROM THE ELEMENTS				
			(H _T ^o -H ₂₉₈ ^o)/T J·mol ⁻¹ ·K ⁻¹	-(G _T ^o -H ₂₉₈ ^o)/T	Δ _f H ^o kJ·mol ⁻¹	Δ _f G ^o	Log K _f
298.15	34.20	205.80	0.00	205.80	-20.6	-33.4	5.86
300	34.21	206.01	0.21	205.80	-20.6	-33.5	5.84
400	35.48	216.01	8.85	207.15	-24.7	-37.5	4.89
500	37.22	224.11	14.35	209.76	-27.9	-40.3	4.21
600	39.05	231.05	18.31	212.74	-30.6	-42.5	3.70
700	40.85	237.21	21.40	215.81	-32.9	-44.3	3.31
800	42.58	242.78	23.94	218.83	-34.9	-45.8	2.99
900	44.21	247.89	26.11	221.78	-89.7	-46.0	2.67
1000	45.72	252.63	27.99	224.63	-90.1	-41.1	2.15
1100	47.13	257.05	29.67	227.38	-90.4	-36.2	1.72
1200	48.41	261.21	31.18	230.03	-90.6	-31.3	1.36
1300	49.58	265.13	32.55	232.58	-90.7	-26.3	1.06
1400	50.62	268.84	33.80	235.04	-90.8	-21.4	0.80
1500	51.55	272.37	34.96	237.41	-90.8	-16.4	0.57
1600	52.35	275.72	36.02	239.70	-90.8	-11.5	0.37
1700	53.04	278.92	37.00	241.91	-90.8	-6.5	0.20
1800	53.60	281.96	37.91	244.06	-90.7	-1.6	0.05

Melting T	K	Boiling T	K
Δ _{sub} H ^o	kJ	Δ _{vap} H ^o	kJ
H ₂₉₈ -H ₀	9.96 kJ	Molar Vol.	2478.97 J·bar ⁻¹ 24789.7 cm ³

ALABANDITE

Formula wt 87.004

MnS: Cubic crystals 298.15 to 1800 K. Reference state for sulfur is orthorhombic sulfur.

Temp. K	C_p°	S_T°	FORMATION FROM THE ELEMENTS				
			$(H_T^\circ - H_{298}^\circ)/T$ J·mol ⁻¹ ·K ⁻¹	$-(G_T^\circ - H_{298}^\circ)/T$	$\Delta_f H^\circ$ kJ·mol ⁻¹	$\Delta_f G^\circ$	Log K_f
298.15	49.98	80.30	0.00	80.30	-213.9	-218.7	38.32
300	49.99	80.61	0.31	80.30	-213.9	-218.8	38.09
400	51.10	95.13	12.86	82.27	-216.2	-220.3	28.77
500	52.14	106.65	20.62	86.04	-217.9	-221.2	23.10
600	52.83	116.22	25.93	90.29	-219.3	-221.7	19.30
700	53.25	124.40	29.81	94.59	-220.6	-222.0	16.56
800	53.55	131.53	32.76	98.78	-221.9	-222.1	14.50
900	53.84	137.85	35.08	102.77	-276.3	-220.9	12.82
1000	54.21	143.55	36.98	106.57	-278.7	-214.7	11.22
1100	54.73	148.74	38.56	110.17	-278.9	-208.3	9.89
1200	55.44	153.53	39.94	113.59	-279.1	-201.9	8.79
1300	56.39	158.00	41.17	116.83	-279.3	-195.5	7.85
1400	57.60	162.22	42.30	119.93	-281.7	-188.9	7.05
1500	59.10	166.24	43.36	122.88	-284.2	-182.2	6.34
1600	60.91	170.11	44.40	125.71	-296.9	-174.7	5.70
1700	63.04	173.87	45.43	128.43	-297.3	-167.0	5.13
1800	65.51	177.54	46.48	131.06	-297.4	-159.4	4.62

Melting T	K	Boiling T	K
$\Delta_{\text{m}} H^\circ$	kJ	$\Delta_{\text{vp}} H^\circ$	kJ
$H_{298}^\circ - H_0^\circ$	kJ	Molar Vol.	2.146 J·bar ⁻¹ 21.46 cm ³

9/30/92

MOLYBDENITE

Formula wt 160.072

MoS₂: Hexagonal crystals 298.15 to 1200 K. Reference state for sulfur is orthorhombic sulfur.

Temp. K	C _p ^o	S _T ^o	(H _T ^o -H ₂₉₈ ^o)/T J·mol ⁻¹ ·K ⁻¹	-(G _T ^o -H ₂₉₈ ^o)/T	FORMATION FROM THE ELEMENTS		
					Δ _f H ^o kJ·mol ⁻¹	Δ _f G ^o	Log K _f
298.15	63.51	62.60	0.00	62.60	-271.8	-262.8	46.04
300	63.63	62.99	0.39	62.60	-271.8	-262.7	45.75
400	68.45	82.01	16.85	65.16	-276.8	-259.5	33.88
500	71.58	97.65	27.50	70.14	-280.2	-254.7	26.61
600	73.77	110.90	35.04	75.86	-282.7	-249.4	21.71
700	75.35	122.40	40.69	81.70	-284.6	-243.7	18.18
800	76.54	132.54	45.10	87.44	-286.2	-237.7	15.52
900	77.44	141.61	48.65	92.96	-393.7	-229.5	13.32
1000	78.12	149.81	51.56	98.24	-392.5	-211.3	11.03
1100	78.65	157.28	54.00	103.28	-391.3	-193.2	9.17
1200	79.04	164.14	56.07	108.07	-390.1	-175.3	7.63

Melting T	K	Boiling T	K
Δ _{fus} H ^o	kJ	Δ _{vap} H ^o	kJ
H ₂₉₈ ^o -H ₀ ^o	8.82 kJ	Molar Vol.	3.202 J·bar ⁻¹ 32.02 cm ³

MILLERITE

Formula wt 90.756

NiS: Rhombohedral crystals 298.15 to 623 K; hexagonal crystals 623 to melting point 1066 K.
Reference state for sulfur is orthorhombic sulfur.

Temp. K	C_p°	S_T°	$(H_T^\circ - H_{298}^\circ)/T$ J·mol ⁻¹ ·K ⁻¹	$-(G_T^\circ - H_{298}^\circ)/T$	FORMATION FROM THE ELEMENTS		
					$\Delta_f H^\circ$ kJ·mol ⁻¹	$\Delta_f G^\circ$	Log K_f
298.15	47.11	52.97	0.00	52.97	-91.0	-88.3	15.47
300	47.24	53.26	0.29	52.97	-91.0	-88.3	15.38
400	50.79	67.36	12.55	54.81	-93.4	-87.3	11.40
500	53.68	79.04	20.42	58.62	-95.1	-85.6	8.94
600	56.27	89.04	26.22	62.82	-96.4	-83.6	7.27
700	59.45	102.68	34.91	67.77	-94.4	-81.7	6.10
800	62.55	110.79	38.18	72.61	-94.6	-80.3	5.24
900	65.65	118.37	41.05	77.32	-147.6	-77.0	4.47
1000	68.74	125.44	43.68	81.76	-145.9	-69.2	3.61
1100	71.13	159.58	72.73	86.85	-114.7	-62.5	2.97

Melting T	1066 K	Boiling T	K
$\Delta_{fus} H^\circ$	kJ	$\Delta_{vap} H^\circ$	kJ
$H_{298}^\circ - H_0^\circ$	8.47 kJ	Molar Vol.	1.689 J·bar ⁻¹ 16.89 cm ³

HEAZLEWOODITE

Formula wt 240.202

Ni_3S_2 : Hexagonal crystals 298.15 to 834 K; cubic crystals 834 K to incongruent melting point 1064 K; liquid 1064 to 1400 K. Reference state for sulfur is orthorhombic sulfur.

Temp. K	C_p°	S_T°	FORMATION FROM THE ELEMENTS				
			$(H_T^\circ - H_{298}^\circ)/T$	$-(G_T^\circ - H_{298}^\circ)/T$	$\Delta_f H^\circ$	$\Delta_f G^\circ$	Log K_f
			$\text{J}\cdot\text{mol}^{-1}\cdot\text{K}^{-1}$		$\text{kJ}\cdot\text{mol}^{-1}$		
298.15	118.24	133.20	0.00	133.20	-216.3	-210.2	36.82
300	118.45	133.93	0.73	133.20	-216.3	-210.1	36.59
400	129.01	169.52	31.54	137.98	-221.3	-207.8	27.14
500	136.05	199.12	51.79	147.34	-224.7	-204.1	21.32
600	141.59	224.42	66.29	158.12	-227.8	-199.7	17.38
700	148.35	246.72	77.51	169.22	-230.1	-194.8	14.53
800	158.39	267.14	86.95	180.20	-230.5	-191.1	12.48
900	189.15	355.52	159.38	196.14	-278.4	-187.1	10.86
1000	191.81	375.52	162.41	213.11	-272.8	-177.3	9.26
1100	189.12	411.84	182.56	229.28	-247.9	-168.7	8.01
1200	189.12	428.28	183.11	245.17	-242.7	-161.7	7.03
1300	189.12	443.42	183.57	259.85	-237.9	-155.1	6.23
1400	189.12	457.44	183.97	273.47	-233.3	-148.9	5.56

Melting T	1064 K	Boiling T	K
$\Delta_{\text{fus}} H^\circ$	19.66 kJ	$\Delta_{\text{vap}} H^\circ$	kJ
$H_{298}^\circ - H_0^\circ$	21.50 kJ	Molar Vol.	4.095 $\text{J}\cdot\text{bar}^{-1}$ 40.95 cm^3

GALENA

Formula wt 239.266

PbS: Cubic crystals 298.15 to 900 K. Reference state for sulfur is orthorhombic sulfur.

Temp. K	C_p°	S_T°	FORMATION FROM THE ELEMENTS				
			$(H_T^\circ - H_{298}^\circ)/T$ J·mol ⁻¹ ·K ⁻¹	$-(G_T^\circ - H_{298}^\circ)/T$	$\Delta_f H^\circ$ kJ·mol ⁻¹	$\Delta_f G^\circ$	Log K_f
298.15	49.49	91.70	0.00	91.70	-98.3	-96.8	16.95
300	49.52	92.01	0.31	91.70	-98.3	-96.8	16.85
400	51.16	106.48	12.81	93.66	-100.6	-96.1	12.55
500	52.80	118.07	20.65	97.42	-102.1	-94.9	9.91
600	54.44	127.84	26.14	101.70	-103.3	-93.3	8.12
700	56.08	136.36	30.30	106.05	-109.0	-90.8	6.77
800	57.72	143.95	33.63	110.32	-109.5	-88.1	5.75
900	59.36	150.84	36.40	114.45	-162.9	-84.3	4.90

Melting T	1400 K	Boiling T	K
H (fusion)	kJ	$\Delta_{\text{vap}} H^\circ$	kJ
$H_{298}^\circ - H_0^\circ$	11.51 kJ	Molar Vol.	3.149 J·bar ⁻¹ 31.49 cm ³

9/30/92

STIBNITE

Formula wt 339.698

Sb_2S_3 : Orthorhombic crystals 298.15 to 900 K. Reference state for sulfur is orthorhombic sulfur.

Temp. K	C_p°	S_T°	$(H_T^\circ - H_{298}^\circ)/T$ J·mol ⁻¹ ·K ⁻¹	$-(G_T^\circ - H_{298}^\circ)/T$	FORMATION FROM THE ELEMENTS		
					$\Delta_f H^\circ$ kJ·mol ⁻¹	$\Delta_f G^\circ$	Log K_f
298.15	119.75	182.00	0.00	182.00	-151.4	-149.8	26.25
300	119.81	182.74	0.74	182.00	-151.4	-149.8	26.09
400	123.38	217.70	30.96	186.74	-158.1	-149.0	19.46
500	126.46	245.58	49.76	195.82	-162.7	-146.3	15.28
600	128.94	268.86	62.76	206.10	-166.0	-142.7	12.42
700	130.92	288.89	72.36	216.53	-168.6	-138.6	10.34
800	132.51	306.48	79.78	226.70	-170.8	-134.1	8.76
900	133.80	322.17	85.72	236.45	-332.2	-126.2	7.33

Melting T	829 K	Boiling T	K
$\Delta_{\text{m}} H^\circ$	kJ	$\Delta_{\text{vap}} H^\circ$	kJ
$H_{298}^\circ - H_0^\circ$	kJ	Molar Vol.	7.341 J·bar ⁻¹ 73.41 cm ³

HERZENBERGITE

Formula wt 150.776

Sns: Orthorhombic crystals 298.15 to 875 K; cubic crystals 875 to melting point 1153 K.
Liquid 1153 to 1300 K. Reference state for sulfur is orthorhombic sulfur.

Temp. K	C_p°	S_T°	FORMATION FROM THE ELEMENTS				
			$(H_T^\circ - H_{298}^\circ)/T$	$-(G_T^\circ - H_{298}^\circ)/T$	$\Delta_f H^\circ$	$\Delta_f G^\circ$	Log K_f
			$J \cdot mol^{-1} \cdot K^{-1}$		$kJ \cdot mol^{-1}$		
298.15	49.25	77.00	0.00	77.00	-106.5	-104.6	18.33
300	49.32	77.30	0.30	77.00	-106.5	-104.6	18.22
400	50.87	91.76	12.81	78.95	-108.9	-103.9	13.57
500	52.02	103.22	20.52	82.70	-110.6	-102.5	10.70
600	54.51	112.91	25.96	86.95	-119.0	-99.3	8.65
700	58.40	121.50	30.30	91.20	-119.6	-96.0	7.16
800	63.50	129.71	34.12	95.59	-119.5	-92.7	6.05
900	54.04	137.47	37.81	99.66	-171.8	-88.1	5.11
1000	57.07	143.32	39.59	103.73	-170.9	-78.9	4.12
1100	60.11	148.90	41.32	107.58	-169.7	-69.7	3.31
1200	75.61	181.98	69.64	112.34	-136.3	-62.0	2.70
1300	75.61	188.03	70.10	117.93	-133.5	-55.9	2.25

Melting T	1153 K	Boiling T	K
$\Delta_{fus} H^\circ$	31.59 kJ	$\Delta_{vap} H^\circ$	kJ
$H_{298}^\circ - H_0^\circ$	kJ	Molar Vol.	2.901 J·bar ⁻¹ 29.01 cm ³

10/1/92

BERNDTITE

Formula wt 182.842

SnS₂: Hexagonal crystals 298.15 to 1000 K. Reference state for sulfur is orthorhombic sulfur.

Temp. K	C _p ^o	S _T ^o	(H _T ^o -H ₂₉₈ ^o)/T J·mol ⁻¹ ·K ⁻¹	-(G _T ^o -H ₂₉₈ ^o)/T	FORMATION FROM THE ELEMENTS		
					Δ _f H ^o kJ·mol ⁻¹	Δ _f G ^o	Log K _f
298.15	70.12	87.50	0.00	87.50	-149.8	-141.5	24.79
300	70.17	87.93	0.43	87.50	-149.8	-141.5	24.63
400	72.05	108.41	18.13	90.28	-154.7	-138.4	18.08
500	73.52	124.64	29.06	95.58	-158.2	-134.0	14.00
600	75.19	138.19	36.60	101.59	-168.1	-127.5	11.10
700	77.13	149.92	42.25	107.67	-170.0	-120.6	9.00
800	79.33	160.36	46.75	113.61	-171.4	-113.5	7.41
900	81.74	169.84	50.50	119.34	-278.6	-104.0	6.04
1000	84.33	178.59	53.75	124.84	-276.9	-84.7	4.42

Melting T	K	Boiling T	K
Δ _m H ^o	kJ	Δ _{vp} H ^o	kJ
H ₂₉₈ ^o -H ₀ ^o	kJ	Molar Vol.	4.096 J·bar ⁻¹ 40.96 cm ³

TUNGSTENITE

Formula wt 247.982

WS₂: Hexagonal crystals 298.15 to 1500 K. Reference state for sulfur is orthorhombic sulfur.

Temp. K	C _p ^o	S _T ^o	(H _T ^o -H ₂₉₈ ^o)/T J·mol ⁻¹ ·K ⁻¹	-(G _T ^o -H ₂₉₈ ^o)/T	FORMATION FROM THE ELEMENTS		
					Δ _f H ^o kJ·mol ⁻¹	Δ _f G ^o	Log K _f
298.15	63.83	67.80	0.00	67.80	-241.6	-233.0	40.81
300	63.99	68.20	0.39	67.80	-241.6	-232.9	40.55
400	69.67	87.50	17.10	70.39	-246.5	-229.8	30.00
500	72.41	103.37	27.92	75.45	-249.8	-225.2	23.53
600	74.01	116.72	35.48	81.25	-252.2	-220.0	19.16
700	75.09	128.22	41.06	87.15	-254.1	-214.5	16.01
800	75.90	138.30	45.37	92.93	-255.6	-208.8	13.63
900	76.57	147.28	48.80	98.48	-363.1	-200.7	11.65
1000	77.16	155.38	51.61	103.77	-361.9	-182.7	9.54
1100	77.71	162.76	53.95	108.80	-360.6	-164.9	7.83
1200	78.24	169.54	55.96	113.58	-359.4	-147.1	6.40
1300	78.76	175.82	57.69	118.13	-358.2	-129.5	5.20
1400	79.29	181.68	59.21	122.47	-357.0	-111.9	4.18
1500	79.83	187.17	60.57	126.60	-355.8	-94.5	3.29

Melting T	K	Boiling T	K
Δ _{fm} H ^o	kJ	Δ _{vp} H ^o	kJ
H ₂₉₈ ^o -H ₀ ^o	11.01 kJ	Molar Vol.	3.207 J·bar ⁻¹ 32.07 cm ³

SPHALERITE

Formula wt 97.456

ZnS: Cubic crystals 298.15 K to 1300 K. Reference state for sulfur is orthorhombic sulfur.

Temp. K	C_p°	S_T°	FORMATION FROM THE ELEMENTS				
			$(H_T^\circ - H_{298}^\circ)/T$ J·mol ⁻¹ ·K ⁻¹	$-(G_T^\circ - H_{298}^\circ)/T$	$\Delta_f H^\circ$ kJ·mol ⁻¹	$\Delta_f G^\circ$ kJ·mol ⁻¹	Log K_f
298.15	45.76	58.70	0.00	58.70	-204.1	-199.6	34.97
300	45.82	58.98	0.28	58.70	-204.1	-199.6	34.75
400	48.30	72.53	12.00	60.53	-206.6	-198.0	25.85
500	49.93	83.50	19.43	64.06	-208.3	-195.6	20.44
600	51.12	92.71	24.62	68.09	-209.6	-193.0	16.80
700	52.04	100.66	28.47	72.19	-218.0	-190.1	14.18
800	52.79	107.66	31.47	76.19	-219.1	-186.0	12.14
900	53.42	113.92	33.87	80.04	-273.2	-180.7	10.49
1000	53.96	119.57	35.85	83.72	-272.8	-170.4	8.90
1100	54.43	124.74	37.52	87.22	-272.4	-160.2	7.61
1200	54.85	129.49	38.95	90.54	-387.1	-148.1	6.45
1300	55.23	133.90	40.19	93.71	-385.6	-128.2	5.15

Melting T	K	Boiling T	K
$\Delta_{fus} H^\circ$	kJ	$\Delta_{vap} H^\circ$	kJ
$H_{298}^\circ - H_0^\circ$	8.82 kJ	Molar Vol.	2.383 J·bar ⁻¹ 23.83 cm ³

WURTZITE

Formula wt 97.456

ZnS: Hexagonal crystals 298.15 to 1300 K. Reference state for sulfur is orthorhombic sulfur.

Temp. K	C_p°	S_T°	$(H_T^\circ - H_{298}^\circ)/T$	$-(G_T^\circ - H_{298}^\circ)/T$	FORMATION FROM THE ELEMENTS		
					$\Delta_f H^\circ$	$\Delta_f G^\circ$	Log K_f
			$J \cdot mol^{-1} \cdot K^{-1}$		$kJ \cdot mol^{-1}$		
298.15	45.89	58.80	0.00	58.80	-203.8	-199.4	34.93
300	45.96	59.08	0.28	58.80	-203.8	-199.3	34.71
400	48.72	72.74	12.09	60.64	-206.2	-197.7	25.82
500	50.13	83.77	19.57	64.20	-207.9	-195.4	20.41
600	51.09	93.00	24.75	68.25	-209.2	-192.8	16.78
700	51.86	100.94	28.57	72.37	-217.7	-189.8	14.17
800	52.55	107.91	31.52	76.38	-218.8	-185.8	12.13
900	53.21	114.13	33.90	80.24	-272.9	-180.6	10.48
1000	53.86	119.77	35.86	83.91	-272.5	-170.3	8.90
1100	54.50	124.94	37.52	87.41	-272.1	-160.1	7.60
1200	55.15	129.71	38.97	90.74	-386.8	-148.0	6.44
1300	55.80	134.15	40.24	93.91	-385.2	-128.2	5.15

Melting T	K	Boiling T	K
$\Delta_{\text{m}} H^\circ$	kJ	$\Delta_{\text{vap}} H^\circ$	kJ
$H_{298}^\circ - H_0^\circ$	8.85 kJ	Molar Vol.	2.385 $J \cdot \text{bar}^{-1}$ 23.85 cm^3

BERTHIERITE

Formula wt 427.611

FeSb_2S_4 : Orthorhombic crystals 298.15 to 836 K. Reference state for sulfur is orthorhombic sulfur.

Temp. K	C_p°	S_T°	$(H_T^\circ - H_{298}^\circ)/T$ J·mol ⁻¹ ·K ⁻¹	$-(G_T^\circ - H_{298}^\circ)/T$	FORMATION FROM THE ELEMENTS		
					$\Delta_f H^\circ$ kJ·mol ⁻¹	$\Delta_f G^\circ$	Log K_f
298.15	175.23	245.00	0.00	245.00	-256.2	-255.8	44.81
300	175.60	246.09	1.08	245.00	-256.2	-255.8	44.54
400	186.17	298.40	46.33	252.06	-264.1	-255.4	33.36
500	189.05	340.31	74.64	265.67	-269.1	-252.8	26.40
600	190.44	374.90	93.83	281.07	-272.9	-249.1	21.69
700	191.92	404.37	107.73	296.63	-276.0	-244.9	18.27
800	193.91	430.12	118.37	311.74	-279.0	-240.2	15.68
900	196.48	453.10	126.91	326.20	-494.4	-230.9	13.40

Melting T	K	Boiling T	K
$\Delta_{\text{fus}} H^\circ$	kJ	$\Delta_{\text{vap}} H^\circ$	kJ
$H_{298}^\circ - H_0^\circ$	kJ	Molar Vol.	9.222 J·bar ⁻¹ 92.22 cm ³

CHALCOSTIBITE

Formula wt 249.428

CuSbS_2 : Orthorhombic crystals 298.15 to 826 K. Reference state for sulfur is orthorhombic sulfur.

Temp. K	C_p°	S_T°	FORMATION FROM THE ELEMENTS				
			$(H_T^\circ - H_{298}^\circ)/T$ J·mol ⁻¹ ·K ⁻¹	$-(G_T^\circ - H_{298}^\circ)/T$	$\Delta_f H^\circ$ kJ·mol ⁻¹	$\Delta_f G^\circ$ kJ·mol ⁻¹	Log K_f
298.15	100.15	149.20	0.00	149.20	-130.8	-132.7	23.25
300	100.22	149.82	0.62	149.20	-130.8	-132.7	23.11
400	104.26	179.20	26.02	153.18	-134.8	-133.3	17.40
500	108.30	202.90	42.07	160.83	-137.2	-132.6	13.85
600	112.34	223.01	53.45	169.56	-138.7	-131.5	11.45
700	116.38	240.63	62.15	178.48	-139.3	-130.3	9.72
800	120.42	256.43	69.18	187.25	-139.5	-129.0	8.42
900	124.46	270.85	75.10	195.75	-245.5	-125.5	7.29

Melting T	826 K	Boiling T	K
$\Delta_{\text{m}} H^\circ$	kJ	$\Delta_{\text{vp}} H^\circ$	kJ
$H_{298}^\circ - H_0^\circ$	kJ	Molar Vol.	5.006 J·bar ⁻¹ 50.06 cm ³

ACANTHITE (ARGENTITE)

Formula wt 247.802

Ag₂S: Monoclinic crystals 298.15 to 451.3 K; cubic crystals (argentite) 451.3 to 865 K.
 γ phase 865 to 1000 K. Reference state for sulfur is ideal S₂ gas at p = 1 bar.

Temp. K	C _p ^o	S _T ^o	(H _T ^o -H ₂₉₈ ^o)/T	-(G _T ^o -H ₂₉₈ ^o)/T	FORMATION FROM THE ELEMENTS		
					Δ _f H ^o	Δ _f G ^o	Log K _f
			J·mol ⁻¹ ·K ⁻¹		kJ·mol ⁻¹		
298.15	75.31	142.89	0.00	142.89	-96.3	-79.5	13.93
300	75.39	143.35	0.46	142.89	-96.3	-79.4	13.83
400	80.47	165.67	19.78	145.89	-95.3	-73.9	9.65
500	87.26	193.79	41.08	152.71	-89.6	-69.2	7.23
600	86.03	209.59	48.67	160.92	-88.1	-65.3	5.68
700	84.80	222.75	53.91	168.84	-86.7	-61.6	4.60
800	84.69	234.05	57.75	176.30	-85.7	-58.1	3.79
900	80.38	244.84	61.53	183.31	-84.1	-54.7	3.17
1000	80.57	253.28	63.38	189.90	-83.8	-51.5	2.69

Melting T	K	Boiling T	K
Δ _{fm} H ^o	kJ	Δ _{vp} H ^o	kJ
H ₂₉₈ ^o -H ₀ ^o	17.132 kJ	Molar Vol.	3.419 J·bar ⁻¹ 34.19 cm ³
A=	-8.355E+01	B=	3.273E-02
		C=	-5.14E+05

REALGAR

Formula wt 106.988

AsS: Monoclinic crystals 298.15 to melting point 580 K; liquid 580 to 800 K.
Reference state for sulfur is ideal S₂ gas at p = 1 bar.

Temp. K	C _p ^o	S _T ^o	(H _T ^o -H ₂₉₈ ^o)/T	-(G _T ^o -H ₂₉₈ ^o)/T	FORMATION FROM THE ELEMENTS		
					Δ _f H ^o	Δ _f G ^o	Log K _f
			J·mol ⁻¹ ·K ⁻¹		kJ·mol ⁻¹		
298.15	47.02	63.50	0.00	63.50	-95.2	-69.5	12.17
300	47.08	63.80	0.29	63.51	-95.2	-69.3	12.07
400	49.32	77.68	12.29	65.39	-94.5	-60.8	7.94
500	51.18	88.88	19.88	69.00	-93.8	-52.4	5.48
600	67.12	110.35	36.84	73.51	-86.0	-44.5	3.87
700	71.48	121.00	41.46	79.54	-83.6	-37.7	2.82
800	77.50	130.90	45.57	85.33	-80.7	-31.4	2.05

Melting T	580 K	Boiling T	K
Δ _m H ^o	6.668 kJ	Δ _{vap} H ^o	kJ
H ₂₉₈ ^o -H ₀ ^o	kJ	Molar Vol.	2.980 J·bar ⁻¹ 29.80 cm ³
A=	-84.07	B=	0.06734
		C=	-4.98E+05

3/25/92

GREENOCKITE

Formula wt 144.477

Cds: Cubic crystals 298.15 to 1100 K. Reference state for sulfur is ideal S₂ gas at p = 1 bar.

Temp. K	C _p ^o	S _T ^o	FORMATION FROM THE ELEMENTS				
			(H _T ^o -H ₂₉₈ ^o)/T J·mol ⁻¹ ·K ⁻¹	-(G _T ^o -H ₂₉₈ ^o)/T	Δ _f H ^o kJ·mol ⁻¹	Δ _f G ^o	Log K _f
298.15	47.30	72.18	0.00	72.18	-213.9	-186.0	32.58
300	47.36	72.47	0.29	72.18	-213.9	-185.8	32.35
400	49.46	86.42	12.35	74.07	-213.4	-176.5	23.05
500	50.70	97.60	19.91	77.69	-212.8	-167.4	17.48
600	51.68	106.93	25.12	81.81	-218.6	-158.2	13.78
700	52.55	114.96	28.98	85.99	-218.1	-148.2	11.06
800	53.37	122.03	31.98	90.06	-217.6	-138.3	9.03
900	54.16	128.37	34.40	93.97	-217.1	-128.4	7.45
1000	54.93	134.11	36.41	97.70	-216.5	-118.5	6.19
1100	55.67	139.38	38.13	101.25	-314.8	-102.9	4.89

Melting T	K	Boiling T	K
Δ _{fus} H ^o	kJ	Δ _{vap} H ^o	kJ
H ₂₉₈ ^o -H ₀ ^o	8.81 kJ	Molar Vol.	2.993 J·bar ⁻¹ 29.93 cm ³

A= -2.177E+02

B= 9.880E-02

C= 2.109E+05

9/24/92

CATTIERITE

Formula wt 123.065

CoS₂: Cubic crystals 298.15 to 1000 K. Reference state for sulfur is ideal S₂ gas at p = 1 bar.

Temp. K	C _p ^o	S _T ^o	(H _T ^o -H ₂₉₈ ^o)/T	-(G _T ^o -H ₂₉₈ ^o)/T	FORMATION FROM THE ELEMENTS		
					Δ _f H ^o	Δ _f G ^o	Log K _f
			J·mol ⁻¹ ·K ⁻¹		kJ·mol ⁻¹		
298.15	68.26	74.80	0.00	74.80	-279.5	-224.8	39.38
300	68.39	75.22	0.42	74.80	-279.5	-224.5	39.08
400	74.28	95.76	18.20	77.56	-278.2	-206.3	26.94
500	78.63	112.82	29.87	82.96	-276.8	-188.5	19.69
600	82.38	127.50	38.31	89.18	-275.1	-171.0	14.89
700	85.85	140.46	44.86	95.60	-273.4	-153.8	11.48
800	89.16	152.14	50.19	101.95	-271.9	-136.8	8.93
900	92.38	162.83	54.70	108.13	-269.8	-120.0	6.97
1000	95.55	172.72	58.63	114.10	-267.7	-103.5	5.41

Melting T	K	Boiling T	K
Δ _{fus} H ^o	kJ	Δ _{vap} H ^o	kJ
H ₂₉₈ ^o -H ₀ ^o	12.30 kJ	Molar Vol.	2.552 J·bar ⁻¹ 25.52 cm ³

A= -2.710E+02

B= 1.682E-01

C= -3.57E+05

3/26/92

COVELLITE

Formula wt 95.612

CuS: Hexagonal crystals 298.15 to 800 K. Reference state for sulfur is ideal S₂ gas at p = 1 bar.

Temp. K	C _p ^o	S _T ^o	(H _T ^o -H ₂₉₈ ^o)/T	-(G _T ^o -H ₂₉₈ ^o)/T	FORMATION FROM THE ELEMENTS		
					Δ _f H ^o	Δ _f G ^o	Log K _f
			J·mol ⁻¹ ·K ⁻¹	kJ·mol ⁻¹			
298.15	47.53	67.40	0.00	67.40	-118.9	-95.1	16.66
300	47.59	67.69	0.29	67.40	-118.9	-95.0	16.53
400	50.29	81.77	12.47	69.30	-118.1	-87.1	11.37
500	52.62	93.24	20.27	72.98	-117.3	-79.4	8.30
600	54.82	103.03	25.84	77.19	-116.3	-71.9	6.26
700	56.94	111.64	30.14	81.51	-115.2	-64.6	4.82
800	59.03	119.38	33.62	85.77	-113.9	-57.5	3.75

Melting T	780i K	Boiling T	K
Δ _{fm} H ^o	kJ	Δ _{vap} H ^o	kJ
H ₂₉₈ ^o -H ₀ ^o	9.45 kJ	Molar Vol.	2.042 J·bar ⁻¹ 20.42 cm ³
A=	-1.148E+02	B=	7.208E-02
		C=	-1.60E+05

CHALCOCITE

Formula wt 159.158

Cu_2S : Orthorhombic crystals 298.15 to 376 K; hexagonal crystals 376 to 710 K; cubic crystals 710 to melting point 1403 K. Reference state for sulfur is ideal S_2 gas at $p = 1$ bar.

Temp. K	C_p°	S_f°	FORMATION FROM THE ELEMENTS				
			$(H_f^\circ - H_{298}^\circ)/T$ J·mol ⁻¹ ·K ⁻¹	$-(G_f^\circ - H_{298}^\circ)/T$	$\Delta_f H^\circ$ kJ·mol ⁻¹	$\Delta_f G^\circ$	Log K_f
298.15	76.84	116.20	0.00	116.20	-148.2	-129.1	22.61
300	77.01	116.67	0.47	116.20	-148.2	-129.0	22.45
400	98.83	151.07	31.14	119.93	-142.5	-123.0	16.06
500	95.31	172.84	44.33	128.51	-139.7	-118.5	12.38
600	92.30	189.93	52.56	137.37	-137.3	-114.5	9.97
700	89.79	203.97	58.06	145.91	-135.3	-110.8	8.27
800	82.76	216.94	62.85	154.09	-132.9	-107.6	7.02
900	82.50	226.66	65.04	161.62	-132.1	-104.5	6.06
1000	85.02	235.65	67.02	168.63	-131.1	-101.5	5.30
1100	85.02	243.77	68.68	175.09	-130.3	-98.6	4.68
1200	85.02	251.17	70.03	181.14	-129.7	-95.7	4.17
1300	85.02	257.95	71.71	186.24	-128.7	-92.2	3.71
1400	85.02	264.23	72.15	192.08	-155.6	-89.2	3.33

Melting T	1403 K	Boiling T	K
$\Delta_{\text{fus}} H^\circ$	kJ	$\Delta_{\text{vap}} H^\circ$	kJ
$H_{298}^\circ - H_0^\circ$	15.80 kJ	Molar Vol.	2.748 J·bar ⁻¹ 27.48 cm ³

A= -1.304E+02

B= 2.957E-02

C= -6.73E+05

01/13/93

CHALCOPYRITE

Formula wt 183.525

CuFeS₂: Tetragonal crystals 298.15 to 820 K; tetragonal crystals 820 to 930 K; cubic crystals 930 to 1200 K. Reference state for sulfur is ideal S₂ gas at p = 1 bar. Above 820 K, phase is called ISS (intermediate solid solution).

Temp. K	C _p ^o	S _T ^o	(H _T ^o -H ₂₉₈ ^o)/T	-(G _T ^o -H ₂₉₈ ^o)/T	FORMATION FROM THE ELEMENTS		
					Δ _f H ^o	Δ _f G ^o	Log K _f
			J·mol ⁻¹ ·K ⁻¹	kJ·mol ⁻¹			
298.15	95.80	124.90	0.00	124.90	-323.5	-274.8	48.14
300	96.24	125.49	0.59	124.90	-323.5	-274.5	47.79
400	106.26	155.01	26.15	128.86	-321.7	-258.4	33.74
500	109.15	179.02	42.45	136.57	-319.8	-242.8	25.37
600	114.53	199.34	53.97	145.38	-317.9	-227.6	19.81
700	123.84	217.64	63.24	154.41	-315.6	-212.7	15.87
800	136.83	234.99	71.59	163.40	-312.6	-198.2	12.94
900	203.75	264.70	91.48	173.22	-298.0	-185.0	10.74
1000	172.49	285.00	101.42	183.58	-290.2	-173.0	9.04
1100	172.49	301.44	107.88	193.56	-285.3	-161.5	7.67
1200	172.49	316.45	113.27	203.18	-279.8	-150.6	6.55

Melting T	K	Boiling T	K
Δ _{sub} H ^o	kJ	Δ _{sub} H ^o	kJ
H ₂₉₈ ^o -H ₀ ^o	18.34 kJ	Molar Vol.	4.392 J·bar ⁻¹ 43.92 cm ³

A= -2.9995E+02

B= 1.2712E-01

C= -1.19E+06

BORNITE

Formula wt 501.841

Cu_5FeS_4 : Orthorhombic crystals 298.15 to 470 K; cubic crystals 470 to 535 K; cubic crystals 535 to 1200 K. Reference state for sulfur is ideal S_2 gas at $p = 1$ bar.

Temp. K	C_p°	S_T°	$(H_T^\circ - H_{298}^\circ)/T$ J·mol ⁻¹ ·K ⁻¹	$-(G_T^\circ - H_{298}^\circ)/T$	FORMATION FROM THE ELEMENTS		
					$\Delta_f H^\circ$ kJ·mol ⁻¹	$\Delta_f G^\circ$	Log K_f
298.15	242.90	398.50	0.00	398.50	-628.8	-554.1	97.07
300	243.20	400.00	1.50	398.50	-628.7	-553.6	96.39
400	260.60	472.40	64.09	408.31	-625.3	-529.1	69.09
500	369.45	549.41	121.22	428.19	-612.9	-506.0	52.86
600	327.89	615.63	161.33	454.30	-600.0	-485.9	42.30
700	323.50	665.90	184.73	481.17	-591.4	-467.7	34.90
800	325.20	709.20	202.19	507.01	-583.4	-450.6	29.42
900	327.30	747.53	215.89	531.64	-576.1	-434.4	25.21
1000	332.90	782.29	227.29	555.00	-569.5	-419.1	21.89
1100	340.00	814.34	237.21	577.13	-563.5	-404.3	19.20
1200	348.30	844.27	246.12	598.15	-556.7	-390.1	16.98

Melting T	K	Boiling T	K
$\Delta_{\text{m}} H^\circ$	kJ	$\Delta_{\text{vap}} H^\circ$	kJ
$H_{298}^\circ - H_0^\circ$	53.01 kJ	Molar Vol.	9.873 J·bar ⁻¹ 98.73 cm ³

A= -5.714E+02

B= 1.542E-01

C= -2.625E+06

3/26/92

TROILITE

Formula wt 87.913

FeS: Hexagonal crystals (NiAs structure) 298.15 to a complex transition at 411 K and a Néel temperature at 590 K; paramagnetic 590 to melting point at 1468 K; liquid 1468 to 1800 K. Reference state for sulfur is ideal S₂ gas at p = 1 bar.

Temp. K	C _p ^o	S _T ^o	(H _T ^o -H ₂₉₈ ^o)/T J·mol ⁻¹ ·K ⁻¹	-(G _T ^o -H ₂₉₈ ^o)/T	FORMATION FROM THE ELEMENTS		
					Δ _f H ^o kJ·mol ⁻¹	Δ _f G ^o	Log K _f
298.15	50.49	60.30	0.00	60.30	-166.9	-142.8	25.01
300	50.64	60.62	0.31	60.31	-166.9	-142.6	24.83
400	70.02	76.87	14.44	62.43	-165.5	-134.7	17.59
500	72.06	102.86	34.29	68.57	-158.7	-128.1	13.39
600	67.33	116.98	41.52	75.46	-155.8	-122.3	10.65
700	58.13	126.32	44.23	82.09	-154.9	-116.8	8.71
800	57.73	134.00	45.90	88.10	-154.5	-111.4	7.27
900	58.65	140.86	47.27	93.59	-154.6	-106.0	6.15
1000	60.64	147.13	48.49	98.64	-155.3	-100.6	5.25
1100	62.00	152.82	49.52	103.30	-156.8	-95.0	4.51
1200	62.99	158.17	50.52	107.65	-157.5	-89.3	3.89
1300	63.99	163.32	51.56	111.76	-156.5	-83.7	3.36
1400	64.99	168.22	52.60	115.62	-155.3	-78.2	2.92
1500	71.13	194.95	75.20	119.75	-121.7	-73.4	2.56
1600	71.13	199.51	74.94	124.57	-120.3	-70.2	2.29
1700	71.13	203.82	74.72	129.10	-119.8	-67.1	2.06
1800	71.13	207.88	74.52	133.36	-119.0	-64.0	1.86
Melting T	1468 K			Boiling T		K	
Δ _{fm} H ^o	32.34 kJ			Δ _{vp} H ^o		kJ	
H ₂₉₈ ^o -H ₀ ^o	9.351 kJ			Molar Vol.		1.820	J·bar ⁻¹
						18.20	cm ³
	A= -1.488E+02		B= 4.910E-02		C= -8.05E+05		

2/17/93

PYRRHOTITE

Formula wt 80.932

Fe_{0.875}S: Monoclinic crystals 298.15 to combined structural and magnetic transition at 590 K; hexagonal crystal (NiAs-type) 590 to 1000 K. Reference state for sulfur is ideal S₂ gas at p = 1 bar.

Temp. K	C _p ^o	S _T ^o	(H _T ^o -H ₂₉₈ ^o)/T	-(G _T ^o -H ₂₉₈ ^o)/T	FORMATION FROM THE ELEMENTS		
					Δ _f H ^o	Δ _f G ^o	Log K _f
			J·mol ⁻¹ ·K ⁻¹	kJ·mol ⁻¹			
298.15	49.88	60.70	0.00	60.70	-161.8	-138.8	24.31
300	50.01	60.70	0.31	60.39	-161.7	-138.5	24.12
400	56.24	76.28	13.53	62.75	-160.4	-131.1	17.12
500	63.56	89.57	22.76	66.81	-158.6	-124.0	12.95
600	67.35	104.51	32.47	72.04	-155.0	-117.5	10.23
700	65.30	114.53	37.37	77.16	-153.0	-111.2	8.30
800	57.42	122.64	40.28	82.36	-151.9	-105.4	6.88
900	57.19	129.39	42.17	87.22	-151.6	-99.6	5.78
1000	58.38	135.46	43.71	91.75	-151.9	-93.8	4.90

Melting T	K	Boiling T	K
Δ _{lv} H ^o	kJ	Δ _{vp} H ^o	kJ
H ₂₉₈ ^o -H ₀ ^o	9.21 kJ	Molar Vol.	1.749 J·bar ⁻¹ 17.49 cm ³

A= -1.513E+02

B= 5.811E-02

C= -4.30E+05

01/13/93

PYRITE

Formula wt 119.979

FeS₂: Cubic crystals 298.15 to 1000 K. Reference state for sulfur is ideal S₂ gas at p = 1 bar.

Temp. K	C _p ^o	S _T ^o	(H _T ^o -H ₂₉₈ ^o)/T	-(G _T ^o -H ₂₉₈ ^o)/T	FORMATION FROM THE ELEMENTS		
					Δ _f H ^o	Δ _f G ^o	Log K _f
			J·mol ⁻¹ ·K ⁻¹		kJ·mol ⁻¹		
298.15	62.17	52.90	0.00	52.90	-300.1	-239.8	42.01
300	62.39	53.29	0.38	52.90	-300.1	-239.4	41.69
400	69.15	72.34	16.88	55.45	-299.5	-219.3	28.64
500	71.95	88.10	27.64	60.45	-298.7	-199.3	20.82
600	73.93	101.39	35.20	66.20	-298.0	-179.5	15.63
700	75.90	112.94	40.87	72.07	-297.4	-159.8	11.93
800	78.10	123.21	45.38	77.83	-297.0	-140.2	9.15
900	80.57	132.55	49.15	83.40	-296.8	-120.6	7.00
1000	83.29	141.18	52.43	88.75	-297.1	-101.1	5.28

Melting T	1015i K	Boiling T	K
Δ _{fm} H ^o	kJ	Δ _{vap} H ^o	kJ
H ₂₉₈ ^o -H ₀ ^o	9.63 kJ	Molar Vol.	2.394 J·bar ⁻¹ 23.94 cm ³

A= -2.967E+02

B= 1.958E-01

C= -1.36E-05

9/25/92

MARCASITE

Formula wt 119.979

FeS₂: Orthorhombic crystals 298.15 to 700 K. Reference state for sulfur is ideal S₂ gas at p = 1 bar.

Temp. K	C _p ^o	S _T ^o	(H _T ^o -H ₂₉₈ ^o)/T	-(G _T ^o -H ₂₉₈ ^o)/T	FORMATION FROM THE ELEMENTS		
					Δ _f H ^o	Δ _f G ^o	Log K _f
			J·mol ⁻¹ ·K ⁻¹	kJ·mol ⁻¹			
298.15	62.43	53.90	0.00	53.90	-298.1	-238.1	41.71
300	62.60	54.29	0.39	53.90	-298.1	-237.7	41.39
400	69.17	73.31	16.86	56.45	-297.4	-217.7	28.42
500	72.44	89.13	27.68	61.45	-296.6	-197.8	20.66
600	74.59	102.53	35.32	67.21	-295.9	-178.1	15.50
700	77.00	114.20	41.10	73.11	-295.2	-158.5	11.83

Melting T	K	Boiling T	K
Δ _m H ^o	kJ	Δ _{vap} H ^o	kJ
H ₂₉₈ ^o -H ₀ ^o	9.74 kJ	Molar Vol.	2.458 J·bar ⁻¹ 24.58 cm ³

A= -2.952E+02

B= 1.955E-01

C= -1.08E+05

9/25/92

HYDROGEN SULFIDE

Formula wt 34.082

H₂S: Ideal gas at p = 1 bar, 298.15 to 1800 K. Reference state for sulfur is ideal S₂ gas at p = 1 bar.

Temp. K	C _p ^o	S _T ^o	(H _T ^o -H ₂₉₈ ^o)/T J·mol ⁻¹ ·K ⁻¹	-(G _T ^o -H ₂₉₈ ^o)/T	FORMATION FROM THE ELEMENTS		
					Δ _f H ^o kJ·mol ⁻¹	Δ _f G ^o	Log K _f
298.15	34.20	205.80	0.00	205.80	-84.9	-73.3	12.84
300	34.21	206.01	0.21	205.80	-84.9	-73.2	12.75
400	35.48	216.01	8.85	207.15	-86.0	-69.1	9.03
500	37.22	224.11	14.35	209.76	-87.0	-64.8	6.77
600	39.05	231.05	18.31	212.74	-87.9	-60.3	5.25
700	40.85	237.21	21.40	215.81	-88.7	-55.6	4.15
800	42.58	242.78	23.94	218.83	-89.2	-50.8	3.32
900	44.21	247.89	26.11	221.78	-89.7	-46.0	2.67
1000	45.72	252.63	27.99	224.63	-90.1	-41.1	2.15
1100	47.13	257.05	29.67	227.38	-90.4	-36.2	1.72
1200	48.41	261.21	31.18	230.03	-90.6	-31.3	1.36
1300	49.58	265.13	32.55	232.58	-90.7	-26.3	1.06
1400	50.62	268.84	33.80	235.04	-90.8	-21.4	0.80
1500	51.55	272.37	34.96	237.41	-90.8	-16.4	0.57
1600	52.35	275.72	36.02	239.70	-90.8	-11.5	0.37
1700	53.04	278.92	37.00	241.91	-90.8	-6.5	0.20
1800	53.60	281.96	37.91	244.06	-90.7	-1.6	0.05

Melting T	K	Boiling T	K
Δ _{sub} H ^o	kJ	Δ _{vap} H ^o	kJ
H ₂₉₈ ^o -H ₀ ^o	9.96 kJ	Molar Vol.	2478.97 J·bar ⁻¹ 24789.7 cm ³

A= -9.067E+01

B= 4.942E-02

C= 2.447E+05

3/26/92

ALABANDITE

Formula wt 87.004

MnS: Cubic crystals 298.15 to 1800 K. Reference state for sulfur is ideal S₂ gas at p = 1 bar.

Temp. K	C _p ^o	S _T ^o	FORMATION FROM THE ELEMENTS				
			(H _T ^o -H ₂₉₈ ^o)/T J·mol ⁻¹ ·K ⁻¹	-(G _T ^o -H ₂₉₈ ^o)/T	Δ _f H ^o kJ·mol ⁻¹	Δ _f G ^o	Log K _f
298.15	49.98	80.30	0.00	80.30	-278.2	-258.6	45.30
300	49.99	80.61	0.31	80.30	-278.2	-258.5	45.00
400	51.10	95.13	12.86	82.27	-277.5	-252.0	32.91
500	52.14	106.65	20.62	86.04	-277.0	-245.7	25.66
600	52.83	116.22	25.93	90.29	-276.6	-239.4	20.84
700	53.25	124.40	29.81	94.59	-276.4	-231.3	17.41
800	53.55	131.53	32.76	98.78	-276.3	-227.1	14.83
900	53.84	137.85	35.08	102.77	-276.3	-220.9	12.82
1000	54.21	143.55	36.98	106.57	-278.7	-214.7	11.22
1100	54.73	148.74	38.56	110.17	-278.9	-208.3	9.89
1200	55.44	153.53	39.94	113.59	-279.1	-201.9	8.79
1300	56.39	158.00	41.17	116.83	-279.3	-195.5	7.85
1400	57.60	162.22	42.30	119.93	-281.7	-188.9	7.05
1500	59.10	166.24	43.36	122.88	-284.2	-182.2	6.34
1600	60.91	170.11	44.40	125.71	-296.9	-174.7	5.70
1700	63.04	173.87	45.43	128.43	-297.3	-167.0	5.13
1800	65.51	177.54	46.48	131.06	-297.4	-159.4	4.62

Melting T	K	Boiling T	K
Δ _{fus} H ^o	kJ	Δ _{vap} H ^o	kJ
H ₂₉₈ ^o -H ₀ ^o	kJ	Molar Vol.	2.146 J·bar ⁻¹ 21.46 cm ³

A= -2.807E+02

B= 6.621E-02

C= 2.459E+05

3/26/92

MOLYBDENITE

Formula wt 160.072

MoS₂: Hexagonal crystals 298.15 to 1200 K. Reference state for sulfur is ideal S₂ gas at p = 1 bar.

Temp. K	C _p ^o	S _T ^o	(H _T ^o -H ₂₉₈ ^o)/T	-(G _T ^o -H ₂₉₈ ^o)/T	FORMATION FROM THE ELEMENTS		
					Δ _f H ^o	Δ _f G ^o	Log K _f
			J·mol ⁻¹ ·K ⁻¹	kJ·mol ⁻¹			
298.15	63.51	62.60	0.00	62.60	-400.4	-342.5	60.00
300	63.63	62.99	0.39	62.60	-400.4	-342.1	59.57
400	68.45	82.01	16.85	65.16	-399.6	-322.8	42.16
500	71.58	97.65	27.50	70.14	-398.5	-303.8	31.73
600	73.77	110.90	35.04	75.86	-397.4	-284.9	24.80
700	75.35	122.40	40.69	81.70	-396.2	-266.3	19.87
800	76.54	132.54	45.10	87.44	-395.0	-247.8	16.18
900	77.44	141.61	48.65	92.96	-393.7	-229.5	13.32
1000	78.12	149.81	51.56	98.24	-392.5	-211.3	11.04
1100	78.65	157.28	54.00	103.28	-391.3	-193.2	9.17
1200	79.04	164.14	56.07	108.07	-390.1	-175.3	7.63

Melting T	K	Boiling T	K
Δ _{fus} H ^o	kJ	Δ _{vap} H ^o	kJ
H ₂₉₈ ^o -H ₀ ^o	8.818 kJ	Molar Vol.	3.202 J·bar ⁻¹ 32.02 cm ³
A= -3.933E+02		B= 1.822E-01	C= -3.21E+05

MILLERITE

Formula wt 90.756

NiS: Rhombohedral crystals 298.15 to 623 K; hexagonal crystals 623 to melting point at 1066 K. Reference state for sulfur is ideal S₂ gas at p = 1 bar.

Temp. K	C _p ^o	S _T ^o	(H _T ^o -H ₂₉₈ ^o)/T	-(G _T ^o -H ₂₉₈ ^o)/T	FORMATION FROM THE ELEMENTS		
					Δ _f H ^o	Δ _f G ^o	Log K _f
			J·mol ⁻¹ ·K ⁻¹		kJ·mol ⁻¹		
298.15	47.11	52.97	0.00	52.97	-155.3	-128.2	22.45
300	47.24	53.26	0.29	52.97	-155.3	-128.0	22.29
400	50.79	67.36	12.55	54.81	-154.8	-119.0	15.53
500	53.68	79.04	20.42	58.62	-154.2	-110.1	11.50
600	56.27	89.04	26.22	62.82	-153.8	-101.3	8.82
700	59.45	102.68	34.91	67.77	-150.2	-93.0	6.94
800	62.55	110.79	38.18	72.61	-149.0	-85.4	5.57
900	65.65	118.37	41.05	77.32	-147.6	-77.0	4.47
1000	68.74	125.44	43.68	81.76	-145.9	-69.2	3.61
1100	71.13	159.58	72.73	86.85	-114.7	-62.5	2.97

Melting T	1066 K	Boiling T	K
Δ _{fus} H ^o	kJ	Δ _{vap} H ^o	kJ
H ₂₉₈ ^o -H ₀ ^o	53.01 kJ	Molar Vol.	1.689 J·bar ⁻¹ 16.89 cm ³

A= -1.434E+02

B= 7.351E-02

C= -6.29E+05

4/1/92

HEAZLEWOODITE

Formula wt 240.202

Ni_3S_2 : Hexagonal crystals 298.15 to 834 K; cubic crystals 834 K to incongruent melting point 1064 K; liquid 1064 to 1400 K. Reference state for sulfur is ideal S_2 gas at $p = 1$ bar.

Temp. K	C_p°	S_T°	$(H_T^\circ - H_{298}^\circ)/T$	$-(G_T^\circ - H_{298}^\circ)/T$	FORMATION FROM THE ELEMENTS		
					$\Delta_f H^\circ$	$\Delta_f G^\circ$	Log K_f
			J·mol ⁻¹ ·K ⁻¹		kJ·mol ⁻¹		
298.15	118.24	133.20	0.00	133.20	-344.9	-289.9	50.78
300	118.45	133.93	0.73	133.20	-344.9	-289.5	50.41
400	129.01	169.52	31.54	137.98	-344.0	-271.2	35.41
500	136.05	199.12	51.79	147.34	-343.0	-253.1	26.44
600	141.59	224.42	66.29	158.12	-342.5	-235.2	20.47
700	148.35	246.72	77.51	169.22	-341.7	-217.3	16.22
800	158.39	267.14	86.95	180.20	-339.3	-201.1	13.13
900	189.15	355.52	159.38	196.14	-278.4	-187.1	10.86
1000	191.81	375.52	162.41	213.11	-272.8	-177.3	9.26
1100	189.12	411.84	182.56	229.28	-247.9	-168.7	8.01
1200	189.12	428.28	183.11	245.17	-242.7	-161.7	7.04
1300	189.12	443.42	183.57	259.85	-237.9	-155.1	6.23
1400	189.12	457.44	183.97	273.47	-233.3	-148.9	5.56

Melting T	1064 K	Boiling T	K
$\Delta_{\text{fus}} H^\circ$	19.66 kJ	$\Delta_{\text{vap}} H^\circ$	kJ
$H_{298}^\circ - H_0^\circ$	21.501 kJ	Molar Vol.	4.095 J·bar ⁻¹ 40.95 cm ³

A= -2.815E+02

B= 1.016E-01

C= -3.71E+06

4/1/92

GALENA

Formula wt 239.266

Pbs: Cubic crystals 298.15 to 900 K. Reference state for sulfur is ideal S₂ gas at p = 1 bar.

FORMATION FROM THE ELEMENTS

Temp. K	C _p ^o	S _T ^o	(H _T ^o -H ₂₉₈ ^o)/T J·mol ⁻¹ ·K ⁻¹	-(G _T ^o -H ₂₉₈ ^o)/T	Δ _f H ^o kJ·mol ⁻¹	Δ _f G ^o	Log K _f
298.15	49.49	91.70	0.00	91.70	-162.6	-136.6	23.93
300	49.52	92.01	0.31	91.70	-162.6	-136.4	23.76
400	51.16	106.48	12.81	93.66	-161.9	-127.8	16.69
500	52.80	118.07	20.65	97.42	-161.3	-119.4	12.47
600	54.44	127.84	26.14	101.70	-160.6	-111.0	9.67
700	56.08	136.36	30.30	106.05	-164.8	-102.0	7.61
800	57.72	143.95	33.63	110.32	-163.9	-93.1	6.08
900	59.36	150.84	36.40	114.45	-162.9	-84.3	4.90

Melting T	1400 K	Boiling T	K
Δ _{fus} H ^o	kJ	Δ _{vap} H ^o	kJ
H ₂₉₈ ^o -H ₀ ^o	kJ	Molar Vol.	3.149 J·bar ⁻¹ 31.49 cm ³

A= -1.640E+02

B= 8.830E-02

C= 9.946E+04

9/25/92

STIBNITE

Formula wt 339.698

Sb_2S_3 : Orthorhombic crystals 298.15 to 900 K. Reference state for sulfur is ideal S_2 gas at $p = 1$ bar.

Temp. K	C_p°	S_T°	$(H_T^\circ - H_{298}^\circ)/T$ J·mol ⁻¹ ·K ⁻¹	$-(G_T^\circ - H_{298}^\circ)/T$	FORMATION FROM THE ELEMENTS		
					$\Delta_f H^\circ$ kJ·mol ⁻¹	$\Delta_f G^\circ$	Log K_f
298.15	119.75	182.00	0.00	182.00	-344.3	-269.4	47.19
300	119.81	182.74	0.74	182.00	-344.3	-269.8	46.82
400	123.38	217.70	30.96	186.74	-342.2	-244.1	31.88
500	126.46	245.58	49.76	195.82	-340.1	-219.8	22.96
600	128.94	268.86	62.76	206.10	-338.0	-195.9	17.06
700	130.92	288.89	72.36	216.53	-335.9	-172.4	12.87
800	132.51	306.48	79.78	226.70	-334.0	-149.2	9.74
900	133.80	322.17	85.72	236.45	-332.2	-126.2	7.33

Melting T	829 K	Boiling T	K
$\Delta_{fus} H^\circ$	kJ	$\Delta_{vap} H^\circ$	kJ
$H_{298}^\circ - H_0^\circ$	kJ	Molar Vol.	7.341 J·bar ⁻¹ 73.41 cm ³

A = -3.338E+02

B = 2.315E-01

C = -4.19E+05

4/1/92

HERZENBERGITE

Formula wt 150.776

Sns: Orthorhombic crystals 298.15 to 875 K; cubic crystals 875 to melting point 1153 K.
Liquid 1153 to 1300 K. Reference state for sulfur is ideal S₂ gas at p = 1 bar.

Temp. K	C _p ^o	S _T ^o	FORMATION FROM THE ELEMENTS				
			(H _T ^o -H ₂₉₈ ^o)/T	-(G _T ^o -H ₂₉₈ ^o)/T	Δ _f H ^o	Δ _f G ^o	Log K _f
			J·mol ⁻¹ ·K ⁻¹		kJ·mol ⁻¹		
298.15	49.25	77.00	0.00	77.00	-170.8	-144.5	25.31
300	49.32	77.30	0.30	77.00	-170.8	-144.3	25.13
400	50.89	91.76	12.81	78.96	-170.2	-135.6	17.71
500	52.03	103.22	20.52	82.70	-169.8	-127.0	13.26
600	54.52	112.91	25.96	86.95	-176.4	-117.1	10.19
700	58.41	121.50	30.30	91.20	-175.4	-107.3	8.00
800	63.50	129.71	34.12	95.59	-173.9	-97.7	6.38
900	54.04	137.47	37.81	99.66	-171.8	-88.1	5.11
1000	57.07	143.32	39.59	103.73	-170.9	-78.9	4.12
1100	60.11	148.90	41.32	107.58	-169.7	-69.7	3.31
1200	75.61	181.98	69.64	112.34	-136.3	-62.0	2.70
1300	75.61	188.03	70.10	117.93	-133.5	-55.9	2.25

Melting T	1153 K	Boiling T	K
Δ _{sub} H ^o	31.59 kJ	Δ _{sub} H ^o	kJ
H ₂₉₈ ^o -H ₀ ^o	kJ	Molar Vol.	2.901 J·bar ⁻¹ 29.01 cm ³

A= -1.696E+02

B= 8.941E-02

C= -1.74E+05

4/1/92

BERNDTITE

Formula wt 182.842

SnS₂: Hexagonal crystals 298.15 to 1000 K. Reference state for sulfur is ideal S₂ gas at p = 1 bar.

Temp. K	C _p ^o	S _T ^o	(H _T ^o -H ₂₉₈ ^o)/T J·mol ⁻¹ ·K ⁻¹	-(G _T ^o -H ₂₉₈ ^o)/T	FORMATION FROM THE ELEMENTS		
					Δ _f H ^o kJ·mol ⁻¹	Δ _f G ^o	Log K _f
298.15	70.12	87.50	0.00	87.50	-278.4	-221.2	38.75
300	70.17	87.93	0.43	87.50	-278.4	-220.8	38.45
400	72.05	108.41	18.13	90.28	-277.4	-201.8	26.35
500	73.52	124.64	29.06	95.58	-276.6	-183.0	19.12
600	75.19	138.19	36.60	101.59	-282.8	-163.1	14.19
700	77.13	149.92	42.25	107.67	-281.6	-143.2	10.69
800	79.33	160.36	46.75	113.61	-280.2	-123.5	8.06
900	81.74	169.84	50.50	119.34	-278.6	-104.0	6.04
1000	84.33	178.59	53.75	124.84	-276.9	-84.7	4.42

Melting T	K	Boiling T	K
Δ _m H ^o	kJ	Δ _{vp} H ^o	kJ
H ₂₉₈ ^o -H ₀ ^o	kJ	Molar Vol.	4.096 J·bar ⁻¹ 40.96 cm ³

A= -2.818E+02

B= 1.973E-01

C= 1.613E+05

4/1/92

TUNGSTENITE

Formula wt 247.982

WS₂: Hexagonal crystals 298.15 to 1500 K. Reference state for sulfur is ideal S₂ gas at p = 1 bar.

Temp. K	C _p ^o	S _T ^o	(H _T ^o -H ₂₉₈ ^o)/T	-(G _T ^o -H ₂₉₈ ^o)/T	FORMATION FROM THE ELEMENTS		
					Δ _f H ^o	Δ _f G ^o	Log K _f
			J·mol ⁻¹ ·K ⁻¹	kJ·mol ⁻¹			
298.15	63.83	67.80	0.00	67.80	-370.2	-312.7	54.77
300	63.99	68.20	0.39	67.80	-370.2	-312.3	54.37
400	69.67	87.50	17.10	70.39	-369.3	-293.1	38.28
500	72.41	103.37	27.92	75.45	-368.1	-274.2	28.65
600	74.01	116.72	35.48	81.25	-366.9	-255.6	22.25
700	75.09	128.22	41.06	87.15	-365.6	-237.1	17.69
800	75.90	138.30	45.37	92.93	-364.4	-218.8	14.29
900	76.57	147.28	48.80	98.48	-363.1	-200.7	11.65
1000	77.16	155.38	51.61	103.77	-361.9	-182.7	9.54
1100	77.71	162.76	53.95	108.80	-360.6	-164.9	7.83
1200	78.24	169.54	55.96	113.58	-359.4	-147.1	6.40
1300	78.76	175.82	57.69	118.13	-358.2	-129.5	5.20
1400	79.29	181.68	59.21	122.47	-357.0	-111.9	4.18
1500	79.83	187.17	60.57	126.60	-355.8	-94.5	3.29

Melting T	K	Boiling T	239.1	K
Δ _m H ^o	kJ	Δ _{vap} H ^o	20.41	kJ
H ₂₉₈ ^o -H ₀ ^o	11.01 kJ	Molar Vol.	3.207	J·bar ⁻¹ 32.07 cm ³

A= -3.610E+02

B= 1.782E-01

C= -4.51E+05

4/1/92

SPHALERITE

Formula wt 97.456

ZnS: Cubic crystals to 1300 K. Wurtzite is the stable form of ZnS above 1300 K.
Reference state for sulfur is ideal S₂ gas at p = 1 bar.

Temp. K	C _p ^o	S _T ^o	(H _T ^o -H ₂₉₈ ^o)/T	-(G _T ^o -H ₂₉₈ ^o)/T	FORMATION FROM THE ELEMENTS		
					Δ _f H ^o	Δ _f G ^o	Log K _f
			J·mol ⁻¹ ·K ⁻¹	kJ·mol ⁻¹			
298.15	45.76	58.70	0.00	58.70	-268.4	-239.5	41.95
300	45.82	58.98	0.28	58.70	-268.4	-239.3	41.66
400	48.30	72.53	12.00	60.53	-267.9	-229.7	29.99
500	49.93	83.50	19.43	64.06	-267.4	-220.2	23.00
600	51.12	92.71	24.62	68.09	-266.9	-210.7	18.35
700	52.04	100.66	28.47	72.19	-273.8	-201.3	15.02
800	52.79	107.66	31.47	76.19	-273.5	-191.0	12.47
900	53.42	113.92	33.87	80.04	-273.2	-180.7	10.49
1000	53.96	119.57	35.85	83.72	-272.8	-170.4	8.90
1100	54.43	124.74	37.52	87.22	-272.4	-160.2	7.61
1200	54.85	129.49	38.95	90.54	-387.1	-148.1	6.45
1300	55.23	133.90	40.19	93.71	-385.6	-128.2	5.15

Melting T	K	Boiling T	K
Δ _{fus} H ^o	kJ	Δ _{vap} H ^o	kJ
H ₂₉₈ ^o -H ₀ ^o	8.82 kJ	Molar Vol.	2.383 J·bar ⁻¹ 23.83 cm ³

A= -2.821E+02

B= 1.131E-01

C= 8.609E+05

WURTZITE

Formula wt 97.456

ZnS: Hexagonal crystals 298.15 to 1300 K. Reference state for sulfur is ideal S₂ gas at p = 1 bar.

Temp. K	C _p ^o	S _T ^o	FORMATION FROM THE ELEMENTS				
			(H _T ^o -H ₂₉₈ ^o)/T	-(G _T ^o -H ₂₉₈ ^o)/T	Δ _f H ^o	Δ _f G ^o	Log K _f
			J·mol ⁻¹ ·K ⁻¹		kJ·mol ⁻¹		
298.15	45.89	58.80	0.00	58.80	-268.1	-239.2	41.91
300	45.96	59.08	0.28	58.80	-268.1	-239.0	41.62
400	48.72	72.74	12.09	60.64	-267.6	-229.4	29.96
500	50.13	83.77	19.57	64.20	-267.1	-219.9	22.97
600	51.09	93.00	24.75	68.25	-266.6	-210.5	18.33
700	51.86	100.94	28.57	72.37	-273.5	-201.2	15.01
800	52.55	107.91	31.52	76.38	-273.2	-190.9	12.46
900	53.21	114.13	33.90	80.24	-272.9	-180.6	10.48
1000	53.86	119.77	35.86	83.91	-272.5	-170.3	8.90
1100	54.50	124.94	37.52	87.41	-272.1	-160.1	7.60
1200	55.15	129.71	38.97	90.74	-386.8	-148.0	6.44
1300	55.80	134.15	40.24	93.91	-385.2	-128.2	5.15

Melting T	K	Boiling T	K
Δ _{fus} H ^o	kJ	Δ _{vap} H ^o	kJ
H ₂₉₈ ^o -H ₀ ^o	8.85 kJ	Molar Vol.	2.385 J·bar ⁻¹ 23.85 cm ³

A= -2.8172E+02

B= 1.1284E-01

C= 8.613E+06

01/06/93

BERTHIERITE

Formula wt 427.611

FeSb_2S_4 : Orthorhombic crystals 298.15 to 836 K. Reference state for sulfur is ideal S_2 gas at $p = 1$ bar.

FORMATION FROM THE ELEMENTS

Temp. K	C_p°	S_T°	$(H_T^\circ - H_{298}^\circ)/T$ $\text{J}\cdot\text{mol}^{-1}\cdot\text{K}^{-1}$	$-(G_T^\circ - H_{298}^\circ)/T$	$\Delta_f H^\circ$ $\text{kJ}\cdot\text{mol}^{-1}$	$\Delta_f G^\circ$	Log K_f
298.15	175.23	245.00	0.00	245.00	-513.4	-415.2	72.75
300	175.60	246.09	1.08	245.00	-513.3	-414.6	72.18
400	186.17	298.40	46.33	252.06	-509.5	-382.2	49.91
500	189.05	340.31	74.64	265.67	-505.8	-350.8	36.65
600	190.44	374.90	93.83	281.07	-502.3	-320.1	27.87
700	191.92	404.37	107.73	296.63	-499.2	-290.0	21.64
800	193.91	430.12	118.37	311.74	-496.6	-260.3	17.00
900	196.48	453.10	126.91	326.20	-494.4	-230.9	13.40

Melting T	K	Boiling T	K
$\Delta_{\text{fus}} H^\circ$	kJ	$\Delta_{\text{vap}} H^\circ$	kJ
$H_{298}^\circ - H_0^\circ$	kJ	Molar Vol.	9.222 $\text{J}\cdot\text{bar}^{-1}$ 92.22 cm^3

A= -4.957E+02

B= 2.954E-01

C= -6.84E+05

CHALCOSTIBITE

Formula wt 249.428

CuSbS₂: Orthorhombic crystals 298.15 to 826 K. Reference state for sulfur is ideal S₂ gas at p = 1 bar.

Temp. K	C _p ^o	S _T ^o	FORMATION FROM THE ELEMENTS				
			(H _T ^o -H ₂₉₈ ^o)/T	-(G _T ^o -H ₂₉₈ ^o)/T	Δ _f H ^o	Δ _f G ^o	Log K _f
			J·mol ⁻¹ ·K ⁻¹		kJ·mol ⁻¹		
298.15	100.15	149.20	0.00	149.20	-259.4	-212.4	37.21
300	100.22	149.82	0.62	149.20	-259.4	-212.1	36.93
400	104.26	179.20	26.02	153.18	-257.5	-196.6	25.68
500	108.30	202.90	42.07	160.83	-255.5	-181.6	18.97
600	112.34	223.01	53.45	169.56	-253.3	-167.0	14.54
700	116.38	240.63	62.15	178.48	-250.9	-152.9	11.41
800	120.42	256.43	69.18	187.25	-248.3	-139.0	9.08
900	124.46	270.85	75.10	195.75	-245.5	-125.5	7.29

Melting T	826 K	Boiling T	K
Δ _{fus} H ^o	kJ	Δ _{vap} H ^o	kJ
H ₂₉₈ ^o -H ₀ ^o	kJ	Molar Vol.	5.006 J·bar ⁻¹ 50.06 cm ³

A= -2.486E+02

B= 1.377E-01

C= -4.38E+05

2/17/93

CORUNDUM

Formula wt 101.961

Al₂O₃: Rhombohedral crystals 298.15 to 1800 K.

Temp. K	C _p ^o	S _T ^o	FORMATION FROM THE ELEMENTS				
			(H _T ^o -H ₂₉₈ ^o)/T	-(G _T ^o -H ₂₉₈ ^o)/T	Δ _f H ^o	Δ _f G ^o	Log K _f
			J·mol ⁻¹ ·K ⁻¹		kJ·mol ⁻¹		
298.15	79.10	50.92	0.00	50.92	-1675.7	-1582.3	277.20
300	79.53	51.41	0.49	50.92	-1675.7	-1581.7	275.39
400	96.45	76.87	22.60	54.28	-1676.3	-1550.2	202.43
500	106.04	99.51	38.40	61.11	-1676.0	-1518.7	158.66
600	112.31	119.43	50.23	69.21	-1675.3	-1487.3	129.48
700	116.79	137.10	59.43	77.67	-1674.4	-1456.1	108.65
800	120.19	152.93	66.82	86.10	-1673.5	-1424.9	93.04
900	122.88	167.24	72.91	94.34	-1672.7	-1393.9	80.90
1000	125.08	180.31	78.02	102.29	-1693.4	-1361.5	71.12
1100	126.93	192.32	82.38	109.93	-1692.3	-1328.3	63.08
1200	128.52	203.43	86.16	117.27	-1691.2	-1295.3	56.38
1300	129.91	213.78	89.48	124.30	-1690.0	-1262.3	50.72
1400	131.13	223.45	92.41	131.04	-1688.8	-1229.5	45.87
1500	132.23	232.53	95.03	137.51	-1687.4	-1196.8	41.67
1600	133.23	241.10	97.39	143.72	-1686.0	-1164.1	38.00
1700	134.14	249.21	99.52	149.68	-1684.5	-1131.5	34.77
1800	134.99	256.90	101.47	155.43	-1683.0	-1099.0	31.89

Melting T	2345 K	Boiling T	K
Δ _{sub} H ^o	kJ	Δ _{vap} H ^o	kJ
H ₂₉₈ ^o -H ₀ ^o	10.016 kJ	Molar Vol.	2.558 J·bar ⁻¹ 25.58 cm ³

A= -1.686E+03

B= 3.257E-01

C= 6.538E+05

BOEHMITE

Formula wt 59.988

AlO(OH): Orthorhombic crystals 298.15 to 600 K.

Temp. K	C_p°	S_T°	FORMATION FROM THE ELEMENTS				
			$(H_T^\circ - H_{298}^\circ)/T$ J·mol ⁻¹ ·K ⁻¹	$-(G_T^\circ - H_{298}^\circ)/T$	$\Delta_f H^\circ$ kJ·mol ⁻¹	$\Delta_f G^\circ$	Log K_f
298.15	54.24	37.20	0.00	37.20	-996.4	-918.4	160.90
300	54.50	37.54	0.34	37.20	-996.4	-917.9	159.82
400	66.40	54.95	15.46	39.49	-997.3	-891.6	116.43
500	74.51	70.70	26.51	44.19	-997.3	-865.2	90.38
600	80.03	84.80	35.00	49.80	-997.0	-838.8	73.02

Melting T	K	Boiling T	K
$\Delta_{fus} H^\circ$	kJ	$\Delta_{vap} H^\circ$	kJ
$H_{298}^\circ - H_0^\circ$	8.83 kJ	Molar Vol.	1.954 J·bar ⁻¹ 19.54 cm ³

A= -9.976E+02

B= 2.646E-01

C= 2.644E+04

8/27/92

DIBORON TRIOXIDE

Formula wt 69.620

B₂O₃: Hexagonal crystals 298.15 to melting point 723 K.

Temp. K	C _p ^o	S _T ^o	(H _T ^o -H ₂₉₈ ^o)/T	-(G _T ^o -H ₂₉₈ ^o)/T	FORMATION FROM THE ELEMENTS		
					Δ _f H ^o	Δ _f G ^o	Log K _f
			J·mol ⁻¹ ·K ⁻¹		kJ·mol ⁻¹		
298.15	62.60	54.00	0.00	54.00	-1273.5	-1194.4	209.24
300	62.93	54.39	0.39	54.00	-1273.5	-1193.9	207.87
400	78.07	74.68	18.02	56.67	-1273.6	-1167.3	152.43
500	89.31	93.37	31.20	62.17	-1273.3	-1140.8	119.17
600	98.08	110.46	41.65	68.81	-1272.6	-1114.3	97.01
700	105.19	126.13	50.23	75.90	-1271.6	-1088.0	81.19
800	129.70	175.88	89.55	86.33	-1244.7	-1064.5	69.50
900	129.70	191.16	94.02	97.14	-1241.6	-1042.1	60.48
1000	129.70	204.83	97.58	107.25	-1238.7	-1020.1	53.28
1100	129.70	217.19	100.51	116.68	-1236.1	-998.4	47.41
1200	129.70	228.47	102.94	125.53	-1233.6	-976.9	42.52
1300	129.70	238.86	105.00	133.86	-1231.3	-955.6	38.39
1400	129.70	248.47	106.76	141.71	-1229.2	-934.5	34.86
1500	129.70	257.42	108.29	149.13	-1227.1	-913.5	31.81
1600	129.70	265.79	109.63	156.16	-1225.2	-892.6	29.14
1700	129.70	273.65	110.81	162.84	-1223.5	-871.9	26.79
1800	129.70	281.06	111.86	169.20	-1221.8	-851.2	24.70

Melting T 723 K

Boiling T K

Δ_{fu}H^o 24.07 kJΔ_{vap}H^o kJH₂₉₈^o-H₀^o 9.30 kJMolar Vol. 2.722 J·bar⁻¹
27.22 cm³

A= -1.240E+03

B= 2.148E-01

C= -2.28E+06

9/9/92

BARIUM MONOXIDE

Formula wt 153.326

BaO: Cubic crystals 298.15 to 1800 K.

Temp. K	C_p°	S_T°	$(H_T^\circ - H_{298}^\circ)/T$ J·mol ⁻¹ ·K ⁻¹	$-(G_T^\circ - H_{298}^\circ)/T$	FORMATION FROM THE ELEMENTS		
					$\Delta_f H^\circ$ kJ·mol ⁻¹	$\Delta_f G^\circ$	Log K_f
298.15	47.28	72.07	0.00	72.07	-548.1	-520.4	91.17
300	47.35	72.36	0.29	72.07	-548.1	-520.2	90.58
400	49.98	86.37	12.41	73.96	-547.7	-511.0	66.73
500	51.78	97.73	20.11	77.62	-548.0	-501.8	52.42
600	53.17	107.30	25.51	81.79	-548.9	-492.5	42.87
700	54.33	115.58	29.55	86.04	-549.0	-483.1	36.05
800	55.36	122.91	32.71	90.20	-549.5	-473.6	30.92
900	56.29	129.48	35.28	94.20	-549.5	-464.1	26.94
1000	57.15	135.46	37.42	98.03	-549.5	-454.6	23.75
1100	57.96	140.94	39.25	101.69	-557.8	-444.3	21.10
1200	58.73	146.02	40.85	105.17	-557.8	-434.0	18.89
1300	59.48	150.75	42.25	108.50	-557.8	-423.7	17.02
1400	60.19	155.18	43.51	111.68	-557.6	-413.4	15.42
1500	60.89	159.36	44.64	114.72	-557.2	-403.1	14.04
1600	61.58	163.31	45.68	117.63	-556.8	-392.9	12.83
1700	62.25	167.07	46.63	120.43	-556.3	-382.6	11.76
1800	62.90	170.64	47.52	123.12	-555.8	-372.4	10.81
Melting T	2286 K				Boiling T	K	
$\Delta_{\text{m}} H^\circ$	kJ				$\Delta_{\text{v}} H^\circ$	kJ	
$H_{298}^\circ - H_0^\circ$	9.98 kJ				Molar Vol.	2.559 J·bar ⁻¹ 25.59 cm ³	
	A= -5.518E+02		B= 9.893E-02		C= 2.781E-01		

8/27/92

BROMELLITE

Formula wt 25.012

BeO: Hexagonal crystals 298.15 to 1800 K.

Temp. K	C_p°	S_T°	$(H_T^\circ - H_{298}^\circ)/T$ J·mol ⁻¹ ·K ⁻¹	$-(G_T^\circ - H_{298}^\circ)/T$	FORMATION FROM THE ELEMENTS		
					$\Delta_f H^\circ$ kJ·mol ⁻¹	$\Delta_f G^\circ$	Log K_f
298.15	25.56	13.77	0.00	13.77	-609.4	-580.1	101.63
300	25.76	13.93	0.16	13.77	-609.4	-579.9	100.97
400	33.93	22.57	7.68	14.89	-609.7	-570.0	74.44
500	38.90	30.71	13.46	17.25	-609.6	-560.1	58.51
600	42.28	38.12	18.00	20.12	-609.4	-550.2	47.90
700	44.73	44.83	21.65	23.18	-609.0	-540.4	40.32
800	46.61	50.93	24.66	26.28	-608.6	-530.6	34.64
900	48.09	56.51	27.18	29.33	-608.2	-520.9	30.23
1000	49.30	61.64	29.33	32.31	-607.7	-511.2	26.70
1100	50.31	66.39	31.20	35.19	-607.3	-501.6	23.82
1200	51.18	70.81	32.83	37.98	-606.9	-492.0	21.41
1300	51.94	74.93	34.27	40.66	-606.6	-482.4	19.38
1400	52.62	78.81	35.55	43.25	-606.3	-472.9	17.64
1500	53.24	82.46	36.71	45.75	-606.0	-463.4	16.14
1600	53.82	85.91	37.77	48.15	-620.3	-453.5	14.80
1700	54.37	89.19	38.73	50.47	-619.7	-443.1	13.61
1800	54.90	92.32	39.61	52.71	-619.1	-432.7	12.56

Melting T	2681 K	Boiling T	K
$\Delta_{\text{m}} H^\circ$	kJ	$\Delta_{\text{vap}} H^\circ$	kJ
$H_{298}^\circ - H_0^\circ$	2.88 kJ	Molar Vol.	0.8309 J·bar ⁻¹ 8.309 cm ³

A= -6.089E+02

B= 9.754E-02

C= -4.08E-02

8/27/92

BISMITE

Formula wt 465.959

Bi₂O₃: Monoclinic crystals 298.15 to melting point 1098 K.

Temp. K	C _p ^o	S _T ^o	(H _T ^o -H ₂₉₈ ^o)/T J·mol ⁻¹ ·K ⁻¹	-(G _T ^o -H ₂₉₈ ^o)/T	FORMATION FROM THE ELEMENTS		
					Δ _f H ^o kJ·mol ⁻¹	Δ _f G ^o	Log K _f
298.15	113.55	151.50	0.00	151.50	-573.9	-493.5	86.45
300	113.61	152.20	0.70	151.50	-573.9	-493.0	85.83
400	116.94	185.34	29.34	156.00	-572.0	-466.3	60.89
500	120.28	211.80	47.20	164.60	-570.2	-440.1	45.98
600	123.62	234.02	59.66	174.36	-591.3	-411.9	35.86
700	126.95	253.33	69.03	184.30	-589.5	-382.2	28.52
800	130.29	270.50	76.48	194.02	-587.3	-352.7	23.03
900	133.62	286.03	82.64	203.39	-584.7	-323.5	18.78
1000	136.96	300.29	87.91	212.38	-581.9	-294.7	15.39

Melting T	1098 K	Boiling T	K
Δ _m H ^o	kJ	Δ _{vp} H ^o	kJ
H ₂₉₈ ^o -H ₀ ^o	kJ	Molar Vol.	4.973 J·bar ⁻¹ 49.73 cm ³

A= -5.909E+02

B= 2.957E-01

C= 8.426E+05

8/27/92

CARBON MONOXIDE

Formula wt 28.010

CO: Ideal gas at p = 1 bar, 298.15 to 2200 K.

Temp. K	C_p°	S_T°	$(H_T^\circ - H_{298}^\circ)/T$ J·mol ⁻¹ ·K ⁻¹	$-(G_T^\circ - H_{298}^\circ)/T$	FORMATION FROM THE ELEMENTS		
					$\Delta_f H^\circ$ kJ·mol ⁻¹	$\Delta_f G^\circ$	Log K_f
298.15	29.14	197.27	0.00	197.27	-110.5	-137.1	24.01
300	29.13	197.45	0.18	197.27	-110.5	-137.2	23.89
400	29.15	205.80	7.39	198.41	-110.1	-146.2	19.09
500	29.79	212.37	11.81	200.57	-110.0	-155.2	16.22
600	30.55	217.87	14.87	203.00	-110.2	-164.2	14.30
700	31.29	222.64	17.16	205.48	-110.5	-173.2	12.93
800	31.97	226.86	18.97	207.89	-110.9	-182.2	11.89
900	32.58	230.66	20.45	210.21	-111.4	-191.0	11.09
1000	33.14	234.12	21.69	212.43	-112.0	-199.9	10.44
1100	33.64	237.31	22.75	214.55	-112.6	-208.6	9.91
1200	34.09	240.25	23.68	216.57	-113.2	-217.3	9.46
1300	34.50	243.00	24.50	218.50	-113.9	-226.0	9.08
1400	34.86	245.57	25.22	220.34	-114.6	-234.6	8.75
1500	35.18	247.98	25.88	222.11	-115.3	-243.1	8.47
1600	35.47	250.26	26.47	223.80	-116.0	-251.6	8.21
1700	35.72	252.42	27.01	225.42	-116.7	-260.1	7.99
1800	35.94	254.47	27.50	226.97	-117.4	-268.5	7.79
Melting T	68.05 K				Boiling T		K
$\Delta_{\text{sub}} H^\circ$	0.837 kJ				$\Delta_{\text{vap}} H^\circ$		kJ
$H_{298}^\circ - H_0^\circ$	8.67 kJ				Molar Vol.	2478.97 J·bar ⁻¹	24789.7 cm ³
	A= -1.131E+02		B= -8.667E-02		C= 1.858E+05		

4/4/92

CARBON DIOXIDE

Formula wt 44.010

CO₂: Ideal gas at p = 1 bar, 298.15 to 2200 K.

Temp. K	C _p ^o	S _T ^o	(H _T ^o -H ₂₉₈ ^o)/T	-(G _T ^o -H ₂₉₈ ^o)/T	FORMATION FROM THE ELEMENTS		
					Δ _f H ^o	Δ _f G ^o	Log K _f
			J·mol ⁻¹ ·K ⁻¹	kJ·mol ⁻¹			
298.15	37.12	213.79	0.00	213.79	-393.5	-394.4	69.09
300	37.20	214.02	0.23	213.79	-393.5	-394.4	68.67
400	41.20	225.28	9.98	215.30	-393.6	-394.7	51.54
500	44.62	234.85	16.58	218.28	-393.7	-394.9	41.26
600	47.39	243.24	21.49	221.75	-393.8	-395.2	34.40
700	49.64	250.72	25.36	225.37	-394.0	-395.4	29.50
800	51.48	257.47	28.51	228.96	-394.2	-395.6	25.83
900	53.01	263.63	31.15	232.48	-394.4	-395.7	22.97
1000	54.29	269.28	33.40	235.88	-394.6	-395.9	20.68
1100	55.38	274.51	35.35	239.16	-394.8	-396.0	18.80
1200	56.31	279.37	37.06	242.31	-395.0	-396.1	17.24
1300	57.10	283.90	38.57	245.34	-395.2	-396.1	15.92
1400	57.79	288.16	39.92	248.25	-395.5	-396.2	14.78
1500	58.38	292.17	41.13	251.04	-395.7	-396.3	13.80
1600	58.90	295.95	42.23	253.73	-395.9	-396.3	12.94
1700	59.35	299.54	43.22	256.32	-396.1	-396.3	12.18
1800	59.74	302.94	44.13	258.82	-396.3	-396.3	11.50

Melting T

K

Boiling T

K

Δ_{sub}H^o

kJ

Δ_{sub}H^o

kJ

H₂₉₈^o-H₀^o

9.36 kJ

Molar Vol. 2478.97 J·bar⁻¹
24789.7 cm³

A= -3.944E+02

B= -1.248E-03

C= 5.480E-02

12/17/91

LIME

Formula wt 56.077

CaO: Cubic crystals 298.15 to 1800 K.

Temp. K	C_p^o	S_T^o	$(H_T^o - H_{298}^o)/T$	$-(G_T^o - H_{298}^o)/T$	FORMATION FROM THE ELEMENTS		
					$\Delta_f H^o$	$\Delta_f G^o$	Log K_f
			$J \cdot mol^{-1} \cdot K^{-1}$		$kJ \cdot mol^{-1}$		
298.15	42.07	38.10	0.00	38.10	-635.1	-603.1	105.66
300	42.21	38.36	0.26	38.10	-635.1	-602.9	104.97
400	46.99	51.25	11.43	39.83	-634.7	-592.2	77.33
500	49.34	62.01	18.80	43.22	-634.2	-581.6	60.76
600	50.72	71.14	24.01	47.13	-633.7	-571.2	49.72
700	51.65	79.03	27.90	51.14	-633.4	-560.8	41.84
800	52.35	85.98	30.91	55.07	-634.0	-550.3	35.93
900	52.90	92.18	33.32	58.85	-634.0	-539.9	31.33
1000	53.36	97.78	35.31	62.47	-634.2	-529.4	27.65
1100	53.77	102.88	36.97	65.91	-634.7	-518.9	24.64
1200	54.13	107.58	38.38	69.19	-643.3	-507.7	22.10
1300	54.47	111.92	39.61	72.32	-643.1	-496.4	19.95
1400	54.80	115.97	40.68	75.29	-643.0	-485.1	18.10
1500	55.10	119.76	41.63	78.13	-642.8	-473.8	16.50
1600	55.40	123.33	42.48	80.84	-642.6	-462.6	15.10
1700	55.68	126.69	43.25	83.44	-642.4	-451.3	13.87
1800	55.96	129.88	43.95	85.94	-790.9	-437.9	12.71

Melting T	3200 K	Boiling T	K
$\Delta_{fus} H^o$	kJ	$\Delta_{vap} H^o$	kJ
$H_{298}^o - H_0^o$	6.75 kJ	Molar Vol.	1.676 $J \cdot bar^{-1}$ 16.76 cm^3

A= -6.395E+02

B= 1.105E-01

C= 3.497E+05

8/27/92

PORTLANDITE

Formula wt 74.093

Ca(OH)₂: Hexagonal crystals 298.15 to 700 K.

Temp. K	C _p ^o	S _T ^o	(H _T ^o -H ₂₉₈ ^o)/T	-(G _T ^o -H ₂₉₈ ^o)/T	FORMATION FROM THE ELEMENTS		
					Δ _f H ^o	Δ _f G ^o	Log K _f
			J·mol ⁻¹ ·K ⁻¹	kJ·mol ⁻¹			
298.15	87.51	83.40	0.00	83.40	-986.1	-898.0	157.33
300	87.75	83.94	0.54	83.40	-986.1	-897.5	156.27
400	97.94	110.71	23.73	86.98	-985.3	-868.1	113.36
500	104.19	133.29	39.24	94.05	-983.9	-838.9	87.64
600	108.23	152.67	50.43	102.24	-982.3	-810.1	70.52
700	110.89	169.57	58.89	110.68	-980.7	-781.5	58.32

Melting T	K	Boiling T	K
Δ _{fus} H ^o	kJ	Δ _{vap} H ^o	kJ
H ₂₉₈ ^o -H ₀ ^o	14.16 kJ	Molar Vol.	3.306 J·bar ⁻¹ 33.06 cm ³

A= -9.810E+02

B= 2.857E-01

C= -1.98E+05

4/8/92

CERIANITE

Formula wt 172.114

CeO₂: Cubic crystals 298.15 to 1800 K.

Temp. K	C _p ^o	S _T ^o	(H _T ^o -H ₂₉₈ ^o)/T J·mol ⁻¹ ·K ⁻¹	-(G _T ^o -H ₂₉₈ ^o)/T	FORMATION FROM THE ELEMENTS		
					Δ _f H ^o kJ·mol ⁻¹	Δ _f G ^o	Log K _f
298.15	61.63	62.30	0.00	62.30	-1088.7	-1024.6	179.51
300	61.78	62.68	0.38	62.30	-1088.7	-1024.2	178.33
400	67.52	81.33	16.52	64.80	-1087.9	-1002.9	130.96
500	70.83	96.78	27.08	69.70	-1086.9	-981.7	102.56
600	73.11	109.91	34.57	75.33	-1085.9	-960.7	83.64
700	74.86	121.31	40.21	81.11	-1085.0	-940.0	70.14
800	76.29	131.40	44.63	86.77	-1084.1	-919.3	60.02
900	77.52	140.46	48.22	92.25	-1083.4	-898.7	52.16
1000	78.62	148.69	51.20	97.48	-1085.7	-878.3	45.87
1100	79.63	156.23	53.74	102.49	-1090.5	-857.4	40.71
1200	80.56	163.20	55.94	107.26	-1089.8	-836.2	36.40
1300	81.45	169.68	57.87	111.81	-1089.1	-815.2	32.75
1400	82.29	175.75	59.58	116.17	-1088.3	-794.1	29.63
1500	83.09	181.45	61.12	120.33	-1087.4	-773.1	26.92
1600	83.88	186.84	62.52	124.32	-1086.5	-752.2	24.56
1700	84.64	191.95	63.80	128.15	-1085.6	-731.3	22.47
1800	85.38	196.81	64.98	131.83	-1084.5	-710.5	20.62

Melting T	K	Boiling T	K
Δ _{lv} H ^o	kJ	Δ _{vap} H ^o	kJ
H ₂₉₈ ^o -H ₀ ^o	10.37 kJ	Molar Vol.	2.385 J·bar ⁻¹ 23.85 cm ³

A= -1.0865E+03	B= 2.088E-01	C= -5.536E-02
----------------	--------------	---------------

8/27/92

COBALT MONOXIDE

Formula wt 74.933

CoO: Cubic crystals 298.15 to 1800 K.

Temp. K	C_p°	S_T°	$(H_T^\circ - H_{298}^\circ)/T$	$-(G_T^\circ - H_{298}^\circ)/T$	FORMATION FROM THE ELEMENTS		
					$\Delta_f H^\circ$	$\Delta_f G^\circ$	Log K_f
			$J \cdot mol^{-1} \cdot K^{-1}$		$kJ \cdot mol^{-1}$		
298.15	43.34	52.83	0.00	52.83	-237.9	-214.1	37.51
300	43.62	53.10	0.27	52.83	-237.9	-214.0	37.25
400	51.88	67.04	12.37	54.68	-237.1	-206.1	26.91
500	54.00	78.90	20.53	58.37	-236.0	-198.5	20.73
600	54.51	88.80	26.16	62.64	-235.1	-191.0	16.63
700	54.67	97.22	30.22	66.99	-234.3	-183.8	13.71
800	54.90	104.53	33.29	71.24	-234.1	-176.5	11.53
900	55.30	111.02	35.71	75.30	-233.6	-169.4	9.83
1000	55.92	116.87	37.70	79.17	-233.4	-162.3	8.48
1100	56.75	122.24	39.39	82.85	-233.3	-155.2	7.37
1200	57.76	127.22	40.88	86.34	-233.5	-148.0	6.44
1300	58.95	131.89	42.22	89.67	-234.1	-140.9	5.66
1400	60.28	136.30	43.46	92.84	-235.1	-133.8	4.99
1500	61.75	140.51	44.63	95.88	-234.9	-126.6	4.41
1600	63.34	144.55	45.75	98.80	-234.4	-119.4	3.90
1700	65.03	148.44	46.84	101.60	-233.6	-112.2	3.45
1800	66.81	152.21	47.90	104.31	-249.0	-104.6	3.04

Melting T	2078 K	Boiling T	K
$\Delta_{\text{sub}} H^\circ$	kJ	$\Delta_{\text{vap}} H^\circ$	kJ
$H_{298}^\circ - H_0^\circ$	9.45 kJ	Molar Vol.	1.164 J·bar ⁻¹ 11.64 cm ³

A= -2.336E+02

B= 7.152E-02

C= -1.63E+05

9/9/92

TRICOBALT TETROXIDE

Formula wt 240.797

Co₃O₄: Cubic crystals 298.15 to 1000 K.

Temp. K	C _p ^o	S _T ^o	(H _T ^o -H ₂₉₈ ^o)/T	-(G _T ^o -H ₂₉₈ ^o)/T	FORMATION FROM THE ELEMENTS		
					Δ _f H ^o	Δ _f G ^o	Log K _f
			J·mol ⁻¹ ·K ⁻¹	kJ·mol ⁻¹			
298.15	123.39	109.30	0.00	109.30	-918.8	-802.2	140.54
300	123.85	110.06	0.76	109.30	-918.8	-801.5	139.54
400	142.51	148.50	34.08	114.42	-919.0	-762.3	99.54
500	154.69	181.68	57.05	124.63	-918.5	-723.1	75.54
600	164.32	210.76	74.15	136.61	-917.5	-684.1	59.56
700	172.75	236.73	87.64	149.09	-916.3	-645.4	48.16
800	180.54	260.31	98.77	161.54	-916.2	-606.5	39.60
900	187.96	282.01	108.27	173.74	-914.6	-567.9	32.96
1000	195.14	302.18	116.60	185.58	-913.1	-529.5	27.66

Melting T	K	Boiling T	K
Δ _{liq} H ^o	kJ	Δ _{vap} H ^o	kJ
H ₂₉₈ ^o -H ₀ ^o	18.13 kJ	Molar Vol.	3.977 J·bar ⁻¹ 39.77 cm ³

A= -9.157E+02

B= 3.866E-01

C= -1.61E+05

9/9/92

ESKOLAITE

Formula wt 151.990

Cr₂O₃: Rhombohedral crystals 298.15 to 1800 K.

Temp. K	C _p ^o	S _T ^o	(H _T ^o -H ₂₉₈ ^o)/T J·mol ⁻¹ ·K ⁻¹	-(G _T ^o -H ₂₉₈ ^o)/T	FORMATION FROM THE ELEMENTS		
					Δ _f H ^o kJ·mol ⁻¹	Δ _f G ^o	Log K _f
298.15	105.41	81.20	0.00	81.20	-1134.7	-1053.1	184.49
300	105.63	81.85	0.65	81.20	-1134.7	-1052.6	183.26
400	113.62	113.48	28.02	85.46	-1133.1	-1025.4	133.90
500	117.83	139.32	45.60	93.73	-1131.3	-998.7	104.33
600	120.55	161.06	57.87	103.19	-1129.5	-972.4	84.65
700	122.58	179.80	66.98	112.82	-1127.8	-946.3	70.62
800	124.22	196.28	74.03	122.25	-1126.2	-920.5	60.10
900	125.65	211.00	79.69	131.31	-1124.8	-894.9	51.94
1000	126.95	224.30	84.35	139.95	-1123.7	-869.4	45.41
1100	128.15	236.46	88.28	148.18	-1122.7	-844.1	40.08
1200	129.30	247.66	91.65	156.01	-1122.1	-818.7	35.64
1300	130.40	258.05	94.59	163.46	-1121.7	-793.5	31.88
1400	131.47	267.76	97.19	170.57	-1121.7	-768.2	28.66
1500	132.52	276.86	99.51	177.36	-1122.0	-743.0	25.87
1600	133.55	285.45	101.60	183.85	-1122.6	-717.7	23.43
1700	134.56	293.58	103.51	190.06	-1123.6	-692.4	21.27
1800	135.57	301.29	105.26	196.03	-1125.0	-666.9	19.35

Melting T	2603 K	Boiling T	K
Δ _{fus} H ^o	kJ	Δ _{vap} H ^o	kJ
H ₂₉₈ ^o -H ₀ ^o	9.45 kJ	Molar Vol.	2.909 J·bar ⁻¹ 29.09 cm ³

A= -1.1225E+03

B= 2.533E-01

C= -5.635E-01

10/1/92

TENORITE

Formula wt 79.545

CuO: Monoclinic crystals 298.15 to 1400 K.

Temp. K	C_p°	S_T°	$(H_T^\circ - H_{298}^\circ)/T$ J·mol ⁻¹ ·K ⁻¹	$-(G_T^\circ - H_{298}^\circ)/T$	FORMATION FROM THE ELEMENTS		
					$\Delta_f H^\circ$ kJ·mol ⁻¹	$\Delta_f G^\circ$	Log K_f
298.15	42.30	42.60	0.00	42.60	-156.1	-128.3	22.48
300	42.44	42.86	0.26	42.60	-156.1	-128.2	22.32
400	47.07	55.80	11.47	44.33	-155.6	-118.9	15.53
500	49.32	66.57	18.83	47.74	-154.8	-109.9	11.48
600	50.80	75.70	24.04	51.65	-154.0	-100.9	8.79
700	51.98	83.62	27.95	55.67	-153.2	-92.2	6.88
800	53.05	90.63	31.02	59.61	-152.3	-83.5	5.45
900	54.09	96.94	33.53	63.41	-151.4	-74.9	4.35
1000	55.13	102.69	35.64	67.06	-150.5	-66.5	3.47
1100	56.18	108.00	37.46	70.54	-149.6	-58.1	2.76
1200	57.25	112.93	39.06	73.87	-148.7	-49.9	2.17
1300	58.33	117.56	40.50	77.05	-147.9	-41.7	1.67
1400	59.43	121.92	41.81	80.10	-160.2	-33.1	1.23

Melting T	K	Boiling T	K
$\Delta_{\text{m}} H^\circ$	kJ	$\Delta_{\text{vap}} H^\circ$	kJ
$H_{298}^\circ - H_0^\circ$	7.10 kJ	Molar Vol.	1.222 J·bar ⁻¹ 12.22 cm ³

A= -1.506E+02

B= 8.412E-02

C= -2.64E+05

CUPRITE

Formula wt 143.091

Cu₂O: Cubic crystals 298.15 to 1509 K.

Temp. K	C _p ^o	S _T ^o	(H _T ^o -H ₂₉₈ ^o)/T	-(G _T ^o -H ₂₉₈ ^o)/T	FORMATION FROM THE ELEMENTS		
					Δ _f H ^o	Δ _f G ^o	Log K _f
			J·mol ⁻¹ ·K ⁻¹		kJ·mol ⁻¹		
298.15	62.54	92.40	0.00	92.40	-170.6	-147.8	25.89
300	62.59	92.79	0.39	92.40	-170.6	-147.7	25.71
400	67.18	111.37	16.47	94.90	-170.6	-140.0	18.28
500	71.49	126.85	27.07	99.79	-170.3	-132.4	13.83
600	74.27	140.16	34.72	105.43	-169.8	-124.9	10.87
700	76.00	151.74	40.50	111.24	-169.3	-117.4	8.76
800	77.28	161.98	45.02	116.95	-168.7	-110.0	7.18
900	78.60	171.15	48.68	122.48	-168.2	-102.7	5.96
1000	80.33	179.52	51.75	127.77	-167.6	-95.5	4.99
1100	82.76	187.29	54.46	132.83	-167.0	-88.3	4.19
1200	86.10	194.62	56.95	137.68	-166.4	-81.2	3.53
1300	90.51	201.68	59.35	142.33	-165.6	-74.1	2.98
1400	96.12	208.59	61.77	146.82	-191.0	-66.2	2.47
1500	103.03	215.45	64.28	151.16	-189.4	-57.4	2.00

Melting T	1509 K	Boiling T	K
Δ _{fm} H ^o	kJ	Δ _{vp} H ^o	kJ
H ₂₉₈ ^o -H ₀ ^o	kJ	Molar Vol.	2.344 J·bar ⁻¹ 23.44 cm ³

A= -1.690E+02

B= 7.367E-02

C= -6.26E+04

8/26/92

WUSTITE

Formula wt 68.887

Fe_{0.947}O: Rhombohedral crystals 298.15 to melting point 1652 K.

Temp. K	C _p ^o	S _T ^o	(H _T ^o -H ₂₉₈ ^o)/T	-(G _T ^o -H ₂₉₈ ^o)/T	FORMATION FROM THE ELEMENTS		
					Δ _f H ^o	Δ _f G ^o	Log K _f
			J·mol ⁻¹ ·K ⁻¹	kJ·mol ⁻¹			
298.15	48.13	56.60	0.00	56.60	-266.3	-244.9	42.91
300	48.27	56.90	0.30	56.60	-266.3	-244.8	42.62
400	51.99	71.43	12.87	58.56	-265.2	-237.8	31.05
500	52.78	83.13	20.79	62.34	-264.2	-231.1	24.14
600	53.04	92.78	26.15	66.64	-263.4	-224.6	19.55
700	53.38	100.98	30.01	70.97	-262.8	-218.1	16.28
800	53.95	108.14	32.97	75.18	-262.6	-211.8	13.83
900	54.76	114.54	35.34	79.20	-262.7	-205.4	11.92
1000	55.80	120.36	37.33	83.03	-263.4	-199.0	10.40
1100	57.05	125.74	39.07	86.67	-264.9	-192.5	9.14
1200	58.48	130.76	40.62	90.14	-265.6	-185.9	8.09
1300	60.05	135.51	42.06	93.45	-264.7	-179.3	7.20
1400	61.76	140.02	43.40	96.62	-263.7	-172.8	6.45
1500	63.58	144.34	44.69	99.65	-262.7	-166.3	5.79
1600	65.51	148.50	45.93	102.58	-261.6	-159.9	5.22
Melting T	1652 K			Boiling T	K		
Δ _{lv} H ^o	kJ			Δ _{lv} H ^o	kJ		
H ₂₉₈ ^o -H ₀ ^o	kJ			Molar Vol.	1.204 J·bar ⁻¹ 12.04 cm ³		
A= -2.632E+02		B= 6.455E-02		C= -8.06E+04			

2/5/93

FERROUS OXIDE (Fictive)

Formula wt 71.846

FeO: Cubic crystals 298.15 to 1800 K.

Temp. K	C_p°	S_T°	$(H_T^\circ - H_{298}^\circ)/T$ J·mol ⁻¹ ·K ⁻¹	$-(G_T^\circ - H_{298}^\circ)/T$	FORMATION FROM THE ELEMENTS		
					$\Delta_f H^\circ$ kJ·mol ⁻¹	$\Delta_f G^\circ$	Log K_f
298.15	47.68	60.60	0.00	60.60	-272.0	-251.4	44.05
300	47.75	60.90	0.29	60.60	-272.0	-251.3	43.75
400	50.26	75.03	12.52	62.51	-271.2	-244.5	31.93
500	51.47	86.39	20.20	66.19	-270.5	-237.9	24.85
600	52.26	95.84	25.48	70.36	-269.9	-231.5	20.15
700	52.91	103.95	29.35	74.60	-269.6	-225.1	16.79
800	53.51	111.05	32.33	78.72	-269.6	-218.7	14.28
900	54.11	117.39	34.72	82.67	-270.0	-212.3	12.32
1000	54.72	123.12	36.69	86.43	-271.0	-205.9	10.75
1100	55.34	128.37	38.36	90.01	-273.0	-199.3	9.46
1200	55.98	133.21	39.80	93.41	-274.1	-192.5	8.38
1300	56.63	137.72	41.07	96.65	-273.7	-185.7	7.46
1400	57.30	141.94	42.20	99.73	-273.3	-179.0	6.68
1500	57.98	145.91	43.23	102.68	-273.0	-172.3	6.00
1600	58.68	149.68	44.18	105.50	-272.7	-165.6	5.40
1700	59.38	153.26	45.05	108.21	-273.4	-158.8	4.88
1800	60.10	156.67	45.87	110.81	-273.6	-152.1	4.41

Melting T	K	Boiling T	K
$\Delta_{\text{fus}} H^\circ$	kJ	$\Delta_{\text{vap}} H^\circ$	kJ
$H_{298}^\circ - H_0^\circ$	kJ	Molar Vol.	1.200 J·bar ⁻¹ 12.00 cm ³

A= -2.719E+02

B= 6.634E-02

C= 7.599E+04

2/24/94

HEMATITE

Formula wt 159.692

Fe₂O₃: Rhombohedral crystal 298.15 to Neél temperature 950 K. Hexagonal crystals 950 to 1800 K.

Temp. K	C _p ^o	S _T ^o	(H _T ^o -H ₂₉₈ ^o)/T J·mol ⁻¹ ·K ⁻¹	-(G _T ^o -H ₂₉₈ ^o)/T	FORMATION FROM THE ELEMENTS		
					Δ _f H ^o kJ·mol ⁻¹	Δ _f G ^o	Log K _f
298.15	104.05	87.40	0.00	87.40	-826.2	-744.4	130.41
300	104.32	88.04	0.64	87.40	-826.2	-743.9	129.51
400	120.29	120.27	28.59	91.68	-824.6	-716.6	93.58
500	131.72	148.44	48.16	100.28	-822.3	-689.9	72.07
600	139.33	173.16	62.75	110.41	-819.6	-663.6	57.77
700	146.52	195.17	74.19	120.98	-816.9	-637.8	47.59
800	156.12	215.32	83.79	131.53	-814.0	-612.4	39.99
900	170.22	234.47	92.57	141.90	-810.9	-587.4	34.09
950	179.45	243.91	96.89	147.03	-809.3	-575.3	31.65
950	151.69	244.58	97.54	147.03	-807.9	-575.3	31.65
1000	148.49	252.27	100.16	152.11	-808.9	-562.8	29.40
1100	143.55	266.18	104.32	161.86	-810.8	-538.0	25.55
1200	140.74	278.53	107.45	171.08	-811.9	-513.2	22.34
1300	140.07	289.76	109.98	179.78	-810.1	-488.4	19.62
1400	141.42	300.18	112.16	188.02	-808.5	-463.8	17.30
1500	144.64	310.03	114.21	195.82	-806.9	-439.2	15.29
1600	149.58	319.52	116.26	203.26	-805.2	-414.7	13.54
1700	156.06	328.77	118.40	210.37	-804.9	-390.3	11.99
1800	163.95	337.91	120.71	217.20	-803.1	-366.0	10.62
Melting T	1895 K				Boiling T	K	
Δ _{fm} H ^o					Δ _{vp} H ^o	kJ	
H ₂₉₈ ^o -H ₀ ^o	65.10 kJ				Molar Vol.	3.027 J·bar ⁻¹ 30.27 cm ³	
A=	-8.089E+02	B=	2.466E-01	C=	-8.423E+05		

9/9/92

MAGNETITE

Formula wt 231.539

Fe_3O_4 : Cubic (ferrimagnetic) crystals 298.15 to Neél temperature 845.5 K. Cubic crystals (paramagnetic) 845.5 to 1800 K.

Temp. K	C_p°	S_T°	$(H_T^\circ - H_{298}^\circ)/T$ J·mol ⁻¹ ·K ⁻¹	$-(G_T^\circ - H_{298}^\circ)/T$	FORMATION FROM THE ELEMENTS		
					$\Delta_f H^\circ$ kJ·mol ⁻¹	$\Delta_f G^\circ$	Log K_f
298.15	150.90	146.14	0.00	146.14	-1115.7	-1012.7	177.42
300	151.40	147.07	0.93	146.14	-1114.6	-1012.1	176.21
400	176.18	194.21	41.81	152.40	-1113.0	-977.9	127.70
500	192.90	235.43	70.45	164.98	-1109.2	-944.5	98.67
600	207.91	271.89	92.08	179.81	-1104.8	-912.0	79.40
700	228.68	305.38	110.00	195.38	-1099.5	-880.3	65.69
800	260.76	337.86	126.70	211.16	-1092.7	-849.4	55.46
845.5	330.50	354.00	135.66	218.34	-1087.8	-835.3	51.60
900	213.93	369.13	142.05	227.08	-1085.1	-819.5	47.56
1000	205.97	391.22	148.81	242.41	-1085.5	-790.0	41.27
1100	201.45	410.62	153.78	256.84	-1089.1	-760.3	36.10
1200	199.28	428.04	157.65	270.39	-1091.0	-730.4	31.79
1300	198.76	443.96	160.82	283.14	-1088.6	-700.4	28.14
1400	199.43	458.71	163.55	295.16	-1086.5	-670.6	25.02
1500	201.00	472.52	165.99	306.53	-1084.6	-641.0	22.32
1600	203.23	485.56	168.24	317.32	-1082.9	-611.5	19.96
1700	205.99	497.96	170.38	327.58	-1084.1	-582.0	17.88
1800	209.15	509.82	172.45	337.37	-1083.7	-552.4	16.03

Melting T 1870 K

Boiling T K

 $\Delta_{\text{fus}} H^\circ$ kJ $\Delta_{\text{vap}} H^\circ$ kJ $H_{298}^\circ - H_0^\circ$ 102.80 kJMolar Vol. 4.452 J·bar⁻¹
44.52 cm³

A= -1.086E+03

B= 2.969E-01

c+ -1.437E+06

9/9/92

STEAM

Formula wt 18.015

H₂O: Ideal gas at p = 1 bar, 298.15 to 2500 K.

Temp. K	C _p ^o	S _T ^o	(H _T ^o -H ₂₉₈ ^o)/T	-(G _T ^o -H ₂₉₈ ^o)/T	FORMATION FROM THE ELEMENTS		
					Δ _f H ^o	Δ _f G ^o	Log K _f
			J·mol ⁻¹ ·K ⁻¹	kJ·mol ⁻¹			
298.15	33.59	188.84	0.00	188.84	-241.8	-228.6	40.05
300	33.59	189.05	0.21	188.84	-241.8	-228.5	39.79
400	34.04	198.75	8.59	190.16	-242.9	-223.9	29.24
500	35.09	206.45	13.78	192.67	-243.9	-219.0	22.88
600	36.34	212.96	17.43	195.52	-244.8	-214.0	18.63
700	37.66	218.66	20.23	198.43	-245.7	-208.8	15.58
800	38.97	223.77	22.49	201.28	-246.5	-203.5	13.28
900	40.27	228.44	24.39	204.05	-247.2	-198.0	11.49
1000	41.53	232.75	26.04	206.70	-247.8	-192.6	10.06
1100	42.76	236.76	27.51	209.26	-248.4	-187.0	8.88
1200	43.94	240.53	28.83	211.71	-248.9	-181.4	7.90
1300	45.07	244.10	30.03	214.06	-249.4	-175.7	7.06
1400	46.15	247.48	31.15	216.33	-249.8	-170.1	6.35
1500	47.19	250.70	32.18	218.51	-250.2	-164.4	5.72
1600	48.18	253.77	33.15	220.62	-250.5	-158.6	5.18
1700	49.12	256.72	34.06	222.66	-250.7	-152.9	4.70
1800	50.01	259.56	34.93	224.63	-251.0	-147.1	4.27

Melting T

K

Boiling T

K

Δ_{fm}H^o

kJ

Δ_{vap}H^o

kJ

H₂₉₈^o-H₀^o

kJ

Molar Vol. 2478.97 J·bar⁻¹
24789.7 cm³

A= -2.4896E+02

B= 5.632E-02

C= 3.354E+05

8/26/92

DIPOTASSIUM MONOXIDE

Formula wt 94.196

K₂O: Cubic crystals 298.15 to 1200 K.

Temp. K	C _p ^o	S _T ^o	FORMATION FROM THE ELEMENTS				
			(H _T ^o -H ₂₉₈ ^o)/T	-(G _T ^o -H ₂₉₈ ^o)/T	Δ _f H ^o	Δ _f G ^o	Log K _f
			J·mol ⁻¹ ·K ⁻¹		kJ·mol ⁻¹		
298.15	83.68	94.10	0.00	94.10	-363.2	-322.1	56.43
300	83.79	94.62	0.52	94.10	-363.2	-321.9	56.04
400	88.89	119.45	21.99	97.45	-367.0	-307.3	40.13
500	93.39	139.77	35.83	103.94	-365.6	-292.6	30.56
600	97.64	157.17	45.78	111.40	-363.7	-278.1	24.21
700	101.78	172.54	53.48	119.05	-361.4	-264.0	19.70
800	105.85	186.39	59.77	126.62	-358.6	-250.3	16.34
900	109.90	199.10	65.12	133.98	-355.5	-237.0	13.75
1000	113.92	210.88	69.80	141.08	-352.0	-224.0	11.70
1100	117.92	221.93	73.99	147.94	-506.2	-202.1	9.60
1200	121.92	232.36	77.82	154.54	-500.2	-174.7	7.61

Melting T	K	Boiling T	K
Δ _{sub} H ^o	kJ	Δ _{sub} H ^o	kJ
H ₂₉₈ ^o -H ₀ ^o	kJ	Molar Vol.	4.038 J·bar ⁻¹ 40.38 cm ³

A= -3.816E+02

B= 1.640E-01

C= 1.032E+06

5/20/93

DILITHIUM MONOXIDE

Formula wt 29.881

Li₂O: Cubic crystals 298.15 to melting point 1700 K.

Temp. K	C _p ^o	S _T ^o	(H _T ^o -H ₂₉₈ ^o)/T	-(G _T ^o -H ₂₉₈ ^o)/T	FORMATION FROM THE ELEMENTS		
					Δ _f H ^o	Δ _f G ^o	Log K _f
			J·mol ⁻¹ ·K ⁻¹		kJ·mol ⁻¹		
298.15	54.10	37.60	0.00	37.60	-597.9	-561.2	98.31
300	54.33	37.94	0.33	37.60	-597.9	-561.0	97.67
400	63.61	54.96	15.10	39.86	-598.7	-548.5	71.63
500	69.52	69.83	25.43	44.40	-605.4	-535.3	55.92
600	73.98	82.91	33.16	49.75	-605.7	-521.2	45.38
700	77.67	94.60	39.26	55.34	-605.6	-507.1	37.84
800	80.87	105.19	44.27	60.92	-605.2	-493.1	32.20
900	83.72	114.88	48.50	66.38	-604.4	-479.1	27.81
1000	86.29	123.83	52.15	71.68	-603.4	-465.3	24.30
1100	88.63	132.17	55.36	76.81	-602.2	-451.5	21.44
1200	90.76	139.98	58.22	81.75	-600.7	-437.9	19.06
1300	92.70	147.32	60.80	86.51	-599.1	-424.4	17.05
1400	94.46	154.25	63.15	91.11	-597.3	-411.0	15.33
1500	96.05	160.83	65.29	95.54	-595.3	-397.7	13.85
1600	97.47	167.07	67.25	99.82	-593.2	-384.6	12.56
1700	98.72	173.02	69.07	103.95	-881.4	-357.3	10.98
Melting T	1700 K				Boiling T	K	
Δ _m H ^o	kJ				Δ _{vap} H ^o	kJ	
H ₂₉₈ ^o -H ₀ ^o	kJ				Molar Vol.	1.476 J·bar ⁻¹ 14.76 cm ³	
A= -6.086E+02			B= 1.425E-01		C= 4.563E+06		

12/7/92

PERICLASE

Formula wt 40.304

MgO: Cubic crystals 298.15 to 1800 K.

Temp. K	C_p°	S_T°	$(H_T^\circ - H_{298}^\circ)/T$ J·mol ⁻¹ ·K ⁻¹	$-(G_T^\circ - H_{298}^\circ)/T$	FORMATION FROM THE ELEMENTS		
					$\Delta_f H^\circ$ kJ·mol ⁻¹	$\Delta_f G^\circ$	Log K_f
298.15	37.26	26.90	0.00	26.90	-601.6	-569.3	99.74
300	37.40	27.13	0.23	26.90	-601.6	-569.1	99.09
400	42.70	38.70	10.26	28.44	-601.6	-558.3	72.90
500	45.57	48.57	17.06	31.51	-601.4	-547.4	57.19
600	47.37	57.05	21.97	35.07	-601.1	-536.7	46.72
700	48.61	64.45	25.69	38.75	-600.8	-526.0	39.25
800	49.53	71.00	28.62	42.38	-600.5	-515.3	33.64
900	50.26	76.88	30.98	45.89	-600.4	-504.7	29.29
1000	50.87	82.21	32.94	49.26	-608.9	-493.3	25.77
1100	51.40	87.08	34.60	52.48	-608.9	-481.8	22.88
1200	51.90	91.57	36.02	55.56	-609.0	-470.2	20.47
1300	52.36	95.75	37.26	58.49	-609.0	-458.6	18.43
1400	52.82	99.64	38.35	61.29	-736.4	-443.9	16.56
1500	53.28	103.30	39.33	63.97	-735.0	-423.1	14.73
1600	53.76	106.76	40.22	66.54	-733.5	-402.3	13.13
1700	54.25	110.03	41.03	69.00	-732.1	-381.7	11.73
1800	54.76	113.15	41.78	71.37	-730.6	-361.1	10.48

Melting T 3125 K

Boiling T K

 $\Delta_{\text{fus}} H^\circ$ kJ $\Delta_{\text{vap}} H^\circ$ kJ $H_{298}^\circ - H_0^\circ$ 5.17 kJMolar Vol. 1.125 J·bar⁻¹
11.25 cm³

A= -6.373E+02

B= 1.449E-01

C= 2.512E+06

8/26/92

BRUCITE

Formula wt 58.320

Mg(OH)₂: Hexagonal crystals 298.15 to 900 K.

Temp. K	C _p ^o	S _T ^o	(H _T ^o -H ₂₉₈ ^o)/T J·mol ⁻¹ ·K ⁻¹	-(G _T ^o -H ₂₉₈ ^o)/T	FORMATION FROM THE ELEMENTS		
					Δ _f H ^o kJ·mol ⁻¹	Δ _f G ^o	Log K _f
298.15	77.27	63.20	0.00	63.20	-924.5	-833.5	146.02
300	77.66	63.68	0.48	63.20	-924.5	-832.9	145.02
400	91.89	88.23	21.78	66.45	-924.4	-802.4	104.78
500	99.29	109.60	36.61	73.00	-923.4	-772.0	80.64
600	104.00	128.15	47.47	80.68	-922.1	-741.8	64.58
700	107.44	144.45	55.80	88.65	-920.6	-711.9	53.12
800	110.20	158.98	62.43	96.55	-919.0	-682.1	44.54
900	112.57	172.10	67.87	104.23	-917.3	-652.6	37.88

Melting T	K	Boiling T	K
Δ _m H ^o	kJ	Δ _{vap} H ^o	kJ
H ₂₉₈ ^o -H ₀ ^o	11.40 kJ	Molar Vol.	2.463 J·bar ⁻¹ 24.63 cm ³
A=	-9.195E+02	B=	2.971E-01
		C=	-2.30E+05

MANGANOSITE

Formula wt 70.937

MnO: Cubic crystals 298.15 to 1800 K.

Temp. K	C_p°	S_T°	$(H_T^\circ - H_{298}^\circ)/T$ J·mol ⁻¹ ·K ⁻¹	$-(G_T^\circ - H_{298}^\circ)/T$	FORMATION FROM THE ELEMENTS		
					$\Delta_f H^\circ$ kJ·mol ⁻¹	$\Delta_f G^\circ$	Log K_f
298.15	44.10	59.71	0.00	59.71	-385.2	-362.9	63.58
300	44.16	59.98	0.27	59.71	-385.2	-362.8	63.16
400	46.81	73.07	11.60	61.48	-384.9	-355.3	46.40
500	48.73	83.74	18.84	64.90	-384.5	-348.0	36.35
600	50.24	92.76	23.95	68.81	-384.3	-340.7	29.66
700	51.49	100.60	27.80	72.80	-384.1	-333.4	24.88
800	52.57	107.55	30.83	76.72	-384.0	-326.2	21.30
900	53.52	113.80	33.30	80.50	-383.9	-319.0	18.51
1000	54.38	119.48	35.37	84.12	-386.2	-311.7	16.28
1100	55.17	124.70	37.13	87.57	-386.2	-304.3	14.45
1200	55.91	129.53	38.67	90.87	-386.3	-296.8	12.92
1300	56.59	134.04	40.02	94.02	-386.3	-289.4	11.63
1400	57.24	138.26	41.23	97.03	-388.6	-281.9	10.52
1500	57.87	142.23	42.31	99.91	-391.1	-274.1	9.54
1600	58.46	145.98	43.31	102.67	-403.8	-265.6	8.67
1700	59.03	149.54	44.21	105.33	-404.4	-256.9	7.89
1800	59.59	152.93	45.05	107.88	-404.9	-248.3	7.20

Melting T	2054 K	Boiling T	K
$\Delta_{fm} H^\circ$	kJ	$\Delta_{vap} H^\circ$	kJ
$H_{298}^\circ - H_0^\circ$	kJ	Molar Vol.	1.322 J·bar ⁻¹ 13.22 cm ³

A= -3.880E+02

B= 7.651E-02

C= 2.398E+05

4/9/92

PYROLUSITE

Formula wt 86.937

MnO₂: Crystals 298.15 to 850 K.

Temp. K	C _p ^o	S _T ^o	(H _T ^o -H ₂₉₈ ^o)/T	-(G _T ^o -H ₂₉₈ ^o)/T	FORMATION FROM THE ELEMENTS		
					Δ _f H ^o	Δ _f G ^o	Log K _f
			J·mol ⁻¹ ·K ⁻¹	kJ·mol ⁻¹			
298.15	54.76	52.75	0.00	52.75	-520.0	-465.0	81.47
300	54.94	53.09	0.34	52.75	-520.0	-464.7	80.91
400	63.21	70.11	15.09	55.01	-519.8	-446.3	58.27
500	68.34	84.81	25.27	59.54	-519.1	-427.9	44.71
600	71.21	97.56	32.72	64.84	-518.4	-409.8	35.67
700	72.68	108.66	38.33	70.32	-517.7	-391.7	29.23
800	73.36	118.41	42.67	75.74	-517.2	-373.8	24.40
900	73.65	127.07	46.10	80.97	-516.8	-355.9	20.65

Melting T	K	Boiling T	K
Δ _{fus} H ^o	kJ	Δ _{vap} H ^o	kJ
H ₂₉₈ ^o -H ₀ ^o	kJ	Molar Vol.	1.661 J·bar ⁻¹ 16.61 cm ³
A= -5.172E+02	B= 1.795E-01	C= -1.20E+05	

8/26/92

BIXBYITE

Formula wt 157.874

Mn₂O₃: Cubic crystals 298.15 to 1400 K.

Temp. K	C _p ^o	S _T ^o	(H _T ^o -H ₂₉₈ ^o)/T	-(G _T ^o -H ₂₉₈ ^o)/T	FORMATION FROM THE ELEMENTS		
					Δ _f H ^o	Δ _f G ^o	Log K _f
			J·mol ⁻¹ ·K ⁻¹	kJ·mol ⁻¹			
298.15	101.81	113.70	0.00	113.70	-959.0	-882.1	154.53
300	101.93	114.33	0.63	113.70	-959.0	-881.6	153.49
400	108.49	144.55	26.77	117.78	-958.4	-855.9	111.76
500	114.61	169.43	43.74	125.69	-957.6	-830.3	86.74
600	120.05	190.81	56.01	134.80	-956.9	-804.9	70.08
700	124.93	209.69	65.52	144.18	-956.0	-779.7	58.18
800	129.38	226.67	73.22	153.45	-955.2	-754.5	49.27
900	133.49	242.15	79.69	162.45	-954.2	-729.5	42.34
1000	137.37	256.42	85.27	171.15	-957.7	-704.5	36.80
1100	141.07	269.68	90.18	179.51	-956.6	-679.3	32.26
1200	144.63	282.11	94.57	187.55	-955.3	-654.1	28.47
1300	148.09	293.82	98.55	195.27	-953.8	-629.0	25.27
1400	151.47	304.92	102.21	202.71	-956.7	-604.0	22.54

Melting T	K	Boiling T	K
Δ _m H ^o	kJ	Δ _{vp} H ^o	kJ
H ₂₉₈ ^o -H ₀	17.56 kJ	Molar Vol.	3.137 J·bar ⁻¹ 31.37 cm ³

A= -9.550E+02

B= 2.508E-01

C= -1.645E+05

8/27/92

HAUSMANNITE

Formula wt 228.812

 Mn_3O_4 : Tetragonal crystals 298.15 to 1400 K.

Temp. K	C_p°	S_T°	$(H_T^\circ - H_{298}^\circ)/T$ J·mol ⁻¹ ·K ⁻¹	$-(G_T^\circ - H_{298}^\circ)/T$	FORMATION FROM THE ELEMENTS		
					$\Delta_f H^\circ$ kJ·mol ⁻¹	$\Delta_f G^\circ$	Log K_f
298.15	142.02	164.10	0.00	164.10	-1384.5	-1282.5	224.68
300	142.52	164.98	0.88	164.10	-1384.5	-1281.8	223.18
400	158.37	208.55	38.62	169.94	-1383.4	-1247.7	162.93
500	165.03	244.68	63.30	181.38	-1382.1	-1214.0	126.82
600	169.49	275.18	80.64	194.54	-1381.0	-1180.5	102.77
700	173.64	301.61	93.63	207.99	-1380.2	-1147.1	85.60
800	178.04	325.08	103.90	221.18	-1379.5	-1113.8	72.73
900	182.86	346.33	112.40	233.93	-1379.0	-1080.7	62.72
1000	188.12	365.86	119.71	246.16	-1385.1	-1047.4	54.71
1100	193.77	384.05	126.18	257.87	-1384.4	-1013.7	48.14
1200	199.78	401.17	132.06	269.11	-1383.3	-980.0	42.66
1300	206.12	417.41	137.51	279.90	-1381.8	-946.5	38.03
1400	212.72	432.92	142.65	290.28	-1386.7	-912.9	34.06

Melting T	K	Boiling T	K
$\Delta_{fus} H^\circ$	kJ	$\Delta_{vap} H^\circ$	kJ
$H_{298}^\circ - H_0^\circ$	24.78 kJ	Molar Vol.	4.695 J·bar ⁻¹ 46.95 cm ³

A= -1.3809E+03	B= 3.3405E-01	C= -9.874E+05
----------------	---------------	---------------

4/10/92

BRAUNITE

Formula wt 604.645

Mn₇SiO₁₂: Tetragonal crystals 298.15 to 1500 K.

Temp. K	C _p ^o	S _T ^o	(H _T ^o -H ₂₉₈ ^o)/T	-(G _T ^o -H ₂₉₈ ^o)/T	FORMATION FROM THE ELEMENTS		
					Δ _f H ^o	Δ _f G ^o	Log K _f
			J·mol ⁻¹ ·K ⁻¹	kJ·mol ⁻¹			
298.15	380.79	416.40	0.00	416.40	-4260.0	-3944.7	691.09
300	382.01	418.76	2.35	416.41	-4260.0	-3942.8	686.48
400	428.72	535.79	103.74	432.05	-4258.2	-3837.2	501.08
500	456.30	634.62	171.68	462.94	-4254.9	-3732.3	389.91
600	476.35	719.66	220.85	498.81	-4251.4	-3628.2	315.86
700	492.85	794.36	258.56	535.80	-4247.8	-3524.6	263.00
800	507.45	861.14	288.78	572.37	-4244.2	-3421.5	223.40
900	520.96	921.70	313.83	607.87	-4240.7	-3318.8	192.62
1000	533.78	977.26	335.19	642.07	-4252.6	-3216.4	168.00
1100	546.15	1028.71	353.81	674.91	-4248.9	-3112.9	147.82
1200	558.21	1076.75	370.34	706.41	-4244.5	-3009.8	131.01
1300	570.07	1121.90	385.25	736.65	-4239.4	-2907.1	116.81
1400	581.76	1164.58	398.87	765.71	-4249.7	-2804.4	104.63
1500	593.34	1205.11	411.45	793.66	-4260.6	-2700.4	94.04

Melting T	K	Boiling T	K
Δ _{fm} H ^o	kJ	Δ _{vap} H ^o	kJ
H ₂₉₈ ^o -H ₀ ^o	65.68 kJ	Molar Vol.	12.508 J·bar ⁻¹ 125.08 cm ³
A=	-4.2437E+03	B=	1.0286E+00
		C=	-6.946E+05

02/24/94

MOLYBDITE

Formula wt 143.938

MoO₃: Orthorhombic crystals 298.15 to melting point 1074 K; liquid 1074 to 1500 K.

Temp. K	C _p ^o	S _T ^o	(H _T ^o -H ₂₉₈ ^o)/T J·mol ⁻¹ ·K ⁻¹	-(G _T ^o -H ₂₉₈ ^o)/T	FORMATION FROM THE ELEMENTS		
					Δ _f H ^o kJ·mol ⁻¹	Δ _f G ^o	Log K _f
298.15	74.91	77.70	0.00	77.70	-745.2	-668.1	117.04
300	75.13	78.16	0.46	77.70	-745.2	-667.6	116.24
400	83.02	101.00	20.24	80.76	-744.1	-641.9	83.82
500	87.78	120.06	33.29	86.77	-742.7	-616.5	64.40
600	91.85	136.42	42.71	93.71	-741.1	-591.4	51.48
700	95.89	150.89	50.02	100.87	-739.3	-566.6	42.28
800	100.08	163.96	56.01	107.95	-737.2	-542.0	35.39
900	104.46	176.00	61.15	114.85	-734.8	-517.8	30.05
1000	109.03	187.24	65.71	121.53	-732.2	-493.8	25.79
1100	126.95	197.87	69.85	128.02	-729.2	-470.1	22.32
1200	126.95	207.97	73.71	134.26	-725.8	-446.7	19.44
1300	126.95	217.67	77.36	140.31	-722.0	-423.6	17.02
1400	126.95	227.02	80.85	146.17	-717.9	-400.8	14.95
1500	126.95	236.09	84.22	151.87	-713.3	-378.3	13.17

Melting T	1074 K	Boiling T	K
Δ _{lv} H ^o	48.91 kJ	Δ _{vap} H ^o	kJ
H ₂₉₈ ^o -H ₀ ^o	12.59 kJ	Molar Vol.	3.056 J·bar ⁻¹ 30.56 cm ³

A= -7.299E+02

B= 2.358E-01

C= -8.02E+05

8/27/92

NITROGEN DIOXIDE

Formula wt 46.006

NO₂: Ideal gas at p = 1 bar, 298.15 to 1800 K.

Temp. K	C _p ^o	S _T ^o	FORMATION FROM THE ELEMENTS				
			(H _T ^o -H ₂₉₈ ^o)/T	-(G _T ^o -H ₂₉₈ ^o)/T	Δ _f H ^o	Δ _f G ^o	Log K _f
			J·mol ⁻¹ ·K ⁻¹		kJ·mol ⁻¹		
298.15	37.00	240.10	0.00	240.10	33.1	51.2	-8.98
300	37.05	240.33	0.23	240.10	33.1	51.4	-8.94
400	40.16	251.39	9.81	241.59	32.5	57.5	-7.51
500	43.29	260.70	16.20	244.50	32.2	63.8	-6.67
600	45.91	268.83	20.94	247.89	32.0	70.2	-6.11
700	48.02	276.08	24.66	251.41	31.9	76.6	-5.71
800	49.71	282.60	27.69	254.91	31.9	83.0	-5.42
900	51.06	288.54	30.22	258.32	31.9	89.3	-5.18
1000	52.16	293.98	32.36	261.62	32.0	95.7	-5.00
1100	53.05	298.99	34.20	264.79	32.1	102.1	-4.85
1200	53.77	303.64	35.80	267.84	32.3	108.4	-4.72
1300	54.36	307.97	37.21	270.76	32.4	114.8	-4.61
1400	54.85	312.01	38.45	273.56	32.5	121.1	-4.52
1500	55.25	315.81	39.56	276.26	32.6	127.4	-4.44
1600	55.58	319.39	40.55	278.84	32.8	133.7	-4.37
1700	55.86	322.77	41.44	281.33	32.9	140.1	-4.30
1800	56.09	325.97	42.25	283.72	33.0	146.4	-4.25

Melting T	K	Boiling T	K
Δ _{fus} H ^o	kJ	Δ _{vap} H ^o	kJ
H ₂₉₈ ^o -H ₀ ^o	kJ	Molar Vol.	2478.97 J·bar ⁻¹ 24789.7 cm ³

A= 3.210E+01

B= 6.353E-02

C= 1.451E+04

5/06/93

DISODIUM MONOXIDE

Formula wt 61.979

Na₂O: Cubic crystals 298.15 to melting point 1193 K.

Temp. K	C _p ^o	S _T ^o	FORMATION FROM THE ELEMENTS				
			(H _T ^o -H ₂₉₈ ^o)/T J·mol ⁻¹ ·K ⁻¹	-(G _T ^o -H ₂₉₈ ^o)/T	Δ _f H ^o kJ·mol ⁻¹	Δ _f G ^o	Log K _f
298.15	69.10	75.30	0.00	75.30	-414.8	-376.0	65.87
300	69.26	75.73	0.43	75.30	-414.8	-375.7	65.42
400	76.30	96.68	18.57	78.11	-420.2	-362.3	47.31
500	81.34	114.27	30.64	83.63	-420.1	-347.8	36.33
600	85.26	129.46	39.43	90.03	-419.3	-333.4	29.03
700	88.47	142.85	46.21	96.64	-418.2	-319.2	23.82
800	91.20	154.85	51.67	103.18	-416.7	-305.1	19.92
900	93.60	165.73	56.20	109.53	-414.9	-291.3	16.91
1000	95.74	175.71	60.05	115.66	-413.0	-277.7	14.50

Melting T	1193 K	Boiling T	K
Δ _{lv} H ^o	kJ	Δ _{lv} H ^o	kJ
H ₂₉₈ ^o -H ₈	12.40 kJ	Molar Vol.	2.588 J·bar ⁻¹ 25.88 cm ³

A= -4.180E+02

B= 1.407E-01

C= -5.93E+03

9/10/92

BUNSENITE

Formula wt 74.689

NiO: Rhombohedral (distorted cubic) crystals 298.15 to Néel temperature 519 K. Cubic crystals 519 to 1800 K.

FORMATION FROM THE ELEMENTS

Temp. K	C_p°	S_T°	$(H_T^\circ - H_{298}^\circ)/T$ J·mol ⁻¹ ·K ⁻¹	$-(G_T^\circ - H_{298}^\circ)/T$	$\Delta_f H^\circ$ kJ·mol ⁻¹	$\Delta_f G^\circ$	Log K_f
298.15	44.49	37.99	0.00	37.99	-239.3	-211.1	36.99
300	44.70	38.27	0.28	37.99	-239.3	-211.0	36.73
400	53.00	52.38	12.52	39.86	-238.6	-201.6	26.33
500	64.90	65.25	21.59	43.66	-237.3	-192.5	20.11
519	69.15	67.74	23.25	44.49	-236.8	-190.9	19.21
600	56.01	76.07	27.86	48.21	-236.2	-183.6	15.99
700	54.22	84.55	31.73	52.82	-235.6	-175.0	13.05
800	53.66	91.74	34.50	57.24	-235.1	-166.8	10.89
900	53.83	98.06	36.63	61.43	-234.5	-157.8	9.16
1000	54.43	103.76	38.38	65.38	-234.0	-149.3	7.80
1100	55.29	108.99	39.88	69.11	-233.5	-140.8	6.69
1200	56.29	113.84	41.20	72.64	-233.1	-132.4	5.76
1300	57.37	118.39	42.40	75.99	-232.6	-124.0	4.98
1400	58.48	122.68	43.51	79.17	-232.1	-115.7	4.32
1500	59.57	126.76	44.55	82.21	-231.6	-107.4	3.74
1600	60.62	130.63	45.52	85.11	-231.1	-99.1	3.24
1700	61.61	134.34	46.44	87.90	-230.6	-90.9	2.79
1800	62.52	137.89	47.30	90.59	-247.3	-82.0	2.38

Melting T	2257 K	Boiling T	K
$\Delta_m H^\circ$	kJ	$\Delta_m H^\circ$	kJ
$H_{298}^\circ - H_0^\circ$	6.69 kJ	Molar Vol.	1.097 J·bar ⁻¹ 10.97 cm ³

A= -2.331E+02

B= 8.392E-02

C= -2.85E+05

9/9/92

LITHARGE

Formula wt 223.199

PbO: Tetragonal crystals (red) 298.15 to 1000 K.

Temp. K	C_p°	S_f°	FORMATION FROM THE ELEMENTS				
			$(H_f^\circ - H_{298}^\circ)/T$	$-(G_f^\circ - H_{298}^\circ)/T$	$\Delta_f H^\circ$	$\Delta_f G^\circ$	Log K_f
			$J \cdot mol^{-1} \cdot K^{-1}$		$kJ \cdot mol^{-1}$		
298.15	45.77	66.50	0.00	66.50	-219.0	-188.9	33.10
300	45.89	66.78	0.28	66.50	-219.0	-188.7	32.86
400	50.51	80.69	12.33	68.37	-218.4	-178.7	23.34
500	53.20	92.27	20.25	72.02	-217.5	-168.9	17.65
600	55.13	102.15	25.91	76.24	-216.6	-159.3	13.87
700	56.70	110.77	30.20	80.57	-220.5	-149.0	11.12
800	58.08	118.43	33.60	84.83	-219.4	-138.9	9.07
900	59.35	125.35	36.39	88.96	-218.3	-128.9	7.48
1000	60.55	131.66	38.75	92.92	-216.9	-119.0	6.22

Melting T	K	Boiling T	K
$\Delta_{fus} H^\circ$	kJ	$\Delta_{vap} H^\circ$	kJ
$H_{298}^\circ - H_0^\circ$	kJ	Molar Vol.	2.391 $J \cdot bar^{-1}$ 23.91 cm^3

A= -2.194E+02

B= 1.004E-01

C= 4.877E+04

9/9/92

PLATTNERITE

Formula wt 239.199

PbO₂: Tetragonal crystals 298.15 to 1200 K.

Temp. K	C _p ^o	S _T ^o	FORMATION FROM THE ELEMENTS				
			(H _T ^o -H ₂₉₈ ^o)/T	-(G _T ^o -H ₂₉₈ ^o)/T	Δ _f H ^o	Δ _f G ^o	Log K _f
	J·mol ⁻¹ ·K ⁻¹		J·mol ⁻¹ ·K ⁻¹		kJ·mol ⁻¹		
298.15	61.17	71.80	0.00	71.80	-277.4	-218.3	38.25
300	61.35	72.18	0.38	71.80	-277.4	-218.0	37.95
400	68.23	90.90	16.59	74.31	-276.6	-198.3	25.89
500	71.82	106.54	27.31	79.23	-275.4	-178.8	18.68
600	74.11	119.85	34.93	84.92	-274.2	-159.6	13.89
700	75.79	131.41	40.65	90.76	-277.8	-139.8	10.43
800	77.14	141.62	45.13	96.49	-276.5	-120.2	7.85
900	78.30	150.77	48.75	102.02	-275.1	-100.7	5.84
1000	79.34	159.08	51.76	107.32	-273.7	-81.4	4.25
1100	80.31	166.69	54.31	112.37	-272.1	-62.2	2.96
1200	81.23	173.71	56.52	117.20	-270.5	-43.2	1.88

Melting T	K	Boiling T	K
Δ _{lv} H ^o	kJ	Δ _{lv} H ^o	kJ
H ₂₉₈ ^o -H ₀ ^o	36.78 kJ	Molar Vol.	2.501 J·bar ⁻¹ 25.01 cm ³

A= -2.752E+02

B= 1.937E-01

C= -7.72E+04

9/9/92

MINIUM

Formula wt 685.598

Pb₃O₄: Tetragonal crystals 298.15 to 1800 K.

Temp. K	C _p ^o	S _T ^o	(H _T ^o -H ₂₉₈ ^o)/T J·mol ⁻¹ ·K ⁻¹	-(G _T ^o -H ₂₉₈ ^o)/T	FORMATION FROM THE ELEMENTS		
					Δ _f H ^o kJ·mol ⁻¹	Δ _f G ^o	Log K _f
298.15	154.90	212.00	0.00	212.00	-718.7	-601.6	105.40
300	155.37	212.96	0.96	212.00	-718.7	-600.9	104.62
400	172.92	260.35	42.01	218.35	-716.3	-562.0	73.38
500	182.83	300.08	69.25	230.83	-713.0	-523.7	54.71
600	189.73	334.06	88.78	245.27	-709.5	-486.2	42.33
700	195.21	363.73	103.61	260.12	-720.3	-446.9	33.35
800	199.94	390.11	115.36	274.75	-716.3	-408.1	26.65
900	204.22	413.91	125.00	288.91	-711.8	-369.8	21.46
1000	208.23	435.64	133.12	302.51	-707.0	-332.1	17.35
1100	212.07	455.66	140.13	315.54	-701.8	-294.9	14.00
1200	215.78	474.28	146.28	328.00	-696.2	-258.1	11.24
1300	219.41	491.69	151.76	339.93	-690.2	-221.9	8.91
1400	222.97	508.08	156.72	351.36	-683.9	-186.1	6.94
1500	226.49	523.59	161.26	362.33	-677.3	-150.7	5.25
1600	229.97	538.31	165.44	372.87	-670.4	-115.8	3.78
1700	233.43	552.36	169.34	383.02	-663.1	-81.4	2.50
1800	236.86	565.80	173.00	392.80	-655.6	-47.4	1.37

Melting T	K	Boiling T	K
Δ _{fus} H ^o	kJ	Δ _{vap} H ^o	kJ
H ₂₉₈ ^o -H ₀ ^o	kJ	Molar Vol.	7.681 J·bar ⁻¹ 76.81 cm ³

A= -6.975E+02

B= 3.642E-01

C= -1.26E+06

8/21/92

SULFUR DIOXIDE

Formula wt 64.065

SO₂: Ideal gas at p = 1 bar, 298.15 to 2500 K.

Temp. K	C _p ^o	S _T ^o	FORMATION FROM THE ELEMENTS				
			(H _T ^o -H ₂₉₈ ^o)/T	-(G _T ^o -H ₂₉₈ ^o)/T	Δ _f H ^o	Δ _f G ^o	Log K _f
			J·mol ⁻¹ ·K ⁻¹	kJ·mol ⁻¹			
298.15	39.85	248.20	0.00	248.20	-296.8	-300.1	52.57
300	39.92	248.45	0.25	248.20	-296.8	-300.1	52.25
400	43.48	260.42	10.61	249.81	-300.2	-300.9	39.30
500	46.53	270.47	17.50	252.96	-302.7	-300.8	31.43
600	48.92	279.17	22.55	256.62	-304.7	-300.3	26.14
700	50.78	286.86	26.45	260.40	-306.3	-299.4	22.34
800	52.23	293.74	29.59	264.15	-307.7	-298.3	19.48
900	53.38	299.96	32.17	267.78	-362.1	-296.0	17.18
1000	54.29	305.63	34.34	271.29	-362.0	-288.6	15.08
1100	55.01	310.84	36.19	274.65	-361.9	-281.3	13.36
1200	55.60	315.65	37.78	277.87	-361.8	-274.0	11.93
1300	56.07	320.12	39.17	280.95	-361.7	-266.7	10.71
1400	56.46	324.29	40.39	283.90	-361.6	-259.3	9.68
1500	56.79	328.20	41.47	286.72	-361.5	-252.1	8.78
1600	57.06	331.87	42.44	289.43	-361.5	-244.8	7.99
1700	57.29	335.34	43.31	292.03	-361.4	-237.4	7.30
1800	57.49	338.62	44.09	294.53	-361.4	-230.2	6.68

Melting T	K	Boiling T	K
Δ _{fusion} H ^o	kJ	Δ _{vaporization} H ^o	kJ
H ₂₉₈ ^o -H ₀ ^o	10.55 kJ	Molar Vol.	2478.97 J·bar ⁻¹ 24789.7 cm ³

A= -3.536E+02

B= 6.628E-02

C= 3.246E+06

9/9/92

SULFUR TRIOXIDE

Formula wt 80.064

SO₃: Ideal gas at p = 1 bar, 298.15 to 2200 K.

Temp. K	C _p ^o	S _T ^o	(H _T ^o -H ₂₉₈ ^o)/T J·mol ⁻¹ ·K ⁻¹	-(G _T ^o -H ₂₉₈ ^o)/T	FORMATION FROM THE ELEMENTS		
					Δ _f H ^o kJ·mol ⁻¹	Δ _f G ^o	Log K _f
298.15	50.63	256.80	0.00	256.80	-395.7	-371.0	64.99
300	50.77	257.11	0.31	256.80	-395.7	-370.8	64.56
400	57.69	272.70	13.82	258.88	-399.3	-362.2	47.30
500	63.09	286.18	23.16	263.02	-401.8	-352.6	36.84
600	67.16	298.06	30.17	267.89	-403.6	-342.6	29.83
700	70.26	308.66	35.69	272.97	-405.0	-332.3	24.80
800	72.64	318.20	40.16	278.04	-406.0	-321.9	21.02
900	74.49	326.87	43.88	282.99	-460.0	-310.2	18.00
1000	75.93	334.80	47.02	287.78	-459.6	-293.6	15.34
1100	77.07	342.09	49.70	292.39	-459.0	-277.0	13.15
1200	77.96	348.83	52.02	296.82	-458.5	-260.5	11.34
1300	78.68	355.10	54.04	301.06	-458.0	-244.0	9.80
1400	79.25	360.96	55.82	305.13	-457.4	-227.6	8.49
1500	79.71	366.44	57.40	309.04	-456.9	-211.2	7.35
1600	80.08	371.60	58.81	312.79	-456.3	-194.8	6.36
1700	80.38	376.46	60.07	316.39	-455.8	-178.5	5.48
1800	80.64	381.06	61.20	319.86	-455.3	-162.2	4.71

Melting T	K	Boiling T	K
Δ _m H ^o	kJ	Δ _{vap} H ^o	kJ
H ₂₉₈ ^o -H ₀ ^o	kJ	Molar Vol.	2478.97 J·bar ⁻¹ 24789.7 cm ³

A= -4.504E+02	B= 1.580E-01	C= 3.103E+06
---------------	--------------	--------------

SILICON MONOXIDE

Formula wt 44.085

SiO: Ideal gas at p = 1 bar, 298.15 to 1800 K.

Temp. K	C_p°	S_T°	$(H_T^\circ - H_{298}^\circ)/T$	$-(G_T^\circ - H_{298}^\circ)/T$	FORMATION FROM THE ELEMENTS		
					$\Delta_f H^\circ$	$\Delta_f G^\circ$	Log K_f
			J·mol ⁻¹ ·K ⁻¹		kJ·mol ⁻¹		
298.15	29.90	211.60	0.00	211.60	-100.4	-127.3	22.30
300	29.92	211.79	0.18	211.60	-100.4	-127.5	22.19
400	31.15	220.55	7.77	212.79	-101.0	-136.4	17.81
500	32.38	227.64	12.57	215.07	-101.6	-145.2	15.17
600	33.39	233.64	15.96	217.68	-102.3	-153.8	13.39
700	34.19	238.85	18.51	220.34	-103.0	-162.4	12.12
800	34.82	243.45	20.51	222.95	-103.7	-170.8	11.15
900	35.33	247.59	22.13	225.46	-104.4	-179.2	10.40
1000	35.72	251.33	23.47	227.86	-105.2	-187.4	9.79
1100	36.04	254.75	24.60	230.15	-106.0	-195.6	9.29
1200	36.30	257.90	25.56	232.33	-106.9	-203.7	8.87
1300	36.51	260.81	26.40	234.41	-107.8	-211.8	8.51
1400	36.67	263.52	27.13	236.40	-108.7	-219.7	8.20
1500	36.81	266.06	27.77	238.29	-109.7	-227.6	7.93
1600	36.93	268.44	28.34	240.10	-110.7	-235.5	7.69
1700	37.03	270.68	28.84	241.84	-162.0	-242.8	7.46
1800	37.11	272.80	29.30	243.50	-162.8	-247.5	7.18

Melting T

K

Boiling T

K

 $\Delta_{\text{fus}} H^\circ$

kJ

 $\Delta_{\text{vap}} H^\circ$

kJ

 $H_{298}^\circ - H_0^\circ$

8.71 kJ

Molar Vol.

2478.97 J·bar⁻¹
24789.7 cm³

A= -1.084E+02

B= -7.908E-02

C= 4.562E+05

4/10/92

QUARTZ

Formula wt 60.084

SiO₂: Trigonal crystals 298.15 to α - β transition at 844 K. β -crystals 844 to 1700.
The melting point is estimated to be 1700 K. Liquid 1700 to 1800 K.

Temp. K	C _p ^o	S _T ^o	FORMATION FROM THE ELEMENTS				
			(H _T ^o -H ₂₉₈ ^o)/T	-(G _T ^o -H ₂₉₈ ^o)/T	$\Delta_f H^\circ$	$\Delta_f G^\circ$	Log K _f
			J·mol ⁻¹ ·K ⁻¹		kJ·mol ⁻¹		
298.15	44.59	41.46	0.00	41.46	-910.7	-856.3	150.01
300	44.78	41.74	0.28	41.46	-910.7	-855.9	149.03
400	53.27	55.85	12.52	43.33	-910.9	-837.7	109.38
500	59.68	68.45	21.34	47.11	-910.5	-819.4	85.60
600	65.04	79.82	28.18	51.64	-909.8	-801.2	69.75
700	69.82	90.21	33.80	56.41	-908.8	-783.2	58.44
800	74.25	99.83	38.58	61.25	-907.4	-765.3	49.97
900	68.62	109.00	42.93	66.07	-905.6	-747.7	43.39
1000	69.12	116.25	45.52	70.73	-904.8	-730.2	38.14
1100	69.74	122.87	47.69	75.18	-904.1	-712.8	33.85
1200	70.43	128.96	49.56	79.40	-903.3	-695.4	30.27
1300	71.17	134.63	51.19	83.44	-902.5	-678.1	27.25
1400	71.96	139.93	52.65	87.28	-901.8	-660.9	24.66
1500	72.77	144.92	53.96	90.96	-901.0	-643.7	22.41
1600	73.60	149.65	55.16	94.49	-900.2	-626.6	20.46
1700	74.45	154.14	56.27	97.87	-949.6	-609.0	18.71
1800	81.37	164.31	62.89	101.42	-938.5	-589.6	17.11

Melting T	K	Boiling T	K
$\Delta_{\text{fus}} H^\circ$	kJ	$\Delta_{\text{vap}} H^\circ$	kJ
H ₂₉₈ ^o -H ₀ ^o	6.916 kJ	Molar Vol.	2.269 J·bar ⁻¹ 22.69 cm ³

A= -9.047E+02

B= 1.744E-01

C= -3.39E+05

01/06/93

CRISTOBALITE

Formula wt 60.084

SiO₂: Tetragonal crystals, α , 298.15 to 523 K. Cubic crystals, β , 523 to 1800 K.

Temp. K	C _p ^o	S _T ^o	(H _T ^o -H ₂₉₈ ^o)/T	-(G _T ^o -H ₂₉₈ ^o)/T	FORMATION FROM THE ELEMENTS		
					$\Delta_f H^\circ$	$\Delta_f G^\circ$	Log K _f
			J·mol ⁻¹ ·K ⁻¹		kJ·mol ⁻¹		
298.15	44.95	43.40	0.00	43.40	-908.4	-854.6	149.71
300	45.15	43.70	0.28	43.42	-908.4	-854.2	148.73
400	50.73	57.93	12.63	45.31	-908.5	-836.1	109.19
500	68.59	70.56	21.48	49.08	-908.2	-818.1	85.46
600	62.06	84.60	29.96	54.64	-906.5	-800.7	69.71
700	65.23	94.42	34.78	59.64	-905.8	-783.1	58.44
800	67.34	103.28	38.73	64.55	-905.0	-765.7	49.99
900	68.82	111.30	41.99	69.31	-904.2	-748.3	43.43
1000	69.92	118.61	44.74	73.87	-903.3	-731.0	38.18
1100	70.77	125.32	47.07	78.26	-902.4	-713.8	33.90
1200	71.44	131.50	49.07	82.43	-901.6	-696.7	30.33
1300	72.00	137.24	50.81	86.43	-900.7	-679.7	27.31
1400	72.47	142.60	52.34	90.26	-899.9	-662.7	24.73
1500	72.87	147.61	53.70	93.91	-899.1	-645.8	22.49
1600	73.22	152.32	54.91	97.41	-898.3	-628.9	20.53
1700	73.53	156.77	55.99	100.78	-947.8	-611.7	18.79
1800	73.82	160.98	56.98	104.00	-946.8	-591.9	17.18

Melting T	1996 K	Boiling T	K
$\Delta_{\text{fus}} H^\circ$	kJ	$\Delta_{\text{vap}} H^\circ$	kJ
H ₂₉₈ ^o -H ₀ ^o	7.04 kJ	Molar Vol.	2.574 J·bar ⁻¹ 25.74 cm ³

A= -9.029E+02

B= 1.719E-01

C= -2.62E+05

01/06/93

COESITE

Formula wt 60.084

SiO₂: Monoclinic crystals 298.15 to 1800 K.

Temp. K	C _p ^o	S _T ^o	(H _T ^o -H ₂₉₈ ^o)/T J·mol ⁻¹ ·K ⁻¹	-(G _T ^o -H ₂₉₈ ^o)/T	FORMATION FROM THE ELEMENTS		
					Δ _f H ^o kJ·mol ⁻¹	Δ _f G ^o	Log K _f
298.15	45.46	38.50	0.00	38.50	-907.8	-852.5	149.35
300	45.58	38.78	0.28	38.50	-907.8	-852.2	148.37
400	52.60	52.85	12.48	40.37	-908.0	-833.6	108.85
500	58.51	65.26	21.12	44.13	-907.7	-815.0	85.14
600	62.81	76.33	27.73	48.59	-907.2	-796.5	69.34
700	65.84	86.25	32.97	53.28	-906.5	-778.1	58.06
800	67.94	95.19	37.22	57.97	-905.6	-759.8	49.61
900	69.41	103.28	40.72	62.56	-904.7	-741.6	43.04
1000	70.45	110.65	43.64	67.01	-903.8	-723.6	37.79
1100	71.23	117.40	46.12	71.28	-902.9	-705.6	33.50
1200	71.86	123.63	48.24	75.39	-902.0	-687.7	29.93
1300	72.45	129.40	50.08	79.33	-901.1	-669.9	26.91
1400	73.06	134.79	51.70	83.10	-900.2	-652.1	24.33
1500	73.75	139.86	53.14	86.71	-899.3	-634.4	22.09
1600	74.56	144.64	54.46	90.19	-898.5	-616.8	20.14
1700	75.54	149.19	55.67	93.52	-947.7	-598.8	18.40
1800	76.71	153.54	56.80	96.74	-946.6	-578.2	16.78

Melting T	K	Boiling T	K
Δ _m H ^o	kJ	Δ _{vap} H ^o	kJ
H ₂₉₈ ^o -H ₀ ^o	6.89 kJ	Molar Vol.	2.064 J·bar ⁻¹ 20.64 cm ³

A= -9.036E+02

B= 1.799E-01

C= -2.39E+05

STISHOVITE

Formula wt 60.084

SiO₂: Tetragonal crystals 298.15 to 1800 K.

Temp. K	C _p ^o	S _T ^o	(H _T ^o -H ₂₉₈ ^o)/T J·mol ⁻¹ ·K ⁻¹	-(G _T ^o -H ₂₉₈ ^o)/T	FORMATION FROM THE ELEMENTS		
					Δ _f H ^o kJ·mol ⁻¹	Δ _f G ^o	Log K _f
298.15	42.99	27.78	0.00	27.78	-861.3	-802.8	140.65
300	43.24	28.05	0.27	27.78	-861.3	-802.4	139.72
400	53.50	42.04	12.42	29.62	-861.5	-782.8	102.22
500	59.42	54.67	21.28	33.39	-861.2	-763.1	79.72
600	63.14	65.85	27.97	37.89	-860.6	-743.6	64.73
700	65.60	75.78	33.18	42.61	-859.8	-724.1	54.03
800	67.32	84.66	37.34	47.32	-859.0	-704.8	46.02
900	68.58	92.67	40.75	51.92	-858.2	-685.6	39.79
1000	69.58	99.95	43.58	56.36	-857.4	-666.4	34.81
1100	70.42	106.62	45.99	60.63	-856.5	-647.4	30.74
1200	71.20	112.78	48.05	64.72	-855.7	-628.4	27.35
1300	71.97	118.51	49.86	68.64	-854.9	-609.5	24.49
1400	72.79	123.87	51.47	72.40	-854.0	-590.6	22.04
1500	73.68	128.92	52.92	76.00	-853.2	-571.8	19.91
1600	74.68	133.71	54.25	79.46	-852.3	-553.1	18.06
1700	75.80	138.27	55.48	82.79	-901.6	-534.0	16.41
1800	77.06	142.64	56.65	85.99	-900.3	-512.4	14.87

Melting T	K	Boiling T	K
Δ _m H ^o	kJ	Δ _{vap} H ^o	kJ
H ₂₉₈ ^o -H ₀ ^o	7.74 kJ	Molar Vol.	1.4014 J·bar ⁻¹ 14.014 cm ³

A= -8.572E+02

B= 1.907E-01

C= -2.28E+05

12/17/91

SILICA GLASS

Formula wt 60.084

SiO₂: Glass 298.15 to estimated melting point 1700 K.

Temp. K	C _p ^o	S _T ^o	(H _T ^o -H ₂₉₈ ^o)/T	-(G _T ^o -H ₂₉₈ ^o)/T	FORMATION FROM THE ELEMENTS		
					Δ _f H ^o	Δ _f G ^o	Log K _f
			J·mol ⁻¹ ·K ⁻¹		kJ·mol ⁻¹		
298.15	37.94	48.50	0.00	48.50	-901.6	-849.3	148.79
300	38.36	48.74	0.24	48.50	-901.6	-849.0	147.81
400	53.17	62.11	11.89	50.22	-902.0	-831.3	108.56
500	59.95	74.79	20.90	53.89	-901.7	-813.7	85.00
600	63.64	86.07	27.74	58.33	-901.0	-796.1	69.31
700	65.93	96.07	33.04	63.02	-900.2	-778.7	58.11
800	67.53	104.98	37.26	67.72	-899.4	-761.4	49.71
900	68.77	113.01	40.69	72.31	-898.6	-744.2	43.19
1000	69.84	120.31	43.56	76.75	-897.7	-727.1	37.98
1100	70.82	127.01	45.99	81.02	-896.8	-710.1	33.72
1200	71.79	133.22	48.10	85.12	-895.9	-693.2	30.17
1300	72.77	139.00	49.96	89.04	-895.0	-676.3	27.17
1400	73.81	144.43	51.63	92.81	-894.1	-659.5	24.61
1500	74.90	149.56	53.14	96.42	-893.1	-642.8	22.38
1600	76.07	154.43	54.54	99.90	-892.1	-626.1	20.44
1700	77.32	159.08	55.84	103.24	-941.2	-609.1	18.71

Melting T	1700 K	Boiling T	K
Δ _m H ^o	kJ	Δ _{vap} H ^o	kJ
H ₂₉₈ ^o -H ₀ ^o	6.998 kJ	Molar Vol.	2.727 J·bar ⁻¹ 27.27 cm ³

A= -8.966E+02

B= 1.694E-01

C= -3.06E+05

2/25/93

CASSITERITE

Formula wt 150.709

SnO₂: Tetragonal crystals 298.15 to 1903 K.

Temp. K	C _p ^o	S _T ^o	(H _T ^o -H ₂₉₈ ^o)/T	-(G _T ^o -H ₂₉₈ ^o)/T	FORMATION FROM THE ELEMENTS		
					Δ _f H ^o	Δ _f G ^o	Log K _f
			J·mol ⁻¹ ·K ⁻¹		kJ·mol ⁻¹		
298.15	53.22	49.02	0.00	49.02	-577.6	-515.8	90.36
300	53.54	49.35	0.33	49.02	-577.6	-515.4	89.74
400	65.09	66.56	15.27	51.29	-577.4	-494.7	64.60
500	70.83	81.76	25.86	55.90	-576.6	-474.1	49.53
600	74.28	95.00	33.66	61.34	-582.6	-452.3	39.38
700	76.66	106.64	39.64	66.99	-581.1	-430.8	32.14
800	78.46	117.00	44.39	72.61	-579.5	-409.4	26.73
900	79.92	126.32	48.26	78.07	-577.8	-388.2	22.53
1000	81.18	134.81	51.49	83.32	-576.0	-367.3	19.18
1100	82.30	142.60	54.24	88.36	-574.1	-346.5	16.45
1200	83.33	149.81	56.62	93.19	-572.2	-325.9	14.18
1300	84.30	156.52	58.71	97.80	-570.2	-305.4	12.27
1400	85.21	162.80	60.57	102.22	-568.2	-285.1	10.64
1500	86.10	168.71	62.25	106.46	-566.1	-265.0	9.23

Melting T	1903 K	Boiling T	K
Δ _{ab} H ^o	kJ	Δ _{vap} H ^o	kJ
H ₂₉₈ ^o -H ₀ ^o	8.38 kJ	Molar Vol.	2.155 J·bar ⁻¹ 21.55 cm ³

A= -5.763E+02

B= 2.084E-01

C= -1.755E+05

6/11/93

STRONTIUM MONOXIDE

Formula wt 103.619

SrO: Cubic crystals 298.15 to 1800 K.

Temp. K	C_p°	S_T°	$(H_T^\circ - H_{298}^\circ)/T$ J·mol ⁻¹ ·K ⁻¹	$-(G_T^\circ - H_{298}^\circ)/T$	FORMATION FROM THE ELEMENTS		
					$\Delta_f H^\circ$ kJ·mol ⁻¹	$\Delta_f G^\circ$ kJ·mol ⁻¹	Log K_f
298.15	45.41	55.52	0.00	55.52	-591.3	-560.7	98.22
300	45.49	55.80	0.28	55.52	-591.3	-560.5	97.59
400	48.66	69.37	12.02	57.35	-590.8	-550.3	71.86
500	50.62	80.45	19.55	60.89	-590.2	-540.2	56.43
600	52.06	89.81	24.86	64.95	-589.5	-530.3	46.16
700	53.24	97.93	28.83	69.10	-588.9	-520.5	38.84
800	54.26	105.10	31.95	73.16	-588.4	-510.7	33.35
900	55.19	111.55	34.48	77.07	-588.5	-501.0	29.07
1000	56.04	117.41	36.59	80.82	-587.7	-491.3	25.66
1100	56.86	122.79	38.40	84.39	-594.7	-481.3	22.86
1200	57.63	127.77	39.97	87.80	-594.7	-471.0	20.50
1300	58.38	132.41	41.36	91.06	-594.7	-460.7	18.51
1400	59.11	136.76	42.60	94.17	-594.5	-450.4	16.80
1500	59.83	140.87	43.72	97.14	-594.4	-440.1	15.33
1600	60.53	144.75	44.75	100.00	-594.1	-429.8	14.03
1700	61.22	148.44	45.70	102.74	-730.7	-418.4	12.86
1800	61.90	151.96	46.58	105.38	-728.5	-400.1	11.61

Melting T	K	Boiling T	K
$\Delta_{\text{fus}} H^\circ$	kJ	$\Delta_{\text{vap}} H^\circ$	kJ
$H_{298}^\circ - H_0^\circ$	8.675 kJ	Molar Vol.	2.069 J·bar ⁻¹ 20.69 cm ³

A= -5.956E+02

B= 1.047E-01

C= 3.940E+05

10/2/92

THORIANITE

Formula wt 264.037

ThO₂: Cubic crystals 298.15 to 1200 K.

Temp. K	C _p ^o	S _T ^o	FORMATION FROM THE ELEMENTS				
			(H _T ^o -H ₂₉₈ ^o)/T	-(G _T ^o -H ₂₉₈ ^o)/T	Δ _f H ^o	Δ _f G ^o	Log K _f
			J·mol ⁻¹ ·K ⁻¹		kJ·mol ⁻¹		
298.15	61.79	65.20	0.00	65.20	-1226.4	-1169.2	204.84
300	61.95	65.58	0.38	65.20	-1226.4	-1168.9	203.51
400	67.82	84.31	16.60	67.72	-1225.5	-1149.8	150.15
500	70.95	99.81	27.18	72.63	-1224.4	-1131.0	118.15
600	72.99	112.94	34.66	78.28	-1223.2	-1112.5	96.85
700	74.52	124.31	40.25	84.06	-1222.0	-1094.1	81.64
800	75.78	134.34	44.61	89.73	-1220.8	-1075.9	70.25
900	76.88	143.34	48.14	95.20	-1219.7	-1057.9	61.40
1000	77.88	151.49	51.06	100.43	-1218.6	-1040.0	54.32
1100	78.82	158.96	53.54	105.41	-1217.5	-1022.2	48.54
1200	79.72	165.85	55.69	110.17	-1216.5	-1004.5	43.72

Melting T	K	Boiling T	K
Δ _{fus} H ^o	kJ	Δ _{vap} H ^o	kJ
H ₂₉₈ ^o -H ₀ ^o	10.56 kJ	Molar Vol.	2.637 J·bar ⁻¹ 26.37 cm ³

A= -1.219E+03

B= 1.794E-01

C= -3.21E+05

9/10/92

RUTILE

Formula wt 79.879

TiO₂: Tetragonal crystals 298.15 to 1800 K.

Temp. K	C _p ^o	S _T ^o	(H _T ^o -H ₂₉₈ ^o)/T	-(G _T ^o -H ₂₉₈ ^o)/T	FORMATION FROM THE ELEMENTS		
					Δ _f H ^o	Δ _f G ^o	Log K _f
			J·mol ⁻¹ ·K ⁻¹		kJ·mol ⁻¹		
298.15	55.29	50.62	0.00	50.62	-944.0	-888.8	155.70
300	55.49	50.96	0.34	50.62	-944.0	-888.4	154.68
400	63.19	68.12	15.21	52.91	-943.6	-869.9	113.60
500	67.29	82.70	25.25	57.45	-942.8	-851.6	88.96
600	69.85	95.21	32.49	62.72	-942.0	-833.4	72.56
700	71.62	106.12	37.96	68.16	-941.0	-815.4	60.85
800	72.92	115.77	42.25	73.52	-940.1	-797.5	52.07
900	73.94	124.42	45.72	78.70	-939.1	-779.8	45.26
1000	74.77	132.25	48.58	83.67	-938.3	-762.1	39.81
1100	75.45	139.41	50.99	88.42	-937.6	-744.5	35.35
1200	76.04	146.00	53.06	92.95	-941.0	-726.9	31.64
1300	76.55	152.11	54.85	97.26	-940.0	-709.1	28.49
1400	76.99	157.80	56.41	101.39	-939.0	-691.4	25.79
1500	77.39	163.13	57.80	105.33	-938.0	-673.7	23.46
1600	77.76	168.13	59.03	109.10	-937.2	-656.1	21.42
1700	78.09	172.86	60.14	112.71	-936.5	-638.5	19.62
1800	78.39	177.33	61.15	116.18	-935.9	-621.0	18.02
Melting T	2103 K				Boiling T		K
Δ _{fm} H ^o	kJ				Δ _{vap} H ^o		kJ
H ₂₉₈ ^o -H ₀ ^o	8.67 kJ				Molar Vol.		1.882 J·bar ⁻¹ 18.82 cm ³
A= -9.385E+02			B= 1.766E-01		C= -2.66E+05		

4/5/93

ANATASE

Formula wt 79.879

TiO₂: Tetragonal crystals 298.15 to 1300 K.

Temp. K	C _p ^o	S _T ^o	(H _T ^o -H ₂₉₈ ^o)/T	-(G _T ^o -H ₂₉₈ ^o)/T	FORMATION FROM THE ELEMENTS		
					Δ _f H ^o	Δ _f G ^o	Log K _f
			J·mol ⁻¹ ·K ⁻¹		kJ·mol ⁻¹		
298.15	55.32	49.90	0.00	49.90	-938.7	-883.2	154.74
300	55.59	50.24	0.34	49.90	-938.7	-882.9	153.72
400	64.71	67.69	15.47	52.22	-938.2	-864.4	112.87
500	68.60	82.60	25.76	56.85	-937.3	-846.0	88.38
600	70.69	95.31	33.09	62.22	-936.3	-827.8	72.07
700	72.07	106.32	38.56	67.75	-935.3	-809.8	60.43
800	73.15	116.01	42.82	73.19	-934.3	-792.0	51.71
900	74.10	124.68	46.24	78.44	-933.3	-774.2	44.93
1000	75.01	132.54	49.07	83.46	-932.5	-756.6	39.52
1100	75.91	139.73	51.47	88.26	-931.8	-739.1	35.09
1200	76.82	146.37	53.55	92.83	-935.2	-721.4	31.40
1300	77.74	152.56	55.37	97.19	-934.0	-703.7	28.27

Melting T	K	Boiling T	K
Δ _{fm} H ^o	kJ	Δ _{vp} H ^o	kJ
H ₂₉₈ ^o -H ₀ ^o	kJ	Molar Vol.	2.052 J·bar ⁻¹ 20.52 cm ³

A= -9.331E+02

B= 1.767E-01

C= -2.60E+05

9/10/92

URANINITE

Formula wt 270.028

UO₂: Cubic crystals 298.15 to 1800 K.

Temp. K	C _p ^o	S _T ^o	(H _T ^o -H ₂₉₈ ^o)/T	-(G _T ^o -H ₂₉₈ ^o)/T	FORMATION FROM THE ELEMENTS		
					Δ _f H ^o	Δ _f G ^o	Log K _f
			J·mol ⁻¹ ·K ⁻¹		kJ·mol ⁻¹		
298.15	63.60	77.03	0.00	77.03	-1084.9	-1031.7	180.75
300	63.82	77.42	0.39	77.03	-1084.9	-1031.4	179.58
400	71.65	97.01	17.37	79.65	-1083.9	-1013.7	132.38
500	75.51	113.46	28.64	84.81	-1082.7	-996.3	104.08
600	77.96	127.45	36.67	90.78	-1081.5	-979.2	85.24
700	79.82	139.62	42.71	96.91	-1080.5	-962.2	71.80
800	81.42	150.38	47.45	102.93	-1079.7	-945.4	61.72
900	82.90	160.06	51.31	108.75	-1079.3	-928.6	53.89
1000	84.31	168.87	54.54	114.33	-1081.6	-911.7	47.62
1100	85.70	176.97	57.31	119.66	-1085.3	-894.5	42.48
1200	87.07	184.48	59.73	124.75	-1084.1	-877.2	38.18
1300	88.45	191.51	61.89	129.62	-1082.7	-860.0	34.56
1400	89.84	198.11	63.83	134.28	-1081.2	-843.0	31.45
1500	91.24	204.36	65.61	138.74	-1089.3	-825.4	28.74
1600	92.64	210.29	67.26	143.03	-1088.5	-807.8	26.37
1700	94.05	215.95	68.79	147.16	-1087.7	-790.3	24.28
1800	95.48	221.37	70.24	151.13	-1086.8	-772.8	22.43

Melting T	3151 K	Boiling T	K
Δ _{sub} H ^o	kJ	Δ _{sub} H ^o	kJ
H ₂₉₈ ^o -H ₀ ^o	11.28 kJ	Molar Vol.	2.4618 J·bar ⁻¹ 24.618 cm ³

A= -1.083E+03

B= 1.718E-01

C= 1.932E+04

12/17/91

KARELIANITE

Formula wt 149.881

 V_2O_3 : Rhombohedral crystals 298.15 to 1800 K.

Temp. K	C_p°	S_T°	$(H_T^\circ - H_{298}^\circ)/T$	$-(G_T^\circ - H_{298}^\circ)/T$	FORMATION FROM THE ELEMENTS		
					$\Delta_f H^\circ$	$\Delta_f G^\circ$	Log K_f
			$J \cdot mol^{-1} \cdot K^{-1}$		$kJ \cdot mol^{-1}$		
298.15	104.96	98.10	0.00	98.10	-1218.8	-1139.0	199.55
300	105.33	98.75	0.65	98.10	-1218.8	-1138.6	198.23
400	117.82	131.04	28.62	102.42	-1217.1	-1112.0	145.21
500	123.52	158.01	47.09	110.92	-1214.9	-1086.0	113.45
600	127.11	180.86	60.14	120.72	-1212.6	-1060.4	92.32
700	129.99	200.68	69.92	130.76	-1210.1	-1035.3	77.25
800	132.67	218.21	77.60	140.62	-1207.7	-1010.5	65.97
900	135.32	233.99	83.86	150.13	-1205.2	-986.0	57.22
1000	138.04	248.39	89.14	159.25	-1202.6	-961.7	50.24
1100	140.84	261.68	93.72	167.96	-1200.1	-937.8	44.53
1200	143.74	274.05	97.76	176.29	-1197.4	-914.1	39.79
1300	146.73	285.68	101.41	184.26	-1194.7	-890.5	35.78
1400	149.80	296.66	104.76	191.90	-1192.0	-866.3	32.36
1500	152.95	307.11	107.87	199.24	-1189.2	-844.1	29.39
1600	156.17	317.08	110.79	206.29	-1186.2	-821.3	26.81
1700	159.46	326.65	113.55	213.09	-1183.4	-798.5	24.53
1800	162.80	335.85	116.19	219.66	-1180.4	-775.9	22.52

Melting T	K	Boiling T	K
$\Delta_{fus} H^\circ$	kJ	$\Delta_{vap} H^\circ$	kJ
$H_{298}^\circ - H_0^\circ$	kJ	Molar Vol.	2.985 $J \cdot bar^{-1}$ 29.85 cm^3

A= -1.197E+03

B= 2.355E-01

C= -1.14E+06

6/11/93

TUNGSTEN DIOXIDE

Formula wt 215.849

WO₂: Monoclinic crystals 298.15 to 1800 K.

Temp. K	C _p ^o	S _T ^o	(H _T ^o -H ₂₉₈ ^o)/T J·mol ⁻¹ ·K ⁻¹	-(G _T ^o -H ₂₉₈ ^o)/T	FORMATION FROM THE ELEMENTS		
					Δ _f H ^o kJ·mol ⁻¹	Δ _f G ^o	Log K _f
298.15	55.78	50.60	0.00	50.60	-589.7	-533.9	93.53
300	55.98	50.95	0.34	50.60	-589.7	-533.5	92.89
400	63.60	68.22	15.32	52.90	-589.1	-514.9	67.24
500	67.83	82.91	25.43	57.48	-588.1	-496.4	51.86
600	70.74	95.54	32.75	62.79	-586.9	-478.2	41.63
700	73.02	106.62	38.35	68.28	-585.6	-460.2	34.34
800	74.97	116.51	42.81	73.70	-584.1	-442.4	28.89
900	76.72	125.44	46.48	78.96	-582.6	-424.8	24.65
1000	78.35	133.61	49.58	84.02	-581.1	-407.3	21.28
1100	79.90	141.15	52.27	88.88	-579.4	-390.0	18.52
1200	81.39	148.16	54.63	93.53	-577.7	-372.9	16.23
1300	82.85	154.74	56.75	97.99	-575.9	-355.9	14.30
1400	84.28	160.93	58.66	102.26	-574.0	-339.1	12.65
1500	85.69	166.79	60.42	106.37	-572.0	-322.3	11.22
1600	87.09	172.37	62.04	110.32	-570.0	-305.8	9.98
1700	88.47	177.69	63.56	114.13	-567.9	-289.3	8.89
1800	89.85	182.78	64.98	117.80	-565.8	-273.0	7.92

Melting T	K	Boiling T	K
Δ _{fus} H ^o	kJ	Δ _{vap} H ^o	kJ
H ₂₉₈ ^o -H ₀ ^o	kJ	Molar Vol.	2.003 J·bar ⁻¹ 20.03 cm ³

A= -5.776E+02

B= 1.702E-01

C= -6.726E+05

9/10/92

ZINCITE

Formula wt 81.389

ZnO: Hexagonal crystals 298.15 to 1800 K.

Temp. K	C_p°	S_T°	$(H_T^\circ - H_{298}^\circ)/T$ J·mol ⁻¹ ·K ⁻¹	$-(G_T^\circ - H_{298}^\circ)/T$	FORMATION FROM THE ELEMENTS		
					$\Delta_f H^\circ$ kJ·mol ⁻¹	$\Delta_f G^\circ$	Log K_f
298.15	40.42	43.20	0.00	43.20	-350.5	-320.4	56.12
300	40.53	43.45	0.25	43.20	-350.5	-320.2	55.75
400	44.56	55.73	10.89	44.85	-350.3	-310.1	40.49
500	46.74	65.93	17.86	48.07	-349.9	-300.1	31.35
600	48.22	74.59	22.80	51.79	-349.6	-290.2	25.26
700	49.38	82.11	26.52	55.60	-356.6	-280.2	20.91
800	50.37	88.77	29.44	59.34	-356.4	-269.4	17.59
900	51.28	94.76	31.81	62.94	-356.1	-258.5	15.00
1000	52.13	100.20	33.80	66.40	-355.8	-247.7	12.94
1100	52.94	105.21	35.51	69.71	-355.5	-236.9	11.25
1200	53.74	109.85	36.99	72.86	-470.2	-224.2	9.75
1300	54.52	114.18	38.31	75.87	-468.6	-203.7	8.18
1400	55.29	118.25	39.50	78.76	-467.0	-183.4	6.84
1500	56.06	122.09	40.57	81.52	-465.3	-163.1	5.68
1600	56.82	125.74	41.57	84.17	-463.6	-143.0	4.67
1700	57.58	129.20	42.49	86.72	-461.8	-123.0	3.78
1800	58.34	132.52	43.35	89.17	-460.0	-103.3	3.00

Melting T 2242 K

Boiling T K

 $\Delta_{fus} H^\circ$ kJ $\Delta_{vap} H^\circ$ kJ $H_{298}^\circ - H_0^\circ$ 6.93 kJMolar Vol. 1.434 J·bar⁻¹
14.34 cm³

10/7/92

BADDELEYITE

Formula wt 123.223

ZrO₂: Monoclinic crystals 298.15 to 1478 K. Tetragonal crystals 1478 to 1800 K.

Temp. K	C _p ^o	S _T ^o	(H _T ^o -H ₂₉₈ ^o)/T J·mol ⁻¹ ·K ⁻¹	-(G _T ^o -H ₂₉₈ ^o)/T	FORMATION FROM THE ELEMENTS		
					Δ _f H ^o kJ·mol ⁻¹	Δ _f G ^o	Log K _f
298.15	56.18	50.40	0.00	50.40	-1100.6	-1042.9	182.70
300	56.35	50.75	0.35	50.40	-1100.6	-1042.5	181.51
400	63.21	67.99	15.28	52.70	-1100.1	-1023.2	133.61
500	67.51	82.59	25.33	57.26	-1099.2	-1004.1	104.89
600	70.45	95.17	32.62	62.55	-1098.2	-985.1	85.76
700	72.57	106.20	38.18	68.02	-1097.1	-966.4	72.11
800	74.16	116.00	42.58	73.41	-1095.9	-947.8	61.88
900	75.38	124.80	46.16	78.64	-1094.8	-929.4	53.94
1000	76.32	132.80	49.13	83.66	-1093.7	-911.0	47.59
1100	77.06	140.11	51.64	88.47	-1092.7	-892.8	42.40
1200	77.63	146.84	53.78	93.05	-1095.5	-874.5	38.06
1300	78.08	153.07	55.64	97.43	-1094.2	-856.1	34.40
1400	78.41	158.87	57.25	101.62	-1092.9	-837.8	31.26
1478	78.62	163.13	58.37	104.75	-1092.2	-822.5	29.07
1500	74.48	168.28	62.60	105.68	-1085.8	-819.8	28.55
1600	74.48	173.09	63.34	109.75	-1085.0	-802.1	26.18
1700	74.48	177.60	64.00	113.60	-1084.4	-784.4	24.10
1800	74.48	181.86	64.58	117.28	-1083.8	-766.7	22.25
Melting T	3123 K				Boiling T		K
Δ _{sub} H ^o	kJ				Δ _{sub} H ^o		kJ
H ₂₉₈ ^o -H ₀ ^o	8.75 kJ				Molar Vol.		2.115 J·bar ⁻¹ 21.15 cm ³
A= -1.0934E+03			B= 1.81734E-01		C= -4.273.01E+05		

CHRYSOBERYL

Formula wt 126.973

BeAl₂O₄: Orthorhombic crystals 298.15 to 1800 K.

Temp. K	C _p ^o	S _T ^o	(H _T ^o -H ₂₉₈ ^o)/T	-(G _T ^o -H ₂₉₈ ^o)/T	FORMATION FROM THE ELEMENTS		
					Δ _f H ^o	Δ _f G ^o	Log K _f
			J·mol ⁻¹ ·K ⁻¹	kJ·mol ⁻¹			
298.15	105.40	66.26	0.00	66.26	-2298.5	-2176.2	381.26
300	106.01	66.91	0.65	66.26	-2298.5	-2175.5	378.78
400	130.76	101.12	30.36	70.76	-2299.3	-2134.3	278.71
500	145.88	132.05	52.07	79.98	-2298.9	-2093.0	218.66
600	155.80	159.58	68.58	91.00	-2297.8	-2051.9	178.64
700	162.63	184.14	81.57	102.58	-2296.5	-2011.1	150.07
800	167.53	206.19	92.01	114.18	-2295.1	-1970.4	128.65
900	171.18	226.15	100.62	125.53	-2293.8	-1929.9	112.01
1000	174.02	244.33	107.82	136.51	-2314.0	-1888.0	98.62
1100	176.33	261.03	113.95	147.09	-2312.7	-1845.5	87.63
1200	178.34	276.46	119.23	157.23	-2311.3	-1803.1	78.48
1300	180.18	290.81	123.85	166.96	-2309.8	-1760.7	70.75
1400	181.97	304.23	127.94	176.29	-2308.5	-1718.6	64.12
1500	183.80	316.85	131.60	185.25	-2307.0	-1676.5	58.38
1600	185.72	328.77	134.92	193.85	-2320.1	-1634.2	53.34
1700	187.80	340.09	137.97	202.12	-2318.1	-1591.3	48.89
1800	190.08	350.89	140.80	210.09	-2316.1	-1548.6	44.94

Melting T	K	Boiling T	K
Δ _{fm} H ^o	kJ	Δ _{vap} H ^o	kJ
H ₂₉₈ ^o -H ₀ ^o	13.09 kJ	Molar Vol.	3.432 J·bar ⁻¹ 34.32 cm ³

A= -2.308E+03	B= 4.208E-01	C= 5.946E+05
---------------	--------------	--------------

7/17/92

CALCIUM FERRITE

Formula wt 215.770

CaFe₂O₄: Orthorhombic crystals 298.15 to melting point 1510 K.

Temp. K	C _p ^o	S _T ^o	FORMATION FROM THE ELEMENTS				
			(H _T ^o -H ₂₉₈ ^o)/T	-(G _T ^o -H ₂₉₈ ^o)/T	Δ _f H ^o	Δ _f G ^o	Log K _f
			J·mol ⁻¹ ·K ⁻¹		kJ·mol ⁻¹		
298.15	153.65	145.40	0.00	145.40	-1520.3	-1412.4	247.44
300	153.95	146.35	0.95	145.40	-1520.3	-1411.7	245.79
400	164.04	192.25	40.65	151.59	-1518.1	-1375.8	179.66
500	168.83	229.41	65.85	163.56	-1516.0	-1340.5	140.04
600	172.11	260.50	83.30	177.20	-1514.4	-1305.6	113.66
700	174.98	287.24	96.19	191.05	-1513.4	-1270.9	94.83
800	177.81	310.79	106.22	204.58	-1513.8	-1236.1	80.71
900	180.73	331.90	114.33	217.57	-1514.3	-1201.4	69.73
1000	183.77	351.10	121.12	229.98	-1516.4	-1166.6	60.93
1100	186.94	368.76	126.96	241.80	-1520.3	-1131.4	53.72
1200	190.24	385.17	132.10	253.07	-1530.6	-1095.3	47.68
1300	193.66	400.53	136.70	263.83	-1529.0	-1059.1	42.55
1400	197.17	415.01	140.89	274.12	-1527.2	-1023.0	38.17
1500	200.78	428.74	144.77	283.97	-1525.4	-987.1	34.37

Melting T	1510 K	Boiling T	K
Δ _{sub} H ^o	108.2 kJ	Δ _{sub} H ^o	kJ
H ₂₉₈ ^o -H ₀ ^o	25.42 kJ	Molar Vol.	4.498 J·bar ⁻¹ 44.98 cm ³

A= -1.519E+03

B= 3.537E-01

C= 1.473E+05

5/15/92

DICALCIUM FERRITE

Formula wt 271.847

Ca₂Fe₂O₅: Orthorhombic crystals 298.15 to melting point 1750 K.

Temp. K	C _p ^o	S _T ^o	(H _T ^o -H ₂₉₈ ^o)/T	-(G _T ^o -H ₂₉₈ ^o)/T	FORMATION FROM THE ELEMENTS		
					Δ _f H ^o	Δ _f G ^o	Log K _f
			J·mol ⁻¹ ·K ⁻¹		kJ·mol ⁻¹		
298.15	192.91	188.80	0.00	188.80	-2138.3	-1999.9	350.37
300	193.61	190.00	1.19	188.80	-2138.3	-1999.1	348.06
400	217.91	249.55	52.79	196.76	-2135.4	-1953.1	255.04
500	228.76	299.48	87.02	212.45	-2131.9	-1907.9	199.31
600	234.54	341.74	111.17	230.57	-2128.7	-1863.4	162.22
700	238.04	378.18	129.06	249.12	-2126.1	-1819.4	135.76
800	240.40	410.13	142.84	267.29	-2126.2	-1775.5	115.92
900	242.13	438.55	153.78	284.77	-2125.7	-1731.7	100.50
1000	243.51	464.13	162.69	301.45	-2127.3	-1687.8	88.16
1100	244.66	487.40	170.09	317.31	-2131.2	-1643.7	78.05
1200	245.69	508.73	176.35	332.38	-2149.8	-1598.0	69.56
1300	246.63	528.44	181.72	346.72	-2148.0	-1552.1	62.36
1400	247.52	546.74	186.39	360.36	-2146.4	-1506.4	56.20
1500	248.37	563.85	190.49	373.36	-2144.9	-1460.7	50.86
1600	249.20	579.91	194.13	385.77	-2143.7	-1415.1	46.20
1700	250.02	595.04	197.40	397.64	-2144.4	-1369.5	42.08
Melting T	1750 K			Boiling T		K	
Δ _{fu} H ^o	31.65 kJ			Δ _{vap} H ^o		kJ	
H ₂₉₈ ^o -H ₀ ^o	25.42 kJ			Molar Vol.		6.718 J·bar ⁻¹ 67.18 cm ³	
A= -2.135E+03			B= 4.491E-01		C= 1.854E+05		

7/22/92

PEROVSKITE

Formula wt 135.956

CaTiO₃: Orthorhombic crystals 1530 K; cubic crystals 1530 to 1800 K.

Temp. K	C _p ^o	S _T ^o	(H _T ^o -H ₂₉₈ ^o)/T	-(G _T ^o -H ₂₉₈ ^o)/T	FORMATION FROM THE ELEMENTS		
					Δ _f H ^o	Δ _f G ^o	Log K _f
			J·mol ⁻¹ ·K ⁻¹		kJ·mol ⁻¹		
298.15	97.65	93.64	0.00	93.64	-1660.6	-1574.8	275.89
300	98.17	94.25	0.60	93.64	-1660.6	-1574.3	274.10
400	114.28	125.13	27.38	97.74	-1659.5	-1545.6	201.83
500	119.98	151.34	45.42	105.92	-1657.8	-1517.4	158.51
600	122.60	173.47	58.09	115.38	-1656.2	-1489.4	129.66
700	124.31	192.50	67.43	125.07	-1654.8	-1461.7	109.07
800	125.83	209.20	74.63	134.56	-1654.4	-1434.1	93.64
900	127.43	224.11	80.41	143.70	-1653.4	-1406.7	81.64
1000	129.21	237.62	85.20	152.43	-1652.7	-1379.3	72.04
1100	131.20	250.03	89.29	160.74	-1652.4	-1352.0	64.20
1200	133.39	261.54	92.87	168.67	-1664.1	-1323.9	57.63
1300	135.76	272.31	96.08	176.23	-1662.5	-1295.6	52.06
1400	138.31	282.46	99.00	183.46	-1660.8	-1267.5	47.29
1500	141.01	292.10	101.71	190.38	-1658.9	-1239.4	43.16
1600	134.01	302.46	105.26	197.20	-1655.3	-1211.8	39.56
1700	134.01	310.58	106.95	203.63	-1654.4	-1184.1	36.38
1800	134.01	318.28	108.47	209.81	-1802.2	-1154.3	33.50
Melting T	2188 K				Boiling T	K	
Δ _m H ^o	kJ				Δ _{vap} H ^o	kJ	
H ₂₉₈ ^o -H ₀ ^o	kJ				Molar Vol.	3.363	J·bar ⁻¹
						33.63	cm ³
A= -1.657E+03			B= 2.783E-01		C= -4.73E+04		

5/15/92

HERCYNITE

Formula wt 173.808

FeAl₂O₄: Cubic crystals 298.15 to 1400 K.

Temp. K	C _p ^o	S _T ^o	(H _T ^o -H ₂₉₈ ^o)/T J·mol ⁻¹ ·K ⁻¹	-(G _T ^o -H ₂₉₈ ^o)/T	FORMATION FROM THE ELEMENTS		
					Δ _f H ^o kJ·mol ⁻¹	Δ _f G ^o	Log K _f
298.15	128.91	117.00	0.00	117.00	-1950.5	-1838.1	322.03
300	129.38	117.80	0.80	117.00	-1950.5	-1837.4	319.92
400	148.11	157.85	35.52	122.34	-1950.1	-1799.7	235.02
500	159.35	192.20	59.24	132.96	-1948.9	-1762.3	184.10
600	167.07	221.97	76.60	145.37	-1947.5	-1725.1	150.18
700	172.83	248.18	89.95	158.22	-1946.0	-1688.1	125.97
800	177.38	271.56	100.61	170.95	-1944.7	-1651.4	107.82
900	181.11	292.68	109.35	183.33	-1943.9	-1614.7	93.71
1000	184.28	311.93	116.69	195.24	-1965.2	-1576.7	82.36
1100	187.01	329.62	122.96	206.66	-1965.7	-1537.8	73.02
1200	189.43	346.00	128.40	217.60	-1965.2	-1498.9	65.25
1300	191.59	361.25	133.18	228.07	-1963.1	-1460.1	58.67
1400	193.55	375.52	137.42	238.10	-1961.0	-1421.6	53.04

Melting T	K	Boiling T	K
Δ _{fusion} H ^o	kJ	Molar Vol.	4.075 J·bar ⁻¹ 40.75 cm ³
H ₂₉₈ ^o -H ₀ ^o	kJ		

A= -1.955E+03 B= 3.799E-01 C= 3.842E+05

7/17/92

CHROMITE

Formula wt 223.837

FeCr₂O₄: Cubic crystals 298.15 to 1800 K.

Temp. K	C _p ^o	S _T ^o	(H _T ^o -H ₂₉₈ ^o)/T J·mol ⁻¹ ·K ⁻¹	-(G _T ^o -H ₂₉₈ ^o)/T	FORMATION FROM THE ELEMENTS		
					Δ _f H ^o kJ·mol ⁻¹	Δ _f G ^o	Log K _f
298.15	133.58	146.00	0.00	146.00	-1445.5	-1344.5	235.55
300	133.95	146.83	0.82	146.00	-1445.5	-1343.9	233.99
400	149.91	187.72	36.25	151.47	-1444.7	-1310.1	171.08
500	160.48	222.38	60.10	162.27	-1443.4	-1276.6	133.36
600	167.91	252.33	77.49	174.84	-1441.7	-1243.4	108.25
700	173.37	278.64	90.81	187.83	-1440.1	-1210.5	90.33
800	177.55	302.08	101.40	200.67	-1438.6	-1177.8	76.90
900	180.85	323.19	110.05	213.13	-1437.5	-1145.3	66.47
1000	183.55	342.39	117.27	225.11	-1437.3	-1112.8	58.13
1100	185.84	359.99	123.40	236.59	-1438.0	-1080.4	51.30
1200	187.86	376.25	128.69	247.56	-1438.3	-1047.8	45.62
1300	189.69	391.36	133.32	258.04	-1437.3	-1015.3	40.80
1400	191.42	405.48	137.40	268.08	-1436.6	-982.9	36.67
1500	193.10	418.74	141.06	277.68	-1436.3	-950.5	33.10
1600	194.77	431.26	144.37	286.89	-1436.4	-918.1	29.97
1700	196.47	443.12	147.38	295.74	-1437.8	-885.7	27.21
1800	198.22	454.40	150.16	304.24	-1439.1	-853.2	24.76

Melting T	K	Boiling T	K
Δ _{fus} H ^o	kJ	Δ _{vap} H ^o	kJ
H ₂₉₈ ^o -H ₀ ^o	kJ	Molar Vol.	4.401 J·bar ⁻¹ 44.01 cm ³

A= -1.437E+03

B= 3.242E-01

C= -4.01E+05

5/15/92

ILMENITE

Formula wt 151.725

FeTiO₃: Rhombohedral crystals 298.15 to 1640 K.

Temp. K	C _p ^o	S _T ^o	(H _T ^o -H ₂₉₈ ^o)/T	-(G _T ^o -H ₂₉₈ ^o)/T	FORMATION FROM THE ELEMENTS		
					Δ _f H ^o	Δ _f G ^o	Log K _f
			J·mol ⁻¹ ·K ⁻¹		kJ·mol ⁻¹		
298.15	99.18	108.90	0.00	108.90	-1232.0	-1155.0	202.43
300	99.47	109.51	0.61	108.90	-1232.0	-1155.0	201.10
400	111.62	139.94	26.97	112.97	-1231.1	-1129.5	147.49
500	119.20	165.72	44.72	121.01	-1229.7	-1104.2	115.35
600	124.35	187.94	57.58	130.36	-1228.1	-1079.2	93.95
700	128.16	207.41	67.41	140.00	-1226.6	-1054.6	78.69
800	131.26	224.73	75.20	149.53	-1225.2	-1030.1	67.26
900	134.02	240.35	81.58	158.77	-1224.1	-1005.8	58.37
1000	136.71	254.61	86.96	167.65	-1223.6	-981.5	51.27
1100	139.50	267.77	91.61	176.16	-1224.1	-957.3	45.46
1200	142.50	280.03	95.72	184.31	-1227.7	-933.0	40.61
1300	145.81	291.57	99.45	192.12	-1225.1	-908.5	36.50
1400	149.48	302.51	102.89	199.62	-1222.3	-884.2	32.99
1500	153.58	312.96	106.13	206.83	-1219.4	-860.2	29.95
1600	158.15	323.01	109.23	213.78	-1216.3	-836.3	27.30

Melting T	K	Boiling T	K
Δ _m H ^o	kJ	Δ _{vap} H ^o	kJ
H ₂₉₈ ^o -H ₀ ^o	16.992 kJ	Molar Vol.	3.169 J·bar ⁻¹ 31.69 cm ³

A= -1.224E+03

B= 2.424E-01

C= -3.82E-01

5/15/92

ULVOSPINEL

Formula wt 223.572

 Fe_2TiO_4 : Cubic crystals 298.15 to 1800 K.

Temp. K	C_p°	S_T°	$(H_T^\circ - H_{298}^\circ)/T$	$-(G_T^\circ - H_{298}^\circ)/T$	FORMATION FROM THE ELEMENTS		
					$\Delta_f H^\circ$	$\Delta_f G^\circ$	Log K_f
	J·mol ⁻¹ ·K ⁻¹		kJ·mol ⁻¹				
298.15	142.27	180.40	0.00	180.40	-1493.8	-1399.9	245.26
300	142.86	181.28	0.88	180.40	-1493.8	-1399.4	243.64
400	160.79	225.33	39.04	186.29	-1492.2	-1368.1	178.65
500	167.80	262.05	64.17	197.88	-1490.3	-1337.3	139.70
600	172.68	293.08	81.85	211.22	-1488.6	-1306.8	113.77
700	177.71	320.07	95.18	224.89	-1487.2	-1276.6	95.26
800	183.47	344.16	105.85	238.32	-1485.9	-1246.6	81.40
900	190.06	366.15	114.83	251.31	-1485.1	-1216.8	70.62
1000	197.44	386.55	122.72	263.83	-1485.4	-1187.0	62.00
1100	205.52	405.74	129.87	275.87	-1486.9	-1157.0	54.94
1200	214.21	423.99	136.53	287.45	-1490.4	-1127.0	49.05
1300	223.43	441.50	142.86	298.63	-1485.5	-1096.9	44.07
1400	233.11	458.41	148.96	309.45	-1480.1	-1067.2	39.82
1500	243.18	474.83	154.90	319.93	-1473.9	-1037.9	36.14
1600	253.60	490.86	160.74	330.11	-1467.1	-1009.0	32.94
1700	264.33	506.55	166.52	340.03	-1461.5	-980.6	30.13
1800	275.32	521.97	172.26	349.71	-1454.1	-952.5	27.64

Melting T	K	Boiling T	K
$\Delta_{\text{m}} H^\circ$	kJ	$\Delta_{\text{vap}} H^\circ$	kJ
$H_{298}^\circ - H_0^\circ$	kJ	Molar Vol.	4.682 J·bar ⁻¹ 46.82 cm ³

A= -1.482E+03

B= 2.956E-01

C= -5.73E+05

SPINEL

Formula wt 142.266

MgAl₂O₄: Cubic crystals 298.15 to 1800 K.

Temp. K	C _p ^o	S _T ^o	(H _T ^o -H ₂₉₈ ^o)/T	-(G _T ^o -H ₂₉₈ ^o)/T	FORMATION FROM THE ELEMENTS		
					Δ _f H ^o	Δ _f G ^o	Log K _f
			J·mol ⁻¹ ·K ⁻¹		kJ·mol ⁻¹		
298.15	115.94	88.70	0.00	88.70	-2299.1	-2176.6	381.32
300	116.46	89.42	0.72	88.70	-2299.1	-2175.9	378.84
400	137.26	126.06	32.51	93.56	-2299.8	-2134.6	278.74
500	149.86	158.14	54.81	103.34	-2299.5	-2093.3	218.68
600	158.57	186.28	71.41	114.87	-2298.6	-2052.1	178.65
700	165.13	211.24	84.35	126.89	-2297.5	-2011.2	150.07
800	170.33	233.64	94.78	138.85	-2296.5	-1970.3	128.65
900	174.63	253.96	103.42	150.53	-2295.3	-1929.7	111.99
1000	178.29	272.55	110.73	161.82	-2324.3	-1886.9	98.56
1100	181.48	289.70	117.02	172.67	-2323.0	-1843.2	87.52
1200	184.31	305.61	122.51	183.10	-2321.6	-1799.7	78.33
1300	186.85	320.46	127.37	193.10	-2320.0	-1756.1	70.56
1400	189.17	334.40	131.70	202.70	-2445.7	-1709.8	63.79
1500	191.29	347.52	135.60	211.92	-2442.3	-1657.3	57.71
1600	193.27	359.93	139.15	220.79	-2438.9	-1605.1	52.40
1700	195.12	371.70	142.38	229.32	-2435.3	-1553.0	47.72
1800	196.85	382.91	145.36	237.54	-2431.6	-1501.2	43.56

Melting T	K	Boiling T	K
Δ _{fus} H ^o	kJ	Δ _{vap} H ^o	kJ
H ₂₉₈ ^o -H ₀ ^o	15.41 kJ	Molar Vol.	3.971 J·bar ⁻¹ 39.71 cm ³

A= -2.3446E+03

B= 4.598E-01

C= 3.114E+06

5/21/93

MAGNESIOCHROMITE (picrochromite)

Formula wt 192.295

MgCr₂O₄: Cubic crystals 298.15 to 1800 K.

Temp. K	C _p ^o	S _T ^o	(H _T ^o -H ₂₉₈ ^o)/T	-(G _T ^o -H ₂₉₈ ^o)/T	FORMATION FROM THE ELEMENTS		
					Δ _f H ^o	Δ _f G ^o	Log K _f
			J·mol ⁻¹ ·K ⁻¹		kJ·mol ⁻¹		
298.15	126.82	106.00	0.00	106.00	-1783.6	-1669.1	292.41
300	127.37	106.79	0.78	106.00	-1783.6	-1668.4	290.48
400	147.88	146.60	35.31	111.29	-1783.2	-1630.0	212.85
500	158.71	180.87	59.00	121.87	-1781.8	-1591.8	166.29
600	165.47	210.44	76.22	134.22	-1780.1	-1554.0	135.28
700	170.18	236.32	89.32	147.00	-1778.2	-1516.4	113.16
800	173.72	259.29	99.66	159.63	-1776.5	-1479.2	96.58
900	176.54	279.92	108.05	171.87	-1774.9	-1442.1	83.70
1000	178.86	298.64	115.02	183.62	-1782.1	-1404.5	73.36
1100	180.85	315.79	120.92	194.87	-1781.2	-1366.8	64.90
1200	182.60	331.60	125.99	205.61	-1780.4	-1329.1	57.85
1300	184.16	346.28	130.40	215.87	-1779.9	-1291.6	51.89
1400	185.57	359.98	134.29	225.68	-1907.2	-1250.9	46.67
1500	186.88	372.83	137.76	235.07	-1905.9	-1204.0	41.93
1600	188.09	384.93	140.86	244.06	-1905.0	-1157.2	37.78
1700	189.23	396.36	143.68	252.69	-1904.5	-1110.5	34.12
1800	190.31	407.21	146.24	260.97	-1904.3	-1063.8	30.87

Melting T	K	Boiling T	K
Δ _{fm} H ^o	kJ	Δ _{vp} H ^o	kJ
H ₂₉₈ ^o -H ₀ ^o	kJ	Molar Vol.	4.356 J·bar ⁻¹ 43.56 cm ³

A= -1.7945E+03	B= 3.960E-01	C= 1.0556E+00
----------------	--------------	---------------

MAGNESIOFERRITE

Formula wt 199.997

MgFe₂O₄: Cubic (α) crystals 298.15 to 665 K. Cubic (β) crystals 665 to 1230 K. γ-crystals 1230 to 1800 K.

Temp. K	C _p ^o	S _T ^o	(H _T ^o -H ₂₉₈ ^o)/T	-(G _T ^o -H ₂₉₈ ^o)/T	FORMATION FROM THE ELEMENTS		
					Δ _f H ^o	Δ _f G ^o	Log K _f
			J·mol ⁻¹ ·K ⁻¹		kJ·mol ⁻¹		
298.15	143.72	121.80	0.00	121.80	-1441.5	-1329.6	232.93
300	144.10	122.62	0.71	121.91	-1441.5	-1328.9	231.38
400	164.30	167.06	39.35	127.71	-1439.7	-1291.6	168.66
500	180.83	205.54	66.02	139.52	-1437.0	-1254.9	131.09
600	196.01	239.86	86.43	153.43	-1433.4	-1218.8	106.10
700	187.13	269.98	102.86	167.12	-1429.3	-1182.7	88.25
800	188.40	295.05	113.47	181.58	-1427.4	-1147.6	74.93
900	189.68	317.31	121.87	195.44	-1426.5	-1112.7	64.58
1000	190.95	337.36	128.71	208.65	-1435.8	-1077.1	56.26
1100	192.23	355.62	134.43	221.19	-1438.4	-1041.0	49.43
1200	193.50	372.40	139.30	233.10	-1439.6	-1004.9	43.74
1300	180.93	388.05	143.60	244.45	-1437.5	-968.8	38.93
1400	186.64	401.67	146.47	255.20	-1564.3	-929.6	34.68
1500	192.36	414.74	149.34	265.40	-1561.9	-884.4	30.80
1600	198.07	427.34	152.21	275.13	-1559.3	-839.3	27.40
1700	203.79	439.52	155.07	284.45	-1558.1	-794.3	24.40
1800	209.50	451.33	157.94	293.39	-1555.6	-749.4	21.75

Melting T	K	Boiling T	K
Δ _m H ^o	kJ	Δ _{vp} H ^o	kJ
H ₂₉₈ ^o -H ₀ ^o	kJ	Molar Vol.	4.457 J·bar ⁻¹ 44.57 cm ³

A= -1.464E+03

B= 3.886E-01

C= 1.938E+06

5/20/93

GEIKIELITE

Formula wt 120.183

MgTiO₃: Rhombohedral crystals 298.15 to 1800 K.

Temp. K	C _p ^o	S _T ^o	(H _T ^o -H ₂₉₈ ^o)/T	-(G _T ^o -H ₂₉₈ ^o)/T	FORMATION FROM THE ELEMENTS		
					Δ _f H ^o	Δ _f G ^o	Log K _f
			J·mol ⁻¹ ·K ⁻¹	kJ·mol ⁻¹			
298.15	93.03	74.64	0.00	74.64	-1572.8	-1484.4	260.05
300	93.37	75.22	0.57	74.64	-1572.8	-1483.8	258.35
400	106.87	104.13	25.64	78.49	-1572.3	-1454.2	189.90
500	114.55	128.87	42.72	86.16	-1571.2	-1424.8	148.85
600	119.39	150.22	55.12	95.10	-1569.8	-1395.7	121.50
700	122.69	168.88	64.55	104.33	-1568.4	-1366.8	101.99
800	125.10	185.43	71.98	113.46	-1566.9	-1338.1	87.37
900	127.01	200.28	77.99	122.29	-1565.5	-1309.6	76.00
1000	128.65	213.75	82.97	130.77	-1572.9	-1280.5	66.88
1100	130.19	226.08	87.20	138.89	-1572.0	-1251.3	59.42
1200	131.72	237.47	90.84	146.63	-1575.1	-1222.0	53.19
1300	133.32	248.08	94.05	154.03	-1573.7	-1192.7	47.92
1400	135.06	258.02	96.91	161.11	-1699.6	-1160.3	43.29
1500	136.97	267.41	99.52	167.89	-1696.7	-1121.9	39.07
1600	139.09	276.31	101.93	174.39	-1693.7	-1083.6	35.38
1700	141.44	284.81	104.18	180.63	-1690.7	-1045.5	32.12
1800	144.04	292.97	106.32	186.65	-1687.6	-1007.7	29.24

Melting T	K	Boiling T	K
Δ _{fusion} H ^o	kJ	Δ _{evap} H ^o	kJ
H ₂₉₈ ^o -H ₀ ^o	13.64 kJ	Molar Vol.	3.086 J·bar ⁻¹ 30.86 cm ³

A= -1.601E+03

B= 3.214E-01

C= 2.118E+06

5/20/92

PYROPHANITE

Formula wt 150.816

MnTiO₃: Rhombohedral crystals 298.15 to 1600 K.

Temp. K	C _p ^o	S _T ^o	(H _T ^o -H ₂₉₈ ^o)/T J·mol ⁻¹ ·K ⁻¹	-(G _T ^o -H ₂₉₈ ^o)/T	FORMATION FROM THE ELEMENTS		
					Δ _f H ^o kJ·mol ⁻¹	Δ _f G ^o	Log K _f
298.15	99.86	104.90	0.00	104.90	-1360.1	-1280.9	224.41
300	100.18	105.52	0.62	104.90	-1360.1	-1280.4	222.94
400	111.74	136.14	27.14	109.00	-1359.2	-1254.0	163.75
500	117.59	161.76	44.70	117.06	-1358.0	-1227.8	128.27
600	121.20	183.54	57.17	126.37	-1356.7	-1201.9	104.63
700	123.74	202.43	66.51	135.92	-1355.5	-1176.2	87.77
800	125.71	219.08	73.79	145.29	-1354.3	-1150.7	75.13
900	127.36	233.99	79.65	154.34	-1353.4	-1125.3	65.31
1000	128.80	247.48	84.50	162.99	-1354.8	-1099.9	57.45
1100	130.11	259.82	88.58	171.24	-1354.2	-1074.5	51.02
1200	131.33	271.19	92.10	179.10	-1357.8	-1048.9	45.66
1300	132.48	281.75	95.16	186.59	-1356.8	-1023.2	41.11
1400	133.59	291.61	97.86	193.75	-1358.2	-997.6	37.22
1500	134.66	300.86	100.28	200.58	-1359.8	-971.7	33.84
1600	135.71	309.59	102.46	207.13	-1371.7	-945.2	30.86

Melting T	K	Boiling T	K
Δ _{fus} H ^o	kJ	Δ _{vap} H ^o	kJ
H ₂₉₈ ^o -H ₀ ^o	16.69 kJ	Molar Vol.	3.277 J·bar ⁻¹ 32.77 cm ³

A= -1.355E+03

B= 2.557E-01

C= -1.72E+05

2/24/94

TREVORITE

Formula wt 234.382

NiFe₂O₄: Cubic crystals 298.15 to 1000 K.

Temp. K	C _p ^o	S _T ^o	(H _T ^o -H ₂₉₈ ^o)/T	-(G _T ^o -H ₂₉₈ ^o)/T	FORMATION FROM THE ELEMENTS		
					Δ _f H ^o	Δ _f G ^o	Log K _f
			J·mol ⁻¹ ·K ⁻¹		kJ·mol ⁻¹		
298.15	146.87	140.90	0.00	140.90	-1070.5	-965.1	169.08
300	147.18	141.81	0.91	140.90	-1070.5	-964.5	167.93
400	164.04	186.46	39.58	146.88	-1068.8	-929.4	121.36
500	181.00	224.88	66.17	158.71	-1066.4	-894.8	93.47
600	198.00	259.38	86.72	172.66	-1063.2	-860.7	74.93
700	215.02	291.18	103.83	187.35	-1059.0	-827.3	61.73
800	232.05	321.01	118.80	202.21	-1053.7	-795.0	51.91
900	249.09	349.32	132.33	217.00	-1047.6	-762.5	44.25
1000	266.13	376.45	144.86	231.59	-1041.6	-731.1	38.19

Melting T	K	Boiling T	K
Δ _m H ^o	kJ	Δ _{vap} H ^o	kJ
H ₂₉₈ ^o -H ₀ ^o	kJ	Molar Vol.	4.365 J·bar ⁻¹ 43.65 cm ³

A= -1.053E+03

B= 3.232E-01

C= -8.04E+05

5/26/93

FRANKLINITE

Formula wt 241.082

ZnFe₂O₄: Tetragonal crystals 298.15 to 600 K.

Temp. K	C _p ^o	S _T ^o	(H _T ^o -H ₂₉₈ ^o)/T	-(G _T ^o -H ₂₉₈ ^o)/T	FORMATION FROM THE ELEMENTS		
					Δ _f H ^o	Δ _f G ^o	Log K _f
			J·mol ⁻¹ ·K ⁻¹	kJ·mol ⁻¹			
298.15	193.37	150.70	0.00	150.70	-1188.1	-1082.1	189.58
300	193.61	151.90	1.19	150.70	-1188.0	-1081.5	188.30
400	203.23	209.05	50.62	158.43	-1181.9	-1046.9	136.71
500	209.32	255.09	81.78	173.31	-1175.7	-1013.9	105.91
600	214.01	293.68	103.44	190.24	-1169.9	-982.0	85.49

Melting T	K	Boiling T	K
Δ _m H ^o	kJ	Δ _{vap} H ^o	kJ
H ₂₉₈ ^o -H ₀ ^o	kJ	Molar Vol.	4.494 J·bar ⁻¹ 44.94 cm ³
A= -1.167E+03	B= 3.112E-01	C= -7.364E+05	

2/24/94

ZINC TITANIUM SPINEL

Formula wt 242.658

 Zn_2TiO_4 : Tetragonal crystals 298.15 to 1800 K.

Temp. K	C_p°	S_T°	$(H_T^\circ - H_{298}^\circ)/T$ J·mol ⁻¹ ·K ⁻¹	$-(G_T^\circ - H_{298}^\circ)/T$	FORMATION FROM THE ELEMENTS		
					$\Delta_f H^\circ$ kJ·mol ⁻¹	$\Delta_f G^\circ$	Log K_f
298.15	133.58	143.10	0.00	143.10	-1652.1	-1538.4	269.52
300	134.01	143.93	0.83	143.10	-1652.1	-1537.7	267.74
400	151.80	185.13	36.53	148.60	-1651.4	-1499.7	195.83
500	163.31	220.32	60.81	159.51	-1649.9	-1461.9	152.72
600	171.49	250.85	78.61	172.25	-1647.9	-1424.5	124.01
700	177.64	277.77	92.33	185.44	-1660.3	-1387.3	103.52
800	182.45	301.82	103.31	198.51	-1658.2	-1348.4	88.04
900	186.31	323.54	112.32	211.21	-1655.8	-1309.8	76.02
1000	189.48	343.34	119.89	223.45	-1653.3	-1271.5	66.42
1100	192.12	361.52	126.34	235.19	-1650.9	-1233.5	58.57
1200	194.36	378.34	131.91	246.42	-1882.6	-1191.6	51.87
1300	196.26	393.97	136.79	257.18	-1877.3	-1134.2	45.57
1400	197.90	408.58	141.10	267.48	-1872.1	-1077.3	40.19
1500	199.31	422.28	144.93	277.35	-1866.8	-1020.7	35.54
1600	200.54	435.18	148.37	286.81	-1861.6	-964.4	31.48
1700	201.60	447.37	151.47	295.90	-1856.4	-908.5	27.91
1800	202.54	458.93	154.28	304.64	-1851.3	-852.9	24.75

Melting T	K	Boiling T	K
$\Delta_{fus} H^\circ$	kJ	$\Delta_{vap} H^\circ$	kJ
$H_{298}^\circ - H_0^\circ$	kJ	Molar Vol.	4.558 J·bar ⁻¹ 45.58 cm ³

A= -1.751E+03

B= 4.850E-01

C= 6.790E+06

9/11/92

BROMARGYRITE

Formula wt 187.772

AgBr: Cubic crystals 298.15 to melting point 703 K. Liquid 703 to 1000 K.

Temp. K	C_p°	S_T°	$(H_T^\circ - H_{298}^\circ)/T$	$-(G_T^\circ - H_{298}^\circ)/T$	FORMATION FROM THE ELEMENTS		
					$\Delta_f H^\circ$	$\Delta_f G^\circ$	Log K_f
			$J \cdot mol^{-1} \cdot K^{-1}$	$kJ \cdot mol^{-1}$			
298.15	52.38	107.10	0.00	107.10	-100.4	-97.0	16.99
300	52.50	107.42	0.32	107.10	-100.4	-96.9	16.88
400	58.94	123.41	14.17	109.24	-114.6	-92.8	12.11
500	65.39	137.25	23.77	113.48	-112.9	-87.5	9.14
600	71.83	149.75	31.24	118.50	-110.5	-82.6	7.19
700	78.27	161.30	37.50	123.80	-107.6	-78.2	5.83
703	78.46	162.63	37.70	124.93	-107.5	-78.3	5.82
800	62.34	182.76	52.14	130.62	-96.8	-75.4	4.92
900	62.34	190.08	53.28	136.80	-95.3	-72.7	4.22
1000	62.34	196.65	54.18	142.47	-93.9	-70.3	3.67

Melting T	703 K	Boiling T	K
$\Delta_{fus} H^\circ$	9.16 kJ	$\Delta_{vap} H^\circ$	kJ
$H_{298}^\circ - H_0^\circ$	kJ	Molar Vol.	2.899 $J \cdot bar^{-1} cm^3$ 28.99
A=	-1.0054E+02	B=	3.173E-02
		C=	-5.577E+05

5/20/93

POTASSIUM BROMIDE

Formula wt 119.002

KBr: Cubic crystals 298.15 to melting point 1007 K. Liquid 1007 to boiling point 1671 K.

Temp. K	C_p°	S_T°	$(H_T^\circ - H_{298}^\circ)/T$	$-(G_T^\circ - H_{298}^\circ)/T$	FORMATION FROM THE ELEMENTS		
					$\Delta_f H^\circ$	$\Delta_f G^\circ$	Log K_f
			J·mol ⁻¹ ·K ⁻¹		kJ·mol ⁻¹		
298.15	52.29	95.90	0.00	95.90	-393.8	-380.4	66.65
300	52.34	96.22	0.32	95.90	-393.8	-380.3	66.22
400	53.86	111.54	13.56	97.98	-411.2	-372.3	48.61
500	54.79	123.65	21.71	101.94	-410.7	-362.6	37.88
600	56.20	133.75	27.33	106.42	-410.1	-353.0	30.73
700	58.21	142.56	31.59	110.97	-409.2	-343.6	25.64
800	60.75	150.49	35.07	115.42	-408.2	-334.3	21.83
900	63.74	157.82	38.09	119.73	-406.8	-325.1	18.87
1000	67.09	164.70	40.82	123.89	-405.2	-316.1	16.51
1100	69.87	196.66	66.62	130.04	-456.6	-305.1	14.49
1200	69.87	202.73	66.89	135.84	-453.6	-291.4	12.68
1300	69.87	208.32	67.12	141.20	-450.6	-278.0	11.17
1400	69.87	213.50	67.32	146.18	-447.6	-264.9	9.88
1500	69.87	218.32	67.49	150.83	-444.6	-251.9	8.77
1600	69.87	222.83	67.64	155.19	-441.6	-239.2	7.81

Melting T	1007 K	Boiling T	K
$\Delta_{\text{m}} H^\circ$	25.5 kJ	$\Delta_{\text{vap}} H^\circ$	kJ
$H_{298}^\circ - H_0^\circ$	12.21 kJ	Molar Vol.	4.328 J·bar ⁻¹ 43.28 cm ³

A= -4.330E+02

B= 1.198E-01

C= 1.642E+06

CHLORARGYRITE

Formula wt 143.321

AgCl: Cubic crystals 298.15 to melting point 728 K; liquid 728 to 1000 K.

Temp. K	C_p°	S_T°	$(H_T^\circ - H_{298}^\circ)/T$ J·mol ⁻¹ ·K ⁻¹	$-(G_T^\circ - H_{298}^\circ)/T$	FORMATION FROM THE ELEMENTS		
					$\Delta_f H^\circ$ kJ·mol ⁻¹	$\Delta_f G^\circ$	Log K_f
298.15	50.79	96.23	0.00	96.23	-127.1	-109.8	19.24
300	50.95	96.54	0.31	96.23	-127.1	-109.7	19.10
400	56.65	112.08	13.77	98.31	-125.9	-104.1	13.59
500	59.70	125.08	22.68	102.40	-124.5	-98.8	10.32
600	61.71	136.15	29.03	107.13	-122.9	-93.8	8.17
700	63.22	145.78	33.81	111.98	-121.2	-89.1	6.65
728	63.81	148.97	34.93	114.04	-120.7	-88.3	6.33
800	66.94	172.34	53.92	118.42	-106.4	-85.9	5.61
900	66.94	180.20	55.37	124.83	-104.4	-83.5	4.84
1000	66.94	187.27	56.52	130.75	-102.5	-81.3	4.25

Melting T	728 K	Boiling T	K
$\Delta_{\text{fus}} H^\circ$	1289 kJ	$\Delta_{\text{vap}} H^\circ$	kJ
$H_{298}^\circ - H_0^\circ$	12.033 kJ	Molar Vol.	2.573 J·bar ⁻¹ 25.73 cm ³

A= -1.102E+02

B= 3.084E-02

C= -8.08E+05

5/20/92

HYDROPHILITE

Formula wt 110.983

CaCl₂: Orthorhombic crystals 298.15 to 1045 K. Liquid 1045 to 1800 K.

Temp. K	C _p ^o	S _T ^o	FORMATION FROM THE ELEMENTS				
			(H _T ^o -H ₂₉₈ ^o)/T J·mol ⁻¹ ·K ⁻¹	-(G _T ^o -H ₂₉₈ ^o)/T	Δ _f H ^o kJ·mol ⁻¹	Δ _f G ^o	Log K _f
298.15	72.83	104.60	0.00	104.60	-795.8	-747.7	130.99
300	72.93	105.05	0.45	104.60	-795.8	-747.4	130.13
400	75.71	126.50	18.99	107.51	-794.4	-731.5	95.52
500	76.86	143.52	30.46	113.07	-793.1	-715.9	74.78
600	78.00	157.63	38.28	119.35	-792.0	-700.5	60.99
700	79.45	169.76	44.06	125.71	-790.9	-685.4	51.14
800	81.26	180.48	48.59	131.89	-790.8	-670.3	43.76
900	83.40	190.18	52.34	137.84	-789.8	-655.3	38.03
1000	85.81	199.09	55.56	143.53	-788.9	-640.4	33.45
1100	102.53	235.46	85.12	150.34	-758.7	-627.1	29.78
1200	102.53	244.37	86.57	157.80	-764.4	-614.6	26.75
1300	102.53	252.58	87.80	164.78	-761.4	-602.2	24.20
1400	102.53	260.17	88.85	171.32	-758.4	-590.1	22.02
1500	102.53	267.24	89.76	177.48	-755.4	-578.2	20.13
1600	102.53	273.86	90.56	183.30	-752.5	-566.4	18.49
1700	102.53	280.07	91.26	188.81	-749.5	-554.9	17.05
1800	102.53	285.93	91.89	194.04	-895.3	-541.4	15.71

Melting T	1045 K	Boiling T	K
Δ _{fus} H ^o	28.54 kJ	Δ _{vap} H ^o	kJ
H ₂₉₈ ^o -H ₀ ^o	15.27 kJ	Molar Vol.	5.075 J·bar ⁻¹ 50.75 cm ³

A= -7.714E+02

B= 1.293E-01

C= -1.447E+06

3/04/94

LAWRENCITE

Formula wt 126.752

FeCl₂: Rhombohedral crystals 298.15 to 950 K; liquid 950 to 1300 K.

Temp. K	C _p ^o	S _T ^o	(H _T ^o -H ₂₉₈ ^o)/T J·mol ⁻¹ ·K ⁻¹	-(G _T ^o -H ₂₉₈ ^o)/T	FORMATION FROM THE ELEMENTS		
					Δ _f H ^o kJ·mol ⁻¹	Δ _f G ^o	Log K _f
298.15	76.34	117.95	0.00	117.95	-341.7	-302.2	52.95
300	76.54	118.42	0.47	117.95	-341.6	-302.0	52.58
400	81.04	141.27	20.23	121.04	-339.8	-289.1	37.75
500	81.49	159.42	32.45	126.96	-338.1	-276.6	28.89
600	81.92	174.30	40.65	133.65	-336.6	-264.4	23.02
700	83.17	187.01	46.63	140.39	-335.4	-252.5	18.84
800	85.31	198.25	51.32	146.93	-334.3	-240.7	15.72
900	88.28	208.46	55.25	153.21	-333.3	-229.1	13.30
1000	102.17	263.64	102.17	161.47	-289.4	-219.8	11.48
1100	102.17	273.34	102.16	171.18	-288.6	-212.8	10.11
1200	102.17	282.21	102.16	180.05	-287.1	-206.0	8.97
1300	102.17	290.41	102.15	188.26	-284.1	-199.4	8.01

Melting T 950 K

Boiling T 1347 K

Δ_mH^o 43.01 kJΔ_{vap}H^o 124.81 kJH₂₉₈^o-H₀^o 16.27 kJMolar Vol. 3.946 J·bar⁻¹
39.46 cm³

A= -3.136E+02

B= 9.168E-02

C= -1.52E+06

3/26/93

MOLYSITE

Formula wt 162.205

FeCl_3 : Crystals 298.15 to melting point 577 K; liquid 577 to boiling point 605 K; Ideal gas (dimer) 605 to 700 K.

Temp. K	C_p°	S_T°	$(H_T^\circ - H_{298}^\circ)/T$ J·mol ⁻¹ ·K ⁻¹	$-(G_T^\circ - H_{298}^\circ)/T$	FORMATION FROM THE ELEMENTS		
					$\Delta_f H^\circ$ kJ·mol ⁻¹	$\Delta_f G^\circ$	Log K_f
298.15	96.67	142.26	0.00	142.26	-399.2	-333.8	58.47
300	96.67	142.86	0.60	142.26	-359.4	-333.4	58.04
400	107.70	171.86	25.72	146.14	-396.9	-311.8	40.71
500	119.86	197.34	43.46	153.88	-393.7	-290.8	30.38
600	133.89	294.42	128.55	165.87	-346.8	-272.3	23.71
700	71.13	344.71	154.70	190.01	-324.5	-263.3	19.64

Melting T	577 K	Boiling T	605 K
$\Delta_{\text{fus}} H^\circ$	43.10 kJ	$\Delta_{\text{vap}} H^\circ$	21.88 kJ
$H_{298}^\circ - H_0^\circ$	19.71 kJ	Molar Vol.	5.786 J·bar ⁻¹ 57.86 cm ³

A= -3.455E+02

B= 1.274E-01

C= -2.375E+06

5/21/92

HYDROGEN CHLORIDE

Formula wt 36.461

HCl: Ideal gas at p = 1 bar, 298.15 to 1800 K.

Temp. K	C_p°	S_T°	$(H_T^\circ - H_{298}^\circ)/T$ J·mol ⁻¹ ·K ⁻¹	$-(G_T^\circ - H_{298}^\circ)/T$	FORMATION FROM THE ELEMENTS		
					$\Delta_f H^\circ$ kJ·mol ⁻¹	$\Delta_f G^\circ$	Log K_f
298.15	29.14	186.90	0.00	186.90	-92.3	-95.3	16.70
300	29.13	187.08	0.18	186.90	-92.3	-95.3	16.60
400	29.05	195.44	7.40	188.04	-92.6	-96.3	12.57
500	29.27	201.94	11.75	190.19	-92.9	-97.2	10.15
600	29.64	207.31	14.70	192.61	-93.3	-98.0	8.53
700	30.10	211.91	16.86	195.05	-93.6	-98.7	7.37
800	30.60	215.96	18.55	197.41	-93.9	-99.4	6.49
900	31.12	219.60	19.92	199.68	-94.1	-100.1	5.81
1000	31.64	222.90	21.06	201.84	-94.4	-100.8	5.26
1100	32.16	225.94	22.05	203.89	-94.6	-101.4	4.82
1200	32.66	228.76	22.91	205.85	-94.8	-102.0	4.44
1300	33.15	231.40	23.68	207.72	-94.9	-102.6	4.12
1400	33.61	233.87	24.37	209.50	-95.0	-103.2	3.85
1500	34.05	236.20	25.00	211.20	-95.2	-103.8	3.61
1600	34.46	238.41	25.58	212.83	-95.3	-104.4	3.41
1700	34.83	240.51	26.12	214.40	-95.3	-104.9	3.22
1800	35.17	242.52	26.61	215.90	-95.4	-105.5	3.06

Melting T	K	Boiling T	K
$\Delta_{fus} H^\circ$	kJ	$\Delta_{vap} H^\circ$	kJ
$H_{298}^\circ - H_0^\circ$	8.64 kJ	Molar Vol.	2478.97 J·bar ⁻¹ 24789.7 cm ³

A= -9.476E+01

B= -6.043E-03

C= 1.185E+05

3/04/93

SYLVITE

Formula wt 74.551

KCl: Cubic crystals 298.15 to 1043 K, melting point; liquid 1043 to fictive boiling point 1475 K.

Temp. K	C_p°	S_T°	$(H_T^\circ - H_{298}^\circ)/T$ J·mol ⁻¹ ·K ⁻¹	$-(G_T^\circ - H_{298}^\circ)/T$	FORMATION FROM THE ELEMENTS		
					$\Delta_f H^\circ$ kJ·mol ⁻¹	$\Delta_f G^\circ$	Log K_f
298.15	51.29	82.59	0.00	82.59	-436.5	-408.6	71.58
300	51.36	82.91	0.32	82.59	-436.5	-408.4	71.10
400	53.41	98.01	13.38	84.64	-438.4	-398.6	52.06
500	54.63	110.06	21.51	88.56	-437.9	-388.8	40.61
600	56.10	120.15	27.14	93.00	-437.2	-379.0	32.99
700	57.99	128.93	31.41	97.52	-436.4	-369.3	27.56
800	60.26	136.82	34.87	101.95	-435.3	-359.8	23.49
900	62.87	144.07	37.83	106.23	-434.0	-350.5	20.34
1000	65.75	150.84	40.48	110.36	-432.4	-341.3	17.83
1100	66.94	182.80	67.19	115.61	-482.9	-329.1	15.63
1200	66.94	189.20	67.72	121.48	-479.5	-315.2	13.72
1300	66.94	195.10	68.18	126.92	-476.1	-301.7	12.12
1400	66.94	200.54	68.56	131.98	-472.7	-288.4	10.76

Melting T	1043 K	Boiling T	1750 K
$\Delta_{\text{fus}} H^\circ$	26.28 kJ	$\Delta_{\text{vap}} H^\circ$	155.39 kJ
$H_{298}^\circ - H_0^\circ$	11.37 kJ	Molar Vol.	3.752 J·bar ⁻¹ 37.52 cm ³

A= -4.584E+02

B= 1.207E-01

C= 1.373E+06

CHLORMAGNESITE

Formula wt 95.210

MgCl₂: Rhombohedral crystals 298.15 to melting point 987 K. Liquid 987 to boiling point 1710 K.

Temp. K	C _p ^o	S _T ^o	(H _T ^o -H ₂₉₈ ^o)/T	-(G _T ^o -H ₂₉₈ ^o)/T	FORMATION FROM THE ELEMENTS		
					Δ _f H ^o	Δ _f G ^o	Log K _f
			J·mol ⁻¹ ·K ⁻¹		kJ·mol ⁻¹		
298.15	71.04	89.60	0.00	89.60	-641.3	-591.8	103.68
300	71.16	90.04	0.44	89.60	-641.3	-591.5	102.98
400	75.63	111.20	18.74	92.46	-639.9	-575.0	75.09
500	78.16	128.37	30.39	97.98	-638.5	-559.0	58.40
600	79.92	142.78	38.51	104.27	-637.0	-543.2	47.29
700	81.32	155.21	44.53	110.68	-635.4	-527.7	39.38
800	82.53	166.15	49.20	116.95	-633.9	-512.4	33.46
900	83.63	175.94	52.97	122.97	-632.5	-497.3	28.86
1000	92.47	228.82	99.37	129.45	-596.4	-482.4	25.20
1100	92.47	237.65	98.74	138.28	-594.3	-470.5	22.34
1200	92.47	245.68	98.22	146.94	-592.3	-459.4	20.00
1300	92.47	253.09	97.78	154.87	-590.2	-448.5	18.02
1400	92.47	259.91	97.40	162.13	-715.6	-434.6	16.22
1500	92.47	266.31	97.07	168.91	-712.2	-414.8	14.44
1600	92.47	272.29	96.78	175.22	-708.8	-395.1	12.90
1700	92.47	277.90	96.53	181.12	-705.5	-375.7	11.54

Melting T	987 K	Boiling T	K
Δ _{fm} H ^o	43.1 kJ	Δ _{vm} H ^o	kJ
H ₂₉₈ ^o -H ₀	13.76 kJ	Molar Vol.	4.081 J·bar ⁻¹ 40.81 cm ³

A= -6.293E+02

B= 1.445E-01

C= -4.868E+05

4/23/93

SCACCHITE

Formula wt 125.844

MnCl₂: Rhombohedral crystals 298.15 to 923 K; liquid 923 to 1400 K.

Temp. K	C _p ^o	S _T ^o	(H _T ^o -H ₂₉₈ ^o)/T	-(G _T ^o -H ₂₉₈ ^o)/T	FORMATION FROM THE ELEMENTS		
					Δ _f H ^o	Δ _f G ^o	Log K _f
			J·mol ⁻¹ ·K ⁻¹	kJ·mol ⁻¹			
298.15	73.01	118.24	0.00	118.24	-481.3	-440.5	77.17
300	73.11	118.69	0.45	118.24	-481.3	-440.2	76.65
400	77.24	140.35	19.19	121.17	-479.9	-426.8	55.73
500	79.80	157.88	31.07	126.81	-478.6	-413.6	43.21
600	81.73	172.60	39.36	133.25	-477.2	-400.8	34.89
700	83.36	185.33	45.53	139.80	-475.9	-388.1	28.96
800	84.84	196.56	50.35	146.21	-474.6	-375.7	24.53
900	86.23	206.63	54.26	152.37	-473.3	-363.4	21.09
1000	94.56	257.19	95.73	161.46	-436.1	-354.4	18.51
1100	94.56	266.19	95.62	170.57	-434.2	-346.3	16.44
1200	94.56	274.43	95.54	178.89	-432.3	-338.4	14.73
1300	94.56	282.00	95.46	186.54	-430.5	-330.6	13.29
1400	94.56	288.99	95.40	193.59	-431.0	-322.9	12.05

Melting T	923 K	Boiling T	K
Δ _{fus} H ^o	37.53 kJ	Δ _{vap} H ^o	kJ
H ₂₉₈ ^o -H ₀ ^o	15.071 kJ	Molar Vol.	4.211 J·bar ⁻¹ 42.11 cm ³
A=	-4.505E+02	B=	9.437E-02
		C=	-1.734E+06

3/26/93

HALITE

Formula wt 58.442

NaCl: Cubic crystals 298.15 to 1073.8 K; liquid 1073.8 to fictive boiling point 1791 K.

Temp. K	C_p°	S_T°	FORMATION FROM THE ELEMENTS				
			$(H_T^\circ - H_{298}^\circ)/T$ J·mol ⁻¹ ·K ⁻¹	$-(G_T^\circ - H_{298}^\circ)/T$	$\Delta_f H^\circ$ kJ·mol ⁻¹	$\Delta_f G^\circ$	Log K_f
298.15	50.51	72.12	0.00	72.12	-411.3	-384.2	67.30
300	50.54	72.43	0.31	72.12	-411.2	-384.0	66.86
400	52.34	87.22	13.09	74.12	-413.5	-374.8	48.94
500	54.14	99.09	21.12	77.97	-413.0	-365.2	38.15
600	55.93	109.12	26.77	82.35	-412.4	-355.6	30.96
700	57.73	117.88	31.07	86.81	-411.5	-346.3	25.84
800	59.53	125.70	34.51	91.19	-410.4	-337.0	22.00
900	61.32	132.82	37.39	95.43	-409.1	-327.9	19.03
1000	63.12	139.37	39.87	99.50	-407.6	-319.0	16.66
1100	68.46	171.89	67.93	103.96	-377.5	-310.8	14.76
1200	68.14	177.83	67.96	109.87	-472.3	-302.4	13.16
1300	67.82	183.27	67.96	115.31	-469.5	-288.3	11.59
1400	67.50	188.29	67.94	120.35	-466.7	-274.5	10.24
1500	67.17	192.93	67.90	125.03	-463.9	-260.9	9.08
1600	66.85	197.26	67.85	129.41	-461.2	-247.4	8.08
1700	66.53	201.30	67.78	133.52	-458.5	-234.2	7.19

Melting T	1074 K	Boiling T	K
$\Delta_{fus} H^\circ$	28.16 kJ	$\Delta_{vap} H^\circ$	kJ
$H_{298}^\circ - H_0^\circ$	10.61 kJ	Molar Vol.	2.702 J·bar ⁻¹ 27.02 cm ³

A= -4.283E+02

B= 1.1044E-01

C= 1.132E+06

5/21/92

NICKELOUS CHLORIDE

Formula wt 129.595

NiCl₂: Rhombohedral crystals 298.15 to melting point.

Temp. K	C _p ^o	S _T ^o	(H _T ^o -H ₂₉₈ ^o)/T	-(G _T ^o -H ₂₉₈ ^o)/T	FORMATION FROM THE ELEMENTS		
					Δ _f H ^o	Δ _f G ^o	Log K _f
			J·mol ⁻¹ ·K ⁻¹		kJ·mol ⁻¹		
298.15	71.68	98.20	0.00	98.20	-304.9	-258.8	45.33
300	71.88	98.64	0.44	98.20	-304.9	-258.5	45.00
400	77.21	120.25	19.14	101.11	-303.6	-243.2	31.76
500	78.34	137.63	30.89	106.74	-302.3	-228.3	23.85
600	78.89	151.96	38.84	113.12	-301.3	-213.6	18.59
700	79.74	164.18	44.62	119.56	-300.4	-199.0	14.85
800	81.06	174.91	49.09	125.82	-299.2	-184.6	12.05
900	82.87	184.55	52.74	131.82	-297.8	-170.3	9.89
1000	85.11	193.40	55.86	137.54	-296.4	-156.2	8.16
1100	87.72	201.63	58.63	143.00	-294.7	-142.3	6.76
1200	90.66	209.39	61.18	148.21	-292.9	-128.5	5.59
1300	93.87	216.77	63.57	153.20	-290.9	-114.9	4.62

Melting T	1303	K	Boiling T	K
Δ _{vap} H ^o	77.17	kJ	Δ _{vap} H ^o	kJ
H ₂₉₈ ^o -H ₀ ^o	14.43	kJ	Molar Vol.	3.670 J·bar ⁻¹ 36.70 cm ³

A = -2.965E+02

B = 1.403E-01

C = -3.75E+05

COTUNNITE

Formula wt 278.105

PbCl₂: Orthorhombic crystals 298.15 to 768 K; liquid 768 to 1000 K.

Temp. K	C _p ^o	S _T ^o	(H _T ^o -H ₂₉₈ ^o)/T	-(G _T ^o -H ₂₉₈ ^o)/T	FORMATION FROM THE ELEMENTS		
					Δ _f H ^o	Δ _f G ^o	Log K _f
			J·mol ⁻¹ ·K ⁻¹	kJ·mol ⁻¹			
298.15	73.18	136.00	0.00	136.00	-359.4	-314.1	55.03
300	73.33	136.45	0.45	136.00	-359.4	-313.8	54.64
400	79.98	158.53	19.56	138.97	-357.9	-298.9	39.03
500	84.51	176.89	32.12	144.77	-356.0	-284.3	29.70
600	87.85	192.61	41.15	151.46	-354.0	-270.2	23.52
700	90.45	206.35	48.01	158.34	-356.6	-255.6	19.07
768	91.89	215.09	51.72	163.37	-355.0	-246.2	16.74
800	113.80	250.41	83.99	166.42	-329.7	-242.4	15.82
900	113.80	263.80	87.31	176.49	-325.0	-231.7	13.45
1000	113.80	275.77	89.96	185.81	-320.3	-221.5	11.57

Melting T	768 K	Boiling T	K
Δ _m H ^o	23.85 kJ	Δ _{vap} H ^o	kJ
H ₂₉₈ ^o -H ₀ ^o	16.94 kJ	Molar Vol.	4.709 J·bar ⁻¹ 47.09 cm ³

A= -3.405E+02

B= 1.218E-01

C= -9.24E+05

5/21/92

FLUORITE

Formula wt 78.075

CaF₂: Cubic crystals 298.15 K to transition at 1424 K.

Temp. K	C _p ^o	S _T ^o	(H _T ^o -H ₂₉₈ ^o)/T	-(G _T ^o -H ₂₉₈ ^o)/T	FORMATION FROM THE ELEMENTS		
					Δ _f H ^o	Δ _f G ^o	Log K _f
			J·mol ⁻¹ ·K ⁻¹		kJ·mol ⁻¹		
298.15	67.68	68.90	0.00	68.90	-1228.0	-1175.3	205.90
300	67.38	69.32	0.42	68.90	-1228.0	-1175.0	204.57
400	69.99	88.47	16.98	71.49	-1227.2	-1157.4	151.14
500	79.35	105.16	28.58	76.58	-1225.8	-1140.1	119.10
600	83.72	120.09	37.48	82.62	-1224.0	-1123.1	97.77
700	83.92	133.05	44.13	88.92	-1222.3	-1106.5	82.56
800	82.48	144.17	49.02	95.15	-1221.8	-1089.9	71.16
900	81.73	153.82	52.68	101.14	-1220.8	-1073.5	62.30
1000	83.53	162.50	55.65	106.85	-1220.0	-1057.1	55.22
1100	89.33	170.70	58.41	112.29	-1219.3	-1040.9	49.43
1200	100.22	178.90	61.40	117.49	-1225.8	-1024.1	44.58
1300	117.06	187.54	65.00	122.54	-1222.2	-1007.4	40.48
1400	140.52	197.03	69.51	127.52	-1216.7	-991.1	36.98

Melting T	1691 K	Boiling T	K
Δ _{fm} H ^o	kJ	Δ _{vap} H ^o	kJ
H ₂₉₈ ^o -H ₀ ^o	11.64 kJ	Molar Vol.	2.454 J·bar ⁻¹ 24.54 cm ³

A= -1.221E+03

B= 1.643E-01

C= -2.93E+05

11/25/92

HYDROGEN FLUORIDE

Formula wt 20.006

HF: Ideal gas at p = 1 bar, 298.15 to 2500 K.

Temp. K	C_p°	S_T°	$(H_T^\circ - H_{298}^\circ)/T$ J·mol ⁻¹ ·K ⁻¹	$-(G_T^\circ - H_{298}^\circ)/T$	FORMATION FROM THE ELEMENTS		
					$\Delta_f H^\circ$ kJ·mol ⁻¹	$\Delta_f G^\circ$	Log K_f
298.15	29.14	173.78	0.00	173.78	-273.3	-275.4	48.25
300	29.15	173.96	0.18	173.78	-273.3	-275.4	47.95
400	29.21	182.36	7.44	174.93	-273.5	-276.1	36.05
500	29.15	188.87	11.79	177.09	-273.7	-276.7	28.91
600	29.18	194.19	14.68	179.51	-274.0	-277.3	24.14
700	29.32	198.70	16.76	181.94	-274.3	-277.9	20.73
800	29.55	202.63	18.34	184.28	-274.6	-278.3	18.17
900	29.86	206.13	19.61	186.52	-275.0	-278.8	16.18
1000	30.20	209.29	20.65	188.64	-275.3	-279.2	14.58
1100	30.59	212.18	21.53	190.65	-275.6	-279.6	13.28
1200	30.99	214.86	22.31	192.56	-276.0	-279.9	12.18
1300	31.40	217.36	22.99	194.37	-276.3	-280.2	11.26
1400	31.81	219.70	23.60	196.10	-276.6	-280.5	10.47
1500	32.22	221.91	24.17	197.75	-276.9	-280.8	9.78
1600	32.63	224.00	24.68	199.32	-277.2	-281.0	9.17
1700	33.02	225.99	25.16	200.83	-277.5	-281.2	8.64
1800	33.39	227.89	25.61	202.28	-277.8	-281.5	8.17

Melting T	K	Boiling T	K
$\Delta_{fus} H^\circ$	kJ	$\Delta_{vap} H^\circ$	kJ
$H_{298}^\circ - H_0^\circ$	8.599 kJ	Molar Vol.	2478.97 J·bar ⁻¹ 24789.7 cm ³

A= -2.759E+02

B= -3.234E-03

C= 1.443E+05

11/19/92

SELLAITE

Formula wt 62.302

MgF₂: Tetragonal crystals 298.15 to melting point 1536 K. Liquid 1536 to 1800 K.

Temp. K	C _p ^o	S _T ^o	(H _T ^o -H ₂₉₈ ^o)/T	-(G _T ^o -H ₂₉₈ ^o)/T	FORMATION FROM THE ELEMENTS		
					Δ _f H ^o	Δ _f G ^o	Log K _f
			J·mol ⁻¹ ·K ⁻¹		kJ·mol ⁻¹		
298.15	61.51	57.20	0.00	57.20	-1124.2	-1071.1	187.64
300	61.69	57.58	0.38	57.20	-1124.2	-1070.7	186.42
400	68.61	76.38	16.67	59.72	-1123.4	-1053.0	137.51
500	72.56	92.15	27.48	64.67	-1122.4	-1035.5	108.18
600	75.16	105.63	35.22	70.40	-1121.2	-1018.2	88.64
700	77.02	117.36	41.07	76.29	-1120.0	-1001.2	74.71
800	78.44	127.74	45.66	82.09	-1118.9	-984.3	64.27
900	79.57	137.05	49.36	87.68	-1117.7	-967.5	56.15
1000	80.50	145.48	52.43	93.05	-1125.3	-950.2	49.63
1100	81.28	153.19	55.02	98.17	-1124.3	-932.7	44.29
1200	81.95	160.29	57.24	103.06	-1123.3	-915.3	39.84
1300	82.53	166.88	59.16	107.71	-1122.3	-898.0	36.08
1400	83.04	173.01	60.85	112.16	-1248.7	-877.7	32.75
1500	83.49	178.75	62.34	116.41	-1246.3	-851.3	29.64
1600	94.56	222.46	100.45	122.01	-1185.0	-827.5	27.01
1700	94.56	228.19	100.10	128.09	-1181.4	-805.2	24.74
1800	94.56	233.59	99.80	133.79	-1177.9	-783.2	22.73

Melting T 1536 K

Boiling T K

Δ_{fm}H^o 58.69 kJΔ_{vp}H^o kJH₂₉₈^o-H₀^o 9.914 kJMolar Vol. 1.961 J·bar⁻¹
19.61 cm³

A= -1.145E+03

B= 1.963E-01

C= 1.628E+06

11/19/92

VILLIAUMITE

Formula wt 41.988

NaF: Cubic crystals 298.15 to melting point 1269 K. Liquid 1269 to 1800 K.

Temp. K	C_p°	S_T°	$(H_T^\circ - H_{298}^\circ)/T$ J·mol ⁻¹ ·K ⁻¹	$-(G_T^\circ - H_{298}^\circ)/T$	FORMATION FROM THE ELEMENTS		
					$\Delta_f H^\circ$ kJ·mol ⁻¹	$\Delta_f G^\circ$	Log K_f
298.15	46.86	51.50	0.00	51.50	-573.6	-543.4	95.20
300	46.94	51.79	0.29	51.50	-573.6	-543.2	94.58
400	49.72	65.74	12.36	53.38	-576.0	-532.9	69.59
500	51.19	77.00	19.98	57.02	-575.7	-522.2	54.55
600	52.53	86.45	25.29	61.16	-575.3	-511.5	44.53
700	54.02	94.66	29.29	65.37	-574.7	-500.9	37.38
800	55.71	101.98	32.48	69.49	-573.9	-490.4	32.02
900	57.59	108.65	35.17	73.48	-573.0	-480.0	27.86
1000	59.63	114.82	37.51	77.31	-571.8	-469.8	24.54
1100	61.82	120.60	39.62	80.98	-570.5	-459.6	21.82
1200	64.12	126.08	41.56	84.52	-665.8	-447.1	19.46
1300	68.51	157.48	69.57	87.91	-629.2	-429.0	17.24
1400	68.51	162.55	69.49	93.06	-626.4	-413.7	15.44
1500	68.51	167.28	69.43	97.85	-623.5	-398.6	13.88
1600	68.51	171.70	69.37	102.33	-620.6	-383.7	12.53
1700	68.51	175.85	69.32	106.53	-617.8	-369.0	11.34
1800	68.51	179.76	69.27	110.49	-615.0	-354.5	10.29

Melting T	1269 K	Boiling T	K
$\Delta_{fus} H^\circ$	33.14 kJ	$\Delta_{vap} H^\circ$	kJ
$H_{298}^\circ - H_0^\circ$	8.49 kJ	Molar Vol.	1.498 J·bar ⁻¹ 14.98 cm ³

A= -6.018E+02

B= 1.344E-01

C= 1.835E+06

11/19/92

CRYOLITE

Formula wt 209.941

Na_3AlF_6 : Monoclinic (α) crystals 298.15 to 836 K transition to cubic (β) crystals. Cubic crystals 836 to 1153 K. γ crystals 1153 to melting point 1290 K. Liquid 1290 to 1800 K.

Temp. K	C_p°	S_T°	FORMATION FROM THE ELEMENTS				
			$(H_T^\circ - H_{298}^\circ)/T$ J·mol ⁻¹ ·K ⁻¹	$-(G_T^\circ - H_{298}^\circ)/T$	$\Delta_f H^\circ$ kJ·mol ⁻¹	$\Delta_f G^\circ$	Log K_f
298.15	217.37	238.50	0.00	238.50	-3316.8	-3152.1	552.22
300	217.73	239.85	1.34	238.50	-3316.8	-3151.0	548.63
400	238.77	305.46	58.16	247.31	-3323.0	-3095.4	404.21
500	251.60	360.26	95.69	264.57	-3320.4	-3038.8	317.45
600	262.30	407.03	122.52	284.51	-3317.0	-2982.8	259.67
700	281.11	448.71	143.68	305.03	-3312.3	-2927.4	218.44
800	315.99	488.31	162.84	325.47	-3305.1	-2872.9	187.58
900	279.88	532.93	186.63	346.30	-3290.1	-2820.0	163.66
1000	284.68	562.66	196.20	366.46	-3295.5	-2767.3	144.54
1100	289.47	590.02	204.46	385.56	-3289.9	-2714.7	128.91
1200	300.41	617.49	213.76	403.73	-3571.9	-2655.4	115.58
1300	396.91	730.45	308.67	421.78	-3447.8	-2580.3	103.67
1400	396.91	759.86	314.97	444.89	-3429.0	-2514.3	93.81
1500	396.91	787.23	320.43	466.80	-3410.1	-2449.6	85.30
1600	396.91	812.84	325.21	487.63	-3391.4	-2386.2	77.90
1700	396.91	836.89	329.43	507.46	-3372.6	-2323.9	71.40
1800	396.91	859.57	333.18	526.39	-3354.0	-2262.7	65.66

Melting T	1290 K	Boiling T	K
$\Delta_{\text{m}} H^\circ$	113.75 kJ	$\Delta_{\text{vap}} H^\circ$	kJ
$H_{298}^\circ - H_0^\circ$	38.223 kJ	Molar Vol.	7.081 J·bar ⁻¹ 70.81 cm ³

A= -3.370E+03

B= 6.097E-01

C= -3.62E+06

11/19/92

CHIOLITE

Formula wt 461.871

$\text{Na}_5\text{Al}_3\text{F}_{14}$: Tetragonal crystals 298.15 to melting point 1010 K.

Temp. K	c_p°	s_T°	$(H_T^\circ - H_{298}^\circ)/T$ J·mol ⁻¹ ·K ⁻¹	$-(G_T^\circ - H_{298}^\circ)/T$	FORMATION FROM THE ELEMENTS		
					$\Delta_f H^\circ$ kJ·mol ⁻¹	$\Delta_f G^\circ$	Log K_f
298.15	453.91	515.30	0.00	515.30	-7546.3	-7174.7	1256.95
300	455.08	518.11	2.80	515.31	-7546.3	-7172.4	1248.79
400	499.34	655.82	122.04	533.78	-7556.5	-7047.1	920.24
500	524.54	770.16	200.20	569.96	-7552.3	-6920.2	722.94
600	542.23	867.43	255.80	611.63	-7546.5	-6794.3	591.49
700	556.38	952.11	297.76	654.35	-7539.6	-6669.5	497.67
800	568.64	1027.22	330.87	696.35	-7532.1	-6545.7	427.38
900	579.80	1094.85	357.91	736.94	-7524.1	-6422.9	372.77
1000	590.28	1156.48	380.63	775.85	-7547.6	-6298.8	329.01

Melting T	1010 K	Boiling T	K
$\Delta_{\text{sub}} H^\circ$	80.831 kJ	$\Delta_{\text{vap}} H^\circ$	kJ
$H_{298}^\circ - H_0^\circ$	38.223 kJ	Molar Vol.	15.408 J·bar ⁻¹ 154.08 cm ³

A= -7.5366E+03

B= 1.239E+00

C= -7.07E+05

11/20/92

IODARGYITE

Formula wt 234.773

AgI: Hexagonal crystals 298.15 to 423 K; cubic crystals 423 to 831 K.

Temp. K	C_p°	S_T°	$(H_T^\circ - H_{298}^\circ)/T$ J·mol ⁻¹ ·K ⁻¹	$-(G_T^\circ - H_{298}^\circ)/T$	FORMATION FROM THE ELEMENTS		
					$\Delta_f H^\circ$ kJ·mol ⁻¹	$\Delta_f G^\circ$	Log K_f
298.15	54.41	115.48	0.00	115.48	-61.8	-66.3	11.61
300	54.60	115.82	0.34	115.48	-61.8	-66.3	11.54
400	64.68	132.91	15.16	117.74	-69.3	-67.6	8.82
500	56.48	160.54	36.15	124.39	-84.0	-66.3	6.93
600	56.48	170.88	39.54	131.34	-82.8	-62.9	5.47
700	56.48	179.54	41.96	137.58	-81.8	-59.6	4.45
800	56.48	187.07	43.78	143.29	-80.8	-56.5	3.69

Melting T	831 K	Boiling T	K
$\Delta_{fus} H^\circ$	kJ	$\Delta_{vap} H^\circ$	kJ
$H_{298}^\circ - H_0^\circ$	kJ	Molar Vol.	4.130 J·bar ⁻¹ 41.30 cm ³
A=	-9.280E+01	B=	4.399E-02
		C=	1.196E+06

11/19/92

MARSHITE

Formula wt 190.450

CuI: Cubic crystals 298.15 to transition point at 643 K. There is a second transition at 679 K. CuI melts at 868 K.

Temp. K	C_p°	S_T°	FORMATION FROM THE ELEMENTS				
			$(H_T^\circ - H_{298}^\circ)/T$ J·mol ⁻¹ ·K ⁻¹	$-(G_T^\circ - H_{298}^\circ)/T$	$\Delta_f H^\circ$ kJ·mol ⁻¹	$\Delta_f G^\circ$	Log K_f
298.15	54.06	96.60	0.00	96.60	-67.8	-69.4	12.16
300	54.14	96.93	0.33	96.60	-67.8	-69.4	12.09
400	57.20	112.92	14.17	98.75	-75.5	-69.7	9.10
500	60.59	125.89	22.98	102.91	-96.4	-66.3	6.92
600	76.90	137.85	30.12	107.73	-94.3	-60.4	5.26
700	68.62	163.05	49.32	113.73	-82.4	-55.6	4.15
800	68.62	172.22	51.74	120.48	-80.1	-51.9	3.39
900	65.75	189.35	62.33	127.02	-70.1	-48.8	2.83
1000	63.45	196.15	62.56	133.59	-68.3	-46.5	2.43
1100	61.43	202.11	62.55	139.56	-66.9	-44.4	2.11
1200	59.68	207.38	62.38	145.00	-65.8	-42.5	1.85
1300	58.20	212.09	62.11	149.98	-65.0	-40.5	1.63
1400	56.99	216.36	61.79	154.57	-77.6	-38.3	1.43

Melting T	868 K	Boiling T	K
$\Delta_{\text{fus}} H^\circ$	7.93 kJ	$\Delta_{\text{vap}} H^\circ$	kJ
$H_{298}^\circ - H_0^\circ$	kJ	Molar Vol.	3.335 J·bar ⁻¹ 33.35 cm ³

A= -7.665E+01

B= 2.882E-02

C= -2.219E+05

11/19/92

WITHERITE

Formula wt 197.336

BaCO₃: Orthorhombic crystals 298.15 to 1079 K; tetragonal crystals 1079 to 1241 K; cubic crystals 1241 to 1600 K.

Temp. K	C _p ^o	S _T ^o	(H _T ^o -H ₂₉₈ ^o)/T	-(G _T ^o -H ₂₉₈ ^o)/T	FORMATION FROM THE ELEMENTS		
					Δ _f H ^o	Δ _f G ^o	Log K _f
			J·mol ⁻¹ ·K ⁻¹	kJ·mol ⁻¹			
298.15	85.32	112.13	0.00	112.13	-1210.9	-1132.2	198.35
300	85.75	112.66	0.53	112.13	-1210.8	-1131.7	197.05
400	99.75	139.57	23.87	115.71	-1209.9	-1105.5	144.36
500	106.60	162.62	39.77	122.84	-1209.3	-1079.4	112.77
600	112.19	182.55	51.38	131.17	-1209.3	-1053.5	91.71
700	118.01	200.28	60.48	139.80	-1208.3	-1027.6	76.68
800	124.41	216.45	68.06	148.38	-1207.4	-1001.8	65.41
900	131.45	231.50	74.71	156.79	-1205.7	-976.2	56.65
1000	139.07	245.74	80.76	164.98	-1203.4	-950.8	49.66
1100	154.81	275.81	102.47	173.34	-1191.2	-925.3	43.94
1200	154.81	289.28	106.83	182.45	-1187.4	-901.3	39.23
1300	158.98	304.39	113.13	191.26	-1180.3	-877.7	35.27
1400	158.98	316.17	116.40	199.77	-1176.1	-854.7	31.89
1500	158.98	327.13	119.24	207.89	-1172.0	-831.8	28.97
1600	158.98	337.39	121.73	215.66	-1167.8	-809.3	26.42

Melting T	K	Boiling T	K
Δ _m H ^o	kJ	Δ _{vp} H ^o	kJ
H ₂₉₈ ^o -H ₀ ^o	kJ	Molar Vol.	4.581 J·bar ⁻¹ 45.81 cm ³

A= -1.196E+03

B= 2.438E-01

C= -9.15E+05

9/11/92

ARAGONITE

Formula wt 100.087

CaCO₃: Orthorhombic crystals 298.15 to 1000 K.

Temp. K	C _p ^o	S _T ^o	(H _T ^o -H ₂₉₈ ^o)/T J·mol ⁻¹ ·K ⁻¹	-(G _T ^o -H ₂₉₈ ^o)/T	FORMATION FROM THE ELEMENTS		
					Δ _f H ^o kJ·mol ⁻¹	Δ _f G ^o	Log K _f
298.15	82.31	87.99	0.00	87.99	-1207.4	-1127.4	197.51
300	82.55	88.50	0.51	87.99	-1207.4	-1126.9	196.21
400	92.67	113.75	22.38	91.37	-1206.7	-1100.2	143.66
500	99.80	135.22	37.18	98.04	-1205.8	-1073.6	112.16
600	105.76	153.96	48.13	105.83	-1204.8	-1047.3	91.17
700	111.17	170.67	56.75	113.92	-1203.7	-1021.2	76.20
800	116.28	185.85	63.87	121.98	-1203.4	-995.0	64.97
900	121.22	199.84	69.97	129.86	-1202.2	-969.1	56.24
1000	126.06	212.86	75.34	137.52	-1201.0	-943.2	49.27

Melting T	K	Boiling T	K
Δ _{fus} H ^o	kJ	Δ _{vap} H ^o	kJ
H ₂₉₈ ^o -H ₀ ^o	14.31 kJ	Molar Vol.	3.415 J·bar ⁻¹ 34.15 cm ³

A= -1.203E+03

B= 2.598E-01

C= -1.96E+05

9/18/92

CALCITE

Formula wt 100.087

CaCO₃: Rhombohedral crystals 298.15 to 1200 K.

Temp. K	C _p ^o	S _T ^o	FORMATION FROM THE ELEMENTS				
			(H _T ^o -H ₂₉₈ ^o)/T J·mol ⁻¹ ·K ⁻¹	-(G _T ^o -H ₂₉₈ ^o)/T	Δ _f H ^o kJ·mol ⁻¹	Δ _f G ^o kJ·mol ⁻¹	Log K _f
298.15	83.47	91.71	0.00	91.71	-1207.4	-1128.5	197.70
300	83.82	92.23	0.52	91.71	-1207.4	-1128.0	196.39
400	97.00	118.36	23.18	95.19	-1206.3	-1101.6	143.86
500	104.55	140.88	38.75	102.13	-1204.9	-1075.6	112.37
600	109.88	160.43	50.18	110.25	-1203.5	-1049.9	91.40
700	114.16	177.70	59.02	118.68	-1202.0	-1024.4	76.44
800	117.88	193.19	66.15	127.04	-1201.6	-999.0	65.23
900	121.28	207.28	72.09	135.18	-1200.3	-973.8	56.52
1000	124.48	220.22	77.17	143.05	-1199.1	-948.7	49.55
1100	127.55	232.23	81.61	150.62	-1198.1	-923.7	43.86
1200	130.53	243.46	85.57	157.89	-1204.9	-898.2	39.10

Melting T	K	Boiling T	K
Δ _{fus} H ^o	kJ	Δ _{vap} H ^o	kJ
H ₂₉₈ ^o -H ₀ ^o	14.48 kJ	Molar Vol.	3.693 J·bar ⁻¹ 36.93 cm ³

A= -1.200E+03

B= 2.518E-01

C= -3.036E+05

10/14/92

DOLOMITE

Formula wt 184.401

CaMg(CO₃)₂: Rhombohedral crystals 298.15 to 1100 K.

Temp. K	C _p ^o	S _T ^o	(H _T ^o -H ₂₉₈ ^o)/T J·mol ⁻¹ ·K ⁻¹	-(G _T ^o -H ₂₉₈ ^o)/T	FORMATION FROM THE ELEMENTS		
					Δ _f H ^o kJ·mol ⁻¹	Δ _f G ^o	Log K _f
298.15	157.51	155.18	0.00	155.18	-2324.5	-2161.3	378.64
300	158.06	156.16	0.97	155.18	-2324.5	-2160.3	376.13
400	183.54	205.32	43.61	161.71	-2323.4	-2105.7	274.97
500	201.89	248.35	73.52	174.83	-2321.4	-2051.4	214.31
600	215.66	286.43	96.12	190.32	-2318.8	-1997.7	173.91
700	226.65	320.53	114.00	206.53	-2316.0	-1944.4	145.09
800	236.08	351.42	128.69	222.74	-2313.9	-1891.4	123.47
900	244.73	379.73	141.10	238.63	-2310.8	-1838.7	106.72
1000	253.15	405.96	151.89	254.07	-2316.2	-1785.7	93.28
1100	261.72	430.48	161.48	269.00	-2312.9	-1732.9	82.28

Melting T	K	Boiling T	K
Δ _{fm} H ^o	kJ	Δ _{vp} H ^o	kJ
H ₂₉₈ ^o -H ₀ ^o	25.98 kJ	Molar Vol.	6.434 J·bar ⁻¹ 64.34 cm ³

A= -2.314E+03

B= 5.283E-01

C= -4.81E+05

5/22/92

SIDERITE

Formula wt 115.856

FeCO₃: Rhombohedral crystals 298.15 to 600 K.

Temp. K	C _p ^o	S _T ^o	(H _T ^o -H ₂₉₈ ^o)/T	-(G _T ^o -H ₂₉₈ ^o)/T	FORMATION FROM THE ELEMENTS		
					Δ _f H ^o	Δ _f G ^o	Log K _f
			J·mol ⁻¹ ·K ⁻¹		kJ·mol ⁻¹		
298.15	82.27	95.47	0.00	95.47	-755.9	-682.8	119.63
300	82.52	95.98	0.51	95.47	-755.9	-682.4	118.81
400	94.34	121.43	22.57	98.86	-755.1	-658.0	85.92
500	102.56	143.43	37.80	105.63	-754.0	-633.8	66.21
600	108.09	162.65	49.08	113.56	-752.9	-609.9	53.09

Melting T	K	Boiling T	K
Δ _{fm} H ^o	kJ	Δ _{vp} H ^o	kJ
H ₂₉₈ ^o -H ₀ ^o	14.59 kJ	Molar Vol.	2.938 J·bar ⁻¹ 29.38 cm ³

A= -7.525E+02

B= 2.383E-01

C= -1.23E+05

5/22/92

MAGNESITE

Formula wt 84.314

MgCO₃: Rhombohedral crystals 298.15 to 1000 K.

Temp. K	C _p ^o	S _T ^o	(H _T ^o -H ₂₉₈ ^o)/T J·mol ⁻¹ ·K ⁻¹	-(G _T ^o -H ₂₉₈ ^o)/T	FORMATION FROM THE ELEMENTS		
					Δ _f H ^o kJ·mol ⁻¹	Δ _f G ^o	Log K _f
298.15	76.09	65.09	0.00	65.09	-1113.3	-1029.5	180.36
300	76.44	65.56	0.47	65.09	-1113.3	-1029.0	179.15
400	90.57	89.67	21.39	68.28	-1112.9	-1000.9	130.70
500	99.92	110.94	36.20	74.73	-1111.9	-973.0	101.65
600	107.38	129.83	47.46	82.37	-1110.6	-945.3	82.30
700	113.96	146.89	56.50	90.39	-1109.1	-917.9	68.49
800	120.06	162.51	64.07	98.44	-1107.3	-890.7	58.16
900	125.88	176.98	70.61	106.37	-1105.3	-863.7	50.13
1000	131.54	190.54	76.42	114.12	-1111.6	-836.3	43.68

Melting T	K	Boiling T	K
Δ _{sub} H ^o	kJ	Δ _{vap} H ^o	kJ
H ₂₉₈ ^o -H ₀ ^o	11.63 kJ	Molar Vol.	2.802 J·bar ⁻¹ 28.02 cm ³
A=	-1.108E+03	B=	2.718E-01
		C=	-2.42E+05

5/22/92

RHODOCHROSITE

Formula wt 114.947

 MnCO_3 : Rhombohedral crystals 298.15 to 600 K.

Temp. K	C_p°	S_T°	$(H_T^\circ - H_{298}^\circ)/T$ J·mol ⁻¹ ·K ⁻¹	$-(G_T^\circ - H_{298}^\circ)/T$	FORMATION FROM THE ELEMENTS		
					$\Delta_f H^\circ$ kJ·mol ⁻¹	$\Delta_f G^\circ$	Log K_f
298.15	80.78	98.03	0.00	98.03	-892.9	-819.1	143.50
300	81.03	98.53	0.50	98.03	-892.9	-818.7	142.54
400	92.38	123.49	22.13	101.36	-892.4	-794.0	103.68
500	100.87	145.05	37.06	107.99	-891.6	-769.5	80.38
600	107.70	164.07	48.29	115.78	-890.6	-745.2	64.87

Melting T	K	Boiling T	K
$\Delta_{\text{fus}} H^\circ$	kJ	$\Delta_{\text{vap}} H^\circ$	kJ
$H_{298}^\circ - H_0^\circ$	14.12 kJ	Molar Vol.	3.107 J·bar ⁻¹ 31.07 cm ³

A= -8.894E+02

B= 2.425E-01

C= -9.44E+04

DAWSONITE

Formula wt 143.995

$\text{NaAlCO}_3(\text{OH})_2$: Orthorhombic crystals 298.15 to 500 K.

Temp. K	C_p°	S_T°	$(H_T^\circ - H_{298}^\circ)/T$ J·mol ⁻¹ ·K ⁻¹	$-(G_T^\circ - H_{298}^\circ)/T$	FORMATION FROM THE ELEMENTS		
					$\Delta_f H^\circ$ kJ·mol ⁻¹	$\Delta_f G^\circ$	Log K_f
298.15	34.52	132.00	0.00	132.00	-1964.0	-1786.0	312.89
300	34.52	132.21	0.21	132.00	-1964.2	-1784.9	310.77
400	34.55	142.15	8.79	133.35	-1980.2	-1722.9	224.98
500	34.58	149.86	13.95	135.91	-1994.4	-1656.9	173.09

Melting T	K	Boiling T	K
$\Delta_{\text{fus}} H^\circ$	kJ	$\Delta_{\text{vap}} H^\circ$	kJ
$H_{298}^\circ - H_0^\circ$	22.17 kJ	Molar Vol.	5.93 J·bar ⁻¹ 59.3 cm ³

A= -2.010E+03

B= 6.937E-01

C= 1.518E+06

7/17/92

STRONTIANITE

Formula wt 147.629

SrCO₃: Orthorhombic crystals 298.15 to 1197 K; hexagonal crystals 1197 to 1400 K.

Temp. K	C _p ^o	S _T ^o	(H _T ^o -H ₂₉₈ ^o)/T J·mol ⁻¹ ·K ⁻¹	-(G _T ^o -H ₂₉₈ ^o)/T	FORMATION FROM THE ELEMENTS		
					Δ _f H ^o kJ·mol ⁻¹	Δ _f G ^o	Log K _f
298.15	81.50	97.07	0.00	97.07	-1218.7	-1137.6	199.29
300	82.03	97.58	0.50	97.07	-1218.7	-1137.1	197.97
400	97.72	123.80	23.26	100.54	-1217.7	-1110.0	144.94
500	102.86	146.24	38.74	107.50	-1216.4	-1083.2	113.16
600	106.05	165.28	49.69	115.58	-1215.2	-1056.6	91.99
700	109.46	181.87	57.98	123.89	-1214.1	-1030.3	76.88
800	113.64	196.75	64.67	132.09	-1213.0	-1004.1	65.56
900	118.69	210.42	70.38	140.04	-1212.4	-978.0	56.76
1000	124.54	223.22	75.50	147.72	-1210.6	-952.0	49.73
1100	131.11	235.40	80.25	155.15	-1216.3	-925.9	43.97
1200	144.77	262.84	100.48	162.36	-1195.5	-899.7	39.16
1300	144.77	274.42	103.89	170.53	-1192.6	-875.1	35.16
1400	144.77	285.15	106.81	178.34	-1189.9	-850.8	31.74

Melting T	K	Boiling T	K
Δ _m H ^o	kJ	Δ _{vp} H ^o	kJ
H ₂₉₈ ^o -H ₀ ^o	kJ	Molar Vol.	3.901 J·bar ⁻¹ 39.01 cm ³
A = -1.210E+03	B = 2.577E-01	C = -4.37E+05	

7/17/92

SMITHSONITE

Formula wt 125.399

ZnCO₃: Rhombohedral crystals 298.15 to 1200 K.

Temp. K	C _p ^o	S _T ^o	FORMATION FROM THE ELEMENTS				
			(H _T ^o -H ₂₉₈ ^o)/T J·mol ⁻¹ ·K ⁻¹	-(G _T ^o -H ₂₉₈ ^o)/T	Δ _f H ^o kJ·mol ⁻¹	Δ _f G ^o kJ·mol ⁻¹	Log K _f
298.15	80.05	81.19	0.00	81.19	-817.0	-735.3	128.82
300	80.29	81.69	0.49	81.19	-817.0	-734.8	127.94
400	91.77	106.42	21.93	84.49	-816.4	-707.5	92.39
500	101.01	127.92	36.86	91.07	-815.4	-680.4	71.08
600	108.79	147.05	48.21	98.83	-814.0	-653.5	56.89
700	115.57	164.34	57.36	106.98	-819.7	-626.8	46.77
800	121.64	180.17	65.02	115.15	-817.9	-599.4	39.13
900	127.19	194.82	71.63	123.20	-815.7	-572.2	33.21
1000	132.34	208.49	77.44	131.05	-813.2	-545.3	28.48
1100	137.18	221.34	82.66	138.68	-810.3	-518.6	24.63
1200	141.77	233.47	87.39	146.08	-922.2	-490.3	21.34

Melting T	K	Boiling T	K
Δ _m H ^o	kJ	Δ _{vp} H ^o	kJ
H ₂₉₈ ^o -H ₀ ^o	13.49 kJ	Molar Vol.	2.828 J·bar ⁻¹ 28.28 cm ³

A= -8.163E+02

B= 2.711E-01

C= 1.690E+04

5/22/92

NITROBARITE

Formula wt 261.337

Ba(NO₃)₂: Cubic crystals 298.15 to 800 K.

Temp. K	C _p ^o	S _T ^o	(H _T ^o -H ₂₉₈ ^o)/T J·mol ⁻¹ ·K ⁻¹	-(G _T ^o -H ₂₉₈ ^o)/T	FORMATION FROM THE ELEMENTS		
					Δ _f H ^o kJ·mol ⁻¹	Δ _f G ^o	Log K _f
298.15	151.35	213.80	0.00	213.80	-992.1	-796.6	139.55
300	151.85	214.74	0.93	213.80	-992.1	-795.4	138.48
400	174.94	261.75	41.70	220.06	-990.5	-730.0	95.33
500	193.67	302.85	70.26	232.59	-988.0	-665.2	69.49
600	210.68	339.68	92.26	247.42	-984.9	-600.9	52.31
700	226.88	373.38	110.34	263.04	-979.6	-537.3	40.09
800	242.65	404.71	125.90	278.81	-973.6	-474.4	30.98

Melting T	K	Boiling T	K
Δ _m H ^o	kJ	Δ _{vap} H ^o	kJ
H ₂₉₈ ^o -H ₀ ^o	kJ	Molar Vol.	8.058 J·bar ⁻¹ 80.58 cm ³
A= -9.791E+02	B= 6.323E-01	C= -5.41E+05	

CALCIUM NITRATE

Formula wt 164.088

Ca(NO₃)₂: Cubic crystals 298.15 to 800 K.

Temp. K	C _p ^o	S _T ^o	(H _T ^o -H ₂₉₈ ^o)/T	-(G _T ^o -H ₂₉₈ ^o)/T	FORMATION FROM THE ELEMENTS		
					Δ _f H ^o	Δ _f G ^o	Log K _f
			J·mol ⁻¹ ·K ⁻¹	kJ·mol ⁻¹			
298.15	149.11	193.30	0.00	193.30	-938.4	-742.6	130.10
300	149.66	194.22	0.92	193.30	-938.4	-741.4	129.08
400	173.76	240.79	41.30	199.49	-936.6	-675.9	88.27
500	192.74	281.65	69.73	211.92	-933.1	-611.2	63.85
600	210.08	318.34	91.69	226.64	-928.4	-547.2	47.64
700	226.83	351.98	109.81	242.18	-922.5	-484.1	36.12
800	243.37	383.35	125.47	257.88	-916.3	-421.8	27.54

Melting T	K	Boiling T	K
Δ _{fus} H ^o	kJ	Δ _{vap} H ^o	kJ
H ₂₉₈ ^o -H ₀ ^o	kJ	Molar Vol.	6.609 J·bar ⁻¹ 66.09 cm ³

A= -9.217E+02

B= 6.267E-01

C= -6.975+05

5/22/92

NITER

Formula wt 101.103

KNO_3 : Orthorhombic crystals 298.15 to 401 K; Rhombohedral crystals 401 to 610 K; liquid 610 to 700 K.

Temp. K	C_p°	S_T°	$(H_T^\circ - H_{298}^\circ)/T$	$-(G_T^\circ - H_{298}^\circ)/T$	FORMATION FROM THE ELEMENTS		
					$\Delta_f H^\circ$	$\Delta_f G^\circ$	Log K_f
			$\text{J}\cdot\text{mol}^{-1}\cdot\text{K}^{-1}$	$\text{kJ}\cdot\text{mol}^{-1}$			
298.15	96.27	133.09	0.00	133.09	-494.5	-394.5	69.12
300	96.27	133.69	0.60	133.09	-494.4	-393.9	68.59
400	108.41	163.09	26.05	137.05	-495.6	-360.1	47.03
500	120.50	204.68	56.74	147.94	-486.8	-328.1	34.27
600	120.50	226.64	67.36	159.28	-484.0	-296.6	25.82
700	123.43	262.08	89.73	172.35	-471.1	-267.0	19.92

Melting T	610 K	Boiling T	K
$\Delta_{\text{fus}} H^\circ$	10.10 kJ	$\Delta_{\text{vap}} H^\circ$	kJ
$H_{298}^\circ - H_0^\circ$	kJ	Molar Vol.	4.804 $\text{J}\cdot\text{bar}^{-1}$ 48.04 cm^3
A=	-4.736E+02	B=	2.981E-01
		C=	-8.83E+05

5/22/92

MAGNESIUM NITRATE

Formula wt 148.315

Mg(NO₃)₂: Cubic crystals 298.15 to 600 K.

Temp. K	C _p ^o	S _T ^o	(H _T ^o -H ₂₉₈ ^o)/T J·mol ⁻¹ ·K ⁻¹	-(G _T ^o -H ₂₉₈ ^o)/T	FORMATION FROM THE ELEMENTS		
					Δ _f H ^o kJ·mol ⁻¹	Δ _f G ^o	Log K _f
298.15	141.92	164.01	0.00	164.01	-790.7	-589.2	103.22
300	142.40	164.89	0.88	164.01	-790.6	-587.9	102.37
400	168.77	209.45	39.54	169.91	-789.5	-520.5	67.97
500	195.63	249.99	68.07	181.92	-786.0	-453.6	47.38
600	222.70	288.05	91.58	196.47	-780.4	-387.6	33.74

Melting T	K	Boiling T	K
Δ _{sub} H ^o	kJ	Δ _{sub} H ^o	kJ
H ₂₉₈ ^o -H ₀ ^o	kJ	Molar Vol.	6.293 J·bar ⁻¹ 62.93 cm ³

A= -7.811E+02

B= 6.577E-01

C= -3.732+05

5/22/92

AMMONIA-NITER

Formula wt 80.043

NH_4NO_3 : Ammonia-niter undergoes phase changes at 305.3, 357.4, 398.4 K. It melts at 442.8 K.

Temp. K	C_p°	S_T°	$(H_T^\circ - H_{298}^\circ)/T$ J·mol ⁻¹ ·K ⁻¹	$-(G_T^\circ - H_{298}^\circ)/T$	FORMATION FROM THE ELEMENTS		
					$\Delta_f H^\circ$ kJ·mol ⁻¹	$\Delta_f G^\circ$	Log K_f
298.15	139.37	151.08	0.00	151.08	-365.6	-183.8	32.20
300	139.37	151.94	0.86	151.08	-365.6	-182.7	31.81
400	190.79	208.94	51.26	157.68	-358.5	-122.3	15.97
500	161.08	260.24	86.69	173.55	-349.1	-64.5	6.74
Melting T					Boiling T		
442.8 K					K		
$\Delta_{\text{m}}H^\circ$					$\Delta_{\text{vp}}H^\circ$		
5.44 kJ					kJ		
$H_{298}^\circ - H_0^\circ$					Molar Vol.		
kJ					4.649 J·bar ⁻¹ 46.49 cm ³		
A= -3.384E+02			B= 5.556E-01		C= -9.90E+05		

5/22/92

SODA NITER

Formula wt 84.995

NaNO_3 : α -crystals 298.15 to 549.2 K. β -crystals 549.2 to 583.2 K. Liquid 583.2 to 700 K.

Temp. K	C_p°	S_T°	$(H_T^\circ - H_{298}^\circ)/T$ J·mol ⁻¹ ·K ⁻¹	$-(G_T^\circ - H_{298}^\circ)/T$	FORMATION FROM THE ELEMENTS		
					$\Delta_f H^\circ$ kJ·mol ⁻¹	$\Delta_f G^\circ$	Log K_f
298.15	93.07	116.52	0.00	116.52	-468.0	-367.1	64.32
300	93.48	117.10	0.58	116.52	-468.0	-366.5	63.81
400	115.76	147.04	26.59	120.45	-469.1	-332.6	43.43
500	138.07	175.27	46.56	128.62	-465.5	-298.9	31.22
600	154.81	234.63	94.82	139.81	-441.2	-266.7	23.22
700	154.81	258.48	103.39	155.09	-435.1	-238.1	17.77

Melting T	K	Boiling T	K
$\Delta_{\text{fus}} H^\circ$	kJ	$\Delta_{\text{vap}} H^\circ$	kJ
$H_{298}^\circ - H_0^\circ$	kJ	Molar Vol.	3.76 J·bar ⁻¹ 37.6 cm ³

A= -4.447E+02

B= 2.995E-01

C= -1.05E+06

5/22/92

STRONTIUM NITRATE

Formula wt 211.630

Sr(NO₃)₂: Crystals 298.15 to 900 K.

Temp. K	C _p ^o	S _T ^o	(H _T ^o -H ₂₉₈ ^o)/T J·mol ⁻¹ ·K ⁻¹	-(G _T ^o -H ₂₉₈ ^o)/T	FORMATION FROM THE ELEMENTS		
					Δ _f H ^o kJ·mol ⁻¹	Δ _f G ^o	Log K _f
298.15	149.93	194.56	0.00	213.80	-978.2	-779.0	136.47
300	149.88	195.49	0.92	213.80	-978.2	-777.8	135.42
400	169.18	240.55	39.98	220.06	-977.0	-711.1	92.86
500	197.81	281.44	68.73	232.59	-973.6	-644.9	67.37
600	220.32	319.61	92.23	247.42	-968.0	-579.7	50.47
700	234.85	354.76	111.66	263.04	-961.1	-515.5	38.47
800	242.20	386.68	127.58	278.81	-953.4	-452.4	29.54
900	243.53	415.33	140.44	274.89	-946.4	-390.1	22.64

Melting T	K	Boiling T	K
Δ _{fm} H ^o	kJ	Δ _{vsp} H ^o	kJ
H ₂₉₈ ^o -H ₀ ^o	kJ	Molar Vol.	7.093 J·bar ⁻¹ 70.93 cm ³

A= -9.566E+02

B= 6.317E-01

C= -9.810+05

5/22/92

ALUMINUM SULFATE

Formula wt 342.154

 $\text{Al}_2(\text{SO}_4)_3$: Orthorhombic crystals 298.15 to 1100 K.

Temp. K	C_p°	S_T°	$(H_T^\circ - H_{298}^\circ)/T$ J·mol ⁻¹ ·K ⁻¹	$-(G_T^\circ - H_{298}^\circ)/T$	FORMATION FROM THE ELEMENTS		
					$\Delta_f H^\circ$ kJ·mol ⁻¹	$\Delta_f G^\circ$	Log K_f
298.15	259.26	239.30	0.00	239.30	-3441.8	-3100.6	543.20
300	260.62	240.91	1.60	239.30	-3441.9	-3098.5	539.48
400	317.35	324.34	74.05	250.30	-3449.3	-2983.5	389.60
500	352.93	399.26	126.52	272.74	-3451.1	-2866.9	299.49
600	376.60	465.84	166.35	299.49	-3449.7	-2750.1	239.41
700	392.79	525.19	197.62	327.57	-3446.5	-2633.7	196.53
800	403.92	578.41	222.75	355.66	-3442.2	-2517.9	164.40
900	411.44	626.45	243.33	383.12	-3596.9	-2399.4	139.25
1000	416.28	670.07	260.40	409.67	-3609.7	-2265.3	118.32
1100	419.06	709.89	274.71	435.18	-3600.9	-2131.3	101.20

Melting T	K	Boiling T	K
$\Delta_{\text{fus}} H^\circ$	kJ	$\Delta_{\text{vap}} H^\circ$	kJ
$H_{298}^\circ - H_0^\circ$	40.22 kJ	Molar Vol.	7.341 J·bar ⁻¹ 73.41 cm ³

A= -3.501E+03

B= 1.233E+00

C= 3.117E+06

6/10/93

BARITE

Formula wt 233.391

BaSO₄: Orthorhombic crystals 298.15 to 1300 K.

Temp. K	C _p ^o	S _T ^o	(H _T ^o -H ₂₉₈ ^o)/T J·mol ⁻¹ ·K ⁻¹	-(G _T ^o -H ₂₉₈ ^o)/T	FORMATION FROM THE ELEMENTS		
					Δ _f H ^o kJ·mol ⁻¹	Δ _f G ^o	Log K _f
298.15	101.75	132.21	0.00	132.21	-1473.6	-1362.5	238.70
300	102.23	132.84	0.63	132.21	-1473.6	-1361.8	237.11
400	119.28	164.94	28.47	136.47	-1476.0	-1324.4	172.95
500	127.17	192.50	47.51	144.99	-1477.5	-1286.4	134.39
600	131.46	216.10	61.17	154.93	-1479.0	-1248.0	108.65
700	134.04	236.57	71.41	165.16	-1479.4	-1209.5	90.25
800	135.72	254.59	79.35	175.24	-1480.1	-1170.9	76.45
900	136.87	270.65	85.68	184.96	-1533.5	-1131.1	65.65
1000	137.69	285.11	90.85	194.27	-1532.4	-1086.5	56.75
1100	138.30	298.27	95.13	203.13	-1539.8	-1041.1	49.44
1200	138.76	310.32	98.75	211.57	-1539.1	-995.8	43.35
1300	139.12	321.44	101.84	219.60	-1538.3	-950.6	38.19

Melting T	K	Boiling T	K
Δ _{fm} H ^o	kJ	Δ _{vp} H ^o	kJ
H ₂₉₈ ^o -H ₀ ^o	kJ	Molar Vol.	5.21 52.10
			J·bar ⁻¹ cm ³

A= -7.496E+01

B= -9.007E-02

C= 4.067E-01

ANHYDRITE

Formula wt 136.142

CaSO₄: Orthorhombic crystals 298.15 to 1000 K.

Temp. K	C _p ^o	S _T ^o	(H _T ^o -H ₂₉₈ ^o)/T J·mol ⁻¹ ·K ⁻¹	-(G _T ^o -H ₂₉₈ ^o)/T	FORMATION FROM THE ELEMENTS		
					Δ _f H ^o kJ·mol ⁻¹	Δ _f G ^o	Log K _f
298.15	101.23	107.40	0.00	107.40	-1434.4	-1321.8	231.57
300	101.57	108.03	0.63	107.40	-1434.5	-1321.1	230.02
400	116.68	139.45	27.87	111.58	-1436.6	-1283.2	167.56
500	127.18	166.68	46.74	119.94	-1437.2	-1244.7	130.03
600	135.03	190.59	60.83	129.77	-1437.0	-1206.3	105.01
700	141.54	211.91	71.90	140.01	-1436.1	-1167.9	87.15
800	147.55	231.20	80.98	150.22	-1435.8	-1129.5	73.75
900	153.59	248.93	88.71	160.21	-1487.3	-1090.2	63.27
1000	160.04	265.44	95.52	169.92	-1484.2	-1046.3	54.65

Melting T	1723 K	Boiling T	K
Δ _{fus} H ^o	28.03 kJ	Δ _{vap} H ^o	kJ
H ₂₉₈ ^o -H ₀ ^o	17.30 kJ	Molar Vol.	4.601 J·bar ⁻¹ 46.01 cm ³

A= -1.4465E+02

B= 3.971E-01

C= 5.860E+05

9/16/92

CHALCOCYANITE

Formula wt 159.610

CuSO₄: Crystals 298.15 to 1200 K.

Temp. K	C _p ^o	S _T ^o	(H _T ^o -H ₂₉₈ ^o)/T J·mol ⁻¹ ·K ⁻¹	-(G _T ^o -H ₂₉₈ ^o)/T	FORMATION FROM THE ELEMENTS		
					Δ _f H ^o kJ·mol ⁻¹	Δ _f G ^o	Log K _f
298.15	139.89	109.50	0.00	109.50	-771.4	-662.3	116.03
300	140.42	110.37	0.86	109.50	-771.3	-661.6	115.19
400	160.73	153.87	38.57	115.30	-769.2	-625.5	81.69
500	172.71	191.11	64.28	126.83	-765.1	-590.1	61.65
600	181.41	223.40	83.11	140.29	-759.9	-555.6	48.37
700	188.56	251.91	97.67	154.24	-753.9	-522.0	38.95
800	194.88	277.51	109.44	168.08	-747.3	-489.3	31.95
900	200.72	300.81	119.26	181.55	-793.4	-456.4	26.49
1000	206.27	322.24	127.68	194.56	-784.6	-419.4	21.91
1100	211.62	342.15	135.07	207.08	-775.6	-383.3	18.20
1200	216.84	360.79	141.67	219.12	-766.1	-348.1	15.15

Melting T

K

Boiling T

K

Δ_{fus}H^o

kJ

Δ_{vap}H^o

kJ

H₂₉₈^o-H₀^o

16.87 kJ

Molar Vol.

4.088 J·bar⁻¹
40.88 cm³

A= -7.631E+02

B= 3.445E-01

C= -1.35E+05

11/25/92

FERRIC SULFATE

Formula wt 399.885

 $\text{Fe}_2(\text{SO}_4)_3$: Orthorhombic crystals 298.15 to 800 K.

Temp. K	C_p°	S_T°	$(H_T^\circ - H_{298}^\circ)/T$ J·mol ⁻¹ ·K ⁻¹	$-(G_T^\circ - H_{298}^\circ)/T$	FORMATION FROM THE ELEMENTS		
					$\Delta_f H^\circ$ kJ·mol ⁻¹	$\Delta_f G^\circ$	Log K_f
298.15	275.03	282.80	0.00	282.80	-2581.9	-2254.4	394.96
300	276.04	284.50	1.70	282.81	-2581.9	-2252.4	392.16
400	319.44	370.29	76.08	294.21	-2588.8	-2142.1	279.73
500	351.71	445.15	128.08	317.07	-2591.1	-2030.2	212.09
600	379.61	511.78	167.72	344.07	-2590.4	-1918.0	166.98
700	405.44	572.26	199.85	372.41	-2587.4	-1806.2	134.78
800	430.16	628.02	227.10	400.92	-2582.5	-1694.9	110.66

Melting T	K	Boiling T	K
$\Delta_{\text{fus}} H^\circ$	kJ	$\Delta_{\text{vap}} H^\circ$	kJ
$H_{298}^\circ - H_0^\circ$	kJ	Molar Vol.	13.08 J·bar ⁻¹ 130.80 cm ³

A= -2.592E+03

B= 1.121E+00

C= 2.722E+05

6/10/93

ARCANITE

Formula wt 174.260

K_2SO_4 : Orthorhombic crystals (α) 298.15 to 856 K. Hexagonal crystals (β) 856 to melting point 1342 K. Liquid 1342 to 1700 K.

Temp. K	C_p°	S_T°	$(H_T^\circ - H_{298}^\circ)/T$	$-(G_T^\circ - H_{298}^\circ)/T$	FORMATION FROM THE ELEMENTS		
					$\Delta_f H^\circ$	$\Delta_f G^\circ$	Log K_f
	J·mol ⁻¹ ·K ⁻¹		kJ·mol ⁻¹				
298.15	130.01	175.56	0.00	175.56	-1437.7	-1319.6	231.18
300	130.44	176.37	0.80	175.56	-1437.7	-1318.9	229.63
400	149.06	216.62	35.70	180.93	-1445.2	-1278.2	166.91
500	163.03	251.43	59.81	191.62	-1445.8	-1236.3	129.15
600	175.17	282.25	78.04	204.21	-1444.9	-1194.5	103.99
700	186.44	310.11	92.73	217.38	-1442.6	-1152.9	86.03
800	197.25	335.71	105.12	230.59	-1439.3	-1111.7	72.59
900	203.55	368.88	125.49	243.39	-1479.5	-1069.8	62.09
1000	189.91	389.40	132.41	256.99	-1474.8	-1024.5	53.51
1100	197.63	407.72	137.86	269.86	-1628.5	-970.4	46.08
1200	219.88	425.78	143.69	282.09	-1620.8	-910.9	39.65
1300	252.38	444.61	150.77	293.84	-1610.5	-852.1	34.24
1400	197.61	485.93	180.08	305.85	-1567.7	-795.0	29.66
1500	197.61	499.57	181.25	318.32	-1561.4	-740.1	25.77
1600	197.61	512.32	182.28	330.04	-1555.0	-685.5	22.38
1700	197.61	524.30	183.18	341.12	-1548.8	-631.3	19.40

Melting T	K	Boiling T	K
$\Delta_{\text{fus}} H^\circ$	kJ	$\Delta_{\text{vap}} H^\circ$	kJ
$H_{298}^\circ - H_0^\circ$	25.43 kJ	Molar Vol.	6.550 J·bar ⁻¹ 65.50 cm ³

A= -1.541E+03

B= 5.285E-02

C= 6.26776E+06

5/27/92

K-AL SULFATE

Formula wt 258.207

KAl(SO₄)₂: Hexagonal crystals 298.15 to 1000 K.

Temp. K	C _p ^o	S _T ^o	(H _T ^o -H ₂₉₈ ^o)/T J·mol ⁻¹ ·K ⁻¹	-(G _T ^o -H ₂₉₈ ^o)/T	FORMATION FROM THE ELEMENTS		
					Δ _f H ^o kJ·mol ⁻¹	Δ _f G ^o	Log K _f
298.15	192.98	204.60	0.00	204.60	-2470.9	-2240.4	392.50
300	193.95	205.80	1.19	204.60	-2470.9	-2239.0	389.83
400	230.89	267.25	54.52	212.73	-2478.5	-2160.8	282.17
500	252.19	321.23	92.07	229.16	-2480.1	-2081.2	217.42
600	267.33	368.61	120.08	248.53	-2479.7	-2001.4	174.24
700	279.58	410.76	142.01	268.75	-2477.9	-1921.9	143.41
800	290.27	448.80	159.89	288.92	-2475.2	-1842.6	120.31
900	300.06	483.57	174.92	308.64	-2577.9	-1761.6	102.24
1000	309.29	515.66	187.90	327.76	-2581.9	-1670.5	87.25

Melting T	K	Boiling T	K
Δ _m H ^o	kJ	Δ _{vap} H ^o	kJ
H ₂₉₈ ^o -H ₀ ^o	32.22 kJ	Molar Vol.	9.233 J·bar ⁻¹ 92.33 cm ³

A= -2.499E+03

B= 8.218E-01

C= 1.235E+06

5/27/92

ALUNITE

Formula wt 414.214

 $KAl_3(OH)_6(SO_4)_2$: Crystals 298.15 to 700 K.

Temp. K	C_p°	S_T°	$(H_T^\circ - H_{298}^\circ)/T$ J·mol ⁻¹ ·K ⁻¹	$-(G_T^\circ - H_{298}^\circ)/T$	FORMATION FROM THE ELEMENTS		
					$\Delta_f H^\circ$ kJ·mol ⁻¹	$\Delta_f G^\circ$	Log K_f
298.15	372.53	321.00	0.00	321.00	-5176.5	-4663.5	817.00
300	374.90	323.31	2.30	321.01	-5176.6	-4660.3	811.41
400	462.28	444.70	107.73	336.96	-5185.9	-4487.0	585.92
500	508.84	553.29	183.69	369.60	-5186.2	-4312.1	450.48
600	539.32	648.92	240.57	408.35	-5183.0	-4137.6	360.20
700	562.22	733.84	284.94	448.90	-5177.7	-3963.8	295.77

Melting T	K	Boiling T	K
$\Delta_{fus} H^\circ$	kJ	$\Delta_{vap} H^\circ$	kJ
$H_{298}^\circ - H_0^\circ$	kJ	Molar Vol.	29.360 J·bar ⁻¹ 293.60 cm ³

A= -5.116E+03

B= 1.594E+00

C= -2.065E+06

11/25/92

LANGBEINITE

Formula wt 414.997

 $K_2Mg_2(SO_4)_3$: Cubic crystals 298.15 to 1203 K.

Temp. K	C_p°	S_T°	$(H_T^\circ - H_{298}^\circ)/T$ J·mol ⁻¹ ·K ⁻¹	$-(G_T^\circ - H_{298}^\circ)/T$	FORMATION FROM THE ELEMENTS		
					$\Delta_f H^\circ$ kJ·mol ⁻¹	$\Delta_f G^\circ$	Log K_f
298.15	318.92	389.30	0.00	389.30	-4071.0	-3733.4	654.05
300	319.93	391.28	1.97	389.31	-4071.1	-3731.3	649.66
400	363.71	489.76	87.32	402.44	-4084.4	-3616.5	472.25
500	393.92	574.34	145.78	428.56	-4088.1	-3499.1	365.54
600	416.52	648.25	189.10	459.15	-4088.9	-3381.1	294.35
700	434.14	713.84	222.90	490.93	-4087.6	-3263.3	243.50
800	448.13	772.75	250.21	522.54	-4085.1	-3145.7	205.39
900	459.30	826.21	272.85	553.36	-4241.1	-3025.2	175.57
1000	468.13	875.08	291.95	583.12	-4250.8	-2889.0	150.90
1100	474.96	920.03	308.29	611.73	-4401.2	-2744.0	130.30
1200	480.00	961.58	322.40	639.18	-4391.4	-2593.8	112.90

Melting T	1203 K	Boiling T	K
$\Delta_{fus} H^\circ$	kJ	$\Delta_{vap} H^\circ$	kJ
$H_{298}^\circ - H_0^\circ$	57.066 kJ	Molar Vol.	14.695 J·bar ⁻¹ 146.95 cm ³

A= -4.191E+03

B= 1.309E+00

C= 6.392E+06

11/25/92

MAGNESIUM SULFATE

Formula wt 120.369

MgSO₄: Crystals 298.15 to 1400 K.

Temp. K	C _p ^o	S _T ^o	(H _T ^o -H ₂₉₈ ^o)/T	-(G _T ^o -H ₂₉₈ ^o)/T	FORMATION FROM THE ELEMENTS		
					Δ _f H ^o	Δ _f G ^o	Log K _f
			J·mol ⁻¹ ·K ⁻¹		kJ·mol ⁻¹		
298.15	95.71	91.40	0.00	91.40	-1284.9	-1170.5	205.07
300	96.10	91.99	0.59	91.40	-1284.9	-1169.8	203.68
400	111.16	121.91	26.54	95.38	-1287.6	-1131.3	147.72
500	120.67	147.80	44.46	103.34	-1288.7	-1092.1	114.08
600	127.99	170.47	57.80	112.67	-1288.9	-1052.7	91.64
700	134.27	190.68	68.28	122.40	-1288.5	-1013.4	75.62
800	140.01	208.99	76.89	132.10	-1287.7	-974.1	63.60
900	145.42	225.80	84.21	141.59	-1339.6	-933.9	54.20
1000	150.64	241.39	90.59	150.80	-1345.4	-888.3	46.40
1100	155.73	255.99	96.28	159.70	-1342.4	-842.7	40.02
1200	160.73	269.75	101.45	168.30	-1339.0	-797.4	34.71
1300	165.66	282.81	106.20	176.61	-1335.2	-752.4	30.23
1400	170.55	295.27	110.62	184.65	-1458.4	-704.6	26.29

Melting T	1400 K	Boiling T	K
Δ _m H ^o	kJ	Δ _{vp} H ^o	kJ
H ₂₉₈ ^o -H ₀ ^o	1539 kJ	Molar Vol.	J·bar ⁻¹ cm ³

A= -1.325E+03

B= 4.385E-01

C= 2.288E+06

11/25/92

MANGANESE SULFATE

Formula wt 151.002

MnSO₄: Orthorhombic crystals 298.15 to 1000 K.

Temp. K	C _p ^o	S _T ^o	(H _T ^o -H ₂₉₈ ^o)/T J·mol ⁻¹ ·K ⁻¹	-(G _T ^o -H ₂₉₈ ^o)/T	FORMATION FROM THE ELEMENTS		
					Δ _f H ^o kJ·mol ⁻¹	Δ _f G ^o	Log K _f
298.15	100.52	127.00	0.00	127.00	-1065.7	-962.1	168.56
300	100.99	127.62	0.62	127.00	-1065.7	-961.5	167.40
400	118.68	159.38	28.17	131.21	-1067.9	-926.6	120.99
500	129.02	187.05	47.38	139.68	-1068.4	-891.3	93.10
600	136.47	211.26	61.63	149.63	-1068.2	-855.8	74.49
700	142.54	232.77	72.77	160.00	-1067.3	-820.5	61.21
800	147.89	252.16	81.83	170.33	-1066.1	-785.3	51.26
900	152.81	269.86	89.45	180.42	-1117.7	-749.2	43.47
1000	157.47	286.21	96.02	190.19	-1116.9	-708.4	36.99

Melting T	K	Boiling T	K
Δ _{fus} H ^o	kJ	Δ _{vap} H ^o	kJ
H ₂₉₈ ^o -H ₀ ^o	kJ	Molar Vol.	4.362 J·bar ⁻¹ 43.62 cm ³

A= -1.077E+03

B= 3.657E-01

C= 5.563E+05

6/10/93

MASCAGNITE

Formula wt 132.141

 $(\text{NH}_4)_2\text{SO}_4$: Orthorhombic crystals 298.15 to 600 K.

Temp. K	C_p°	S_T°	$(H_T^\circ - H_{298}^\circ)/T$ J·mol ⁻¹ ·K ⁻¹	$-(G_T^\circ - H_{298}^\circ)/T$	FORMATION FROM THE ELEMENTS		
					$\Delta_f H^\circ$ kJ·mol ⁻¹	$\Delta_f G^\circ$	Log K_f
298.15	187.48	220.50	0.00	220.50	-1182.7	-903.5	158.29
300	188.00	221.66	1.16	220.50	-1182.7	-901.8	157.01
400	215.88	279.56	51.35	228.21	-1187.6	-807.6	105.46
500	243.76	330.73	87.05	243.68	-1189.3	-712.4	74.42
600	271.64	377.64	115.49	262.15	-1188.2	-617.0	53.72

Melting T	K	Boiling T	K
$\Delta_{\text{fus}} H^\circ$	kJ	$\Delta_{\text{vap}} H^\circ$	kJ
$H_{298}^\circ - H_0^\circ$	kJ	Molar Vol.	7.468 J·bar ⁻¹ 74.68 cm ³

A= -1.193E+03

B= 9.583E-01

C= 3.227E+05

3/24/93

THENARDITE

Formula wt 142.043

Na_2SO_4 : Orthorhombic crystals (V) 298.15 to 450 K. Orthorhombic crystals (III) 450 to 514 K. Hexagonal crystals (I) 514 to 1155 K. Liquid 1155 to 1800 K.

Temp. K	C_p°	S_T°	FORMATION FROM THE ELEMENTS				
			$(H_T^\circ - H_{298}^\circ)/T$ J·mol ⁻¹ ·K ⁻¹	$-(G_T^\circ - H_{298}^\circ)/T$	$\Delta_f H^\circ$ kJ·mol ⁻¹	$\Delta_f G^\circ$	Log K_f
298.15	127.28	149.60	0.00	149.60	-1387.8	-1269.8	222.46
300	127.63	150.35	0.79	149.56	-1387.8	-1269.1	220.96
400	146.82	191.96	36.81	155.15	-1395.1	-1229.0	160.49
500	173.30	234.89	68.03	166.86	-1392.0	-1187.8	124.09
600	170.78	279.30	96.29	183.01	-1384.2	-1148.4	99.97
700	178.92	306.23	107.51	198.72	-1382.5	-1109.2	82.77
800	187.06	330.66	116.95	213.71	-1379.9	-1070.3	69.88
900	195.20	353.16	125.19	227.97	-1429.6	-1030.7	59.82
1000	203.34	374.15	132.60	241.55	-1424.3	-986.7	51.54
1100	211.48	393.91	139.40	254.51	-1418.2	-943.2	44.79
1200	196.37	431.72	165.14	266.58	-1581.8	-895.0	38.96
1300	195.98	447.42	167.53	279.89	-1575.4	-838.0	33.67
1400	195.58	461.93	169.54	292.39	-1569.2	-781.5	29.16
1500	195.19	475.41	171.27	304.14	-1563.0	-725.5	25.26
1600	194.80	487.99	172.75	315.24	-1557.0	-669.9	21.87
1700	194.40	499.79	174.04	325.75	-1551.0	-614.6	18.88
1800	194.01	510.89	175.16	335.73	-1545.2	-559.6	16.24

Melting T	1155 K	Boiling T	K
$\Delta_{\text{m}} H^\circ$	kJ	$\Delta_{\text{vap}} H^\circ$	kJ
$H_{298}^\circ - H_0^\circ$	23.22 kJ	Molar Vol.	5.333 J·bar ⁻¹ 53.33 cm ³

A= -1.482E+03

B= 5.020E-01

C= 6.251E+06

2/5/92

NICKELOUS SULFATE

Formula wt 154.754

NiSO₄: Orthorhombic crystals 298.15 to 1200 K.

Temp. K	C _p ^o	S _T ^o	FORMATION FROM THE ELEMENTS				
			(H _T ^o -H ₂₉₈ ^o)/T	-(G _T ^o -H ₂₉₈ ^o)/T	Δ _f H ^o	Δ _f G ^o	Log K _f
			J·mol ⁻¹ ·K ⁻¹		kJ·mol ⁻¹		
298.15	97.69	101.30	0.00	101.30	-873.2	-762.7	133.61
300	98.19	101.91	0.60	101.30	-873.3	-762.0	132.67
400	116.56	132.98	27.57	105.41	-875.7	-724.7	94.64
500	126.71	160.17	46.46	113.71	-876.5	-686.9	71.76
600	133.62	183.92	60.44	123.48	-876.6	-648.9	56.49
700	139.01	204.93	71.29	133.64	-876.2	-611.0	45.59
800	143.57	223.80	80.05	143.75	-875.0	-573.7	37.46
900	147.67	240.95	87.34	153.61	-926.6	-534.5	31.02
1000	151.47	256.71	93.56	163.14	-923.7	-491.1	25.65
1100	155.08	271.31	98.99	172.32	-920.5	-448.0	21.27
1200	158.56	284.96	103.81	181.15	-917.1	-405.2	17.64

Melting T	K	Boiling T	K
Δ _{fm} H ^o	kJ	Δ _{vp} H ^o	kJ
H ₂₉₈ ^o -H ₀ ^o	15.94 kJ	Molar Vol.	3.857 J·bar ⁻¹ 38.57 cm ³

A= -8.988E+02

B= 4.077E-01

C= 1.381E+06

2/5/93

ANGLESITE

Formula wt 303.264

PbSO₄: Orthorhombic crystals 298.15 to 1100 K.

Temp. K	C _p ^o	S _T ^o	(H _T ^o -H ₂₉₈ ^o)/T	-(G _T ^o -H ₂₉₈ ^o)/T	FORMATION FROM THE ELEMENTS		
					Δ _f H ^o	Δ _f G ^o	Log K _f
			J·mol ⁻¹ ·K ⁻¹	kJ·mol ⁻¹			
298.15	104.33	148.50	0.00	148.50	-920.0	-813.1	142.44
300	104.33	149.15	0.64	148.50	-920.0	-812.4	141.45
400	108.73	179.59	26.96	152.62	-922.7	-776.4	101.38
500	117.63	204.76	44.16	160.59	-924.2	-739.6	77.27
600	128.30	227.13	57.28	169.85	-924.8	-702.6	61.17
700	139.81	247.76	68.24	179.52	-929.1	-664.8	49.61
800	151.76	267.21	77.93	189.28	-927.4	-627.2	40.95
900	163.98	285.79	86.81	198.98	-977.7	-588.7	34.17
1000	176.35	303.70	95.15	208.56	-972.4	-545.8	28.51
1100	188.83	321.10	103.09	218.00	-966.0	-503.4	23.90

Melting T	K	Boiling T	K
Δ _m H ^o	kJ	Δ _{vap} H ^o	kJ
H ₂₉₈ ^o -H ₀ ^o	20.05 kJ	Molar Vol.	4.795 J·bar ⁻¹ 47.95 cm ³

A= -9.455E+02

B= 3.981E-01

C= 1.275E+06

11/25/92

ZINKOSITE

Formula wt 161.454

ZnSO₄: Orthorhombic crystals 298.15 to 1100 K.

Temp. K	C _p ^o	S _T ^o	(H _T ^o -H ₂₉₈ ^o)/T J·mol ⁻¹ ·K ⁻¹	-(G _T ^o -H ₂₉₈ ^o)/T	FORMATION FROM THE ELEMENTS		
					Δ _f H ^o kJ·mol ⁻¹	Δ _f G ^o	Log K _f
298.15	104.12	110.50	0.00	110.50	-980.1	-868.7	152.20
300	104.02	111.14	0.64	110.50	-980.1	-868.1	151.14
400	104.84	140.94	26.38	114.56	-982.9	-830.5	108.46
500	111.90	165.03	42.72	122.31	-984.8	-792.2	82.76
600	121.41	186.25	55.02	131.23	-985.8	-753.6	65.61
700	132.08	205.75	65.26	140.50	-993.3	-714.8	53.34
800	143.36	224.12	74.31	149.81	-992.5	-675.1	44.08
900	155.01	241.67	82.63	159.05	-1043.8	-634.4	36.82
1000	166.88	258.62	90.46	168.16	-1039.6	-589.1	30.77
1100	178.89	275.09	97.95	177.14	-1034.4	-544.3	25.85

Melting T	K	Boiling T	K
Δ _{fm} H ^o	kJ	Δ _{vp} H ^o	kJ
H ₂₉₈ ^o -H ₀ ^o	17.24 kJ	Molar Vol.	4.157 J·bar ⁻¹ 41.57 cm ³
A=	-1.010E+03	B=	4.187E-01
		C=	1.501E+06

11/25/92

BERLINITE

Formula wt 121.953

AlPO₄: Rhombohedral crystals 298.15 to α-β transition at 855 K. β-crystals 855 to 1000 K.

Temp. K	C _p ^o	S _T ^o	(H _T ^o -H ₂₉₈ ^o)/T	-(G _T ^o -H ₂₉₈ ^o)/T	FORMATION FROM THE ELEMENTS		
					Δ _f H ^o	Δ _f G ^o	Log K _f
			J·mol ⁻¹ ·K ⁻¹	kJ·mol ⁻¹			
298.15	93.96	90.80	0.00	90.80	-1733.8	-1617.9	283.44
300	94.15	91.38	0.58	90.80	-1733.8	-1617.1	281.56
400	109.86	120.53	25.86	94.67	-1735.3	-1577.9	206.05
500	122.79	146.53	44.04	102.49	-1735.0	-1538.6	160.73
600	131.82	169.75	57.95	111.80	-1734.0	-1499.4	130.53
700	140.83	190.72	69.12	121.60	-1732.4	-1460.4	108.97
800	153.40	210.29	78.82	131.47	-1730.0	-1421.7	92.82
900	140.70	229.96	88.62	141.34	-1725.9	-1383.4	80.29
1000	142.50	244.88	93.92	150.96	-1735.2	-1344.7	70.24

Melting T	K	Boiling T	K
Δ _{fus} H ^o	kJ	Δ _{vap} H ^o	kJ
H ₂₉₈ ^o -H ₀ ^o	14.76 kJ	Molar Vol.	4.658 J·bar ⁻¹ 46.58 cm ³

A= -1.731E+03

B= 3.866E-01

C= -2.087E+05

11/25/92

WHITLOCKITE

Formula wt 310.177

$\text{Ca}_3(\text{PO}_4)_2$: Rhombohedral crystals 298.15 to 1373 K. Monoclinic crystals 1373 to 1600 K.

Temp. K	C_p°	S_T°	FORMATION FROM THE ELEMENTS				
			$(H_T^\circ - H_{298}^\circ)/T$ J·mol ⁻¹ ·K ⁻¹	$-(G_T^\circ - H_{298}^\circ)/T$	$\Delta_f H^\circ$ kJ·mol ⁻¹	$\Delta_f G^\circ$	Log K_f
298.15	231.63	236.00	0.00	236.00	-4120.8	-3883.6	680.38
300	232.12	237.43	1.43	236.00	-4120.8	-3882.2	675.93
400	255.24	307.49	62.09	245.40	-4122.7	-3802.1	496.50
500	275.30	366.64	102.76	263.88	-4121.9	-3722.1	388.83
600	294.16	418.51	133.10	285.41	-4120.2	-3642.3	317.08
700	312.44	465.23	157.42	307.82	-4117.6	-3562.8	265.85
800	330.43	508.13	177.92	330.21	-4116.6	-3483.5	227.44
900	348.23	548.08	195.86	352.22	-4112.2	-3404.6	197.59
1000	365.93	585.69	211.98	373.70	-4107.0	-3326.2	173.74
1100	383.55	621.39	226.78	394.61	-4101.2	-3248.4	154.25
1200	401.12	655.52	240.57	414.94	-4245.0	-3167.2	137.86
1300	418.67	688.32	253.60	434.72	-4232.6	-3077.8	123.67
1400	330.54	729.26	275.09	454.17	-4205.8	-2989.8	111.55
1500	330.54	752.05	278.79	473.26	-4201.6	-2903.0	101.09
1600	330.54	773.38	282.02	491.36	-4197.5	-2816.6	91.95

Melting T	K	Boiling T	K
$\Delta_{\text{fus}} H^\circ$	kJ	$\Delta_{\text{vap}} H^\circ$	kJ
$H_{298}^\circ - H_0^\circ$	kJ	Molar Vol.	9.762 J·bar ⁻¹ 97.62 cm ³

A= -4.148E+03

B= 8.253E-01

C= 1.823E+06

11/25/92

FLUORAPATITE

Formula wt 504.302

Ca₅(PO₄)₃F: Hexagonal crystals 298.15 to 1600 K.

Temp. K	C _p ^o	S _T ^o	FORMATION FROM THE ELEMENTS				
			(H _T ^o -H ₂₉₈ ^o)/T	-(G _T ^o -H ₂₉₈ ^o)/T	Δ _f H ^o	Δ _f G ^o	Log K _f
			J·mol ⁻¹ ·K ⁻¹		kJ·mol ⁻¹		
298.15	375.94	387.90	0.00	387.90	-6872.0	-6489.7	1136.95
300	377.11	390.23	2.32	387.91	-6872.0	-6487.4	1129.52
400	426.47	506.06	102.70	403.37	-6874.0	-6358.5	830.32
500	458.22	604.87	170.83	434.03	-6871.4	-6229.9	650.82
600	480.47	690.49	220.68	469.80	-6867.7	-6102.0	531.21
700	496.89	765.84	259.02	506.82	-6863.7	-5974.7	445.83
800	509.43	833.05	289.57	543.47	-6864.1	-5847.4	381.79
900	519.24	893.64	314.57	579.07	-6860.4	-5720.6	332.00
1000	527.04	948.77	335.44	613.33	-6857.7	-5594.1	292.20
1100	533.30	999.30	353.15	646.15	-6856.1	-5467.8	259.64
1200	538.35	1045.93	368.38	677.55	-7085.0	-5335.3	232.23
1300	542.44	1089.19	381.62	707.57	-7077.5	-5189.8	208.52
1400	545.74	1129.51	393.23	736.28	-7069.7	-5044.8	188.22
1500	548.40	1167.26	403.49	763.77	-7061.9	-4900.4	170.64
1600	550.50	1202.72	412.62	790.11	-7054.1	-4756.6	155.28

Melting T	K	Boiling T	K
Δ _{fus} H ^o	kJ	Δ _{vap} H ^o	kJ
H ₂₉₈ ^o -H ₀ ^o	63.47 kJ	Molar Vol.	15.756 J·bar ⁻¹ 157.56 cm ³

A= -6.931E+03

B= 1.344E+00

C= 4.048E+06

11/25/92

HYDROXYAPATITE

Formula wt 502.311

Ca₅(PO₄)₃(OH): Hexagonal crystals 298.15 to 1500 K.

Temp. K	C _p ^o	S _T ^o	FORMATION FROM THE ELEMENTS				
			(H _T ^o -H ₂₉₈ ^o)/T	-(G _T ^o -H ₂₉₈ ^o)/T	Δ _f H ^o	Δ _f G ^o	Log K _f
			J·mol ⁻¹ ·K ⁻¹		kJ·mol ⁻¹		
298.15	385.17	390.40	0.00	390.40	-6738.5	-6337.1	1110.22
300	386.83	392.79	2.38	390.41	-6738.5	-6334.7	1102.94
400	446.42	513.36	106.92	406.44	-6740.1	-6199.4	809.55
500	477.29	616.59	178.17	438.42	-6736.9	-6064.6	633.55
600	497.62	705.50	229.81	475.70	-6732.7	-5930.6	516.29
700	513.35	783.43	269.23	514.21	-6728.4	-5797.2	432.58
800	526.86	852.88	300.60	552.28	-6728.4	-5663.9	369.81
900	539.23	915.66	326.44	589.22	-6724.2	-5531.1	321.01
1000	550.97	973.08	348.31	624.77	-6720.7	-5398.8	282.00
1100	562.37	1026.13	367.25	658.88	-6717.9	-5266.7	250.09
1200	573.58	1075.54	383.98	691.57	-6945.1	-5128.6	223.24
1300	584.69	1121.90	398.99	722.90	-6935.1	-4977.6	200.00
1400	595.76	1165.63	412.65	752.98	-6924.2	-4827.4	180.11
1500	606.82	1207.11	425.23	781.88	-6912.5	-4678.0	162.90

Melting T	K	Boiling T	K
Δ _{sub} H ^o	kJ	Δ _{sub} H ^o	kJ
H ₂₉₈ ^o -H ₀ ^o	64.24 kJ	Molar Vol.	15.960 J·bar ⁻¹ 159.60 cm ³

A= -6.777E+03

B= 1.386E+00

C= 2.726E+06

11/25/92

TOPAZ

Formula wt 184.043

Al₂SiO₄F₂: Orthorhombic crystals 298.15 to 1000 K.

Temp. K	C _p ^o	S _T ^o	(H _T ^o -H ₂₉₈ ^o)/T J·mol ⁻¹ ·K ⁻¹	-(G _T ^o -H ₂₉₈ ^o)/T	FORMATION FROM THE ELEMENTS		
					Δ _f H ^o kJ·mol ⁻¹	Δ _f G ^o	Log K _f
298.15	143.63	105.40	0.00	105.40	-3084.5	-2910.6	509.92
300	144.28	106.29	0.89	105.40	-3084.5	-2909.6	506.59
400	172.38	151.96	40.52	111.44	-3084.9	-2851.1	372.31
500	190.31	192.49	68.81	123.68	-3083.7	-2792.8	291.76
600	201.97	228.30	90.10	138.19	-3081.7	-2734.8	238.08
700	209.49	260.04	106.66	153.38	-3079.3	-2677.2	199.77
800	214.10	288.34	119.83	168.51	-3076.9	-2619.9	171.06
900	216.62	313.72	130.46	183.26	-3074.6	-2562.9	148.75
1000	217.54	336.61	139.13	197.47	-3093.9	-2504.7	130.83

Melting T	K	Boiling T	K
Δ _{sub} H ^o	kJ	Molar Vol.	5.153 J·bar ⁻¹ 51.53 cm ³
H ₂₉₈ ^o -H ₀ ^o	19.77 kJ		
A=	-3.079E+03	B=	5.740E-01
		C=	-2.85E+05

7/23/92

KYANITE

Formula wt 162.046

 Al_2SiO_5 : Triclinic crystals 298.15 to 1800 K.

Temp. K	C_p°	S_T°	$(H_T^\circ - H_{298}^\circ)/T$ J·mol ⁻¹ ·K ⁻¹	$-(G_T^\circ - H_{298}^\circ)/T$	FORMATION FROM THE ELEMENTS		
					$\Delta_f H^\circ$ kJ·mol ⁻¹	$\Delta_f G^\circ$	Log K_f
298.15	121.58	82.80	0.00	82.80	-2593.8	-2443.1	428.01
300	122.26	83.55	0.75	82.80	-2593.8	-2442.2	425.21
400	149.25	122.81	34.84	87.97	-2594.7	-2391.4	312.28
500	165.25	157.97	59.44	98.53	-2594.1	-2340.6	244.52
600	175.97	189.10	78.02	111.08	-2592.7	-2290.1	199.36
700	183.70	216.84	92.59	124.24	-2591.0	-2239.8	167.13
800	189.56	241.77	104.36	137.40	-2589.2	-2189.7	142.97
900	194.15	264.37	114.09	150.27	-2587.3	-2139.9	124.19
1000	197.84	285.02	122.29	162.73	-2606.8	-2088.8	109.11
1100	200.85	304.02	129.30	174.72	-2604.6	-2037.1	96.73
1200	203.35	321.61	135.37	186.24	-2602.3	-1985.6	86.43
1300	205.44	337.97	140.68	197.29	-2599.9	-1934.2	77.72
1400	207.20	353.26	145.37	207.89	-2597.5	-1883.2	70.26
1500	208.70	367.61	149.54	218.06	-2595.0	-1832.2	63.80
1600	209.97	381.12	153.28	227.84	-2592.5	-1781.5	58.16
1700	211.06	393.88	156.65	237.23	-2640.1	-1730.4	53.17
1800	211.99	405.97	159.70	246.27	-2637.3	-1677.0	48.66

Melting T	K	Boiling T	K
$\Delta_{\text{fus}} H^\circ$	kJ	$\Delta_{\text{vap}} H^\circ$	kJ
$H_{298}^\circ - H_0^\circ$	15.86 kJ	Molar Vol.	4.415 J·bar ⁻¹ 44.15 cm ³

A= -2.599E+03

B= 5.109E-01

C= 3.358E+05

ANDALUSITE

Formula wt 162.046

 Al_2SiO_5 : Orthorhombic crystals 298.15 to 1800 K.

Temp. K	C_p°	S_T°	$(H_T^\circ - H_{298}^\circ)/T$ J·mol ⁻¹ ·K ⁻¹	$-(G_T^\circ - H_{298}^\circ)/T$	FORMATION FROM THE ELEMENTS		
					$\Delta_f H^\circ$ kJ·mol ⁻¹	$\Delta_f G^\circ$	Log K_f
298.15	122.60	91.39	0.00	91.39	-2589.9	-2441.8	427.77
300	123.26	92.15	0.76	91.39	-2589.9	-2440.8	424.98
400	149.43	131.57	34.98	96.59	-2590.7	-2391.0	312.22
500	165.03	166.71	59.54	107.17	-2590.1	-2341.1	244.56
600	175.54	197.79	78.05	119.74	-2588.8	-2291.4	199.48
700	183.16	225.45	92.55	132.90	-2587.2	-2241.9	167.29
800	188.94	250.30	104.25	146.05	-2585.4	-2192.7	143.17
900	193.49	272.83	113.92	158.90	-2583.6	-2143.8	124.42
1000	197.16	293.41	122.07	171.34	-2603.1	-2093.5	109.35
1100	200.16	312.35	129.04	183.31	-2601.0	-2042.6	96.99
1200	202.67	329.88	135.07	194.80	-2598.8	-1992.0	86.71
1300	204.77	346.18	140.36	205.83	-2596.4	-1941.4	78.01
1400	206.56	361.43	145.02	216.40	-2594.1	-1891.2	70.56
1500	208.08	375.73	149.18	226.55	-2591.6	-1841.1	64.11
1600	209.38	389.20	152.90	236.30	-2589.2	-1791.1	58.47
1700	210.50	401.93	156.26	245.67	-2636.8	-1740.8	53.49
1800	211.46	413.99	159.30	254.69	-2634.1	-1688.2	48.99

Melting T	K	Boiling T	K
$\Delta_{\text{fus}} H^\circ$	kJ	$\Delta_{\text{vap}} H^\circ$	kJ
$H_{298}^\circ - H_0^\circ$	16.90 kJ	Molar Vol.	5.152 J·bar ⁻¹ 51.52 cm ³

A= -2.595E+03

B= 5.027E-01

C= 3.590E+05

7/29/92

SILLIMANITE

Formula wt 162.046

Al₂SiO₅: Orthorhombic crystals 298.15 to 1800 K.

Temp. K	C _p ^o	S _T ^o	(H _T ^o -H ₂₉₈ ^o)/T J·mol ⁻¹ ·K ⁻¹	-(G _T ^o -H ₂₉₈ ^o)/T	FORMATION FROM THE ELEMENTS		
					Δ _f H ^o kJ·mol ⁻¹	Δ _f G ^o	Log K _f
298.15	123.72	95.40	0.00	95.40	-2586.1	-2439.1	427.32
300	124.33	96.17	0.76	95.40	-2586.1	-2438.2	424.52
400	148.88	135.63	35.01	100.62	-2586.9	-2388.8	311.93
500	163.95	170.58	59.40	111.91	-2586.4	-2339.3	244.38
600	174.29	201.44	77.73	123.71	-2585.2	-2289.9	199.35
700	181.88	228.91	92.09	136.81	-2583.7	-2240.9	167.21
800	187.70	253.59	103.70	149.89	-2582.0	-2192.0	143.12
900	192.31	275.97	113.29	162.68	-2580.4	-2143.4	124.39
1000	196.05	296.44	121.39	175.05	-2598.0	-2093.4	109.35
1100	199.13	315.27	128.32	186.95	-2598.0	-2042.8	97.00
1200	201.70	332.71	134.33	198.38	-2595.9	-1992.5	86.73
1300	203.87	348.94	139.60	209.34	-2593.6	-1942.2	78.04
1400	205.71	364.12	144.26	219.86	-2591.4	-1892.3	70.60
1500	207.29	378.37	148.41	229.96	-2589.0	-1842.3	64.16
1600	208.64	391.79	152.13	239.66	-2586.6	-1792.7	58.52
1700	209.80	404.47	155.49	248.98	-2634.3	-1742.6	53.54
1800	210.80	416.50	158.54	257.96	-2631.7	-1690.3	49.05

Melting T	K	Boiling T	K
Δ _{fusion} H ^o	kJ	Δ _{evap} H ^o	kJ
H ₂₉₈ ^o -H ₀ ^o	17.44 kJ	Molar Vol.	4.986 J·bar ⁻¹ 49.86 cm ³

A= -2.592E+03

B= 4.998E-01

C= 4.086E+05

MULLITE

Formula wt 426.052

 $\text{Al}_6\text{Si}_2\text{O}_{13}$: Orthorhombic crystals 298.15 to 1800 K.

Temp. K	C_p°	S_T°	$(H_T^\circ - H_{298}^\circ)/T$ J·mol ⁻¹ ·K ⁻¹	$-(G_T^\circ - H_{298}^\circ)/T$	FORMATION FROM THE ELEMENTS		
					$\Delta_f H^\circ$ kJ·mol ⁻¹	$\Delta_f G^\circ$	Log K_f
298.15	326.13	275.00	0.00	275.00	-6819.2	-6441.8	1128.55
300	327.73	277.02	2.02	275.01	-6819.3	-6439.4	1121.18
400	392.44	381.04	92.29	288.75	-6821.5	-6312.3	824.29
500	431.98	473.17	156.55	316.62	-6820.4	-6185.1	646.14
600	458.88	554.45	204.83	349.62	-6817.5	-6058.3	527.41
700	478.40	626.72	242.59	384.14	-6813.7	-5932.1	442.65
800	493.16	691.61	273.03	418.59	-6809.8	-5806.4	379.11
900	504.65	750.39	298.15	452.24	-6806.0	-5681.2	329.72
1000	513.76	804.05	319.27	484.78	-6866.2	-5552.0	290.00
1100	521.10	853.37	337.30	516.07	-6861.6	-5420.8	257.40
1200	527.05	898.98	352.87	546.11	-6856.7	-5290.0	230.26
1300	531.91	941.36	366.46	574.90	-6851.4	-5159.5	207.31
1400	535.88	980.93	378.43	602.51	-6846.3	-5029.8	187.66
1500	539.13	1018.02	389.04	628.98	-6840.9	-4900.2	170.64
1600	541.76	1052.90	398.50	654.40	-6835.6	-4771.0	155.75
1700	543.88	1085.81	406.99	678.82	-6930.5	-4641.0	142.60
1800	545.56	1116.95	414.65	702.30	-6924.8	-4506.7	130.78

Melting T	2123 K	Boiling T	K
$\Delta_{\text{fus}} H^\circ$	kJ	$\Delta_{\text{vap}} H^\circ$	kJ
$H_{298}^\circ - H_0^\circ$	46.07 kJ	Molar Vol.	13.46 J·bar ⁻¹ 134.6 cm ³

A= -6.844E+03

B= 1.295E+00

C= 1.613E+06

5/4/92

DUMORTIERITE

Formula wt 565.938

 $[Al_{6.75}][]_{.25}Si_3BO_{17.25}(OH)_{.75}$: Orthorhombic crystals 298.15 to 1800 K.

Temp. K	C_p°	S_T°	$(H_T^\circ - H_{298}^\circ)/T$ J·mol ⁻¹ ·K ⁻¹	$-(G_T^\circ - H_{298}^\circ)/T$	FORMATION FROM THE ELEMENTS		
					$\Delta_f H^\circ$ kJ·mol ⁻¹	$\Delta_f G^\circ$	Log K_f
298.15	440.00	334.90	0.00	334.90	-9109.0	-8568.2	1501.08
300	442.08	337.63	2.72	334.91	-9109.1	-8564.9	1491.24
400	532.57	478.13	124.68	353.45	-9112.5	-8382.8	1094.65
500	592.80	603.87	212.67	391.20	-9111.0	-8200.4	856.67
600	634.72	715.87	279.71	436.16	-9106.7	-8018.7	698.07
700	664.89	816.10	332.70	483.41	-9100.7	-7837.8	584.85
800	687.16	906.41	375.68	530.73	-9094.2	-7657.9	499.99
900	703.94	988.36	411.26	577.10	-9087.6	-7478.7	434.04
1000	716.81	1063.23	441.20	622.02	-9153.0	-7295.3	381.06
1100	726.88	1132.04	466.73	665.30	-9145.4	-7109.9	337.61
1200	734.93	1195.64	488.76	706.88	-9137.5	-6925.2	301.44
1300	741.52	1254.74	507.96	746.78	-9129.2	-6741.0	270.85
1400	747.09	1309.90	524.85	785.05	-9121.2	-6557.9	244.67
1500	751.98	1361.61	539.83	821.78	-9112.9	-6375.0	221.99
1600	756.43	1410.29	553.23	857.06	-9104.6	-6192.7	202.17
1700	760.66	1456.27	565.31	890.97	-9246.7	-6009.4	184.64
1800	764.83	1499.87	576.27	923.59	-9237.7	-5819.4	168.87

Melting T	K	Boiling T	K
$\Delta_{fus} H^\circ$	kJ	$\Delta_{vap} H^\circ$	kJ
$H_{298}^\circ - H_0^\circ$	59.84 kJ	Molar Vol.	16.84 J·bar ⁻¹ 168.4 cm ³

A= -9.125E+03

B= 1.833E+00

C= 1.061E+06

EUCLASE

Formula wt 145.084

BeAlSiO₄(OH): Crystals 298.15 to 1800 K.

Temp. K	C _p ^o	S _T ^o	(H _T ^o -H ₂₉₈ ^o)/T	-(G _T ^o -H ₂₉₈ ^o)/T	FORMATION FROM THE ELEMENTS		
					Δ _f H ^o	Δ _f G ^o	Log K _f
			J·mol ⁻¹ ·K ⁻¹		kJ·mol ⁻¹		
298.15	126.83	89.10	0.00	89.10	-2532.9	-2370.2	415.24
300	127.50	89.89	0.78	89.10	-2532.9	-2369.2	412.50
400	156.65	130.86	36.37	94.49	-2533.9	-2314.4	302.22
500	175.85	168.02	62.47	105.55	-2533.3	-2259.5	236.05
600	188.84	201.30	82.52	118.78	-2531.8	-2204.9	191.95
700	197.87	231.13	98.39	132.74	-2529.7	-2150.6	160.48
800	204.36	258.00	111.25	146.75	-2527.4	-2096.6	136.89
900	209.17	282.36	121.88	160.48	-2525.0	-2042.9	118.56
1000	212.92	304.60	130.80	173.80	-2533.3	-1988.7	103.88
1100	216.03	325.04	138.41	186.63	-2530.7	-1934.4	91.85
1200	218.78	343.96	145.00	198.96	-2528.2	-1880.3	81.84
1300	221.41	361.57	150.77	210.80	-2525.6	-1826.4	73.38
1400	224.07	378.08	155.91	222.17	-2523.0	-1772.7	66.14
1500	226.91	393.63	160.55	233.08	-2520.4	-1719.2	59.87
1600	230.01	408.38	164.79	243.58	-2532.2	-1665.5	54.37
1700	233.47	422.42	168.73	253.69	-2579.2	-1610.9	49.50
1800	237.34	435.87	172.43	263.44	-2575.6	-1554.1	45.10

Melting T	K	Boiling T	K
Δ _{fm} H ^o	kJ	Δ _{vp} H ^o	kJ
H ₂₉₈ ^o -H ₀ ^o	16.83 kJ	Molar Vol.	4.686 J·bar ⁻¹ 46.86 cm ³

A= -2.529E+03

B= 5.403E-01

C= -2.31E+05

7/23/92

PHENAKITE

Formula wt 110.107

Be_2SiO_4 : Hexagonal crystals 298.15 to 1800 K. Decomposes to BeO and SiO_2 above 1833 K.

Temp. K	C_p°	S_T°	$(H_T^\circ - H_{298}^\circ)/T$ J·mol ⁻¹ ·K ⁻¹	$-(G_T^\circ - H_{298}^\circ)/T$	FORMATION FROM THE ELEMENTS		
					$\Delta_f H^\circ$ kJ·mol ⁻¹	$\Delta_f G^\circ$	Log K_f
298.15	95.60	63.37	0.00	63.37	-2143.1	-2028.4	355.36
300	96.16	63.96	0.59	63.37	-2143.1	-2027.7	353.04
400	121.33	95.31	27.84	67.47	-2143.9	-1989.0	259.74
500	138.41	124.34	48.35	75.99	-2143.3	-1950.4	203.75
600	150.19	150.68	64.40	86.28	-2142.1	-1911.9	166.44
700	158.46	174.49	77.28	97.21	-2140.3	-1873.7	139.81
800	164.33	196.06	87.82	108.24	-2138.3	-1835.7	119.86
900	168.53	215.67	96.56	119.10	-2136.2	-1798.0	104.35
1000	171.57	233.59	103.92	129.67	-2134.2	-1760.5	91.96
1100	173.77	250.05	110.18	139.87	-2132.2	-1723.3	81.83
1200	175.39	265.24	115.55	149.70	-2130.3	-1686.2	73.39
1300	176.61	279.33	120.20	159.13	-2128.7	-1649.2	66.27
1400	177.57	292.46	124.26	168.19	-2127.2	-1612.4	60.16
1500	178.39	304.74	127.85	176.89	-2125.9	-1575.7	54.87
1600	179.13	316.27	131.03	185.25	-2153.9	-1538.3	50.22
1700	179.88	327.15	133.88	193.28	-2202.4	-1499.4	46.07
1800	180.68	337.46	136.46	201.00	-2200.6	-1458.0	42.31

Melting T	K	Boiling T	K
$\Delta_{\text{fus}} H^\circ$	kJ	$\Delta_{\text{vap}} H^\circ$	kJ
$H_{298}^\circ - H_0^\circ$	12.16 kJ	Molar Vol.	3.718 J·bar ⁻¹ 37.18 cm ³

A= -2.135E+03

B= 3.744E-01

C= -4.46E+05

7/22/92

BERYL

Formula wt 537.502

 $\text{Be}_3\text{Al}_2(\text{Si}_6\text{O}_{18})$: Hexagonal crystals 298.15 to 1800 K.

Temp. K	C_p°	S_T°	$(H_T^\circ - H_{298}^\circ)/T$ J·mol ⁻¹ ·K ⁻¹	$-(G_T^\circ - H_{298}^\circ)/T$	FORMATION FROM THE ELEMENTS		
					$\Delta_f H^\circ$ kJ·mol ⁻¹	$\Delta_f G^\circ$	Log K_f
298.15	417.00	346.70	0.00	346.71	-9006.6	-8500.5	1489.21
300	419.01	349.29	2.58	346.71	-9006.7	-8497.3	1479.48
400	507.82	482.86	118.55	364.32	-9010.0	-8326.9	1087.35
500	567.30	603.00	202.73	400.26	-9008.6	-8156.2	852.05
600	608.30	710.27	267.11	443.16	-9004.7	-7986.0	695.23
700	637.50	806.36	318.05	488.31	-8999.1	-7816.7	583.27
800	659.03	892.96	359.39	533.56	-8992.8	-7648.1	499.36
900	675.52	971.57	393.64	577.93	-8986.1	-7480.5	434.14
1000	688.78	1043.45	422.51	620.94	-9000.6	-7312.1	381.93
1100	700.03	1109.64	447.24	662.40	-8993.5	-7143.5	339.21
1200	710.19	1170.99	468.73	702.26	-8986.1	-6975.7	303.64
1300	719.89	1228.22	487.68	740.54	-8978.7	-6808.5	273.56
1400	729.66	1281.93	504.61	777.31	-8971.1	-6641.9	247.81
1500	739.86	1332.61	519.95	812.66	-8963.4	-6475.7	225.50
1600	750.81	1380.71	534.04	846.67	-8999.0	-6309.0	205.96
1700	762.75	1426.58	547.13	879.44	-9290.5	-6138.4	188.60
1800	775.87	1470.54	559.47	911.07	-9278.7	-5953.2	172.75

Melting T	K	Boiling T	K
$\Delta_{\text{m}} H^\circ$	kJ	$\Delta_{\text{vap}} H^\circ$	kJ
$H_{298}^\circ - H_0^\circ$	64.43 kJ	Molar Vol.	20.33 J·bar ⁻¹ 203.3 cm ³

A= -8.995E+03

B= 1.683E+00

C= -6.74E+05

7/22/92

BERTRANDITE

Formula wt 238.230

 $\text{Be}_4\text{Si}_2\text{O}_7(\text{OH})_2$: Crystals 298.15 to 1400 K.

Temp. K	C_p°	S_T°	$(H_T^\circ - H_{298}^\circ)/T$ J·mol ⁻¹ ·K ⁻¹	$-(G_T^\circ - H_{298}^\circ)/T$	FORMATION FROM THE ELEMENTS		
					$\Delta_f H^\circ$ kJ·mol ⁻¹	$\Delta_f G^\circ$	Log K_f
298.15	224.64	172.10	0.00	172.10	-4580.5	-4295.1	752.46
300	225.83	173.49	1.39	172.10	-4580.6	-4293.3	747.51
400	279.83	246.33	64.67	181.67	-4582.9	-4197.1	548.07
500	317.42	313.06	111.68	201.38	-4582.4	-4100.6	428.38
600	344.16	373.43	148.32	225.11	-4580.2	-4004.5	348.61
700	363.51	428.01	177.75	250.26	-4576.7	-3908.8	291.67
800	377.60	477.52	201.90	275.63	-4572.5	-3813.6	249.00
900	387.80	522.62	222.02	300.60	-4568.1	-3719.0	215.84
1000	395.06	563.88	238.98	324.90	-4563.5	-3624.9	189.34
1100	400.01	601.78	253.41	348.37	-4559.1	-3531.3	167.68
1200	403.13	636.73	265.77	370.96	-4555.0	-3438.0	149.65
1300	404.76	669.07	276.41	392.67	-4551.4	-3345.1	134.41
1400	405.16	699.09	285.60	413.49	-4548.3	-3252.4	121.35

Melting T	K	Boiling T	K
$\Delta_{\text{fus}} H^\circ$	kJ	$\Delta_{\text{vap}} H^\circ$	kJ
$H_{298}^\circ - H_0^\circ$	31.04 kJ	Molar Vol.	9.179 J·bar ⁻¹ 91.79 cm ³

A= -4.564E+03

B= 9.388E-01

C= -1.03E+06

LAWSONITE

Formula wt 314.238

CaAl₂Si₂O₇(OH)₂·H₂O: Crystals 298.15 to 600 K.

Temp. K	C _p ^o	S _T ^o	(H _T ^o -H ₂₉₈ ^o)/T	-(G _T ^o -H ₂₉₈ ^o)/T	FORMATION FROM THE ELEMENTS		
					Δ _f H ^o	Δ _f G ^o	Log K _f
			J·mol ⁻¹ ·K ⁻¹	kJ·mol ⁻¹			
298.15	275.24	230.00	0.00	230.00	-4869.0	-4512.9	790.63
300	276.56	231.71	1.70	230.01	-4869.1	-4510.7	785.37
400	331.03	319.37	77.78	241.59	-4871.0	-4390.9	573.38
500	368.81	397.47	132.37	265.10	-4869.7	-4270.9	446.17
600	400.03	467.54	174.43	293.10	-4866.0	-4151.5	361.41

Melting T	K	Boiling T	K
Δ _m H ^o	kJ	Δ _{vap} H ^o	kJ
H ₂₉₈ ^o -H ₀ ^o	41.36 kJ	Molar Vol.	10.132 J·bar ⁻¹ 101.32 cm ³

A= -4.869E+03

B= 1.196E+00

C= -7.02E+04

7/29/92

GEHLENITE

Formula wt 274.200

$\text{Ca}_2\text{Al}_2\text{SiO}_7$: Tetragonal crystals 298.15 to incongruent melting point at 1866 K.

Temp. K	C_p°	S_T°	$(H_T^\circ - H_{298}^\circ)/T$ J·mol ⁻¹ ·K ⁻¹	$-(G_T^\circ - H_{298}^\circ)/T$	FORMATION FROM THE ELEMENTS		
					$\Delta_f H^\circ$ kJ·mol ⁻¹	$\Delta_f G^\circ$	Log K_f
298.15	206.40	210.10	0.00	210.10	-3985.0	-3785.5	663.19
300	207.12	211.38	1.28	210.10	-3985.0	-3784.3	658.88
400	236.74	275.39	56.76	218.63	-3985.5	-3717.2	485.41
500	255.45	330.37	94.75	235.62	-3984.6	-3650.2	381.33
600	268.56	378.16	122.69	255.48	-3983.2	-3583.5	311.96
700	278.34	420.33	144.25	276.08	-3981.6	-3517.0	262.44
800	285.95	458.01	161.51	296.50	-3981.9	-3450.5	225.29
900	292.04	492.06	175.69	316.37	-3980.8	-3384.2	196.41
1000	297.04	523.09	187.58	335.52	-4001.6	-3316.4	173.23
1100	301.21	551.61	197.73	353.88	-4001.2	-3247.9	154.23
1200	304.73	577.97	206.50	371.47	-4016.6	-3178.2	138.34
1300	307.74	602.48	214.17	388.31	-4014.6	-3108.3	124.89
1400	310.33	625.39	220.95	404.43	-4012.6	-3038.8	113.38
1500	312.57	646.88	226.99	419.89	-4010.3	-2969.3	103.40
1600	314.53	667.11	232.40	434.71	-4008.1	-2900.0	94.67
1700	316.24	686.23	237.28	448.95	-4055.9	-2830.3	86.96
1800	317.74	704.35	241.71	462.64	-4350.6	-2753.9	79.91

Melting T	1866 K	Boiling T	K
$\Delta_{\text{fus}} H^\circ$	kJ	$\Delta_{\text{vap}} H^\circ$	kJ
$H_{298}^\circ - H_0^\circ$	33.21 kJ	Molar Vol.	9.015 J·bar ⁻¹ 90.15 cm ³

A= -4.005E+03

B= 6.909E-01

C= 1.392E+06

7/22/92

ZOISITE

Formula wt 454.357

 $\text{Ca}_2\text{Al}_3\text{Si}_3\text{O}_{12}(\text{OH})$: Orthorhombic crystals 298.15 to 1200 K.

Temp. K	C_p°	S_T°	$(H_T^\circ - H_{298}^\circ)/T$ J·mol ⁻¹ ·K ⁻¹	$-(G_T^\circ - H_{298}^\circ)/T$	FORMATION FROM THE ELEMENTS		
					$\Delta_f H^\circ$ kJ·mol ⁻¹	$\Delta_f G^\circ$ kJ·mol ⁻¹	Log K_f
298.15	350.34	295.85	0.00	295.85	-6901.1	-6504.5	1139.54
300	351.83	298.02	2.17	295.86	-6901.2	-6502.1	1132.08
400	412.84	408.40	97.91	310.49	-6902.5	-6368.7	831.65
500	450.20	504.83	164.89	339.94	-6900.8	-6235.4	651.39
600	476.35	589.34	214.73	374.61	-6897.7	-6102.6	531.27
700	497.24	664.38	253.63	410.74	-6893.8	-5970.4	445.51
800	516.12	732.02	285.28	446.74	-6891.2	-5838.5	381.21
900	534.93	793.89	311.96	481.93	-6886.4	-5707.2	331.23
1000	554.92	851.27	335.25	516.02	-6913.1	-5574.3	291.16
1100	576.93	905.17	356.20	548.97	-6906.3	-5440.7	258.35
1200	601.55	956.41	375.60	580.81	-6914.2	-5306.5	230.98

Melting T	K	Boiling T	K
$\Delta_{\text{m}} H^\circ$	kJ	$\Delta_{\text{vap}} H^\circ$	kJ
$H_{298}^\circ - H_0^\circ$	52.07 kJ	Molar Vol.	13.65 J·bar ⁻¹ 136.5 cm ³

A= -6.898E+03

B= 1.325E+00

C= -1.37E+05

7/22/92

GROSSULAR

Formula wt 450.446

 $\text{Ca}_3\text{Al}_2\text{Si}_3\text{O}_{12}$: Cubic crystals 298.15 to 1200 K.

Temp. K	C_p°	S_T°	$(H_T^\circ - H_{298}^\circ)/T$	$-(G_T^\circ - H_{298}^\circ)/T$	FORMATION FROM THE ELEMENTS		
					$\Delta_f H^\circ$	$\Delta_f G^\circ$	Log K_f
			J·mol ⁻¹ ·K ⁻¹		kJ·mol ⁻¹		
298.15	330.22	260.12	0.00	260.12	-6640.0	-6278.5	1099.94
300	331.57	262.17	2.04	260.13	-6640.1	-6276.2	1092.77
400	389.70	366.16	92.25	273.91	-6640.8	-6154.7	803.71
500	425.80	457.32	155.64	301.68	-6638.6	-6033.4	630.29
600	448.43	537.11	202.69	334.41	-6635.3	-5912.7	514.73
700	463.30	607.42	238.93	368.49	-6631.6	-5792.6	432.24
800	474.02	670.02	267.67	402.34	-6630.9	-5672.6	370.37
900	482.99	726.37	291.11	435.27	-6628.0	-5553.0	322.28
1000	491.81	777.71	310.73	466.98	-6647.1	-5432.2	283.74
1100	501.62	825.04	327.63	497.41	-6645.2	-5310.8	252.18
1200	513.24	869.17	342.60	526.57	-6666.7	-5187.7	225.81

Melting T	K	Boiling T	K
$\Delta_{\text{fus}} H^\circ$	kJ	$\Delta_{\text{vap}} H^\circ$	kJ
$H_{298}^\circ - H_0^\circ$	47.66 kJ	Molar Vol.	12.528 J·bar ⁻¹ 125.28 cm ³

A= -6.637E+03

B= 1.206E+00

C= -1.07E+05

7/22/92

DATOLITE

Formula wt 159.979

CaB(Si₄)OH: Crystals 298.15 to 1000 K. Datolite decomposes in air at about 970 K.

Temp. K	C _p ^o	S _T ^o	(H _T ^o -H ₂₉₈ ^o)/T J·mol ⁻¹ ·K ⁻¹	-(G _T ^o -H ₂₉₈ ^o)/T	FORMATION FROM THE ELEMENTS		
					Δ _f H ^o kJ·mol ⁻¹	Δ _f G ^o	Log K _f
298.15	127.41	110.20	0.00	110.20	-2477.8	-2318.1	406.12
300	127.95	110.99	0.79	110.20	-2477.8	-2317.1	403.44
400	153.07	151.41	35.87	115.54	-2478.7	-2263.4	295.56
500	172.25	187.72	61.31	126.41	-2478.3	-2209.6	230.83
600	187.00	220.49	81.08	139.41	-2477.0	-2155.9	187.69
700	198.17	250.20	97.05	153.14	-2475.0	-2102.6	156.89
800	206.23	277.22	110.23	166.99	-2473.6	-2049.4	133.81
900	211.49	301.84	121.21	180.63	-2471.1	-1996.6	115.87
1000	214.12	324.28	130.39	193.89	-2468.9	-1944.0	101.54

Melting T	K	Boiling T	K
Δ _{fus} H ^o	kJ	Δ _{vap} H ^o	kJ
H ₂₉₈ ^o -H ₀ ^o	19.25 kJ	Molar Vol.	5.332 J·bar ⁻¹ 53.32 cm ³

A= -2.473E+03

B= 5.301E-01

C= -2.53E+05

7/22/92

ILVAITE

Formula wt 408.793

CaFe₃Si₂O₇O(OH): Monoclinic crystals 298.15 to 900 K.

Temp. K	C _p ^o	S _T ^o	(H _T ^o -H ₂₉₈ ^o)/T	-(G _T ^o -H ₂₉₈ ^o)/T	FORMATION FROM THE ELEMENTS		
					Δ _f H ^o	Δ _f G ^o	Log K _f
			J·mol ⁻¹ ·K ⁻¹		kJ·mol ⁻¹		
298.15	298.90	292.30	0.00	292.30	-3692.8	-3437.0	602.13
300	299.90	294.20	1.85	292.35	-3692.8	-3435.4	598.15
400	343.40	387.70	83.02	304.68	-3689.7	-3350.0	437.45
500	362.50	466.50	137.00	329.50	-3685.5	-3265.6	341.14
600	380.90	534.20	176.10	358.10	-3681.0	-3182.0	277.01
700	398.50	594.30	206.70	387.60	-3676.1	-3099.2	231.26
800	408.10	648.10	213.20	434.90	-3686.8	-3031.4	197.93
900	417.80	696.70	251.40	445.30	-3668.6	-2935.3	170.36

Melting T	K	Boiling T	K
Δ _m H ^o	kJ	Δ _{vap} H ^o	kJ
H ₂₉₈ ^o -H ₀ ^o	48.09 kJ	Molar Vol.	10.107 J·bar ⁻¹ 101.07 cm ³
A=	-3.664E+03	B=	8.052E-01
		C=	-1.20E+06

3/5/93

ANDRADITE

Formula wt 508.177

 $\text{Ca}_3\text{Fe}_2\text{Si}_3\text{O}_{12}$: Cubic crystals 298.15 to 1000 K.

Temp. K	C_p°	S_T°	$(H_T^\circ - H_{298}^\circ)/T$ J·mol ⁻¹ ·K ⁻¹	$-(G_T^\circ - H_{298}^\circ)/T$	FORMATION FROM THE ELEMENTS		
					$\Delta_f H^\circ$ kJ·mol ⁻¹	$\Delta_f G^\circ$	Log K_f
298.15	351.88	316.40	0.00	316.40	-5771.0	-5427.0	950.77
300	353.17	318.58	2.17	316.41	-5771.0	-5424.9	944.53
400	406.71	428.17	97.19	330.99	-5770.1	-5309.5	693.33
500	440.29	522.80	162.68	360.11	-5766.8	-5194.7	542.67
600	462.94	605.20	210.95	394.24	-5762.7	-5080.7	442.30
700	478.83	677.82	248.15	429.67	-5758.5	-4967.3	370.66
800	490.20	742.55	277.74	464.81	-5757.4	-4854.2	316.94
900	498.37	800.78	301.82	498.96	-5754.7	-4741.5	275.18
1000	504.17	853.61	321.78	531.83	-5754.2	-4629.0	241.79

Melting T	K	Boiling T	K
$\Delta_{\text{fus}} H^\circ$	kJ	$\Delta_{\text{vap}} H^\circ$	kJ
$H_{298}^\circ - H_0^\circ$	53.49 kJ	Molar Vol.	13.204 J·bar ⁻¹ 132.04 cm ³

A= -5.756E+03

B= 1.128E+00

C= -6.85E+05

7/22/92

MONTICELLITE

Formula wt 156.466

CaMgSiO₄: Orthorhombic crystals 298.15 to 1100 K.

Temp. K	C _p ^o	S _T ^o	(H _T ^o -H ₂₉₈ ^o)/T	-(G _T ^o -H ₂₉₈ ^o)/T	FORMATION FROM THE ELEMENTS		
					Δ _f H ^o	Δ _f G ^o	Log K _f
			J·mol ⁻¹ ·K ⁻¹	kJ·mol ⁻¹			
298.15	123.00	108.10	0.00	108.10	-2251.0	-2132.8	373.64
300	123.46	108.86	0.76	108.10	-2251.0	-2132.0	371.21
400	141.90	147.16	33.96	113.20	-2250.9	-2092.3	273.23
500	153.07	180.11	56.75	123.37	-2249.9	-2052.8	214.45
600	160.69	208.73	73.47	135.26	-2248.6	-2013.5	175.29
700	166.26	233.94	86.35	147.60	-2247.3	-1974.4	147.33
800	170.53	256.44	96.61	159.82	-2246.8	-1935.4	126.37
900	173.91	276.72	105.02	171.70	-2245.6	-1896.6	110.07
1000	176.64	295.19	112.05	183.14	-2253.2	-1857.2	97.01
1100	178.88	312.14	118.03	194.11	-2252.7	-1817.6	86.31

Melting T	K	Boiling T	K
Δ _m H ^o	kJ	Δ _m H ^o	kJ
H ₂₉₈ ^o -H ₀ ^o	18.76 kJ	Molar Vol.	5.13 J·bar ⁻¹ 51.3 cm ³

A= -2.248E+03

B= 3.910E-01

C= -1.25E+05

7/22/92

AKERMANITE

Formula wt 272.628

$\text{Ca}_2\text{MgSi}_2\text{O}_7$: Tetragonal crystals 298.15 to melting point at 1731 K. A small transition at 357.9 K has an enthalpy of 0.68 kJ.

Temp. K	C_p°	S_T°	$(H_T^\circ - H_{298}^\circ)/T$ J·mol ⁻¹ ·K ⁻¹	$-(G_T^\circ - H_{298}^\circ)/T$	FORMATION FROM THE ELEMENTS		
					$\Delta_f H^\circ$ kJ·mol ⁻¹	$\Delta_f G^\circ$	Log K_f
298.15	214.10	212.50	0.00	212.50	-3864.8	-3667.5	642.52
300	214.79	213.83	1.32	212.50	-3864.8	-3666.3	638.35
400	239.88	281.42	58.23	223.19	-3864.4	-3600.9	470.22
500	253.60	336.53	96.03	240.50	-3863.1	-3535.2	369.31
600	263.63	383.69	123.16	260.53	-3861.7	-3469.8	302.06
700	272.19	424.98	143.85	281.13	-3860.3	-3404.6	254.05
800	280.00	461.84	160.38	301.46	-3860.8	-3339.3	218.03
900	287.32	495.25	174.08	321.16	-3859.7	-3274.2	190.03
1000	294.24	525.88	185.76	340.12	-3867.4	-3208.5	167.59
1100	300.75	554.23	195.92	358.32	-3866.9	-3142.6	149.23
1200	306.85	580.67	204.91	375.76	-3882.1	-3075.6	133.87
1300	312.52	605.46	212.97	392.48	-3879.6	-3008.5	120.88
1400	317.73	628.81	220.27	408.54	-4004.1	-2938.5	109.63
1500	322.45	650.84	226.93	423.96	-3999.6	-2862.5	99.68
1600	326.68	671.84	233.03	438.81	-3994.8	-2786.8	90.98
1700	330.38	691.76	238.65	453.11	-4090.1	-2710.5	83.28
1800	382.00	784.60	315.23	469.37	-4253.3	-2629.6	76.31
Melting T	1731 K				Boiling T		K
$\Delta_{\text{fus}} H^\circ$	124.5 kJ				$\Delta_{\text{vap}} H^\circ$		kJ
$H_{298}^\circ - H_0^\circ$	34.91 kJ				Molar Vol.	9.254 J·bar ⁻¹	
						92.54 cm ³	
	A= -3.904E+03		B= 6.968E-01		C= 2.903E+06		

7/22/92

MERWINITE

Formula wt 328.705

 $\text{Ca}_3\text{Mg}(\text{SiO}_4)_2$: Monoclinic crystals 298.15 to 1600 K.

Temp. K	C_p°	S_T°	$(H_T^\circ - H_{298}^\circ)/T$ J·mol ⁻¹ ·K ⁻¹	$-(G_T^\circ - H_{298}^\circ)/T$	FORMATION FROM THE ELEMENTS		
					$\Delta_f H^\circ$ kJ·mol ⁻¹	$\Delta_f G^\circ$	Log K_f
298.15	252.36	253.10	0.00	253.10	-4536.2	-4307.7	754.67
300	253.18	254.66	1.56	253.10	-4536.2	-4306.2	749.77
400	286.77	332.55	69.05	263.50	-4535.6	-4229.6	552.32
500	306.89	398.87	114.76	284.11	-4533.6	-4153.3	433.89
600	320.06	456.07	147.95	308.12	-4531.2	-4077.5	354.97
700	329.37	506.14	173.24	332.90	-4528.9	-4002.1	298.63
800	336.54	550.61	193.22	357.39	-4529.6	-3926.6	256.38
900	342.58	590.60	209.49	381.12	-4528.1	-3851.4	223.52
1000	348.15	626.99	223.08	403.91	-4535.9	-3775.5	197.21
1100	353.67	660.43	234.70	425.73	-4535.9	-3699.5	175.67
1200	359.46	691.45	244.85	446.60	-4559.8	-3621.6	157.64
1300	365.75	720.46	253.90	466.56	-4557.3	-3543.5	142.38
1400	372.69	747.82	262.14	485.68	-4681.7	-3462.5	129.18
1500	380.42	773.79	269.76	504.03	-4676.9	-3375.5	117.54
1600	389.04	798.61	276.94	521.67	-4671.4	-3288.9	107.37

Melting T	K	Boiling T	K
$\Delta_{\text{fus}} H^\circ$	kJ	$\Delta_{\text{vap}} H^\circ$	kJ
$H_{298}^\circ - H_0^\circ$	kJ	Molar Vol.	9.85 J·bar ⁻¹ 98.5 cm ³

A= -4.557E+03

B= 7.840E-01

C= 1.573E+06

7/22/92

TITANITE (SPHENE)

Formula wt 196.041

CaTiSiO₅: Monoclinic crystals 298.15 to 1670 K.

Temp. K	C _p ^o	S _T ^o	(H _T ^o -H ₂₉₈ ^o)/T	-(G _T ^o -H ₂₉₈ ^o)/T	FORMATION FROM THE ELEMENTS		
					Δ _f H ^o	Δ _f G ^o	Log K _f
			J·mol ⁻¹ ·K ⁻¹		kJ·mol ⁻¹		
298.15	138.91	129.20	0.00	129.20	-2596.6	-2454.6	430.03
300	139.51	130.06	0.86	129.20	-2596.6	-2453.8	427.23
400	161.30	173.58	38.59	134.99	-2596.2	-2406.2	314.20
500	172.66	210.90	64.37	146.54	-2594.9	-2358.8	246.42
600	179.92	243.07	83.06	160.01	-2593.3	-2311.7	201.25
700	185.25	271.22	97.29	173.93	-2591.6	-2264.9	169.01
800	189.54	296.24	108.56	187.68	-2590.9	-2218.3	144.83
900	193.24	318.79	117.77	201.02	-2589.3	-2171.8	126.04
1000	196.56	339.32	125.49	213.83	-2588.0	-2125.4	111.02
1100	199.64	358.20	132.09	226.11	-2587.1	-2079.2	98.73
1200	202.55	375.70	137.84	237.86	-2598.2	-2032.3	88.46
1300	205.34	392.02	142.93	249.10	-2596.0	-1985.3	79.77
1400	208.05	407.34	147.48	259.86	-2593.7	-1938.4	72.32
1500	210.70	421.78	151.61	270.17	-2591.3	-1891.7	65.87
1600	213.30	435.47	155.38	280.08	-2588.9	-1845.1	60.23

Melting T	1670 K	Boiling T	K
Δ _m H ^o	kJ	Δ _{vp} H ^o	kJ
H ₂₉₈ ^o -H ₀ ^o	kJ	Molar Vol.	5.574 J·bar ⁻¹ 55.74 cm ³

A= -2.591E+03

B= 4.661E-01

C= -2.27E+05

7/22/92

LARNITE

Formula wt 172.239

α -Ca₂SiO₄: Monoclinic crystals 298.15 to 1000 K. Bredigite (α') is the stable modification of Ca₂SiO₄ between 970 and 1710 K. α -crystals 1710 to 1800 K.

Temp. K	C _p ^o	S _T ^o	(H _T ^o -H ₂₉₈ ^o)/T	-(G _T ^o -H ₂₉₈ ^o)/T	FORMATION FROM THE ELEMENTS		
					$\Delta_f H^\circ$	$\Delta_f G^\circ$	Log K _f
			J·mol ⁻¹ ·K ⁻¹		kJ·mol ⁻¹		
298.15	128.59	127.60	0.00	127.60	-2306.7	-2191.2	383.88
300	128.97	128.40	0.79	127.60	-2306.7	-2190.5	381.39
400	145.20	167.89	35.02	132.88	-2306.3	-2151.8	280.99
500	156.15	201.54	58.21	143.33	-2305.1	-2113.3	220.77
600	164.18	230.76	75.24	155.52	-2303.6	-2075.1	180.65
700	170.37	256.55	88.40	168.15	-2302.1	-2037.1	152.01
800	175.34	279.63	98.97	180.66	-2302.4	-1999.2	130.53
900	179.44	300.53	107.69	192.84	-2301.1	-1961.4	113.83
1000	180.66	319.64	115.05	204.59	-2300.1	-1923.7	100.48
1100	185.28	337.21	121.35	215.86	-2299.6	-1886.1	89.56
1200	189.89	353.50	126.84	226.66	-2315.0	-1847.2	80.41
1300	194.50	368.67	131.66	237.01	-2313.0	-1808.3	72.66
1400	199.11	382.87	135.95	246.92	-2310.8	-1769.6	66.02
1500	203.72	396.23	139.79	256.44	-2308.6	-1731.0	60.28
1600	208.33	408.83	143.26	265.57	-2306.3	-1692.6	55.26
1700	212.94	420.76	146.41	274.35	-2354.1	-1653.8	50.81
1800	205.02	444.84	160.60	284.24	-2628.4	-1610.9	46.75

Melting T	K	Boiling T	K
$\Delta_{\text{fus}} H^\circ$	kJ	$\Delta_{\text{vap}} H^\circ$	kJ
H ₂₉₈ ^o -H ₀ ^o	kJ	Molar Vol.	5.16 J·bar ⁻¹ 51.6 cm ³

A= -2.308E+03

B= 3.850E-01

C= 2.243E+05

7/22/92

CALCIO-OLIVINE

Formula wt 172.239

 γ -Ca₂SiO₄: Orthorhombic crystals 298.15 to 1200 K.

Temp. K	C _p ^o	S _T ^o	(H _T ^o -H ₂₉₈ ^o)/T J·mol ⁻¹ ·K ⁻¹	-(G _T ^o -H ₂₉₈ ^o)/T	FORMATION FROM THE ELEMENTS		
					Δ _f H ^o kJ·mol ⁻¹	Δ _f G ^o	Log K _f
298.15	126.93	120.50	0.00	120.50	-2316.5	-2198.9	385.23
300	127.29	121.29	0.78	120.50	-2316.5	-2198.2	382.73
400	141.80	160.08	34.39	125.69	-2316.3	-2158.7	281.90
500	151.34	192.80	56.87	135.93	-2315.5	-2119.4	221.41
600	158.91	221.08	73.26	147.82	-2314.6	-2080.3	181.10
700	165.57	246.09	85.98	160.10	-2313.6	-2041.3	152.32
800	171.73	268.60	96.32	172.28	-2314.3	-2002.3	130.73
900	177.61	289.17	105.03	184.14	-2313.3	-1963.3	113.95
1000	183.31	308.18	112.57	195.61	-2312.4	-1924.5	100.52
1100	188.89	325.91	119.26	206.66	-2311.7	-1885.7	89.54
1200	194.39	342.58	125.29	217.30	-2326.7	-1845.8	80.34

Melting T	K	Boiling T	K
Δ _{fus} H ^o	kJ	Δ _{vap} H ^o	kJ
H ₂₉₈ ^o -H ₀ ^o	kJ	Molar Vol.	5.801 J·bar ⁻¹ 58.01 cm ³

A= -2.314E+03

B= 3.898E-01

C= -9.84E+04

7/22/92

HATURITE (ALITE)

Formula wt 228.317

 Ca_3SiO_5 : Triclinic crystals 298.15 to 1800 K.

Temp. K	C_p°	S_T°	FORMATION FROM THE ELEMENTS				
			$(H_T^\circ - H_{298}^\circ)/T$ J·mol ⁻¹ ·K ⁻¹	$-(G_T^\circ - H_{298}^\circ)/T$	$\Delta_f H^\circ$ kJ·mol ⁻¹	$\Delta_f G^\circ$	Log K_f
298.15	171.59	168.60	0.00	168.60	-2933.1	-2786.5	488.17
300	172.08	169.66	1.06	168.60	-2933.1	-2785.6	485.00
400	193.33	222.31	46.67	175.64	-2932.2	-2736.5	357.34
500	207.61	267.07	77.51	189.56	-2930.3	-2687.8	280.78
600	218.01	305.89	100.10	205.79	-2928.1	-2639.5	229.78
700	225.97	340.12	117.54	222.58	-2925.9	-2591.5	193.38
800	232.28	370.72	131.50	239.22	-2926.4	-2543.6	166.07
900	237.43	398.39	143.00	255.39	-2924.6	-2495.8	144.85
1000	241.72	423.63	152.66	270.97	-2923.3	-2448.3	127.88
1100	245.33	446.84	160.92	285.92	-2922.8	-2400.8	114.00
1200	248.43	468.33	168.09	300.24	-2946.1	-2351.5	102.35
1300	251.10	488.32	174.38	313.94	-2943.4	-2302.0	92.50
1400	253.43	507.01	179.94	327.07	-2940.4	-2252.8	84.05
1500	255.48	524.57	184.91	339.66	-2937.4	-2203.8	76.74
1600	257.28	541.12	189.38	351.74	-2934.4	-2155.0	70.35
1700	258.89	556.76	193.42	363.34	-2981.4	-2105.9	64.70
1800	260.31	571.60	197.10	374.51	-3424.0	-2048.0	59.43

Melting T	K	Boiling T	K
$\Delta_{\text{melt}} H^\circ$	kJ	$\Delta_{\text{vap}} H^\circ$	kJ
$H_{298}^\circ - H_0^\circ$	kJ	Molar Vol.	7.274 J·bar ⁻¹ 72.74 cm ³
A= -2.936E+03	B= 4.891E-01	C= 4.480E+05	

7/22/92

RANKINITE

Formula wt 288.401

 $\text{Ca}_3\text{Si}_2\text{O}_7$: Monoclinic crystals 298.15 to 1400 K.

Temp. K	C_p°	S_T°	$(H_T^\circ - H_{298}^\circ)/T$ J·mol ⁻¹ ·K ⁻¹	$-(G_T^\circ - H_{298}^\circ)/T$	FORMATION FROM THE ELEMENTS		
					$\Delta_f H^\circ$ kJ·mol ⁻¹	$\Delta_f G^\circ$	Log K_f
298.15	214.35	210.60	0.00	210.60	-3949.0	-3748.1	656.64
300	215.00	211.93	1.32	210.60	-3949.0	-3746.9	652.37
400	242.55	277.86	58.46	219.41	-3948.5	-3679.5	480.48
500	260.37	334.03	97.17	236.86	-3946.9	-3612.4	377.38
600	272.58	382.65	125.45	257.20	-3944.9	-3545.7	308.68
700	281.20	425.35	147.12	278.23	-3942.9	-3479.4	259.63
800	287.38	463.33	164.29	299.04	-3943.7	-3413.0	222.84
900	291.79	497.44	178.22	319.22	-3942.4	-3346.7	194.23
1000	294.89	528.36	189.74	338.61	-3941.8	-3280.6	171.36
1100	296.98	556.57	199.41	357.16	-3942.2	-3214.4	152.64
1200	298.27	582.47	207.60	374.88	-3966.7	-3146.4	136.95
1300	298.92	606.38	214.60	391.78	-3965.3	-3078.1	123.68
1400	299.05	628.54	220.63	407.91	-3964.2	-3009.9	112.30

Melting T	1633	K	Boiling T	K
$\Delta_{\text{fus}} H^\circ$		kJ	$\Delta_{\text{vap}} H^\circ$	kJ
$H_{298}^\circ - H_0^\circ$		kJ	Molar Vol.	9.651 J·bar ⁻¹ 96.51 cm ³

A= -3.948E+03

B= 6.684E-01

C= 5.979E+04

7/22/92

ROSENHAHNITE

Formula wt 366.500

 $\text{Ca}_3\text{Si}_3\text{O}_8(\text{OH})_2$: Triclinic crystals 298.15 to 1800 K.

Temp. K	C_p°	S_T°	FORMATION FROM THE ELEMENTS				
			$(H_T^\circ - H_{298}^\circ)/T$ J·mol ⁻¹ ·K ⁻¹	$-(G_T^\circ - H_{298}^\circ)/T$	$\Delta_f H^\circ$ kJ·mol ⁻¹	$\Delta_f G^\circ$	Log K_f
298.15	289.35	281.80	0.00	281.80	-5198.1	-4882.1	855.31
300	290.58	283.59	1.79	281.81	-5198.1	-4880.2	849.69
400	335.67	374.18	80.33	293.85	-5198.5	-4774.0	623.41
500	359.45	451.87	133.98	317.89	-5197.0	-4668.1	487.66
600	374.84	518.85	172.92	345.93	-5195.0	-4562.4	397.19
700	386.28	577.52	202.61	374.91	-5192.9	-4457.2	332.59
800	395.60	629.73	226.17	403.56	-5193.5	-4351.9	284.14
900	403.70	676.80	245.45	431.35	-5191.8	-4246.8	246.47
1000	411.03	719.72	261.65	458.07	-5190.7	-4141.9	216.35
1100	417.86	759.22	275.54	483.67	-5190.1	-4037.0	191.70
1200	424.36	795.86	287.68	508.18	-5213.4	-3930.4	171.08
1300	430.62	830.07	298.43	531.64	-5210.4	-3823.6	153.63
1400	436.70	862.21	308.09	554.12	-5207.2	-3717.0	138.68
1500	442.66	892.54	316.87	575.68	-5203.6	-3610.7	125.73
1600	448.52	921.30	324.91	596.39	-5199.8	-3504.6	114.41
1700	454.30	948.66	332.35	616.31	-5346.2	-3397.4	104.39
1800	460.02	974.79	339.29	635.50	-5787.1	-3276.3	95.07

Melting T	K	Boiling T	K
$\Delta_{\text{fus}} H^\circ$	kJ	$\Delta_{\text{vap}} H^\circ$	kJ
$H_{298}^\circ - H_0^\circ$	kJ	Molar Vol.	12.646 J·bar ⁻¹ 126.46 cm ³

A= -5.206E+03

B= 1.065E+00

C= 6.937E+05

7/22/92

SPURRITE

Formula wt 444.565

 $\text{Ca}_5(\text{SiO}_4)_2\text{CO}_3$: Crystals 298.15 to 1300 K.

Temp. K	C_p°	S_T°	$(H_T^\circ - H_{298}^\circ)/T$ J·mol ⁻¹ ·K ⁻¹	$-(G_T^\circ - H_{298}^\circ)/T$	FORMATION FROM THE ELEMENTS		
					$\Delta_f H^\circ$ kJ·mol ⁻¹	$\Delta_f G^\circ$	Log K_f
298.15	343.62	331.00	0.00	331.00	-5840.2	-5525.6	968.04
300	344.71	333.13	2.12	331.01	-5840.2	-5523.6	961.73
400	388.72	438.91	93.78	345.13	-5838.1	-5418.4	707.55
500	415.98	528.78	155.67	373.11	-5834.3	-5313.9	555.12
600	434.91	606.39	200.72	405.67	-5830.1	-5210.2	453.58
700	449.02	674.54	235.23	439.31	-5826.2	-5107.2	381.09
800	460.04	735.24	262.67	472.57	-5826.9	-5004.2	326.73
900	468.93	789.96	285.11	504.85	-5824.0	-4901.5	284.47
1000	476.30	839.76	303.87	535.89	-5822.2	-4799.1	250.68
1100	482.51	885.45	319.84	565.62	-5821.7	-4696.9	223.03
1200	487.84	927.67	333.62	594.05	-5861.1	-4591.5	199.86
1300	492.46	966.91	345.66	621.24	-5857.1	-4485.9	180.24

Melting T	K	Boiling T	K
$\Delta_{\text{melt}} H^\circ$	kJ	$\Delta_{\text{vap}} H^\circ$	kJ
$H_{298}^\circ - H_0^\circ$	kJ	Molar Vol.	14.697 J·bar ⁻¹ 146.97 cm ³

A= -5.829E+03

B= 1.031E+00

C= -3.84E+05

7/23/92

TILLEYITE

Formula wt 488.575

 $\text{Ca}_5\text{Si}_2\text{O}_7(\text{CO}_3)_2$: Monoclinic crystals 298.15 to 1200 K.

Temp. K	C_p°	S_T°	$(H_T^\circ - H_{298}^\circ)/T$ J·mol ⁻¹ ·K ⁻¹	$-(G_T^\circ - H_{298}^\circ)/T$	FORMATION FROM THE ELEMENTS		
					$\Delta_f H^\circ$ kJ·mol ⁻¹	$\Delta_f G^\circ$	Log K_f
298.15	383.49	394.00	0.00	394.00	-6372.2	-6013.5	1053.52
300	384.73	396.38	2.37	394.01	-6372.2	-6011.3	1046.63
400	436.64	514.78	104.98	409.80	-6369.6	-5891.3	769.30
500	470.37	616.07	174.89	441.17	-6365.1	-5772.2	603.00
600	494.50	704.07	226.25	477.82	-6360.0	-5654.1	492.22
700	512.82	781.73	265.94	515.80	-6354.9	-5536.8	413.15
800	527.33	851.19	297.74	553.46	-6354.4	-5419.8	353.87
900	539.15	914.01	323.92	590.08	-6350.0	-5303.2	307.78
1000	549.01	971.34	345.95	625.38	-6346.6	-5187.1	270.94
1100	557.38	1024.07	364.80	659.26	-6344.4	-5071.3	240.81
1200	564.58	1072.88	381.16	691.72	-6382.0	-4952.5	215.57

Melting T	K	Boiling T	K
$\Delta_{\text{fus}} H^\circ$	kJ	$\Delta_{\text{vap}} H^\circ$	kJ
$H_{298}^\circ - H_0^\circ$	kJ	Molar Vol.	17.050 J·bar ⁻¹ 170.50 cm ³

A= -6.351E+03

B= 1.165E+00

C= -8.90E+05

01/07/93

COBALT-OLIVINE

Formula wt 209.950

Co₂SiO₄: Orthorhombic crystals 298.15 to 1300 K.

Temp. K	C _p ^o	S _T ^o	(H _T ^o -H ₂₉₈ ^o)/T	-(G _T ^o -H ₂₉₈ ^o)/T	FORMATION FROM THE ELEMENTS		
					Δ _f H ^o	Δ _f G ^o	Log K _f
			J·mol ⁻¹ ·K ⁻¹		kJ·mol ⁻¹		
298.15	133.41	142.60	0.00	142.60	-1412.0	-1308.7	229.27
300	133.83	143.43	0.82	142.60	-1412.0	-1308.0	227.74
400	151.48	184.55	36.46	148.09	-1410.8	-1273.5	166.30
500	162.81	219.65	60.67	158.98	-1409.0	-1239.4	129.47
600	170.44	250.05	78.37	171.68	-1406.8	-1205.7	104.96
700	175.73	276.75	91.92	184.82	-1404.5	-1172.4	87.48
800	179.40	300.47	102.64	197.83	-1403.1	-1139.2	74.38
900	181.91	321.75	111.32	210.43	-1401.1	-1106.3	64.21
1000	183.55	341.01	118.47	222.54	-1399.5	-1073.7	56.08
1100	184.52	358.56	124.43	234.12	-1398.4	-1041.1	49.44

Melting T	1693 K	Boiling T	K
Δ _{fus} H ^o	kJ	Δ _{vap} H ^o	kJ
H ₂₉₈ ^o -H ₀ ^o	22.52 kJ	Molar Vol.	4.449 J·bar ⁻¹ 44.49 cm ³

A= -1.401E+03

B= 3.282E-01

C= -4.72E+05

7/22/92

FAYALITE

Formula wt 203.777

Fe_2SiO_4 : Orthorhombic crystals 298.15 to 1490 K. Fayalite melts incongruently at 1490 K.
Liquid 1490 to 1800 K.

Temp. K	C_p°	S_T°	$(H_T^\circ - H_{298}^\circ)/T$ J·mol ⁻¹ ·K ⁻¹	$-(G_T^\circ - H_{298}^\circ)/T$	FORMATION FROM THE ELEMENTS		
					$\Delta_f H^\circ$ kJ·mol ⁻¹	$\Delta_f G^\circ$	Log K_f
298.15	131.84	151.00	0.00	151.00	-1478.2	-1379.1	241.61
300	132.39	151.82	0.81	151.00	-1478.2	-1378.5	240.02
400	152.14	192.99	36.51	156.48	-1477.1	-1345.4	175.69
500	162.24	228.12	60.73	167.39	-1475.5	-1312.7	137.13
600	168.83	258.31	78.23	180.09	-1473.8	-1280.3	111.45
700	174.03	284.74	91.55	193.19	-1472.3	-1248.1	93.14
800	178.71	308.29	102.16	206.13	-1471.0	-1216.2	79.41
900	183.31	329.60	110.92	218.68	-1470.4	-1184.4	68.74
1000	188.03	349.16	118.39	230.77	-1470.9	-1152.6	60.21
1100	193.02	367.31	124.95	242.36	-1472.9	-1120.7	53.21
1200	198.33	384.33	130.84	253.49	-1473.0	-1088.7	47.39
1300	204.03	400.43	136.25	264.18	-1469.6	-1056.8	42.46
1400	210.14	415.77	141.30	274.46	-1466.0	-1025.2	38.25
1500	240.60	490.58	205.80	284.78	-1372.5	-994.4	34.63
1600	240.60	506.10	207.98	298.12	-1366.1	-969.4	31.65
1700	240.60	520.68	209.89	310.79	-1412.0	-944.3	29.01
1800	240.60	534.43	211.60	322.83	-1406.7	-916.9	26.61

Melting T	1490 K	Boiling T	K
$\Delta_{\text{m}} H^\circ$	89.3 kJ	$\Delta_{\text{vap}} H^\circ$	kJ
$H_{298}^\circ - H_0^\circ$	22.49 kJ	Molar Vol.	4.631 J·bar ⁻¹ 46.31 cm ³

A= -1.457E+03

B= 3.049E-01

C= -1.30E+06

7/22/92

ALMANDINE

Formula wt 497.753

 $\text{Fe}_3\text{Al}_2\text{Si}_3\text{O}_{12}$: Cubic crystals 298.15 to 1200 K.

Temp. K	C_p°	S_T°	FORMATION FROM THE ELEMENTS				
			$(H_T^\circ - H_{298}^\circ)/T$ J·mol ⁻¹ ·K ⁻¹	$-(G_T^\circ - H_{298}^\circ)/T$	$\Delta_f H^\circ$ kJ·mol ⁻¹	$\Delta_f G^\circ$ kJ·mol ⁻¹	Log K_f
298.15	343.29	342.60	0.00	342.60	-5264.7	-4941.9	865.79
300	344.49	344.73	2.12	342.61	-5264.7	-4939.9	860.10
400	396.60	451.51	94.70	356.81	-5264.5	-4831.6	630.93
500	431.35	543.98	158.77	385.21	-5262.0	-4723.6	493.46
600	455.57	624.89	206.33	418.56	-5258.5	-4616.2	401.87
700	472.90	696.49	243.24	453.25	-5254.6	-4509.5	336.50
800	485.47	760.51	272.78	487.73	-5251.0	-4403.3	287.50
900	494.57	818.24	296.94	521.30	-5248.4	-4297.5	249.42
1000	501.06	870.71	317.05	553.66	-5269.5	-4190.5	218.88
1100	505.54	918.69	334.00	584.69	-5271.4	-4082.4	193.85
1200	508.42	962.81	348.42	614.39	-5271.3	-3974.4	173.00

Melting T	1683 K	Boiling T	K
$\Delta_{\text{fus}} H^\circ$	kJ	$\Delta_{\text{vap}} H^\circ$	kJ
$H_{298}^\circ - H_0^\circ$	52.74 kJ	Molar Vol.	11.532 J·bar ⁻¹ 115.32 cm ³

A= -5.257E+03

B= 1.068E+00

C= -3.13E+05

4/6/93

CORDIERITE

Formula wt 584.953

 $Mg_2Al_3(AlSi_5O_{18})$: Orthorhombic crystals 298.15 to 1700 K.

Temp. K	C_p°	S_T°	$(H_T^\circ - H_{298}^\circ)/T$ J·mol ⁻¹ ·K ⁻¹	$-(G_T^\circ - H_{298}^\circ)/T$	FORMATION FROM THE ELEMENTS		
					$\Delta_f H^\circ$ kJ·mol ⁻¹	$\Delta_f G^\circ$	Log K_f
298.15	443.28	407.20	0.00	407.20	-9161.5	-8651.1	1515.61
300	445.39	409.95	2.74	407.21	-9161.6	-8648.0	1505.71
400	528.32	550.66	124.83	425.83	-9164.9	-8476.1	1106.84
500	577.52	674.23	210.80	463.43	-9164.2	-8303.9	867.48
600	611.37	782.68	274.89	507.79	-9161.6	-8132.1	707.94
700	636.90	878.92	324.86	554.06	-9157.8	-7960.8	594.03
800	657.37	965.35	365.18	600.16	-9153.5	-7790.1	508.63
900	674.50	1043.79	398.63	645.16	-9149.2	-7619.9	442.24
1000	689.32	1115.64	426.97	688.67	-9204.5	-7445.9	388.92
1100	702.43	1181.97	451.43	730.54	-9199.3	-7270.2	345.22
1200	714.27	1243.60	472.84	770.76	-9193.4	-7095.1	308.83
1300	725.11	1301.21	491.84	809.37	-9186.9	-6920.4	278.06
1400	735.16	1355.32	508.86	846.45	-9434.8	-6740.2	251.48
1500	744.56	1406.36	524.27	882.09	-9424.6	-6548.0	228.02
1600	753.44	1454.70	538.31	916.38	-9414.0	-6356.6	207.52
1700	761.87	1500.63	551.22	949.41	-9653.8	-6163.4	189.37

Melting T	K	Boiling T	K
$\Delta_{fus} H^\circ$	kJ	$\Delta_{vap} H^\circ$	kJ
$H_{298}^\circ - H_0^\circ$	kJ	Molar Vol.	23.322 J·bar ⁻¹ 233.22 cm ³

A= -9.227E+03

B= 1.785E+00

C= 4.350E+06

7/22/92

FORSTERITE

Formula wt 140.693

Mg₂SiO₄: Orthorhombic crystals 298.15 to 1800 K.

Temp. K	C _p ^o	S _T ^o	(H _T ^o -H ₂₉₈ ^o)/T	-(G _T ^o -H ₂₉₈ ^o)/T	FORMATION FROM THE ELEMENTS		
					Δ _f H ^o	Δ _f G ^o	Log K _f
			J·mol ⁻¹ ·K ⁻¹	kJ·mol ⁻¹			
298.15	118.61	94.11	0.00	94.11	-2173.0	-2053.6	359.78
300	119.10	94.85	0.73	94.11	-2173.0	-2052.9	357.43
400	137.71	131.97	32.92	99.05	-2173.2	-2012.8	262.84
500	148.28	163.92	55.01	108.91	-2172.6	-1972.7	206.09
600	155.77	191.65	71.21	120.44	-2171.6	-1932.9	168.27
700	161.75	216.12	83.73	132.39	-2170.5	-1893.2	141.27
800	166.83	238.06	93.81	144.25	-2169.2	-1853.6	121.03
900	171.25	257.97	102.17	155.80	-2167.9	-1814.2	105.29
1000	175.14	276.22	109.28	166.94	-2183.8	-1773.6	92.64
1100	178.56	293.08	115.42	177.65	-2182.7	-1732.6	82.27
1200	181.54	308.74	120.81	187.93	-2181.3	-1691.8	73.64
1300	184.08	323.38	125.58	197.79	-2179.8	-1651.1	66.34
1400	186.21	337.10	129.84	207.26	-2433.0	-1604.2	59.85
1500	187.92	350.01	133.66	216.35	-2428.5	-1545.1	53.80
1600	189.21	362.18	137.09	225.09	-2424.0	-1486.3	48.52
1700	190.08	373.68	140.19	233.49	-2469.7	-1427.4	43.86
1800	190.53	384.56	142.97	241.59	-2465.0	-1366.2	39.64

Melting T	2163 K	Boiling T	K
Δ _{ms} H ^o	kJ	Δ _{vap} H ^o	kJ
H ₂₉₈ ^o -H ₀ ^o	17.22 kJ	Molar Vol.	4.365 J·bar ⁻¹ 43.65 cm ³

A= -2.240E+03

B= 4.675E-01

C= 4.724E+06

7/22/92

PYROPE

Formula wt 403.127

Mg₃Al₂Si₃O₁₂: Cubic crystals 298.15 to 1570 K.

Temp. K	C _p ^o	S _T ^o	(H _T ^o -H ₂₉₈ ^o)/T	-(G _T ^o -H ₂₉₈ ^o)/T	FORMATION FROM THE ELEMENTS		
					Δ _f H ^o	Δ _f G ^o	Log K _f
			J·mol ⁻¹ ·K ⁻¹		kJ·mol ⁻¹		
298.15	325.76	266.27	0.00	266.27	-6285.0	-5934.5	1039.67
300	327.12	268.29	2.01	266.28	-6285.1	-5932.3	1032.88
400	383.71	370.83	90.96	279.87	-6286.1	-5814.4	759.27
500	419.39	460.56	153.33	307.24	-6284.3	-5696.7	595.12
600	443.59	539.30	199.81	339.49	-6280.9	-5579.5	485.72
700	460.82	609.04	235.93	373.11	-6276.9	-5462.9	407.64
800	473.55	671.45	264.87	406.57	-6272.6	-5346.9	349.11
900	483.27	727.81	288.62	439.19	-6268.5	-5231.4	303.62
1000	490.92	779.14	308.49	470.65	-6311.8	-5112.8	267.06
1100	497.14	826.23	325.36	500.87	-6308.0	-4993.0	237.09
1200	502.37	869.72	339.90	529.82	-6304.0	-4873.7	212.14
1300	506.94	910.11	352.58	557.54	-6299.9	-4754.6	191.04
1400	511.10	947.84	363.75	584.08	-6678.0	-4626.6	172.62
1500	515.01	983.23	373.71	609.52	-6669.6	-4480.3	156.01

Melting T	1570 K	Boiling T	K
Δ _{fus} H ^o	241.0 kJ	Δ _{vap} H ^o	kJ
H ₂₉₈ ^o -H ₀ ^o	47.85 kJ	Molar Vol.	11.312 J·bar ⁻¹ 113.12 cm ³

A= -6.316E+03

B= 1.208E+00

C= 2.167E+06

7/22/92

GLASS

Formula wt 403.127

Mg₃Al₂Si₃O₁₂: Glass 298.15 to glass transition 1020 K.

Temp. K	C _p ^o	S _T ^o	(H _T ^o -H ₂₉₈ ^o)/T	-(G _T ^o -H ₂₉₈ ^o)/T	FORMATION FROM THE ELEMENTS		
					Δ _f H ^o	Δ _f G ^o	Log K _f
			J·mol ⁻¹ ·K ⁻¹		kJ·mol ⁻¹		
298.15	387.18	346.30	0.00	346.3	-6163.0	-5836.3	1022.48
300	387.83	348.70	2.39	346.3	-6162.9	-5834.3	1015.82
400	416.67	464.47	102.57	361.9	-6159.5	-5725.2	747.62
500	437.98	559.83	167.61	392.2	-6155.1	-5617.2	586.81
600	455.32	641.26	214.16	427.1	-6150.3	-5510.0	479.68
700	470.25	712.60	249.70	462.9	-6145.2	-5403.7	403.22
800	483.61	776.28	278.12	498.2	-6140.0	-5298.2	345.93
900	495.85	833.95	301.64	532.3	-6134.8	-5193.2	301.40
1000	507.28	886.79	321.64	565.2	-6176.6	-5085.3	265.62

Melting T	1570 K	Boiling T	K
Δ _{lv} H ^o	kJ	Δ _{lv} H ^o	kJ
H ₂₉₈ ^o -H ₀ ^o	50.09 kJ	Molar Vol.	14.61 J·bar ⁻¹ 146.1 cm ³

A= -6.143E+03

B= 1.058E+00

C= -7.88E+05

10/15/92

TEPHROITE

Formula wt 201.959

Mn_2SiO_4 : Orthorhombic crystals 298.15 to 1524 K. Tephroite melts incongruently at 1524 K.

Temp. K	C_p°	S_T°	$(H_T^\circ - H_{298}^\circ)/T$ J·mol ⁻¹ ·K ⁻¹	$-(G_T^\circ - H_{298}^\circ)/T$	FORMATION FROM THE ELEMENTS		
					$\Delta_f H^\circ$ kJ·mol ⁻¹	$\Delta_f G^\circ$	Log K_f
298.15	128.74	155.90	0.00	155.90	-1731.5	-1631.0	285.73
300	129.11	156.70	0.80	155.90	-1731.5	-1630.3	283.86
400	144.89	196.18	35.00	161.18	-1731.3	-1596.6	208.49
500	155.22	229.69	58.08	171.62	-1730.4	-1563.0	163.29
600	162.48	258.67	74.90	183.76	-1729.5	-1529.7	133.17
700	167.82	284.14	87.82	196.32	-1728.4	-1496.4	111.66
800	171.86	306.82	98.08	208.74	-1727.5	-1463.4	95.55
900	174.96	327.25	106.46	220.79	-1726.6	-1430.4	83.02
1000	177.38	345.82	113.43	232.38	-1730.3	-1397.4	72.99
1100	179.27	362.81	119.34	243.48	-1729.8	-1364.2	64.78
1200	180.74	378.48	124.39	254.08	-1729.2	-1331.0	57.93
1300	181.87	392.99	128.77	264.22	-1728.7	-1297.8	52.15
1400	182.73	406.50	132.60	273.90	-1732.9	-1264.6	47.18
1500	183.36	419.13	135.96	283.17	-1737.6	-1230.8	42.86

Melting T	1524 K	Boiling T	K
$\Delta_{fm} H^\circ$	kJ	$\Delta_{vap} H^\circ$	kJ
$H_{298}^\circ - H_0^\circ$	22.35 kJ	Molar Vol.	4.899 J·bar ⁻¹ 48.99 cm ³

A= -1.730E+03

B= 3.321E-01

C= -3.65E+04

LIEBENBERGITE

Formula wt 209.463

 Ni_2SiO_4 : Orthorhombic crystals 298.15 to 1300 K.

Temp. K	C_p°	S_T°	FORMATION FROM THE ELEMENTS				
			$(H_T^\circ - H_{298}^\circ)/T$ J·mol ⁻¹ ·K ⁻¹	$-(G_T^\circ - H_{298}^\circ)/T$	$\Delta_f H^\circ$ kJ·mol ⁻¹	$\Delta_f G^\circ$ kJ·mol ⁻¹	Log K_f
298.15	123.07	128.10	0.00	128.10	-1396.5	-1288.9	225.81
300	123.50	128.86	0.76	128.10	-1396.5	-1288.3	224.30
400	141.96	167.13	33.93	133.19	-1396.7	-1252.1	163.51
500	153.93	200.18	56.82	143.36	-1396.1	-1216.1	127.04
600	162.20	229.02	73.73	155.29	-1395.6	-1180.1	102.73
700	168.12	254.49	86.81	167.68	-1394.7	-1144.2	85.38
800	172.44	277.24	97.26	179.98	-1393.0	-1109.5	72.44
900	175.61	297.74	105.80	191.94	-1391.2	-1073.1	62.28
1000	177.93	316.37	112.90	203.47	-1389.4	-1037.9	54.21
1100	179.60	333.41	118.89	214.52	-1387.7	-1002.8	47.62
1200	180.74	349.09	124.00	225.09	-1386.2	-967.9	42.13
1300	181.48	363.59	128.40	235.19	-1384.8	-933.1	37.49

Melting T	K	Boiling T	K
$\Delta_{\text{fus}} H^\circ$	kJ	$\Delta_{\text{vap}} H^\circ$	kJ
$H_{298}^\circ - H_0^\circ$	19.72 kJ	Molar Vol.	4.257 J·bar ⁻¹ 42.57 cm ³

A= -1.391E+03

B= 3.528E-01

C= -3.04E+05

7/22/92

Ni₂SiO₄-SPINEL

Formula wt 209.463

Ni₂SiO₄: Cubic crystals 298.15 to 800 K.

Temp. K	C _p ^o	S _T ^o	(H _T ^o -H ₂₉₈ ^o)/T J·mol ⁻¹ ·K ⁻¹	-(G _T ^o -H ₂₉₈ ^o)/T	FORMATION FROM THE ELEMENTS		
					Δ _f H ^o kJ·mol ⁻¹	Δ _f G ^o	Log K _f
298.15	120.73	124.10	0.00	124.10	-1389.7	-1280.9	224.41
300	121.36	124.85	0.75	124.10	-1389.7	-1280.3	222.91
400	143.89	163.28	34.09	129.19	-1389.8	-1243.7	162.41
500	155.08	196.71	57.28	139.43	-1389.1	-1207.3	126.12
600	161.80	225.63	74.18	151.45	-1388.5	-1171.0	101.94
700	166.42	250.93	87.05	163.89	-1387.7	-1134.8	84.68
800	169.91	273.39	97.19	176.20	-1386.2	-1099.7	71.80

Melting T	K	Boiling T	K
Δ _m H ^o	kJ	Δ _{vap} H ^o	kJ
H ₂₉₈ ^o -H ₀ ^o	kJ	Molar Vol.	3.981 J·bar ⁻¹ 39.81 cm ³
A= -1.385E+03	B= 3.578E-01	C= -2.19E+05	

7/29/92

ZIRCON

Formula wt 183.307

ZrSiO₄: Tetragonal crystals 298.15 to 1600 K.

Temp. K	C _p ^o	S _T ^o	(H _T ^o -H ₂₉₈ ^o)/T	-(G _T ^o -H ₂₉₈ ^o)/T	FORMATION FROM THE ELEMENTS		
					Δ _f H ^o	Δ _f G ^o	Log K _f
			J·mol ⁻¹ ·K ⁻¹		kJ·mol ⁻¹		
298.15	98.64	84.03	0.00	84.03	-2034.2	-1919.7	336.32
300	99.03	84.64	0.61	84.03	-2034.2	-1919.0	334.12
400	115.51	115.58	27.45	88.14	-2034.0	-1880.6	245.58
500	126.03	142.57	46.18	96.39	-2032.9	-1842.4	192.47
600	133.27	166.23	60.13	106.10	-2031.3	-1804.4	157.08
700	138.46	187.18	70.97	116.21	-2029.5	-1766.7	131.83
800	142.28	205.93	79.65	126.28	-2027.4	-1729.3	112.91
900	145.12	222.86	86.78	136.08	-2025.4	-1692.2	98.21
1000	147.25	238.27	92.72	145.54	-2023.4	-1655.3	86.46
1100	148.83	252.38	97.76	154.62	-2021.4	-1618.5	76.86
1200	149.97	265.38	102.06	163.32	-2023.2	-1581.8	68.85
1300	150.76	277.42	105.78	171.64	-2021.0	-1545.1	62.08
1400	151.28	288.61	109.01	179.60	-2018.8	-1508.6	56.28
1500	151.55	299.06	111.84	187.22	-2016.7	-1472.2	51.27
1600	151.63	308.84	114.33	194.52	-2014.8	-1436.0	46.88

Melting T	K	Boiling T	K
Δ _{fus} H ^o	kJ	Δ _{vap} H ^o	kJ
H ₂₉₈ ^o -H ₀ ^o	kJ	Molar Vol.	3.926 J·bar ⁻¹ 39.26 cm ³

A= -2.023E+03

B= 3.674E-01

C= -6.21E+05

7/23/92

WOLLASTONITE

Formula wt 116.162

CaSiO₃: Triclinic crystals 298.15 to 1400 K. Pseudowollastonite is stable above 1398 K.

Temp. K	C _p ^o	S _T ^o	(H _T ^o -H ₂₉₈ ^o)/T	-(G _T ^o -H ₂₉₈ ^o)/T	FORMATION FROM THE ELEMENTS		
					Δ _f H ^o	Δ _f G ^o	Log K _f
			J·mol ⁻¹ ·K ⁻¹	kJ·mol ⁻¹			
298.15	86.19	81.69	0.00	81.69	-1634.8	-1549.0	271.37
300	86.50	82.22	0.53	81.69	-1634.8	-1548.5	269.61
400	99.33	109.02	23.77	85.26	-1634.7	-1519.7	198.45
500	107.40	132.12	39.74	92.38	-1633.9	-1491.0	155.76
600	112.94	152.22	51.50	100.71	-1633.0	-1462.5	127.32
700	116.96	169.94	60.58	109.36	-1631.9	-1434.2	107.02
800	120.02	185.77	67.83	117.94	-1631.8	-1405.9	91.80
900	122.44	200.05	73.77	126.28	-1630.9	-1377.8	79.96
1000	124.42	213.06	78.74	134.32	-1630.1	-1349.7	70.50
1100	126.11	225.00	82.97	142.03	-1629.6	-1321.7	62.76
1200	127.60	236.03	86.63	149.41	-1637.1	-1293.1	56.28
1300	128.95	246.30	89.83	156.47	-1635.9	-1264.4	50.80
1400	130.22	255.90	92.67	163.23	-1634.7	-1235.9	46.11

Melting T	K	Boiling T	K
Δ _{sub} H ^o	kJ	Δ _{sub} H ^o	kJ
H ₂₉₈ ^o -H ₀ ^o	13.84 kJ	Molar Vol.	3.990 J·bar ⁻¹ 39.90 cm ³

A= -1.632E+03

B= 2.827E-01

C= -1.12E+05

7/31/92

PSEUDOWOLLASTONITE

Formula wt 116.162

CaSiO₃: Triclinic crystals 298.15 to melting point 1821 K.

Temp. K	C _p ^o	S _T ^o	(H _T ^o -H ₂₉₈ ^o)/T	-(G _T ^o -H ₂₉₈ ^o)/T	FORMATION FROM THE ELEMENTS		
					Δ _f H ^o	Δ _f G ^o	Log K _f
			J·mol ⁻¹ ·K ⁻¹	kJ·mol ⁻¹			
298.15	87.92	87.20	0.00	87.20	-1627.6	-1543.5	270.40
300	88.20	87.74	0.54	87.20	-1627.6	-1542.9	268.64
400	99.53	114.82	24.00	90.82	-1627.4	-1514.7	197.80
500	106.55	137.84	39.86	97.98	-1626.7	-1486.6	155.30
600	111.43	157.72	51.40	106.32	-1625.8	-1458.7	126.99
700	115.06	175.18	60.25	114.93	-1625.0	-1430.9	106.77
800	117.89	190.74	67.28	123.45	-1625.0	-1403.2	91.61
900	120.17	204.76	73.04	131.72	-1624.3	-1375.5	79.83
1000	122.06	217.52	77.85	139.67	-1623.8	-1347.8	70.40
1100	123.65	229.23	81.94	147.29	-1623.6	-1320.3	62.69
1200	125.01	240.05	85.48	154.57	-1631.3	-1292.1	56.24
1300	126.19	250.10	88.56	161.54	-1630.4	-1263.8	50.78
1400	127.23	259.49	91.29	168.21	-1629.4	-1235.7	46.10
1500	128.14	268.30	93.72	174.59	-1628.4	-1207.6	42.05
1600	128.95	276.60	95.89	180.71	-1627.5	-1179.6	38.51
1700	129.68	284.44	97.86	186.58	-1676.7	-1145.1	35.37
1800	130.34	291.87	99.65	192.23	-1824.1	-1118.1	32.44

Melting T	1821 K	Boiling T	K
Δ _{fus} H ^o	57.3 kJ	Δ _{vap} H ^o	kJ
H ₂₉₈ ^o -H ₀ ^o	kJ	Molar Vol.	4.008 J·bar ⁻¹ 40.08 cm ³

A= -1.629E+03

B= 2.815E-01

C= 1.853E+05

7/31/92

CaSiO₃ glass

Formula wt 116.162

CaSiO₃: Glass 298.15 to 1821 K, melting point of pseudowollastonite.

Temp. K	C _p ^o	S _T ^o	FORMATION FROM THE ELEMENTS				
			(H _T ^o -H ₂₉₈ ^o)/T	-(G _T ^o -H ₂₉₈ ^o)/T	Δ _f H ^o	Δ _f G ^o	Log K _f
			J·mol ⁻¹ ·K ⁻¹		kJ·mol ⁻¹		
298.15	86.81	94.80	0.00	94.80	-1608.7	-1526.8	267.49
300	87.12	95.34	0.54	94.80	-1608.7	-1526.3	265.75
400	99.31	122.25	23.86	98.39	-1608.5	-1498.8	195.72
500	106.80	145.27	39.75	105.52	-1607.8	-1471.5	153.72
600	112.43	165.26	51.41	113.85	-1606.9	-1444.3	125.74
700	117.18	182.95	60.47	122.48	-1605.9	-1417.3	105.76
800	121.47	198.88	67.83	131.05	-1605.7	-1390.3	90.78
900	125.49	213.42	74.02	139.41	-1604.5	-1363.5	79.13
1000	129.34	226.85	79.36	147.49	-1603.4	-1336.8	69.82
1100	133.07	239.35	84.07	155.28	-1602.3	-1310.1	62.21
1200	136.74	251.09	88.31	162.78	-1609.0	-1283.0	55.85
1300	140.35	262.17	92.17	170.00	-1606.8	-1255.9	50.46
1400	143.92	272.70	95.74	176.96	-1604.3	-1229.0	45.85
1500	147.46	282.76	99.07	183.68	-1601.5	-1202.3	41.87
1600	150.99	292.38	102.21	190.18	-1598.5	-1175.8	38.39
1700	154.49	301.64	105.18	196.46	-1645.3	-1149.0	35.30
1800	157.98	310.57	108.02	202.56	-1790.2	-1117.8	32.44

Melting T	1821 K	Boiling T	K
Δ _{sub} H ^o	kJ	Δ _{vap} H ^o	kJ
H ₂₉₈ ^o -H ₀ ^o	14.20 kJ	Molar Vol.	4.013 J·bar ⁻¹ 40.13 cm ³

A= -1.606E+03

B= 2.698E-01

C= -6.93E+04

7/31/92

Ca-Al PYROXENE

Formula wt 218.123

CaAl₂SiO₆: Monoclinic crystals 298.15 to 1000 K.

Temp. K	C _p ^o	S _T ^o	(H _T ^o -H ₂₉₈ ^o)/T	-(G _T ^o -H ₂₉₈ ^o)/T	FORMATION FROM THE ELEMENTS		
					Δ _f H ^o	Δ _f G ^o	Log K _f
			J·mol ⁻¹ ·K ⁻¹	kJ·mol ⁻¹			
298.15	164.97	141.00	0.00	141.00	-3306.3	-3129.6	548.27
300	165.63	142.02	1.02	141.00	-3306.3	-3128.5	544.70
400	194.10	193.89	46.01	147.88	-3306.9	-3069.0	400.77
500	212.57	239.32	77.59	161.73	-3306.0	-3009.7	314.41
600	225.29	279.27	101.21	178.06	-3304.3	-2950.5	256.86
700	234.43	314.72	119.62	195.10	-3302.4	-2891.7	215.78
800	241.23	346.49	134.42	212.07	-3301.3	-2833.1	184.98
900	246.45	375.22	146.59	228.63	-3299.5	-2774.7	161.04
1000	250.58	401.40	156.79	244.61	-3319.2	-2715.0	141.81

Melting T	K	Boiling T	K
Δ _m H ^o	kJ	Δ _{vap} H ^o	kJ
H ₂₉₈ ^o -H ₀ ^o	24.40 kJ	Molar Vol.	6.357 J·bar ⁻¹ 63.57 cm ³

A= -3.303E+03

B= 5.877E-01

C= -1.73E+05

04/30/93

HEDENBERGITE

Formula wt 248.092

CaFeSi₂O₆: Monoclinic crystals 298.15 to 1300 K. Decomposes at 1238 K.

Temp. K	C _p ^o	S _T ^o	(H _T ^o -H ₂₉₈ ^o)/T J·mol ⁻¹ ·K ⁻¹	-(G _T ^o -H ₂₉₈ ^o)/T	FORMATION FROM THE ELEMENTS		
					Δ _f H ^o kJ·mol ⁻¹	Δ _f G ^o	Log K _f
298.15	175.30	174.20	0.00	174.20	-2839.9	-2676.3	468.86
300	175.94	175.29	1.08	174.20	-2839.9	-2675.2	465.79
400	201.95	229.81	48.35	181.46	-2839.3	-2620.4	342.18
500	218.13	276.73	80.79	195.94	-2837.6	-2565.9	268.05
600	229.59	317.57	104.69	212.88	-2835.4	-2511.7	218.66
700	238.39	353.65	123.18	230.46	-2833.2	-2457.9	183.41
800	245.51	385.96	138.04	247.92	-2831.8	-2404.4	156.99
900	251.49	415.23	150.32	264.90	-2829.8	-2351.1	136.45
1000	256.67	442.00	160.71	281.29	-2828.6	-2298.0	120.03
1100	261.25	466.68	169.64	297.04	-2828.4	-2244.9	106.60
1200	265.37	489.59	177.45	312.14	-2835.2	-2191.3	95.38
1300	269.13	510.99	184.36	326.63	-2831.6	-2137.6	85.90

Melting T	K	Boiling T	K
Δ _m H ^o	kJ	Δ _{vp} H ^o	kJ
H ₂₉₈ ^o -H ₀ ^o	28.23 kJ	Molar Vol.	6.795 J·bar ⁻¹ 67.95 cm ³

A= -2.830E+03

B= 5.328E-01

C= -4.43E+05

7/31/92

DIOPSIDE

Formula wt 216.550

CaMgSi₂O₆: Monoclinic crystals 298.15 to incongruent melting point at 1668 K.

Temp. K	C _p ^o	S _T ^o	(H _T ^o -H ₂₉₈ ^o)/T	-(G _T ^o -H ₂₉₈ ^o)/T	FORMATION FROM THE ELEMENTS		
					Δ _f H ^o	Δ _f G ^o	Log K _f
			J·mol ⁻¹ ·K ⁻¹		kJ·mol ⁻¹		
298.15	166.78	142.70	0.00	142.70	-3201.5	-3026.8	530.27
300	167.46	143.73	1.03	142.70	-3201.5	-3025.7	526.81
400	195.68	196.12	46.47	149.65	-3201.6	-2967.1	387.45
500	213.25	241.81	78.19	163.62	-3200.2	-2908.6	303.85
600	224.98	281.80	101.74	180.06	-3198.2	-2850.4	248.14
700	233.19	317.13	119.97	197.17	-3196.0	-2792.6	208.38
800	239.21	348.68	134.51	214.17	-3194.6	-2735.0	178.58
900	243.80	377.13	146.41	230.72	-3192.4	-2677.7	155.41
1000	247.47	403.02	156.34	246.68	-3199.1	-2619.9	136.85
1100	250.57	426.75	164.77	261.98	-3197.6	-2562.1	121.66
1200	253.33	448.67	172.03	276.64	-3204.0	-2503.8	108.98
1300	255.94	469.05	178.39	290.66	-3201.7	-2445.5	98.26
1400	258.51	488.11	184.02	304.09	-3326.7	-2384.3	88.96
1500	261.16	506.04	189.07	316.97	-3322.9	-2317.1	80.69
1600	263.96	522.98	193.67	329.32	-3319.0	-2250.2	73.46

Melting T 1668 K

Boiling T K

Δ_{sub}H^o 137.7 kJΔ_{sub}H^o kJH₂₉₈^o-H₀^o 25.24 kJMolar Vol. 6.609 J·bar⁻¹
66.09 cm³

A= -3.213E+03

B= 5.949E-01

C= 9.377E+05

7/31/92

CaMgSi₂O₆ GLASS

Formula wt 216.550

CaMgSi₂O₆: Glass 298.15 to 1400 K.

Temp. K	C _p ^o	S _T ^o	(H _T ^o -H ₂₉₈ ^o)/T	-(G _T ^o -H ₂₉₈ ^o)/T	FORMATION FROM THE ELEMENTS		
					Δ _f H ^o	Δ _f G ^o	Log K _f
			J·mol ⁻¹ ·K ⁻¹	kJ·mol ⁻¹			
298.15	168.31	166.00	0.00	166.00	-3156.1	-2988.3	523.53
300	168.93	167.04	1.04	166.00	-3156.1	-2987.3	520.12
400	196.43	219.69	46.69	172.99	-3156.1	-2931.0	382.74
500	213.62	265.52	78.50	187.02	-3154.7	-2874.9	300.33
600	224.44	305.50	101.99	203.51	-3152.7	-2819.1	245.42
700	232.22	340.70	120.06	220.65	-3150.5	-2763.7	206.22
800	239.22	372.17	134.51	237.65	-3149.2	-2708.4	176.84
900	247.01	400.78	146.57	254.21	-3146.8	-2653.5	154.00
1000	256.65	427.28	157.07	270.21	-3152.9	-2598.1	135.71
1100	268.92	452.30	166.66	285.63	-3150.1	-2542.7	120.74
1200	284.36	476.33	175.80	300.53	-3154.1	-2487.0	108.26
1300	303.39	499.82	184.86	314.96	-3147.9	-2431.7	97.71
1400	326.34	523.12	194.12	328.99	-3267.2	-2373.8	88.56

Melting T	K	Boiling T	K
Δ _{fus} H ^o	kJ	Δ _{vap} H ^o	kJ
H ₂₉₈ ^o -H ₀ ^o	26.94 kJ	Molar Vol.	7.609 J·bar ⁻¹ 76.09 cm ³

A= -3.152E+03

B= 5.546E-01

C= -1.44E+05

10/15/92

FERROSILITE

Formula wt 131.931

FeSiO₃: Orthorhombic crystals 298.15 to 800 K.

Temp. K	C _p ^o	S _T ^o	(H _T ^o -H ₂₉₈ ^o)/T J·mol ⁻¹ ·K ⁻¹	-(G _T ^o -H ₂₉₈ ^o)/T	FORMATION FROM THE ELEMENTS		
					Δ _f H ^o kJ·mol ⁻¹	Δ _f G ^o	Log K _f
298.15	90.63	94.60	0.00	94.60	-1195.2	-1118.0	195.86
300	91.13	95.16	0.56	94.60	-1195.2	-1117.5	194.57
400	109.00	124.16	25.73	98.43	-1194.3	-1091.7	142.56
500	118.06	149.56	43.37	106.18	-1192.6	-1066.2	111.39
600	123.64	171.61	56.32	115.29	-1190.7	-1041.1	90.64
700	127.58	190.98	66.23	124.75	-1188.8	-1016.4	75.84
800	130.65	208.22	74.10	134.12	-1187.0	-991.9	64.76

Melting T	K	Boiling T	K
Δ _{fm} H ^o	kJ	Δ _{vp} H ^o	kJ
H ₂₉₈ ^o -H ₀ ^o	kJ	Molar Vol.	3.300 J·bar ⁻¹ 33.00 cm ³

A= -1.188E+03

B= 2.460E-01

C= -2.90E+05

05/07/93

α -SPODUMENE

Formula wt 186.090

LiAlSi₂O₆: Monoclinic crystals 298.15 to 1200 K.

Temp. K	C _p ^o	S _T ^o	(H _T ^o -H ₂₉₈ ^o)/T	-(G _T ^o -H ₂₉₈ ^o)/T	FORMATION FROM THE ELEMENTS		
					$\Delta_f H^\circ$	$\Delta_f G^\circ$	Log K _f
			J·mol ⁻¹ ·K ⁻¹		kJ·mol ⁻¹		
298.15	158.93	129.30	0.00	129.30	-3053.5	-2880.2	504.59
300	159.48	130.28	0.98	129.30	-3053.5	-2879.2	501.29
400	184.73	179.81	43.93	135.88	-3054.5	-2820.8	368.36
500	203.25	223.13	74.03	149.09	-3057.3	-2762.1	288.55
600	217.12	261.47	96.78	164.69	-3056.3	-2703.2	235.33
700	227.78	295.77	114.76	181.01	-3054.4	-2644.5	197.33
800	236.12	326.75	129.43	197.32	-3052.1	-2586.0	168.85
900	242.75	354.96	141.67	213.29	-3049.6	-2527.9	146.71
1000	248.07	380.82	152.05	228.77	-3057.4	-2469.4	128.98
1100	252.37	404.68	160.98	243.69	-3054.3	-2410.7	114.47
1200	255.84	426.79	168.75	258.04	-3050.9	-2352.3	102.39

Melting T	K	Boiling T	K
$\Delta_m H^\circ$	kJ	$\Delta_{\text{vap}} H^\circ$	kJ
H ₂₉₈ ^o -H ₀ ^o	kJ	Molar Vol.	5.837 J·bar ⁻¹ 58.37 cm ³

A= -3.054E+03

B= 5.849E-01

C= -5.34E+04

9/18/92

β -SPODUMENE

Formula wt 186.090

LiAlSi₂O₆: Tetragonal crystals 298.15 to 1700 K. Melting point is 1696 K.

Temp. K	C _p ^o	S _T ^o	(H _T ^o -H ₂₉₈ ^o)/T J·mol ⁻¹ ·K ⁻¹	-(G _T ^o -H ₂₉₈ ^o)/T	FORMATION FROM THE ELEMENTS		
					$\Delta_f H^\circ$ kJ·mol ⁻¹	$\Delta_f G^\circ$	Log K _f
298.15	162.77	154.40	0.00	154.40	-3025.3	-2859.5	500.96
300	163.37	155.41	1.01	154.40	-3025.3	-2858.5	497.69
400	189.58	206.27	45.11	161.16	-3025.8	-2802.7	365.99
500	207.34	250.60	75.88	174.71	-3028.2	-2746.7	286.94
600	220.36	289.60	98.93	190.68	-3026.8	-2690.5	234.23
700	230.39	324.36	117.02	207.34	-3024.7	-2634.7	196.60
800	238.41	355.66	131.71	223.95	-3022.1	-2579.1	168.40
900	244.98	384.14	143.94	240.19	-3019.3	-2523.9	146.48
1000	250.49	410.24	154.33	255.91	-3026.9	-2468.3	128.93
1100	255.18	434.34	163.29	271.05	-3023.5	-2412.6	114.56
1200	259.22	456.72	171.12	285.60	-3019.9	-2357.2	102.60
1300	262.74	477.61	178.03	299.58	-3016.0	-2302.1	92.50
1400	265.84	497.20	184.20	313.00	-3012.1	-2247.4	83.85
1500	268.58	515.63	189.73	325.90	-3008.0	-2192.9	76.36
1600	271.03	533.05	194.74	338.31	-3003.8	-2138.7	69.82
1700	273.23	549.55	199.29	350.25	-3245.1	-2076.7	63.81

Melting T	1696 K	Boiling T	K
$\Delta_{\text{fus}} H^\circ$	kJ	$\Delta_{\text{vap}} H^\circ$	kJ
H ₂₉₈ ^o -H ₀ ^o	kJ	Molar Vol.	7.825 J·bar ⁻¹ 78.25 cm ³

A= -3.023E+03

B= 5.543E-01

C= -2.00E+05

10/16/92

ENSTATITE

Formula wt 100.389

MgSiO₃: Orthorhombic crystals 298.15 to 1000 K.

Temp. K	C _p ^o	S _T ^o	(H _T ^o -H ₂₉₈ ^o)/T	-(G _T ^o -H ₂₉₈ ^o)/T	FORMATION FROM THE ELEMENTS		
					Δ _f H ^o	Δ _f G ^o	Log K _f
			J·mol ⁻¹ ·K ⁻¹		kJ·mol ⁻¹		
298.15	83.09	66.27	0.00	66.27	-1545.6	-1458.3	255.48
300	83.41	66.78	0.51	66.27	-1545.6	-1457.7	253.81
400	97.40	92.83	23.11	69.73	-1545.6	-1428.4	186.52
500	106.62	115.63	38.95	76.68	-1544.9	-1399.1	146.16
600	112.88	135.66	50.78	84.87	-1543.8	-1370.1	119.27
700	117.44	153.41	59.99	93.42	-1542.5	-1341.2	100.08
800	121.10	169.34	67.41	101.93	-1541.1	-1312.6	85.70
900	124.39	183.80	73.56	110.24	-1539.6	-1284.1	74.52
1000	127.68	197.07	78.81	118.27	-1546.7	-1255.1	65.56

Melting T	K	Boiling T	K
Δ _m H ^o	kJ	Δ _{vap} H ^o	kJ
H ₂₉₈ ^o -H ₀ ^o	11.99 kJ	Molar Vol.	3.131 J·bar ⁻¹ 31.31 cm ³

A= -1.542E+03

B= 2.869E-01

C= -1.78E+05

7/31/92

CLINOENSTATITE

Formula wt 100.389

MgSiO₃: Crystals 298.15 to melting point at 1830 K.

Temp. K	C _p ^o	S _T ^o	(H _T ^o -H ₂₉₈ ^o)/T	-(G _T ^o -H ₂₉₈ ^o)/T	FORMATION FROM THE ELEMENTS		
					Δ _f H ^o	Δ _f G ^o	Log K _f
			J·mol ⁻¹ ·K ⁻¹		kJ·mol ⁻¹		
298.15	82.12	67.86	0.00	67.86	-1545.0	-1458.1	255.45
300	82.34	68.37	0.51	67.86	-1545.0	-1457.6	253.78
400	93.04	93.59	22.36	71.23	-1545.3	-1428.4	186.52
500	101.20	115.27	37.35	77.92	-1545.1	-1399.2	146.17
600	107.42	134.29	48.53	85.76	-1544.6	-1370.0	119.27
700	112.22	151.23	57.30	93.92	-1543.8	-1341.0	100.06
800	115.98	166.47	64.41	102.06	-1542.9	-1312.1	85.67
900	118.95	180.30	70.31	109.99	-1541.9	-1283.3	74.48
1000	121.32	192.96	75.30	117.67	-1549.6	-1253.9	65.49
1100	123.22	204.62	79.57	125.05	-1548.7	-1224.3	58.14
1200	124.73	215.41	83.27	132.13	-1547.7	-1194.9	52.01
1300	125.93	225.44	86.51	138.93	-1546.7	-1165.5	46.83
1400	126.87	234.81	89.36	145.45	-1673.1	-1133.1	42.28
1500	127.60	243.59	91.89	151.70	-1670.8	-1094.6	38.12
1600	128.14	251.84	94.14	157.71	-1668.5	-1056.3	34.48

Melting T	1830 K	Boiling T	K
Δ _{sub} H ^o	61.50 kJ	Δ _{sub} H ^o	kJ
H ₂₉₈ ^o -H ₀ ^o	kJ	Molar Vol.	3.128 J·bar ⁻¹ 31.28 cm ³

A= -1.562E+03

B= 3.088E-01

C= 1.138E+06

10/16/92

MgSiO₃-ILMENITE

Formula wt 100.389

MgSiO₃: Ilmenite structure form stable only at high pressure 298.15 to 700 K.

Temp. K	C _p ^o	S _T ^o	(H _T ^o -H ₂₉₈ ^o)/T J·mol ⁻¹ ·K ⁻¹	-(G _T ^o -H ₂₉₈ ^o)/T	FORMATION FROM THE ELEMENTS		
					Δ _f H ^o kJ·mol ⁻¹	Δ _f G ^o	Log K _f
298.15	102.64	60.40	0.00	60.40	-1486.6	-1397.5	244.83
300	102.63	61.03	0.63	60.40	-1486.6	-1397.0	243.23
400	104.92	90.77	26.33	64.44	-1485.4	-1367.3	178.54
500	109.92	114.69	42.52	72.17	-1484.2	-1337.9	139.77
600	115.98	135.26	54.25	81.01	-1482.8	-1308.8	113.94
700	122.55	153.62	63.53	90.09	-1481.0	-1279.9	95.51

Melting T	K	Boiling T	K
Δ _{liq} H ^o	kJ	Δ _{vap} H ^o	kJ
H ₂₉₈ ^o -H ₀ ^o	kJ	Molar Vol.	2.636 J·bar ⁻¹ 26.36 cm ³

A= -1.481E+03

B= 2.885E-01

C= -1.88E+05

12/9/92

RHODONITE

Formula wt 131.022

MnSiO₃: Triclinic crystals 298.15 to 1600 K. Melts incongruently at 1564 K.

Temp. K	C _p ^o	S _T ^o	(H _T ^o -H ₂₉₈ ^o)/T J·mol ⁻¹ ·K ⁻¹	-(G _T ^o -H ₂₉₈ ^o)/T	FORMATION FROM THE ELEMENTS		
					Δ _f H ^o kJ·mol ⁻¹	Δ _f G ^o	Log K _f
298.15	86.44	100.50	0.00	100.50	-1321.6	-1244.7	218.05
300	86.84	101.04	0.53	100.50	-1321.6	-1244.2	216.63
400	101.42	128.30	24.18	104.12	-1321.4	-1218.4	159.10
500	108.73	151.79	40.43	111.37	-1320.6	-1192.7	124.60
600	113.29	172.04	52.21	119.83	-1319.8	-1167.2	101.61
700	116.61	189.77	61.19	128.58	-1318.9	-1141.9	85.21
800	119.31	205.52	68.29	137.23	-1318.0	-1116.6	72.91
900	121.67	219.71	74.09	145.62	-1317.2	-1091.5	63.35
1000	123.83	232.64	78.96	153.69	-1318.6	-1066.4	55.70
1100	125.87	244.54	83.13	161.41	-1317.8	-1041.3	49.44
1200	127.83	255.58	86.77	168.81	-1317.0	-1016.2	44.23
1300	129.75	265.89	90.01	175.88	-1316.1	-991.1	39.82
1400	131.63	275.57	92.91	182.66	-1317.4	-966.1	36.05
1500	133.50	284.72	95.56	189.16	-1318.9	-940.9	32.76
1600	135.35	293.39	97.99	195.41	-1330.5	-915.1	29.87

Melting T	1564 K	Boiling T	K
Δ _{fm} H ^o	kJ	Δ _{vap} H ^o	kJ
H ₂₉₈ ^o -H ₀ ^o	14.55 kJ	Molar Vol.	3.494 J·bar ⁻¹ 34.94 cm ³

A= -1.318E+03

B= 2.513E-01

C= -1.87E+05

4/5/93

JADEITE

Formula wt 202.139

NaAlSi₂O₆: Monoclinic crystals 298.15 to 1300 K.

Temp. K	C _p ^o	S _T ^o	(H _T ^o -H ₂₉₈ ^o)/T	-(G _T ^o -H ₂₉₈ ^o)/T	FORMATION FROM THE ELEMENTS		
					Δ _f H ^o	Δ _f G ^o	Log K _f
			J·mol ⁻¹ ·K ⁻¹		kJ·mol ⁻¹		
298.15	159.92	133.50	0.00	133.50	-3029.3	-2850.6	499.40
300	160.62	134.49	0.99	133.50	-3029.3	-2849.5	496.13
400	188.41	184.89	44.71	140.19	-3033.0	-2789.1	364.22
500	205.31	228.88	75.25	153.63	-3032.7	-2728.2	285.01
600	217.07	267.41	97.96	169.45	-3031.6	-2667.4	232.21
700	225.96	301.57	115.64	185.93	-3029.9	-2606.8	194.52
800	233.06	332.22	129.89	202.33	-3027.8	-2546.5	166.27
900	238.96	360.02	141.69	218.33	-3025.6	-2486.5	144.31
1000	244.02	385.46	151.67	233.79	-3033.8	-2426.0	126.72
1100	248.44	408.93	160.27	248.66	-3031.1	-2365.3	112.32
1200	252.39	430.72	167.79	262.94	-3125.0	-2302.4	100.22
1300	255.96	451.07	174.44	276.63	-3121.1	-2234.0	89.76

Melting T	K	Boiling T	K
Δ _m H ^o	kJ	Δ _{vap} H ^o	kJ
H ₂₉₈ ^o -H ₀ ^o	kJ	Molar Vol.	6.040 J·bar ⁻¹ 60.40 cm ³

A= -3.039E+03

B= 6.146E-01

C= 4.741E+05

7/31/92

ACMITE

Formula wt 231.004

NaFeSi₂O₆: Monoclinic crystals 298.15 to 1300 K.

Temp. K	C _p ^o	S _T ^o	(H _T ^o -H ₂₉₈ ^o)/T	-(G _T ^o -H ₂₉₈ ^o)/T	FORMATION FROM THE ELEMENTS		
					Δ _f H ^o	Δ _f G ^o	Log K _f
			J·mol ⁻¹ ·K ⁻¹		kJ·mol ⁻¹		
298.15	169.88	170.57	0.00	170.57	-2584.5	-2417.2	423.48
300	170.58	171.62	1.05	170.57	-2584.5	-2416.2	420.69
400	197.52	224.81	47.17	177.64	-2587.4	-2359.8	308.15
500	213.32	270.70	78.93	191.78	-2586.4	-2303.0	240.59
600	224.73	310.65	102.32	208.33	-2584.9	-2246.4	195.57
700	234.07	346.01	120.49	225.52	-2582.9	-2190.2	163.43
800	242.31	377.81	135.21	242.60	-2580.6	-2134.3	139.35
900	249.91	406.80	147.54	259.26	-2578.2	-2078.6	120.64
1000	257.10	433.50	158.13	275.37	-2576.2	-2023.2	105.68
1100	264.04	458.33	167.45	290.88	-2574.5	-1968.0	93.45
1200	270.80	481.60	175.78	305.82	-2668.5	-1910.5	83.16
1300	277.44	503.54	183.35	320.19	-2662.8	-1847.6	74.24

Melting T	K	Boiling T	K
Δ _{fm} H ^o	kJ	Δ _{vp} H ^o	kJ
H ₂₉₈ ^o -H ₀ ^o	26.94 kJ	Molar Vol.	6.460 J·bar ⁻¹ 64.60 cm ³

A= -2.587E+03

B= 5.648E-01

C= 9.860E+04

7/31/92

TREMOLITE

Formula wt 812.366

 $\text{Ca}_2\text{Mg}_5\text{Si}_8\text{O}_{22}(\text{OH})_2$: Monoclinic crystals 298.15 to 1000 K.

Temp. K	C_p°	S_T°	FORMATION FROM THE ELEMENTS				
			$(H_T^\circ - H_{298}^\circ)/T$ J·mol ⁻¹ ·K ⁻¹	$-(G_T^\circ - H_{298}^\circ)/T$	$\Delta_f H^\circ$ kJ·mol ⁻¹	$\Delta_f G^\circ$ kJ·mol ⁻¹	Log K_f
298.15	655.44	548.90	0.00	548.90	-12303.0	-11574.6	2027.77
300	657.85	552.96	4.05	548.91	-12303.1	-11570.0	2014.47
400	774.71	759.08	182.86	576.22	-12304.7	-11325.2	1478.89
500	850.48	940.81	309.46	631.36	-12299.8	-11080.8	1157.59
600	895.82	1100.21	403.71	696.50	-12292.0	-10837.7	943.48
700	926.86	1240.73	476.31	764.42	-12283.0	-10596.1	790.67
800	956.04	1366.36	534.42	831.94	-12275.3	-10355.5	676.13
900	992.18	1480.95	583.18	897.77	-12265.0	-10116.1	587.11
1000	1041.58	1587.91	626.42	961.49	-12295.7	-9874.4	515.78

Melting T	K	Boiling T	K
$\Delta_{\text{fus}} H^\circ$	kJ	$\Delta_{\text{vap}} H^\circ$	kJ
$H_{298}^\circ - H_0^\circ$	97.63 kJ	Molar Vol.	27.290 J·bar ⁻¹ 272.90 cm ³

A= -1.228E+04

B= 2.405E+00

C= -1.24E+06

7/31/92

GRUNERITE

Formula wt 1001.614

$\text{Fe}_7\text{Si}_8\text{O}_{22}(\text{OH})_2$: Monoclinic crystals 298.15 to 900 K.

Temp. K	C_p°	S_T°	FORMATION FROM THE ELEMENTS				
			$(H_T^\circ - H_{298}^\circ)/T$ J·mol ⁻¹ ·K ⁻¹	$-(G_T^\circ - H_{298}^\circ)/T$	$\Delta_f H^\circ$ kJ·mol ⁻¹	$\Delta_f G^\circ$	Log K_f
298.15	681.08	725.00	0.00	725.00	-9623.0	-8964.8	1570.56
300	683.99	729.22	4.21	725.01	-9623.1	-8960.7	1560.17
400	798.99	943.37	189.94	753.43	-9622.2	-8739.9	1141.28
500	871.66	1129.92	319.42	810.50	-9616.4	-8519.9	890.05
600	927.67	1293.95	416.28	877.68	-9607.7	-8301.4	722.68
700	975.82	1440.64	492.84	947.80	-9597.4	-8084.5	603.26
800	1019.77	1573.85	555.99	1017.86	-9586.0	-7869.1	513.79
900	1061.29	1696.37	609.84	1086.53	-9574.5	-7655.1	444.28

Melting T	K	Boiling T	K
$\Delta_{\text{fus}} H^\circ$	kJ	$\Delta_{\text{vap}} H^\circ$	kJ
$H_{298}^\circ - H_0^\circ$	kJ	Molar Vol.	27.870 J·bar ⁻¹ 278.70 cm ³

A= -9.590E+03

B= 2.154E+00

C= -1.52E+06

9/18/92

ANTHOPHYLLITE

Formula wt 780.820

 $Mg_7Si_8O_{22}(OH)_2$: Monoclinic crystals 298.15 to 1200 K.

Temp. K	C_p°	S_T°	FORMATION FROM THE ELEMENTS				
			$(H_T^\circ - H_{298}^\circ)/T$ J·mol ⁻¹ ·K ⁻¹	$-(G_T^\circ - H_{298}^\circ)/T$	$\Delta_f H^\circ$ kJ·mol ⁻¹	$\Delta_f G^\circ$ kJ·mol ⁻¹	Log K_f
298.15	664.02	534.50	0.00	534.50	-12070.0	-11343.4	1987.26
300	667.12	538.62	4.10	534.51	-12070.1	-11338.8	1974.22
400	788.45	748.97	186.60	562.37	-12070.0	-11094.9	1448.81
500	859.43	933.12	314.60	618.53	-12063.8	-10851.7	1133.64
600	907.21	1094.29	409.61	684.68	-12054.7	-10610.1	923.67
700	942.29	1236.89	483.32	753.58	-12043.9	-10370.2	773.82
800	969.58	1364.57	542.46	822.11	-12032.2	-10131.9	661.53
900	991.72	1480.09	591.19	888.90	-12020.3	-9895.0	574.28
1000	1010.24	1585.56	632.19	953.37	-12068.5	-9654.6	504.29
1100	1026.11	1682.61	667.30	1015.31	-12057.1	-9413.7	447.01
1200	1039.97	1772.50	697.79	1074.71	-12045.0	-9174.0	399.32

Melting T	K	Boiling T	K
$\Delta_{fus} H^\circ$	kJ	$\Delta_{vap} H^\circ$	kJ
$H_{298}^\circ - H_0^\circ$	96.78 kJ	Molar Vol.	26.540 J·bar ⁻¹ 265.40 cm ³

A= -1.204E+04

B= 2.389E+00

C= -1.29E+06

4/5/93

GLAUCOPHANE

Formula wt 783.543

 $\text{Na}_2\text{Mg}_3\text{Al}_2\text{Si}_8\text{O}_{22}(\text{OH})_2$: Monoclinic crystals 298.15 to 1200 K.

Temp. K	C_p°	S_T°	$(H_T^\circ - H_{298}^\circ)/T$ J·mol ⁻¹ ·K ⁻¹	$-(G_T^\circ - H_{298}^\circ)/T$	FORMATION FROM THE ELEMENTS		
					$\Delta_f H^\circ$ kJ·mol ⁻¹	$\Delta_f G^\circ$	Log K_f
298.15	645.48	541.20	0.00	541.20	-11964.0	-11230.8	1967.54
300	647.73	545.20	3.99	541.21	-11964.1	-11226.2	1954.61
400	750.28	746.42	178.46	567.95	-11973.3	-10979.0	1433.68
500	823.97	922.19	300.59	621.60	-11971.7	-10730.6	1120.99
600	878.30	1077.46	392.56	684.89	-11966.2	-10482.8	912.59
700	919.33	1216.07	465.02	751.05	-11958.0	-10236.2	763.82
800	950.88	1340.98	523.86	817.12	-11948.3	-9990.9	652.32
900	975.41	1454.45	572.73	881.73	-11937.7	-9746.8	565.68
1000	994.60	1558.26	613.99	944.26	-11973.7	-9500.4	496.24
1100	1009.62	1653.79	649.31	1004.48	-11962.3	-9253.5	439.40
1200	1021.32	1742.16	679.84	1062.32	-12144.0	-9003.0	391.88

Melting T	K	Boiling T	K
$\Delta_{\text{fus}} H^\circ$	kJ	$\Delta_{\text{vap}} H^\circ$	kJ
$H_{298}^\circ - H_0^\circ$	95.62 kJ	Molar Vol.	26.210 J·bar ⁻¹ 262.10 cm ³

A= -1.196E+04

B= 2.462E+00

C= -4.11E+05

8/5/92

ANORTHITE

Formula wt 278.207

CaAl₂Si₂O₈: Triclinic (P $\bar{1}$) crystals 298.15 to 510 K; triclinic (I $\bar{1}$) crystals 510 to melting point 1830 K.

Temp. K	C _p ^o	S _T ^o	(H _T ^o -H ₂₉₈ ^o)/T J·mol ⁻¹ ·K ⁻¹	-(G _T ^o -H ₂₉₈ ^o)/T	FORMATION FROM THE ELEMENTS		
					Δ _f H ^o kJ·mol ⁻¹	Δ _f G ^o	Log K _f
298.15	211.34	199.30	0.00	199.30	-4234.0	-4007.9	702.15
300	212.23	200.61	1.31	199.30	-4234.0	-4006.5	697.57
400	248.25	267.09	58.96	208.12	-4234.6	-3930.5	513.25
500	270.17	325.01	99.17	225.84	-4233.4	-3854.5	402.67
600	285.13	375.67	128.98	246.68	-4231.4	-3778.9	328.98
700	296.26	420.49	152.12	268.37	-4229.1	-3703.7	276.37
800	305.17	460.65	170.71	289.94	-4227.5	-3628.7	236.93
900	312.78	497.04	186.08	310.96	-4225.2	-3554.0	206.27
1000	319.67	530.36	199.10	331.26	-4244.3	-3478.1	181.67
1100	326.21	561.13	210.36	350.78	-4241.8	-3401.6	161.52
1200	332.67	589.80	220.28	369.51	-4246.9	-3324.7	144.72
1300	339.23	616.68	229.18	387.50	-4243.0	-3248.0	130.50
1400	346.03	642.07	237.28	404.79	-4238.6	-3171.7	118.33
1500	353.18	666.18	244.77	421.42	-4233.8	-3095.6	107.79
1600	360.75	689.22	251.78	437.44	-4228.4	-3019.9	98.59
1700	368.81	711.33	258.42	452.90	-4322.7	-2943.6	90.44
1800	377.41	732.65	264.79	467.86	-4464.2	-2860.5	83.01

Melting T 1830 K

Boiling T K

Δ_mH^o 133.0 kJΔ_{vap}H^o kJH₂₉₈^o-H₀^o 33.33 kJMolar Vol. 10.079 J·bar⁻¹
100.79 cm³

A= -4.240E+03

B= 7.634E-01

C= 4.945E+05

7/30/92

CaAl₂Si₂O₈-GLASS

Formula wt 278.207

CaAl₂Si₂O₈: Glass 298.15 to 1500 K.

Temp. K	C _p ^o	S _T ^o	(H _T ^o -H ₂₉₈ ^o)/T J·mol ⁻¹ ·K ⁻¹	-(G _T ^o -H ₂₉₈ ^o)/T	FORMATION FROM THE ELEMENTS		
					Δ _f H ^o kJ·mol ⁻¹	Δ _f G ^o	Log K _f
298.15	210.65	237.30	0.00	237.30	-4163.2	-3948.4	691.73
300	211.54	238.61	1.30	237.30	-4163.2	-3947.1	687.23
400	247.44	304.86	58.76	246.09	-4163.9	-3874.9	505.99
500	269.96	362.65	98.89	263.76	-4162.7	-3802.7	397.26
600	286.17	413.37	128.82	284.55	-4160.7	-3730.9	324.79
700	298.89	458.48	152.24	306.24	-4158.2	-3659.4	273.06
800	309.44	499.09	171.25	327.85	-4156.3	-3588.3	234.28
900	318.53	536.08	187.12	348.96	-4153.5	-3517.4	204.14
1000	326.59	570.06	200.67	369.39	-4171.9	-3445.4	179.97
1100	333.90	601.54	212.45	389.08	-4168.7	-3372.9	160.16
1200	340.62	630.88	222.86	408.03	-4173.0	-3300.1	143.65
1300	346.89	658.40	232.16	426.24	-4168.3	-3227.5	129.68
1400	352.80	684.33	240.57	443.76	-4163.2	-3155.4	117.73
1500	358.41	708.86	248.24	460.62	-4157.8	-3083.6	107.38

Melting T	K	Boiling T	K
Δ _{nu} H ^o	kJ	Δ _{nu} H ^o	kJ
H ₂₉₈ ^o -H ₀ ^o	33.15 kJ	Molar Vol.	10.30 J·bar ⁻¹ 103.0 cm ³

A= -4.164E+03

B= 7.199E-01

C= 1.207E+05

9/16/92

BICCHULITE

Formula wt 292.216

 $\text{Ca}_2\text{Al}_2\text{SiO}_6(\text{OH})_2$: Cubic crystals 298.15 to 1800 K.

Temp. K	C_p°	S_T°	FORMATION FROM THE ELEMENTS				
			$(H_T^\circ - H_{298}^\circ)/T$ J·mol ⁻¹ ·K ⁻¹	$-(G_T^\circ - H_{298}^\circ)/T$	$\Delta_f H^\circ$ kJ·mol ⁻¹	$\Delta_f G^\circ$	Log K_f
298.15	240.87	213.10	0.00	213.10	-4341.2	-4073.0	713.56
300	241.81	214.59	1.49	213.10	-4341.2	-4071.4	708.87
400	277.62	289.63	66.54	223.09	-4342.2	-3981.2	519.88
500	298.60	353.99	111.00	243.00	-4341.6	-3891.0	406.48
600	313.75	409.83	143.58	266.25	-4340.3	-3801.0	330.90
700	326.14	459.15	168.80	290.36	-4338.6	-3711.3	276.93
800	337.06	503.43	189.16	314.27	-4338.6	-3621.5	236.46
900	347.12	543.71	206.16	337.56	-4336.9	-3532.0	204.99
1000	356.66	580.78	220.73	360.05	-4356.6	-3441.2	179.74
1100	365.85	615.21	233.51	381.70	-4354.8	-3349.7	159.06
1200	374.80	647.43	244.91	402.52	-4368.4	-3257.2	141.78
1300	383.59	677.78	255.24	422.53	-4364.0	-3164.7	127.16
1400	392.26	706.52	264.72	441.80	-4359.1	-3072.7	114.64
1500	400.84	733.88	273.51	460.37	-4353.3	-2981.0	103.80
1600	409.35	760.02	281.73	478.29	-4347.0	-2889.7	94.34
1700	417.80	785.09	289.49	495.60	-4390.2	-2798.3	85.98
1800	426.22	809.21	296.85	512.36	-4679.6	-2700.6	78.37

Melting T	K	Boiling T	K
$\Delta_{\text{fus}} H^\circ$	kJ	$\Delta_{\text{vap}} H^\circ$	kJ
$H_{298}^\circ - H_0^\circ$	kJ	Molar Vol.	10.368 J·bar ⁻¹ 103.68 cm ³

A= -4.356E+03

B= 9.167E-01

C= 9.910E+05

7/30/92

MEIONITE (Al/Si ORDERED)

Formula wt 934.709

 $\text{Ca}_4\text{Al}_6\text{Si}_6\text{O}_{24}\text{CO}_3$: Tetragonal crystals 298.15 to 1200 K.

Temp. K	C_p°	S_T°	$(H_T^\circ - H_{298}^\circ)/T$ J·mol ⁻¹ ·K ⁻¹	$-(G_T^\circ - H_{298}^\circ)/T$	FORMATION FROM THE ELEMENTS		
					$\Delta_f H^\circ$ kJ·mol ⁻¹	$\Delta_f G^\circ$	Log K_f
298.15	709.51	715.20	0.00	715.20	-13881.4	-13131.8	2300.58
300	713.05	719.60	4.39	715.21	-13881.5	-13127.1	2285.58
400	844.29	945.01	199.95	745.06	-13882.2	-12875.3	1681.30
500	915.47	1141.70	336.51	805.18	-13877.0	-12624.1	1318.80
600	963.02	1313.04	437.18	875.86	-13869.8	-12374.1	1077.24
700	999.41	1464.33	514.99	949.33	-13861.6	-12125.5	904.80
800	1029.84	1599.81	577.49	1022.32	-13856.8	-11877.6	775.51
900	1056.82	1722.70	629.28	1093.42	-13848.8	-11630.7	675.01
1000	1081.65	1835.34	673.29	1162.05	-13905.1	-11380.3	594.43
1100	1105.08	1939.54	711.49	1228.06	-13896.8	-11128.1	528.42
1200	1127.55	2036.67	745.23	1291.44	-13919.2	-10874.3	473.33

Melting T	K	Boiling T	K
$\Delta_{\text{fus}} H^\circ$	kJ	$\Delta_{\text{vap}} H^\circ$	kJ
$H_{298}^\circ - H_0^\circ$	kJ	Molar Vol.	34.036 J·bar ⁻¹ 340.36 cm ³

A= -1.387E+04

B= 2.495E+00

C= -2.94E+05

7/30/92

MICROCLINE

Formula wt 278.332

KAlSi₃O₈: Triclinic crystals 298.15 to 1400 K.

Temp. K	C _p ^o	S _T ^o	(H _T ^o -H ₂₉₈ ^o)/T	-(G _T ^o -H ₂₉₈ ^o)/T	FORMATION FROM THE ELEMENTS		
					Δ _f H ^o	Δ _f G ^o	Log K _f
			J·mol ⁻¹ ·K ⁻¹	kJ·mol ⁻¹			
298.15	202.13	214.20	0.00	214.20	-3974.6	-3749.3	656.84
300	202.85	215.45	1.25	214.20	-3974.7	-3747.9	652.54
400	236.27	278.64	56.05	222.59	-3978.8	-3671.5	479.44
500	259.96	334.06	94.60	239.46	-3978.7	-3594.6	375.52
600	276.64	383.02	123.63	259.39	-3977.4	-3517.9	306.25
700	288.65	426.62	146.39	280.22	-3975.3	-3441.5	256.80
800	297.58	465.77	164.76	301.01	-3972.8	-3365.4	219.73
900	304.51	501.23	179.91	321.32	-3970.2	-3289.6	190.92
1000	310.21	533.62	192.67	340.95	-3978.0	-3213.4	167.85
1100	315.20	563.42	203.58	359.84	-4054.0	-3132.5	148.74
1200	319.89	591.05	213.08	377.97	-4049.7	-3048.9	132.71
1300	324.56	616.84	221.48	395.37	-4045.3	-2965.7	119.16
1400	329.45	641.07	229.01	412.06	-4040.7	-2882.8	107.56

Melting T	K	Boiling T	K
Δ _{lv} H ^o	kJ	Δ _{lv} H ^o	kJ
H ₂₉₈ ^o -H ₀ ^o	33.99 kJ	Molar Vol.	10.872 J·bar ⁻¹ 108.72 cm ³

A= -4.002E+03

B= 7.941E-01

C= 1.562E+06

7/30/92

SANIDINE

Formula wt 278.332

KAlSi₃O₈: Monoclinic crystals 298.15 to 1400 K.

Temp. K	C _p ^o	S _T ^o	(H _T ^o -H ₂₉₈ ^o)/T	-(G _T ^o -H ₂₉₈ ^o)/T	FORMATION FROM THE ELEMENTS		
					Δ _f H ^o	Δ _f G ^o	Log K _f
			J·mol ⁻¹ ·K ⁻¹	kJ·mol ⁻¹			
298.15	204.55	232.80	0.00	232.80	-3965.6	-3745.8	656.23
300	205.29	234.07	1.26	232.80	-3965.6	-3744.4	651.95
400	238.98	298.03	56.74	241.30	-3969.5	-3670.0	479.24
500	262.28	354.02	95.66	258.36	-3969.2	-3595.1	375.57
600	278.65	403.37	124.87	278.50	-3967.7	-3520.4	306.47
700	290.48	447.26	147.73	299.54	-3965.4	-3446.0	257.14
800	299.30	486.65	166.15	320.51	-3962.7	-3372.0	220.16
900	306.15	522.32	181.34	340.98	-3959.9	-3298.3	191.42
1000	311.72	554.87	194.11	360.76	-3967.6	-3224.2	168.41
1100	316.51	584.81	205.02	379.79	-4043.4	-3145.4	149.36
1200	320.85	612.54	214.49	398.04	-4039.0	-3064.0	133.37
1300	325.03	638.39	222.84	415.55	-4034.5	-2982.9	119.85
1400	329.24	662.63	230.29	432.34	-4029.9	-2902.2	108.28

Melting T	1473 K	Boiling T	K
Δ _{fus} H ^o	kJ	Δ _{vap} H ^o	kJ
H ₂₉₈ ^o -H ₀ ^o	34.02 kJ	Molar Vol.	10.905 J·bar ⁻¹ 109.05 cm ³

A= -3.991E+03

B= 7.728E-01

C= 1.497E+06

5/12/93

KAlSi₃O₈-GLASS

Formula wt 278.332

KAlSi₃O₈: Glass 298.15 to 1300 K.

Temp. K	C _p ^o	S _T ^o	(H _T ^o -H ₂₉₈ ^o)/T	-(G _T ^o -H ₂₉₈ ^o)/T	FORMATION FROM THE ELEMENTS		
					Δ _f H ^o	Δ _f G ^o	Log K _f
			J·mol ⁻¹ ·K ⁻¹	kJ·mol ⁻¹			
298.15	209.41	261.60	0.00	261.60	-3920.8	-3709.6	649.89
300	210.18	262.90	1.29	261.60	-3920.8	-3708.3	645.65
400	244.32	328.36	58.06	270.30	-3924.2	-3636.8	474.90
500	267.66	385.54	97.79	287.75	-3923.3	-3565.0	372.42
600	283.99	435.87	127.54	308.33	-3921.3	-3493.5	304.13
700	295.65	480.57	150.77	329.81	-3918.5	-3422.4	255.38
800	304.11	520.63	169.43	351.20	-3915.3	-3351.7	218.84
900	310.30	556.83	184.76	372.07	-3912.0	-3281.5	190.45
1000	314.88	589.77	197.55	392.22	-3919.3	-3210.9	167.72
1100	318.26	619.95	208.38	411.57	-3994.9	-3135.6	148.89
1200	320.78	647.75	217.65	430.11	-3990.4	-3057.7	133.09
1300	322.67	673.51	225.66	447.85	-3986.0	-2980.1	119.74

Melting T	K	Boiling T	K
Δ _{fus} H ^o	kJ	Δ _{vap} H ^o	kJ
H ₂₉₈ ^o -H ₀ ^o	34.88 kJ	Molar Vol.	11.650 J·bar ⁻¹ 116.50 cm ³

A= -3.937E+03

B= 7.307E-01

C= 9.138E+05

9/16/92

KALIOPHILLITE (KALSILITE)

Formula wt 158.163

KAlSiO₄: Hexagonal crystals 298.15 to 810 K. High kaliophillite 810 to 1800 K.

Temp. K	C _p ^o	S _T ^o	(H _T ^o -H ₂₉₈ ^o)/T J·mol ⁻¹ ·K ⁻¹	-(G _T ^o -H ₂₉₈ ^o)/T	FORMATION FROM THE ELEMENTS		
					Δ _f H ^o kJ·mol ⁻¹	Δ _f G ^o	Log K _f
298.15	119.70	133.26	0.00	133.26	-2124.7	-2008.8	351.92
300	120.07	134.00	0.74	133.26	-2124.7	-2008.1	349.62
400	137.03	170.98	32.79	138.19	-2127.9	-1968.6	257.06
500	150.35	203.04	55.02	148.02	-2127.6	-1928.8	201.49
600	161.63	231.47	71.87	159.61	-2126.5	-1889.1	164.46
700	171.63	257.15	85.42	171.74	-2124.6	-1849.7	138.02
800	180.76	280.68	96.77	183.90	-2122.1	-1810.5	118.21
900	177.65	303.87	106.26	197.61	-2119.4	-1773.3	102.92
1000	177.65	322.58	113.39	209.19	-2128.1	-1734.2	90.59
1100	177.65	339.52	119.23	220.29	-2205.2	-1690.3	80.27
1200	177.65	354.97	124.10	230.87	-2202.5	-1643.6	71.54
1300	177.65	369.19	128.22	240.97	-2199.9	-1597.2	64.17
1400	177.65	382.36	131.75	250.61	-2197.4	-1550.9	57.87
1500	177.65	394.61	134.81	259.80	-2195.0	-1504.8	52.40
1600	177.65	406.08	137.49	268.59	-2192.7	-1458.9	47.63
1700	177.65	416.85	139.85	277.00	-2240.7	-1412.6	43.40
1800	177.65	427.00	141.95	285.05	-2238.3	-1364.0	39.58
Melting T		K			Boiling T		K
Δ _m H ^o		kJ			Δ _{vap} H ^o		kJ
H ₂₉₈ ^o -H ₀ ^o		kJ			Molar Vol.	5.959 J·bar ⁻¹	59.89 cm ³
A= -2.170E+03		B= 4.426E-01		C= 2.954E+06			

1/12/94

LEUCITE

Formula wt 218.247

KAlSi_2O_6 : Tetragonal crystals 298.15 to 955 K. Cubic crystals 955 to melting point 1959 K.

Temp. K	C_p°	S_T°	$(H_T^\circ - H_{298}^\circ)/T$ J·mol ⁻¹ ·K ⁻¹	$-(G_T^\circ - H_{298}^\circ)/T$	FORMATION FROM THE ELEMENTS		
					$\Delta_f H^\circ$ kJ·mol ⁻¹	$\Delta_f G^\circ$	Log K_f
298.15	164.11	200.20	0.00	200.20	-3037.8	-2875.1	503.69
300	164.65	201.22	1.01	200.20	-3037.8	-2874.0	500.40
400	188.61	252.08	45.11	206.98	-3041.2	-2818.8	368.09
500	206.91	296.20	75.69	220.50	-3040.9	-2763.2	288.67
600	222.99	335.36	98.92	236.44	-3039.4	-2707.8	235.73
700	238.01	370.87	117.73	253.15	-3036.8	-2652.8	197.95
800	252.48	403.61	133.67	269.93	-3033.3	-2598.1	169.63
900	266.62	434.16	147.66	286.50	-3028.8	-2544.0	147.64
1000	236.40	462.95	160.23	302.72	-3034.0	-2489.6	130.04
1100	237.04	484.04	165.82	318.22	-3112.9	-2430.5	115.41
1200	238.18	504.71	171.80	332.91	-3110.4	-2368.6	103.10
1300	239.69	523.83	176.96	346.87	-3108.0	-2306.9	92.69
1400	241.46	541.66	181.51	360.15	-3105.6	-2245.4	83.77
1500	243.42	558.39	185.57	372.82	-3103.2	-2184.0	76.05
1600	245.53	574.16	189.25	384.91	-3100.8	-2122.8	69.30
1700	247.74	589.11	192.62	396.49	-3198.6	-2060.8	63.32
1800	250.05	603.34	195.75	407.59	-3195.6	-1994.0	57.86

Melting T	1959 K	Boiling T	K
$\Delta_{\text{m}} H^\circ$	kJ	$\Delta_{\text{vp}} H^\circ$	kJ
$H_{298}^\circ - H_0^\circ$	kJ	Molar Vol.	8.827 J·bar ⁻¹ 88.27 cm ³

A= -3.082E+03

B= 5.979E-01

C= 2.833E+06

EUCRYPTITE

Formula wt 126.006

LiAlSiO₄: α-eucryptite 298.15 to 1300 K. β-eucryptite 1300 to 1600 K.

Temp. K	C _p ^o	S _T ^o	(H _T ^o -H ₂₉₈ ^o)/T J·mol ⁻¹ ·K ⁻¹	-(G _T ^o -H ₂₉₈ ^o)/T	FORMATION FROM THE ELEMENTS		
					Δ _f H ^o kJ·mol ⁻¹	Δ _f G ^o	Log K _f
298.15	113.30	103.80	0.00	103.80	-2123.3	-2009.2	352.00
300	113.85	104.50	0.70	103.80	-2123.3	-2008.5	349.70
400	136.04	140.59	32.02	108.57	-2123.9	-1970.1	257.26
500	149.80	172.53	54.29	118.24	-2126.5	-1931.4	201.76
600	159.40	200.73	71.05	129.68	-2125.4	-1892.4	164.75
700	166.58	225.87	84.21	141.66	-2123.9	-1853.7	138.32
800	172.22	248.49	94.87	153.62	-2122.0	-1815.2	118.52
900	176.81	269.05	103.73	165.32	-2119.9	-1777.0	103.13
1000	180.63	287.88	111.23	176.65	-2128.4	-1738.3	90.80
1100	183.88	305.26	117.69	187.56	-2125.9	-1699.4	80.70
1200	186.69	321.38	123.33	198.05	-2123.2	-1660.7	72.29
1300	189.16	336.42	128.30	208.12	-2120.3	-1622.3	65.18
1400	191.34	350.52	132.73	217.80	-2117.4	-1584.2	59.10
1500	193.29	363.79	136.70	227.09	-2114.3	-1546.2	53.84
1600	195.05	376.32	140.29	236.03	-2111.1	-1508.4	49.24

Melting T	1670 K	Boiling T	K
Δ _{lv} H ^o	kJ	Δ _{lv} H ^o	kJ
H ₂₉₈ ^o -H ₀ ^o	kJ	Molar Vol.	5.363 J·bar ⁻¹ 53.63 cm ³

A= -2.123E+03

B= 3.846E-01

C= -1.10E+05

9/16/92

PETALITE

Formula wt 306.259

$\text{LiAlSi}_4\text{O}_{10}$: Monoclinic crystals 298.15 to 1300 K. Petalite decomposes above about 1100 K.

Temp. K	C_p°	S_T°	$(H_T^\circ - H_{298}^\circ)/T$ J·mol ⁻¹ ·K ⁻¹	$-(G_T^\circ - H_{298}^\circ)/T$	FORMATION FROM THE ELEMENTS		
					$\Delta_f H^\circ$ kJ·mol ⁻¹	$\Delta_f G^\circ$	Log K_f
298.15	245.30	233.20	0.00	233.20	-4886.5	-4610.7	807.75
300	246.32	234.72	1.52	233.20	-4886.6	-4608.9	802.47
400	292.33	312.31	68.84	243.47	-4887.9	-4516.1	589.73
500	323.66	381.13	116.87	264.26	-4889.9	-4422.9	462.05
600	345.43	442.18	153.25	288.92	-4887.5	-4329.8	376.93
700	360.93	496.65	181.87	314.78	-4884.0	-4237.1	316.17
800	372.26	545.63	205.00	340.63	-4879.9	-4144.9	270.63
900	380.77	589.99	224.08	365.91	-4875.5	-4053.3	235.24
1000	387.40	630.46	240.09	390.37	-4881.6	-3961.5	206.92
1100	392.77	667.64	253.73	413.91	-4876.8	-3869.7	183.75
1200	397.36	702.02	265.52	436.50	-4871.9	-3778.3	164.46
1300	401.52	733.99	275.82	458.17	-4866.9	-3687.4	148.16

Melting T	K	Boiling T	K
$\Delta_{\text{fus}} H^\circ$	kJ	$\Delta_{\text{vap}} H^\circ$	kJ
$H_{298}^\circ - H_0^\circ$	38.31 kJ	Molar Vol.	12.840 J·bar ⁻¹ 128.40 cm ³

A= -4.879E+03

B= 9.174E-01

C= -5.17E+05

8/7/92

ALBITE

Formula wt 262.223

NaAlSi₃O₈: Triclinic crystals 298.15 to 1400 K.

Temp. K	C _p ^o	S _T ^o	(H _T ^o -H ₂₉₈ ^o)/T	-(G _T ^o -H ₂₉₈ ^o)/T	FORMATION FROM THE ELEMENTS		
					Δ _f H ^o	Δ _f G ^o	Log K _f
			J·mol ⁻¹ ·K ⁻¹	kJ·mol ⁻¹			
298.15	205.07	207.40	0.00	207.40	-3935.0	-3711.6	650.24
300	205.84	208.67	1.27	207.40	-3935.0	-3710.2	645.98
400	239.68	272.86	56.93	215.93	-3939.0	-3634.8	474.64
500	262.58	328.96	95.91	233.05	-3938.6	-3558.7	371.77
600	278.77	378.34	125.11	253.23	-3937.1	-3482.9	303.20
700	290.66	422.25	147.95	274.30	-3934.7	-3407.4	254.26
800	299.66	461.68	166.38	295.30	-3931.9	-3332.2	217.57
900	306.68	497.39	181.59	315.80	-3929.0	-3257.4	189.05
1000	312.30	530.01	194.39	335.61	-3936.5	-3182.2	166.22
1100	316.95	560.00	205.33	354.67	-3933.1	-3107.0	147.53
1200	320.92	587.75	214.80	372.95	-4026.3	-3029.6	131.87
1300	324.41	613.58	223.10	390.48	-4021.9	-2946.7	118.40
1400	327.61	637.74	230.45	407.28	-4017.4	-2864.2	106.86

Melting T	K	Boiling T	K
Δ _{fus} H ^o	kJ	Δ _{vap} H ^o	kJ
H ₂₉₈ ^o -H ₀ ^o	33.45 kJ	Molar Vol.	10.007 J·bar ⁻¹ 100.07 cm ³

A= -3.949E+03

B= 7.694E-01

C= 7.970E+05

8/7/92

ANALBITE

Formula wt 262.223

NaAlSi₃O₈: Triclinic crystals 298.15 to 1400 K.

Temp. K	C _p ^o	S _T ^o	(H _T ^o -H ₂₉₈ ^o)/T	-(G _T ^o -H ₂₉₈ ^o)/T	FORMATION FROM THE ELEMENTS		
					Δ _f H ^o	Δ _f G ^o	Log K _f
			J·mol ⁻¹ ·K ⁻¹		kJ·mol ⁻¹		
298.15	204.81	225.60	0.00	225.60	-3923.6	-3705.6	649.19
300	205.57	226.87	1.27	225.60	-3923.6	-3704.2	644.95
400	239.71	290.99	56.87	234.11	-3927.6	-3630.6	474.10
500	263.29	347.17	95.94	251.23	-3927.2	-3556.4	371.53
600	279.83	396.72	125.29	271.43	-3925.5	-3482.4	303.16
700	291.73	440.80	148.26	292.54	-3923.1	-3408.7	254.36
800	300.49	480.35	166.77	313.58	-3920.2	-3335.4	217.78
900	307.13	516.15	182.01	334.13	-3917.2	-3262.5	189.35
1000	312.30	548.78	194.79	353.99	-3924.7	-3189.2	166.58
1100	316.50	578.75	205.67	373.08	-3921.3	-3115.8	147.95
1200	320.06	606.45	215.06	391.39	-4014.6	-3040.3	132.34
1300	323.25	632.19	223.26	408.93	-4010.3	-2959.3	118.90
1400	326.24	656.26	230.51	425.75	-4005.9	-2878.6	107.40

Melting T 1391 K

Boiling T K

Δ_mH^o kJΔ_{vp}H^o kJH₂₉₈^o-H₀^o 33.42 kJMolar Vol. 10.043 J·bar⁻¹
100.43 cm³

A= -3.937E+03

B= 7.507E-01

C= 7.781E+05

8/7/92

NaAlSi₃O₈-GLASS

Formula wt 262.223

NaAlSi₃O₈: Glass 298.15 to 1200 K.

Temp. K	C _p ^o	S _T ^o	(H _T ^o -H ₂₉₈ ^o)/T J·mol ⁻¹ ·K ⁻¹	-(G _T ^o -H ₂₉₈ ^o)/T	FORMATION FROM THE ELEMENTS		
					Δ _f H ^o kJ·mol ⁻¹	Δ _f G ^o	Log K _f
298.15	209.90	251.90	0.00	251.90	-3875.5	-3665.3	642.14
300	210.68	253.20	1.30	251.90	-3875.5	-3664.0	637.95
400	246.12	318.98	58.35	260.63	-3878.9	-3593.1	469.21
500	270.03	376.65	98.45	278.19	-3877.8	-3521.8	367.91
600	286.40	427.42	128.49	298.92	-3875.5	-3450.8	300.41
700	298.28	472.50	151.94	320.56	-3872.4	-3380.3	252.23
800	307.73	512.96	170.84	342.12	-3868.9	-3310.2	216.13
900	316.09	549.70	186.52	363.18	-3865.0	-3240.6	188.07
1000	324.30	583.42	199.89	383.54	-3871.5	-3170.7	165.61
1100	333.04	614.74	211.59	403.15	-3866.7	-3100.8	147.24
1200	342.78	644.12	222.11	422.02	-3958.1	-3029.0	131.84

Melting T	K	Boiling T	K
Δ _{fm} H ^o	kJ	Δ _{vp} H ^o	kJ
H ₂₉₈ ^o -H ₀ ^o	34.17 kJ	Molar Vol.	11.010 J·bar ⁻¹ 110.10 cm ³

A= -3.871E+03

B= 7.012E-01

C= -3.14E+05

12/9/92

NEPHELINE

Formula wt 142.054

$\text{NaAlSi}_3\text{O}_8$: Orthorhombic(?) crystals 298.15 to 467 K. Hexagonal crystals 467 to 1180 K. Orthorhombic crystals 1180 to 1521 K. Carnegieite is the stable phase of $\text{NaAlSi}_3\text{O}_8$ between 1521 and 1799 K.

Temp. K	C_p°	S_T°	$(H_T^\circ - H_{298}^\circ)/T$ J·mol ⁻¹ ·K ⁻¹	$-(G_T^\circ - H_{298}^\circ)/T$	FORMATION FROM THE ELEMENTS		
					$\Delta_f H^\circ$ kJ·mol ⁻¹	$\Delta_f G^\circ$	Log K_f
298.15	115.81	124.35	0.00	124.35	-2090.4	-1975.8	346.14
300	116.36	125.12	0.72	124.40	-2090.4	-1975.0	343.88
400	145.90	161.59	32.37	129.22	-2093.5	-1936.3	252.84
500	145.64	196.36	52.55	143.81	-2094.7	-1899.3	198.41
600	152.36	223.80	72.66	151.14	-2091.8	-1858.0	161.75
700	159.07	247.82	84.58	163.24	-2091.0	-1819.0	135.73
800	165.78	269.33	94.14	175.19	-2089.9	-1780.3	116.24
900	172.49	288.91	102.13	186.77	-2088.7	-1741.6	101.08
1000	179.20	306.86	108.99	197.86	-2098.0	-1702.4	88.92
1100	185.91	324.09	115.51	208.58	-2095.7	-1662.9	78.96
1200	178.62	341.12	122.21	218.92	-2188.8	-1621.3	70.57
1300	179.18	355.47	126.58	228.89	-2186.0	-1574.1	63.25
1400	179.73	368.78	130.36	238.42	-2183.4	-1527.2	56.98
1500	180.28	381.20	133.66	247.54	-2180.7	-1480.4	51.55

Melting T	K	Boiling T	K
$\Delta_{\text{fus}} H^\circ$	kJ	$\Delta_{\text{vap}} H^\circ$	kJ
$H_{298}^\circ - H_0^\circ$	kJ	Molar Vol.	5.419 J·bar ⁻¹ 54.19 cm ³

A= -2.118E+03

B= 4.188E-01

C= 1.718E+06

8/7/92

CARNEGIEITE

Formula wt 142.054

NaAlSiO₄: Triclinic crystals 298.15 to 966 K; cubic crystals 966 to melting point 1799 K.

Temp. K	C _p ^o	S _T ^o	(H _T ^o -H ₂₉₈ ^o)/T	-(G _T ^o -H ₂₉₈ ^o)/T	FORMATION FROM THE ELEMENTS		
					Δ _f H ^o	Δ _f G ^o	Log K _f
			J·mol ⁻¹ ·K ⁻¹	kJ·mol ⁻¹			
298.15	119.26	118.70	0.00	118.70	-2089.3	-1973.0	345.65
300	119.69	119.44	0.74	118.70	-2089.3	-1972.2	343.39
400	138.01	156.58	32.94	123.64	-2092.5	-1932.9	252.41
500	151.11	188.84	55.31	133.53	-2092.2	-1893.0	197.76
600	162.14	217.39	72.22	145.17	-2091.0	-1853.3	161.34
700	172.21	243.15	85.79	157.36	-2089.0	-1813.8	135.35
800	181.77	266.77	97.19	169.58	-2086.4	-1774.7	115.87
900	191.02	288.71	107.11	181.60	-2083.1	-1735.9	100.75
1000	181.15	317.40	123.78	193.62	-2082.1	-1697.0	88.64
1100	184.03	334.80	129.13	205.67	-2079.6	-1658.6	78.76
1200	186.92	350.94	133.82	217.12	-2173.7	-1618.1	70.43
1300	189.80	366.01	138.02	227.99	-2170.0	-1571.9	63.16
1400	192.68	380.18	141.82	238.36	-2166.2	-1526.0	56.94
1500	195.57	393.57	145.31	248.26	-2162.1	-1480.4	51.55
1600	198.45	406.29	148.54	257.75	-2157.9	-1435.1	46.85
1700	201.33	418.40	151.56	266.84	-2203.7	-1389.6	42.70
1800	204.21	429.99	154.40	275.59	-2198.8	-1341.9	38.94

Melting T	1799 K	Boiling T	K
Δ _{sub} H ^o	21.7 kJ	Δ _{sub} H ^o	kJ
H ₂₉₈ ^o -H ₀ ^o	19.45 kJ	Molar Vol.	5.603 J·bar ⁻¹ 56.03 cm ³

A= -2.122E+03

B= 4.276E-01

C= 2.200E+06

NaAlSiO₄-GLASS

Formula wt 142.054

NaAlSiO₄: Glass-liquid 298.15 to glass transition 1000 K.

Temp. K	C _p ^o	S _T ^o	(H _T ^o -H ₂₉₈ ^o)/T J·mol ⁻¹ ·K ⁻¹	-(G _T ^o -H ₂₉₈ ^o)/T	FORMATION FROM THE ELEMENTS		
					Δ _f H ^o kJ·mol ⁻¹	Δ _f G ^o	Log K _f
298.15	121.03	134.50	0.00	134.50	-2089.0	-1977.4	346.42
300	121.47	135.25	0.75	134.50	-2089.0	-1976.7	344.17
400	140.22	172.98	33.46	139.52	-2092.0	-1939.0	253.20
500	152.09	205.64	56.09	149.55	-2091.5	-1900.7	198.56
600	159.90	234.11	72.78	161.33	-2090.3	-1862.7	162.16
700	165.10	259.17	85.62	173.55	-2088.8	-1824.9	136.17
800	168.50	281.46	95.79	185.67	-2087.2	-1787.2	116.69
900	170.60	301.44	103.99	197.45	-2085.7	-1749.8	101.56
1000	171.73	319.48	110.72	208.76	-2094.9	-1711.9	89.42

Melting T	K	Boiling T	K
Δ _{fm} H ^o	kJ	Δ _{vap} H ^o	kJ
H ₂₉₈ ^o -H ₀ ^o	19.99 kJ	Molar Vol.	5.686 J·bar ⁻¹ 56.86 cm ³

A= -2.089E+03

B= 3.771E-01

C= -9.27E+04

9/16/92

ANALCIME

Formula wt 220.154

$\text{NaAlSi}_2\text{O}_6 \cdot \text{H}_2\text{O}$: Cubic crystals 298.15 to 800 K. Analcime starts to lose H_2O above 500 K.

Temp. K	C_p°	S_T°	$(H_T^\circ - H_{298}^\circ)/T$	$-(G_T^\circ - H_{298}^\circ)/T$	FORMATION FROM THE ELEMENTS		
					$\Delta_f H^\circ$	$\Delta_f G^\circ$	Log K_f
			$\text{J} \cdot \text{mol}^{-1} \cdot \text{K}^{-1}$		$\text{kJ} \cdot \text{mol}^{-1}$		
298.15	212.23	227.70	0.00	227.70	-3310.1	-3090.0	541.33
300	212.68	229.01	1.31	227.70	-3310.1	-3088.6	537.76
400	237.19	293.54	57.20	236.34	-3313.3	-3014.4	393.63
500	262.19	349.14	95.69	253.45	-3312.2	-2939.8	307.11
600	287.38	399.17	125.54	273.63	-3309.3	-2865.5	249.46
700	312.66	445.37	150.47	294.90	-3304.3	-2792.0	208.33
800	337.99	488.77	172.32	316.45	-3297.3	-2719.2	177.54

Melting T	K	Boiling T	K
$\Delta_{\text{fus}} H^\circ$	kJ	$\Delta_{\text{vap}} H^\circ$	kJ
$H_{298}^\circ - H_0^\circ$	35.74 kJ	Molar Vol.	9.680 $\text{J} \cdot \text{bar}^{-1}$ 96.80 cm^3

A= -3.306E+03

B= 7.344E-01

C= -2.83E+05

5/12/93

DEHYDRATED ANALCIME

Formula wt 202.139

NaAlSi₂O₆: Cubic crystals 298.15 to 1000 K.

Temp. K	C _p ^o	S _T ^o	(H _T ^o -H ₂₉₈ ^o)/T J·mol ⁻¹ ·K ⁻¹	-(G _T ^o -H ₂₉₈ ^o)/T	FORMATION FROM THE ELEMENTS		
					Δ _f H ^o kJ·mol ⁻¹	Δ _f G ^o	Log K _f
298.15	163.05	172.50	0.00	172.50	-2983.1	-2816.0	493.35
300	163.85	173.51	1.01	172.50	-2983.1	-2815.0	490.12
400	194.89	225.37	46.01	179.36	-2986.3	-2758.6	360.23
500	213.59	271.00	77.77	193.23	-2985.3	-2701.8	282.25
600	227.43	311.21	101.60	209.61	-2983.2	-2645.3	230.29
700	238.99	347.16	120.42	226.74	-2980.3	-2589.2	193.20
800	249.32	379.76	135.90	243.86	-2976.8	-2533.5	165.42
900	258.94	409.68	149.04	260.64	-2972.8	-2478.3	143.84
1000	268.12	437.44	160.49	276.95	-2978.8	-2422.9	126.56

Melting T	K	Boiling T	K
Δ _m H ^o	kJ	Δ _{vap} H ^o	kJ
H ₂₉₈ ^o -H ₀ ^o	27.18 kJ	Molar Vol.	J·bar ⁻¹ cm ³
A=	-2.978E+03	B=	5.560E-01
		C=	-3.36E+05

DICKITE

Formula wt 258.160

 $\text{Al}_2\text{Si}_2\text{O}_5(\text{OH})_2$: Triclinic crystals 298.15 to 900 K

Temp. K	C_p°	S_T°	$(H_T^\circ - H_{298}^\circ)/T$ J·mol ⁻¹ ·K ⁻¹	$-(G_T^\circ - H_{298}^\circ)/T$	FORMATION FROM THE ELEMENTS		
					$\Delta_f H^\circ$ kJ·mol ⁻¹	$\Delta_f G^\circ$ kJ·mol ⁻¹	Log K_f
298.15	239.56	197.10	0.00	197.10	-4118.5	-3796.0	665.04
300	240.64	198.59	1.48	197.10	-4118.6	-3794.0	660.58
400	287.65	274.77	67.60	207.17	-4120.4	-3685.5	481.26
500	317.09	342.38	114.78	227.59	-4119.5	-3576.8	373.66
600	334.95	401.91	150.12	251.79	-4117.2	-3468.5	301.95
700	344.93	454.38	177.32	277.06	-4114.4	-3360.6	250.76
800	349.32	500.78	198.59	302.19	-4111.7	-3253.1	212.40
900	349.59	541.97	215.39	326.58	-4109.5	-3145.9	182.58

Melting T	K	Boiling T	K
$\Delta_{\text{fus}} H^\circ$	kJ	$\Delta_{\text{vap}} H^\circ$	kJ
$H_{298}^\circ - H_0^\circ$	kJ	Molar Vol.	9.856 J·bar ⁻¹ 98.56 cm ³

A= -4.113E+03

B= 1.075E+00

C= -3.31E+05

7/29/92

KAOLINITE

Formula wt 258.160

 $\text{Al}_2\text{Si}_2\text{O}_5(\text{OH})_2$: Triclinic crystals 298.15 to 800 K

Temp. K	C_p°	S_T°	$(H_T^\circ - H_{298}^\circ)/T$	$-(G_T^\circ - H_{298}^\circ)/T$	FORMATION FROM THE ELEMENTS		
					$\Delta_f H^\circ$	$\Delta_f G^\circ$	Log K_f
			J·mol ⁻¹ ·K ⁻¹		kJ·mol ⁻¹		
298.15	243.37	200.40	0.00	200.40	-4119.0	-3797.5	665.29
300	244.40	201.91	1.50	200.40	-4119.1	-3795.5	660.84
400	289.53	278.90	68.31	210.59	-4120.6	-3687.3	481.50
500	317.00	346.72	115.53	231.19	-4119.6	-3579.1	373.89
600	333.50	406.10	150.60	255.50	-4117.3	-3471.1	302.18
700	344.03	458.35	177.53	280.82	-4114.5	-3363.7	251.00
800	351.92	504.82	198.85	305.97	-4111.6	-3256.6	212.63

Melting T	K	Boiling T	K
$\Delta_{\text{fus}} H^\circ$	kJ	$\Delta_{\text{vap}} H^\circ$	kJ
$H_{298}^\circ - H_0^\circ$	35.75 kJ	Molar Vol.	9.934 J·bar ⁻¹ 99.34 cm ³
A= -4.115E+03		B= 1.074E+00	
		C= -2.43E+05	

7/29/92

PYROPHYLLITE

Formula wt 360.314

 $\text{Al}_2\text{Si}_4\text{O}_{10}(\text{OH})_2$: Monoclinic crystals 298.15 to 800 K

Temp. K	C_p°	S_T°	$(H_T^\circ - H_{298}^\circ)/T$	$-(G_T^\circ - H_{298}^\circ)/T$	FORMATION FROM THE ELEMENTS		
					$\Delta_f H^\circ$	$\Delta_f G^\circ$	Log K_f
			$\text{J}\cdot\text{mol}^{-1}\cdot\text{K}^{-1}$		$\text{kJ}\cdot\text{mol}^{-1}$		
298.15	293.76	239.40	0.00	239.40	-5640.0	-5266.1	922.58
300	295.04	241.22	1.82	239.41	-5640.1	-5263.8	916.49
400	349.70	334.18	82.47	251.71	-5641.8	-5138.0	670.94
500	386.14	416.37	139.78	276.59	-5640.6	-5012.1	523.60
600	412.51	489.22	183.14	306.08	-5637.5	-4886.7	425.42
700	432.69	554.39	217.41	336.98	-5633.1	-4761.9	355.33
800	448.83	613.25	245.36	367.89	-5628.0	-4637.8	302.81

Melting T	K	Boiling T	K
$\Delta_{\text{fus}} H^\circ$	kJ	$\Delta_{\text{vap}} H^\circ$	kJ
$H_{298}^\circ - H_0^\circ$	42.70 kJ	Molar Vol.	12.81 $\text{J}\cdot\text{bar}^{-1}$ 128.1 cm^3

A= -5.634E+03

B= 1.246E+00

C= -3.54E+05

7/29/92

MARGARITE

Formula wt 398.184

CaAl₂[Al₂Si₂]O₁₀(OH)₂: Monoclinic crystals 298.15 to 1200 K

Temp. K	C _p ^o	S _T ^o	(H _T ^o -H ₂₉₈ ^o)/T J·mol ⁻¹ ·K ⁻¹	-(G _T ^o -H ₂₉₈ ^o)/T	FORMATION FROM THE ELEMENTS		
					Δ _f H ^o kJ·mol ⁻¹	Δ _f G ^o	Log K _f
298.15	323.41	263.60	0.00	263.60	-6244.0	-5858.9	1026.43
300	324.82	265.60	2.00	263.61	-6244.1	-5856.5	1019.68
400	384.97	367.96	90.81	277.15	-6245.9	-5726.9	747.84
500	424.42	458.38	153.83	304.55	-6244.5	-5597.2	584.73
600	452.21	538.35	201.37	336.98	-6241.1	-5468.1	476.03
700	472.69	609.68	238.74	370.94	-6236.7	-5339.6	398.44
800	488.23	673.86	269.00	404.86	-6232.8	-5211.6	340.28
900	500.23	732.08	294.05	438.03	-6228.0	-5084.3	295.08
1000	509.60	785.29	315.16	470.14	-6265.9	-4954.5	258.79
1100	516.96	834.22	333.18	501.04	-6260.8	-4823.6	229.05
1200	522.74	879.46	348.75	530.71	-6263.4	-4692.5	204.26

Melting T	K	Boiling T	K
Δ _{fus} H ^o	kJ	Δ _{vap} H ^o	kJ
H ₂₉₈ ^o -H ₀ ^o	48.14 kJ	Molar Vol.	12.963 J·bar ⁻¹ 129.63 cm ³

A= -6.243E+03

B= 1.291E+00

C= 6.216E+02

7/29/92

PREHNITE

Formula wt 412.384

 $\text{Ca}_2\text{Al}[\text{AlSi}_3\text{O}_{10}](\text{OH})_2$: Orthorhombic crystals 298.15 to 1200 K

Temp. K	C_p°	S_T°	$(H_T^\circ - H_{298}^\circ)/T$ J·mol ⁻¹ ·K ⁻¹	$-(G_T^\circ - H_{298}^\circ)/T$	FORMATION FROM THE ELEMENTS		
					$\Delta_f H^\circ$ kJ·mol ⁻¹	$\Delta_f G^\circ$	Log K_f
298.15	331.12	292.80	0.00	292.80	-6202.6	-5824.7	1020.43
300	332.41	294.85	2.05	292.81	-6202.7	-5822.3	1013.73
400	389.19	398.83	92.23	306.60	-6203.7	-5695.3	743.71
500	427.23	490.03	155.67	334.36	-6201.7	-5568.3	581.71
600	453.51	570.39	203.25	367.14	-6198.0	-5442.0	473.76
700	471.95	641.76	240.39	401.37	-6193.4	-5316.4	396.70
800	484.90	705.68	270.20	435.48	-6190.4	-5191.2	338.94
900	493.85	763.34	294.58	468.76	-6185.9	-5066.5	294.05
1000	499.76	815.71	314.83	500.88	-6203.2	-4940.9	258.08
1100	503.31	863.52	331.82	531.71	-6199.7	-4814.8	228.63
1200	505.00	907.40	346.19	561.21	-6212.4	-4687.7	204.05

Melting T	K	Boiling T	K
$\Delta_{\text{fus}} H^\circ$	kJ	$\Delta_{\text{vap}} H^\circ$	kJ
$H_{298}^\circ - H_0^\circ$	50.66 kJ	Molar Vol.	14.110 J·bar ⁻¹ 141.10 cm ³

A= -6.194E+03

B= 1.255E+00

C= -3.99E+05

5/14/92

MUSCOVITE (Al/Si disordered)

Formula wt 398.308

 $KAl_2[AlSi_3O_{10}](OH)_2$: Crystals 298.15 to 1000 K.

Temp. K	C_p°	S_T°	$(H_T^\circ - H_{298}^\circ)/T$ J·mol ⁻¹ ·K ⁻¹	$-(G_T^\circ - H_{298}^\circ)/T$	FORMATION FROM THE ELEMENTS		
					$\Delta_f H^\circ$ kJ·mol ⁻¹	$\Delta_f G^\circ$	Log K_f
298.15	325.99	306.40	0.00	306.40	-5974.8	-5598.8	980.86
300	327.30	308.42	2.01	306.41	-5974.9	-5596.4	974.40
400	385.47	411.09	91.08	320.01	-5979.1	-5469.5	714.22
500	425.61	501.68	154.21	347.47	-5977.5	-5342.2	558.08
600	454.37	581.96	201.96	379.99	-5973.8	-5215.4	454.03
700	475.51	653.67	239.61	414.06	-5968.6	-5089.5	379.77
800	491.31	718.24	270.13	448.11	-5962.6	-4964.2	324.12
900	503.20	776.83	295.40	481.43	-5956.4	-4839.8	280.89
1000	512.13	830.33	316.64	513.69	-5981.9	-4713.9	246.22

Melting T	K	Boiling T	K
$\Delta_{fus} H^\circ$	kJ	$\Delta_{vap} H^\circ$	kJ
$H_{298}^\circ - H_0^\circ$	49.41 kJ	Molar Vol.	14.081 J·bar ⁻¹ 140.81 cm ³
A=	-5.966E+03	B=	1.253E+00
		C=	-5.87E+05

7/15/92

MUSCOVITE (Al/Si ordered)

Formula wt 398.308

 $KAl_2[AlSi_3O_{10}](OH)_2$: Monoclinic crystals 298.15 to 1000 K.

Temp. K	C_p°	S_T°	$(H_T^\circ - H_{298}^\circ)/T$ J·mol ⁻¹ ·K ⁻¹	$-(G_T^\circ - H_{298}^\circ)/T$	FORMATION FROM THE ELEMENTS		
					$\Delta_f H^\circ$ kJ·mol ⁻¹	$\Delta_f G^\circ$	Log K_f
298.15	325.99	287.70	0.00	287.70	-5990.0	-5608.4	982.55
300	327.30	289.72	2.01	287.71	-5990.1	-5606.0	976.07
400	385.47	392.39	91.08	301.31	-5994.3	-5477.2	715.23
500	425.61	482.98	154.21	328.77	-5992.7	-5348.0	558.69
600	454.37	563.26	201.96	361.29	-5989.0	-5219.4	454.38
700	475.51	634.97	239.61	395.36	-5983.8	-5091.6	379.93
800	491.31	699.54	270.13	429.41	-5977.8	-4964.5	324.14
900	503.20	758.13	295.40	462.73	-5971.6	-4838.2	280.79
1000	512.13	811.63	316.64	494.99	-5997.1	-4710.4	246.04

Melting T	K	Boiling T	K
$\Delta_{\text{melt}} H^\circ$	kJ	$\Delta_{\text{vap}} H^\circ$	kJ
$H_{298}^\circ - H_0^\circ$	49.41 kJ	Molar Vol.	14.081 J·bar ⁻¹ 140.81 cm ³

A= -5.981E+03

B= 1.271E+00

C= -5.87E+05

3/5/93

ANNITE

Formula wt 511.886

KFe₃[AlSi₃O₁₀](OH)₂: Crystals 298.15 to 1000 K

Temp. K	C _p ^o	S _T ^o	(H _T ^o -H ₂₉₈ ^o)/T	-(G _T ^o -H ₂₉₈ ^o)/T	FORMATION FROM THE ELEMENTS		
					Δ _f H ^o	Δ _f G ^o	Log K _f
			J·mol ⁻¹ ·K ⁻¹		kJ·mol ⁻¹		
298.15	390.32	415.00	0.00	415.00	-5149.3	-4798.3	840.62
300	391.81	417.42	2.41	415.01	-5149.3	-4796.1	835.06
400	452.51	539.23	108.03	431.20	-5149.7	-4678.2	610.89
500	491.34	644.64	181.04	463.60	-5144.8	-4560.7	476.45
600	520.03	736.87	235.25	501.62	-5138.3	-4444.5	386.92
700	543.12	818.82	277.63	541.19	-5130.7	-4329.5	323.06
800	562.76	892.65	312.07	580.58	-5122.7	-4215.6	275.24
900	580.11	959.96	340.91	619.05	-5114.9	-4102.6	238.10
1000	595.84	1021.90	365.63	656.28	-5119.0	-3989.8	208.40

Melting T	K	Boiling T	K
Δ _{fm} H ^o	kJ	Δ _{vap} H ^o	kJ
H ₂₉₈ ^o -H ₀ ^o	kJ	Molar Vol.	15.43 J·bar ⁻¹ 154.3 cm ³

A= -5.122E+03

B= 1.135E+00

C= -1.31E+06

7/29/92

PHLOGOPITE (Al/Si Disordered)

Formula wt 417.260

 $\text{KMg}_3[\text{AlSi}_3\text{O}_{10}](\text{OH})_2$: Crystals 298.15 to 1000 K

Temp. K	C_p°	S_T°	$(H_T^\circ - H_{298}^\circ)/T$ J·mol ⁻¹ ·K ⁻¹	$-(G_T^\circ - H_{298}^\circ)/T$	FORMATION FROM THE ELEMENTS		
					$\Delta_f H^\circ$ kJ·mol ⁻¹	$\Delta_f G^\circ$	Log K_f
298.15	354.65	334.60	0.00	334.60	-6226.0	-5846.0	1024.18
300	355.97	336.80	2.19	334.61	-6226.1	-5843.7	1017.45
400	412.17	447.54	98.22	349.32	-6230.1	-5715.4	746.74
500	448.48	543.69	164.88	378.80	-6228.8	-5586.8	583.64
600	473.45	627.79	214.35	413.44	-6225.8	-5458.7	475.21
700	491.23	702.19	252.70	449.48	-6221.8	-5331.2	397.81
800	504.13	768.67	283.37	485.30	-6217.4	-5204.2	339.79
900	513.53	828.62	308.45	520.17	-6213.1	-5077.8	294.70
1000	520.33	883.10	329.31	553.78	-6245.5	-4949.0	258.50

Melting T	K	Boiling T	K
$\Delta_{\text{m}} H^\circ$	kJ	$\Delta_{\text{vap}} H^\circ$	kJ
$H_{298}^\circ - H_0^\circ$	54.08 kJ	Molar Vol.	14.965 J·bar ⁻¹ 149.65 cm ³

A= -6.222E+03

B= 1.273E+00

C= -3.45E+05

7/29/92

PHLOGOPITE (Al/Si ordered)

Formula wt 417.260

KMg₃[AlSi₃O₁₀](OH)₂: Monoclinic crystals 298.15 to 1000 K.

Temp. K	C _p ^o	S _T ^o	(H _T ^o -H ₂₉₈ ^o)/T	-(G _T ^o -H ₂₉₈ ^o)/T	FORMATION FROM THE ELEMENTS		
					Δ _f H ^o	Δ _f G ^o	Log K _f
			J·mol ⁻¹ ·K ⁻¹		kJ·mol ⁻¹		
298.15	354.65	315.90	0.00	315.90	-6246.0	-5860.5	1026.71
300	355.97	318.10	2.19	315.91	-6246.1	-5858.1	1019.96
400	412.17	428.84	98.22	330.62	-6250.1	-5727.9	747.97
500	448.48	524.99	164.88	360.10	-6248.8	-5597.5	584.75
600	473.45	609.09	214.35	394.74	-6245.8	-5467.5	475.97
700	491.23	683.49	252.70	430.78	-6241.8	-5338.1	398.32
800	504.13	749.97	283.37	466.60	-6237.4	-5209.2	340.12
900	513.53	809.92	308.45	501.47	-6233.1	-5081.0	294.89
1000	520.33	814.40	329.31	535.08	-6265.5	-4950.3	258.57

Melting T	K	Boiling T	K
Δ _{fus} H ^o	kJ	Δ _{vap} H ^o	kJ
H ₂₉₈ ^o -H ₀ ^o	kJ	Molar Vol.	14.962 J·bar ⁻¹ 149.62 cm ³
A= -6.242E+03	B= 1.291E+00	C= -3.45E+05	

FLUORPHLOGOPITE (Al/Si disordered)

Formula wt 421.242

KMg₃[AlSi₃O₁₀]F₂: Crystals 298.15 to 1700 K. Approximate melting point 1670 K.

Temp. K	C _p ^o	S _T ^o	(H _T ^o -H ₂₉₈ ^o)/T	-(G _T ^o -H ₂₉₈ ^o)/T	FORMATION FROM THE ELEMENTS		
					Δ _f H ^o	Δ _f G ^o	Log K _f
			J·mol ⁻¹ ·K ⁻¹	kJ·mol ⁻¹			
298.15	342.42	336.30	0.00	336.30	-6355.5	-6015.7	1053.90
300	343.70	338.42	2.12	336.31	-6355.5	-6013.6	1047.04
400	392.83	444.81	94.33	350.48	-6358.5	-5899.0	770.31
500	420.87	535.72	157.05	378.67	-6356.9	-5784.3	604.26
600	439.96	614.23	202.69	411.54	-6354.4	-5670.0	493.60
700	454.48	683.18	237.66	445.52	-6351.3	-5556.2	414.60
800	466.38	744.67	265.53	479.14	-6347.9	-5442.8	355.37
900	476.62	800.21	288.43	511.78	-6344.6	-5329.8	309.33
1000	485.76	850.90	307.71	543.19	-6377.8	-5214.4	272.37
1100	494.13	897.60	324.28	573.32	-6453.5	-5093.6	241.87
1200	501.92	940.93	338.77	602.17	-6448.8	-4970.2	216.34
1300	509.29	981.40	351.60	629.80	-6443.7	-4847.1	194.76
1400	516.32	1019.40	363.12	656.28	-6820.5	-4715.2	175.92
1500	523.09	1055.26	373.56	681.70	-6810.5	-4565.1	158.97
1600	529.64	1089.23	383.11	706.12	-6800.2	-4415.6	144.15
1700	536.01	1121.53	391.92	729.61	-6940.0	-4265.5	131.06

Melting T 1670 K

Boiling T K

Δ_{sub}H^o kJΔ_{sub}H^o kJH₂₉₈^o-H₀^o kJMolar Vol. 14.652 J·bar⁻¹
146.52 cm³

A= -6.476E+03

B= 1.272E+00

C= 8.177E+06

01/14/93

FLUORPHLOGOPITE (Al/Si ordered)

Formula wt 421.242

KMg₃[AlSi₃O₁₀]F₂: Crystals 298.15 to 1700 K. Approximate melting point 1670 K.

Temp. K	C _p ^o	S _T ^o	(H _T ^o -H ₂₉₈ ^o)/T	-(G _T ^o -H ₂₉₈ ^o)/T	FORMATION FROM THE ELEMENTS		
					Δ _f H ^o	Δ _f G ^o	Log K _f
			J·mol ⁻¹ ·K ⁻¹		kJ·mol ⁻¹		
298.15	342.42	336.30	0.00	336.30	-6375.5	-6030.1	1056.43
300	343.70	338.42	2.12	336.31	-6375.5	-6028.0	1049.54
400	392.83	444.81	94.33	350.48	-6378.5	-5911.5	771.95
500	420.87	535.72	157.05	378.67	-6376.9	-5794.9	605.38
600	439.96	614.23	202.69	411.54	-6374.4	-5678.7	494.37
700	454.48	683.18	237.66	445.52	-6371.3	-5563.1	415.11
800	466.38	744.67	265.53	479.14	-6367.9	-5447.8	355.70
900	476.62	800.21	288.43	511.78	-6364.6	-5333.0	309.51
1000	485.76	850.90	307.71	543.19	-6397.8	-5215.7	272.43
1100	494.13	897.60	324.28	573.32	-6473.5	-5093.0	241.84
1200	501.92	940.93	338.77	602.17	-6468.8	-4967.7	216.23
1300	509.29	981.40	351.60	629.80	-6463.7	-4842.8	194.58
1400	516.32	1019.40	363.12	656.28	-6840.5	-4709.0	175.69
1500	523.09	1055.26	373.56	681.70	-6830.5	-4557.0	158.69
1600	529.64	1089.23	383.11	706.12	-6820.2	-4405.7	143.83
1700	536.01	1121.53	391.92	729.61	-6960.0	-4253.7	130.70

Melting T	1670 K	Boiling T	K
Δ _{sub} H ^o	kJ	Δ _{sub} H ^o	kJ
H ₂₉₈ ^o -H ₀ ^o	kJ	Molar Vol.	14.652 J·bar ⁻¹ 146.52 cm ³

A= -6.496E+03

B= 1.291E+00

C= 8.177E+06

01/14/93

TALC

Formula wt 379.266

Mg₃Si₄O₁₀(OH)₂: Monoclinic crystals 298.15 to 800 K.

Temp. K	C _p ^o	S _T ^o	(H _T ^o -H ₂₉₈ ^o)/T	-(G _T ^o -H ₂₉₈ ^o)/T	FORMATION FROM THE ELEMENTS		
					Δ _f H ^o	Δ _f G ^o	Log K _f
			J·mol ⁻¹ ·K ⁻¹	kJ·mol ⁻¹			
298.15	321.77	260.80	0.00	260.80	-5900.0	-5520.1	967.08
300	323.23	262.79	1.99	260.81	-5900.1	-5517.8	960.71
400	386.65	365.29	90.94	274.35	-5901.1	-5390.1	703.85
500	420.68	455.61	153.83	301.78	-5899.0	-5262.5	549.76
600	444.28	534.40	200.28	334.12	-5895.5	-5135.5	447.08
700	475.19	605.03	237.17	367.85	-5890.5	-5009.3	373.79
800	525.90	671.51	269.84	401.68	-5882.6	-4883.9	318.88

Melting T	K	Boiling T	K
Δ _{fus} H ^o	kJ	Δ _{vap} H ^o	kJ
H ₂₉₈ ^o -H ₀ ^o	46.88 kJ	Molar Vol.	13.625 J·bar ⁻¹ 136.25 cm ³

A= -5.890E+03

B= 1.260E+00

C= -4.84E+05

7/29/92

CHRYSTILE (Antigorite)

Formula wt 277.112

Mg₃Si₂O₅(OH)₄: Monoclinic crystals 298.15 to 900 K.

Temp. K	C _p ^o	S _T ^o	(H _T ^o -H ₂₉₈ ^o)/T	-(G _T ^o -H ₂₉₈ ^o)/T	FORMATION FROM THE ELEMENTS		
					Δ _f H ^o	Δ _f G ^o	Log K _f
			J·mol ⁻¹ ·K ⁻¹	kJ·mol ⁻¹			
298.15	274.05	221.30	0.00	221.30	-4360.0	-4032.4	706.44
300	275.12	223.00	1.69	221.31	-4360.1	-4030.3	701.73
400	323.31	309.17	76.44	232.73	-4361.0	-3920.2	511.91
500	356.40	385.10	129.33	255.77	-4359.1	-3810.1	398.03
600	379.00	452.21	169.18	283.03	-4355.4	-3700.7	322.16
700	394.31	511.86	200.32	311.54	-4350.8	-3591.9	268.03
800	404.36	565.22	225.24	339.97	-4345.7	-3483.8	227.47
900	410.50	613.23	245.52	367.71	-4340.7	-3376.4	195.96

Melting T	K	Boiling T	K
Δ _{fm} H ^o	kJ	Δ _{vp} H ^o	kJ
H ₂₉₈ ^o -H ₀ ^o	kJ	Molar Vol.	10.75 J·bar ⁻¹ 107.5 cm ³

A= -4.348E+03

B= 1.081E+00

C= -6.03E+05

5/14/92

PARAGONITE (Al/Si disordered)

Formula wt 382.200

NaAl₂[AlSi₃O₁₀](OH)₂: Monoclinic crystals 298.15 to 800 K.

Temp. K	C _p ^o	S _T ^o	(H _T ^o -H ₂₉₈ ^o)/T	-(G _T ^o -H ₂₉₈ ^o)/T	FORMATION FROM THE ELEMENTS		
					Δ _f H ^o	Δ _f G ^o	Log K _f
			J·mol ⁻¹ ·K ⁻¹		kJ·mol ⁻¹		
298.15	321.50	288.80	0.00	288.80	-5933.0	-5555.7	973.31
300	322.86	290.79	1.99	288.81	-5933.1	-5553.3	966.90
400	380.52	392.22	89.98	302.24	-5937.9	-5426.1	708.56
500	419.03	481.51	152.15	329.36	-5936.9	-5298.2	553.49
600	447.59	560.55	199.12	361.43	-5933.8	-5170.7	450.14
700	470.21	631.30	236.29	395.02	-5929.2	-5043.9	376.37
800	488.92	695.35	266.73	428.62	-5923.5	-4917.8	321.09

Melting T	K	Boiling T	K
Δ _{fus} H ^o	kJ	Δ _{vap} H ^o	kJ
H ₂₉₈ ^o -H ₀ ^o	48.12 kJ	Molar Vol.	13.211 J·bar ⁻¹ 132.11 cm ³

A= -5.931E+03

B= 1.268E+00

C= -2.33E+05

5/14/92

PARAGONITE (Al/Si ordered)

Formula wt 382.200

NaAl₂[AlSi₃O₁₀](OH)₂: Monoclinic crystals 298.15 to 800 K.

Temp. K	C _p ^o	S _T ^o	(H _T ^o -H ₂₉₈ ^o)/T	-(G _T ^o -H ₂₉₈ ^o)/T	FORMATION FROM THE ELEMENTS		
					Δ _f H ^o	Δ _f G ^o	Log K _f
			J·mol ⁻¹ ·K ⁻¹		kJ·mol ⁻¹		
298.15	321.50	277.10	0.00	277.10	-5949.3	-5568.5	975.55
300	322.87	279.09	1.99	277.11	-5949.4	-5566.1	969.12
400	380.52	380.52	89.98	290.54	-5954.2	-5437.7	710.08
500	419.04	469.81	152.16	317.66	-5953.2	-5308.7	554.58
600	447.60	548.85	199.12	349.73	-5950.1	-5180.0	450.95
700	470.21	619.61	236.29	383.32	-5945.5	-5052.0	376.98
800	488.92	683.65	266.73	416.92	-5939.8	-4924.8	321.55

Melting T	K	Boiling T	K
Δ _m H ^o	kJ	Δ _{vap} H ^o	kJ
H ₂₉₈ ^o -H ₀ ^o	48.12 kJ	Molar Vol.	13.211 J·bar ⁻¹ 132.11 cm ³
A=	-5.947E+03	B=	1.279E+00
		C=	-2.34E+05

12/9/92

REFERENCES CITED

1. Adami, L. H., and Conway, K. C., 1966, Heats and free energies of formation of anhydrous carbonates of barium, strontium, and lead: U.S. Bur. Mines Rept. Inv. 6822, 7 p.
2. Adami, L. H., and Kelley, K. K., 1963, Heats of formation of two crystalline hydrates of ferrous sulfate: U. S. Bur. Mines Rept. Inv. 6260, 7 p.
3. Adami, L. H., and King, E. G., 1964, Heats and free energies of formation of sulfides of manganese, iron, zinc, and cadmium: U.S. Bur. Mines Rept. Inv. 6495, 10 p.
4. Adami, L. H., and King, E. G., 1965, Heats of formation of anhydrous sulfates of cadmium, cobalt, copper, nickel, and zinc: U. S. Bur. Mines Rept. Inv. 6617, 10 p.
5. Agoshkov, V. M., Semenov, Yu. V. Malinko, S. V., and Khodakovskiy, I. L., 1977, Enthalpies of datolite and danburite between 298.15 and 973.15 K: *Geochemistry International*, v. 14(6), p. 142-147.
6. Akaogi, M., and Navrotsky, A., 1984, The quartz-cosite-stishovite transformations: new calorimetric measurements and calculations of phase diagrams: *Physics of the Earth and Planetary Interiors*, v. 36, p. 124-134.
7. Amosee, J. and Mathieu, J.C., 1980, The enthalpies of formation of FeWO_4 , MnWO_4 , and their solid solutions: *Jour. Chem. Thermodynamics*, v. 12, p. 683-689.
8. Anovitz, L. M., Essene, E. J., Hemingway, B. S., Komada, N. L., and Westrum, E. F., Jr., 1988, The heat-capacities of grunerite and deerite: phase equilibria in the system Fe-Si-C-O-H and implications for the metamorphism of the banded iron formations: *EOS*, v. 69, p. 515.

9. Anovitz, L. M., Essene, E. J., Metz, G. W., Bohlen, S. R., Westrum, E. F., Jr., and Hemingway, B. S., 1993, Heat capacity and phase equilibria of almandine, $\text{Fe}_3\text{Al}_2\text{Si}_3\text{O}_{12}$: *Geochim. Cosmochim. Acta*, v. 57, p. 4191-4204.
10. Anovitz, L. M., Hemingway, B. S., Westrum, E. F., Jr., Metz, G. W., and Essene, E. J., 1987, Heat capacity measurements for cryolite (Na_3AlF_6) and reactions in the system Na-Fe-Al-Si-O-F: *Geochim. Cosmochim. Acta*, v. 51, p. 3087-3103.
11. Anovitz, L. M., Treiman, A. H., Essene, E. J., Hemingway, B. S., Westrum, E. F., Jr., Wall, V. J., Burriel, R., and Bohlen, S. R., 1985, The heat-capacity of ilmenite and phase equilibria in the system Fe-Ti-O: *Geochim. Cosmochim. Acta*, v. 49, p. 2027-2040.
12. Apps, J. A., Neil, J. M., and Jan, C.-H., 1988, Thermochemical properties of gibbsite, bayerite, boehmite, diaspore, and the aluminate ion between 0 and 350°C: University of California Lawrence Berkeley Rept., LBL-21482.
13. Ashida, T., Kume, S., Ito, E., and Navrotsky, A., 1988, MgSiO_3 ilmenite: heat capacity, thermal expansivity, and enthalpy of transformation: *Phys. Chem. Minerals*, v. 16, p. 239-245.
14. Baker, F. B., Huber, E. J., Jr., Holley, C. E., Jr., and Krikorian, N. H., 1971, Enthalpies of formation of cerium dioxide, cerium sesquicarbide, and cerium dicarbide: *Jour. Chem. Thermodynamics*, v. 3, p. 77-84.
15. Bannister, M. J., 1984, The standard molar Gibbs free energy of formation of PbO. Oxygen concentration cell measurements at low temperatures: *Jour. Chem. Thermodynamics*, v. 16, p. 787-792.

16. Bannister, M. J., 1986, Oxygen concentration-cell determination of the standard molar Gibbs free energy of formation of SnO_2 : *Jour. Chem. Thermodynamics*, v. 18, p. 455-463.
17. Barany, R., 1962, Heats and free energies of formation of calcium tungstate, calcium molybdate, and magnesium molybdate: U.S. Bur. Mines Rept. Inv. 6143, 11 p.
18. Barany, R., 1965, Heats of formation of goethite, ferrous vanadate, and manganese molybdate: U.S. Bur. Mines Rept. Inv. 6618, 10 p.
19. Barany, R., and Adami, L. H., 1965, Heats of formation of anhydrous ferric sulfate and indium sulfate: U. S. Bur. Mines Rept. Inv. 6687, 8 p.
20. Barany, R., and Adami L. H., 1966, Heats of formation of lithium sulfate and five potassium- and lithium-aluminum silicates: U.S. Bur. Mines Rept. Inv. 6873, 18 p.
21. Bartel, J.J. and Westrum, E.F., Jr., 1975, Heat capacities of Fe_3O_4 and ZnFe_2O_4 from 300 to 500 K: *Jour. Chem. Thermodynamics*, v. 7, p. 706-708.
22. Bartel, J.J. and Westrum, E. F., Jr., 1976, Thermodynamics of Fe(II) Fe(III) oxide systems. II zinc and cadmium-doped Fe_3O_4 and crystalline magnetite: *Jour. Chem. Thermodynamics*, v. 8, p. 583-600.
23. Barton, M. D., 1982, The thermodynamic properties of topaz solid solutions and some petrologic applications: *Am. Mineralogist*, v. 67, p. 956-974.
24. Barton, M. D., Haselton, H. T., Jr., Hemingway, B. S., Kleppa, O. J., and Robie, R. A., 1982, The thermodynamic properties of fluor-topaz: *Am. Mineralogist*, v. 67, p. 350-355.

25. Barton, P. B., Jr., 1969, Thermochemical study of the system Fe-As-S: *Geochim. Cosmochim. Acta*, v. 33, p. 841-857.
26. Barton, P. B., Jr., and Bethke, P. M., 1960, Thermodynamic properties of some synthetic zinc and copper minerals: *Am. Jour. Sci.*, v. 258-A, (Bradley volume), p. 21-34.
27. Belitskiy, I. A., Gabunda, S. P., Drebuschak, V. A., Naumov, V. N., and Nogteva, V. V., 1984, The specific heat of edingtonite at 5-316 K and the entropy and enthalpy under standard conditions: *Geochemistry International*, v. 21(3), p. 21-23.
28. Bennington, K. O., 1982, Stability relationships between petalite ($\text{LiAlSi}_4\text{O}_{10}$) and spodumene ($\text{LiAlSi}_2\text{O}_6$): U.S. Bur. Mines Rept. Inv. 8719, 15 p.
29. Bennington, K. O., Beyer, R. P., and Brown, R. R., 1984, Thermodynamic properties of hedenbergite, a complex silicate of Ca, Fe, Mn, and Mg: U.S. Bur. Mines Rept Inv. 8873, 19 p.
30. Bennington, K. O., Beyer, R. P., and Johnson, G. K., 1983, Thermodynamic properties of pollucite (a cesium-aluminum silicate): U.S. Bur. Mines Rept. Inv. 8779, 18 p.
31. Bennington, K. O., and Brown, R. R., 1982, Thermodynamic properties of synthetic acmite ($\text{NaFe}^{3+}\text{Si}_2\text{O}_6$): U.S. Bur. Mines Rept Inv. 8621, 12 p.
32. Bennington, K. O., Brown, R. R., Bell, H. E., and Beyer, R. P., 1987, Thermodynamic properties of two manganese silicates, pyroxmangite and fowlerite: U.S. Bur. Mines Rept Inv. 9064, 22 p.
33. Bennington, K. O., Brown, R. R., and Beyer, R. P., 1984, Thermodynamic properties of aegirine: U.S. Bur. Mines Rept. Inv. 8912, v. 16, p.

34. Bennington, K. O., Ferrante, M. J., and Stuve, J. M., 1978, Thermodynamic data on the amphibole asbestos minerals amosite and crocidolite: U.S. Bur. Mines Rept. Inv. 8265, 30 p.
35. Bennington, K. O., Stuve, J. M., and Ferrante, M. J., 1980, Thermodynamic properties of petalite ($\text{Li}_2\text{Al}_2\text{Si}_8\text{O}_{20}$): U.S. U.S. Bur. Mines Rept. Inv. 8451, 20 p.
36. Berg, R. L., and Vanderzee, C. E., 1978, Thermodynamics of carbon dioxide and carbonic acid: (a) the standard enthalpies of solution of $\text{Na}_2\text{CO}_3(\text{s})$, $\text{NaHCO}_3(\text{s})$, and $\text{CO}_2(\text{g})$ in water at 298.15 K; (b) the standard enthalpies of formation, standard Gibbs energies of formation, and standard entropies of $\text{CO}_2(\text{aq})$, $\text{HCO}_3^-(\text{aq})$, $\text{CO}_3^{2-}(\text{aq})$, $\text{NaHCO}_3(\text{s})$, $\text{Na}_2\text{CO}_3(\text{s})$, $\text{Na}_2\text{CO}_3 \cdot \text{H}_2\text{O}(\text{s})$, and $\text{Na}_2\text{CO}_3 \cdot 10\text{H}_2\text{O}(\text{s})$: Jour. Chem. Thermodynamics, v. 10, p. 1113-1136.
37. Berman, R. G., 1988, Internally consistent thermodynamic data for minerals in the system $\text{Na}_2\text{O}-\text{K}_2\text{O}-\text{CaO}-\text{MgO}-\text{FeO}-\text{Fe}_2\text{O}_3-\text{Al}_2\text{O}_3-\text{SiO}_2-\text{TiO}_2-\text{H}_2\text{O}-\text{CO}_2$: Jour. Petrology, v. 29 pt. 2, p. 445-522.
38. Beyer, R. P., Ferrante, M. J., and Mrazek, R. V., 1983, An automated calorimeter for heat-capacity measurements from 5 to 300 K. The heat capacity of cadmium sulfide from 5.37 to 301.8 K and the relative enthalpy to 1103.4 K: Jour. Chem. Thermodynamics, v. 15, p. 827-834.
39. Boerio, J. and Westrum, E.F., Jr., 1978, Heat capacity and thermodynamic properties of strontium from 5 to 350 K: Jour. Chem. Thermodynamics, v. 10, p. 1-7.
40. Boerio-Goates, J., Artman, J. I., and Woodfield, B. F., 1990, Heat capacity studies of phase transition in langbeinites II. $\text{K}_2\text{Mg}_4(\text{SO}_4)_3$: Phys. Chem. Minerals, v. 17, p. 173-178.
41. Bohlen, S. R., Metz, G. W., Essene, E. J., Anovitz, L. M., Westrum, E. F., Jr., and Wall, V. J., 1983, Thermodynamics and phase equilibrium of ferrosilite: potential oxygen barometer in mantle rocks: EOS, v. 64, p. 350.

42. Bonnicksen, K. R., 1954, High-temperature heat contents of calcium and magnesium ferrites: Am. Chem. Soc. Jour., v. 76, p. 1480-1482.
43. Bonnicksen, K. R., 1955, High-temperature heat contents of some titanates of aluminum, iron, and zinc: Am. Chem. Soc. Jour., v. 77, p. 2152-2154.
44. Bonnicksen, K. R., 1955, High-temperature heat contents of aluminates of calcium and magnesium: Jour. Phys. Chemistry, v. 59, p. 221-221.
45. Boyle, B. J., King, E. G., and Conway, K. C., 1954, Heats of formation of nickel and cobalt oxides (NiO and CoO) by combustion calorimetry: Am. Chem. Soc. Jour., v. 76, p. 3835-3837.
46. Brink, I. J., and Holley, C. E., Jr., 1978, The enthalpy of formation of strontium monoxide: Jour. Chem. Thermodynamics, v. 10, p. 259-266.
47. Brodale, G., and Giauque, W. F., 1958, The heat of hydration of sodium sulfate. Low temperature heat capacity and entropy of sodium sulfate decahydrate: Am. Chem. Soc. Jour., v. 80, p. 2042-2044.
48. Brooks, A. A., 1953, A thermodynamic study of the equilibrium $2\text{Cu}(s) + \text{H}_2\text{S}(g) = \text{Cu}_2\text{S}(l) + \text{H}_2(g)$: Am. Chem. Soc. Jour., v. 75, p. 2464-2467.
49. Brousse, C., Newton, R. C., and Kleppa, O. J., 1984, Enthalpy of formation of forsterite, enstatite, akermanite, monticellite and merwinite at 1073 K by alkali borate solution calorimetry: Geochim. Cosmochim. Acta, v. 48, p. 1081-1088.
50. Bryndzia, L. T., and Kleppa, O. J., 1988, Standard molar enthalpies of formation of realgar (α -AsS) and orpiment (As_2S_3) by high-temperature direct-synthesis calorimetry: Jour. Chem. Thermodynamics, v. 20, p. 755-764.

51. Bryndzia, L. T., and Kleppa, O. J., 1988, High-temperature reaction calorimetry of solid and liquid phases in the quasi-binary system $\text{Ag}_2\text{S-Sb}_2\text{S}_3$: *Geochim. Cosmochim. Acta*, v. 52, p. 167-176.
52. Bryndzia, L.T., and Kleppa, O.J., 1988, Standard enthalpies of formation of sulfides and sulfosalts in the Ag-Bi-S system by high-temperature, direct synthesis calorimetry: *Economic Geology*, v. 83, p. 174-181.
53. Bryndzia, L.T., and Kleppa, O.J., 1988, High-temperature reaction calorimetry of solid and liquid phases in part of the quasi-binary system $\text{Cu}_2\text{S-Sb}_2\text{S}_3$: *Am. Mineralogist*, v. 73, p. 707-713.
54. Busenberg, E., and Plummer, L. N., 1986, The solubility of $\text{BaCO}_3(\text{cr})$ (witherite) in $\text{CO}_2\text{-H}_2\text{O}$ solutions between 0 and 90°C, evaluation of the association constants of $\text{BaHCO}_3^+(\text{aq})$ and $\text{BaCO}_3^\circ(\text{aq})$ between 5 and 80°C, and a preliminary evaluation of the thermodynamic properties of $\text{Ba}^{2+}(\text{aq})$: *Geochim. Cosmochim. Acta*, v. 50, p. 2225-2233.
55. Busenberg, E., Plummer, L. N., and Parker, V. B., 1984, The solubility of strontianite (SrCO_3) in $\text{CO}_2\text{-H}_2\text{O}$ solutions between 2 and 91°C, the association constants of $\text{SrHCO}_3^+(\text{aq})$ and $\text{SrCO}_3(\text{aq})^\circ$ between 5 and 80°C, and an evaluation of the thermodynamic properties of $\text{Sr}^{2+}(\text{aq})$ and $\text{SrCO}_3(\text{cr})$ at 25°C and 1 atm total pressure: *Geochim. Cosmochim. Acta*, v. 48, p. 2021-2035.
56. Carpenter, M. A., McConnell, J. D. C., and Navrotsky, A., 1985, Enthalpies of ordering in the plagioclase feldspar solid solution: *Geochim. Cosmochim. Acta*, v. 49, p. 947-966.
57. Castanet, Robert, 1984, Selected data on the thermodynamic properties of alpha-alumina: *High Temperatures - High Pressures*, v. 16, p. 449-457.

58. Cemic, L., and Kleppa, O. J., 1986, High temperature calorimetry of sulfide systems. I. Thermochemistry of liquid and solid phases of Ni+S: *Geochim. Cosmochim. Acta*, v. 50, p. 1633-1641.
59. Cemic, L., and Kleppa, O. J., 1987, High temperature calorimetry of sulfide systems II. Standard enthalpies of formation of pentlandite and violarite: *Phys. Chem. Minerals*, v. 14, p. 52-57.
60. Cemic, L., and Kleppa, O. J., 1988, High temperature calorimetry of sulfide systems III. Standard enthalpies of formation of phases in the systems Fe-Cu-S and Co-S: *Phys. Chem. Minerals*, v. 16, p. 172-179.
61. Chang, S. S., and Bestul, A. B., 1971, Heat capacities of cubic, monoclinic, and vitreous arsenious oxide from 5 to 360 K: *Jour. Chem. Physics*, v. 55, p. 933-946.
62. Chang, S.S., and Bestul, A.B., 1974, Heat capacities of selenium crystal (trigonal), glass, and liquid from 5 to 360 K: *Jour. Chem. Thermodynamics*, v. 6, p. 325-344.
63. Chang, Y. A., and Ahmad, N., 1982, *Thermodynamic Data on Metal Carbonates and Related Oxides*, (Metallurgical Society of AIME Publ.), 235 p.
64. Charlu, T. V., Newton, R. C., and Kleppa, O. J., 1975, Enthalpies of formation at 970 K of compounds in the system MgO-Al₂O₃-SiO₂ from high temperature solution calorimetry: *Geochim. Cosmochim. Acta*, v. 39, p. 1487-1497.
65. Charlu, T. V., Newton, R. C., and Kleppa, O. J., 1978, Enthalpy of formation of some lime silicates by high-temperature solution calorimetry, with discussion of high pressure phase equilibria: *Geochim. Cosmochim. Acta*, v. 42, p. 367-375.

66. Charlu, T. V., Newton, R. C., and Kleppa, O. J., 1981, Thermochemistry of synthetic $\text{Ca}_2\text{Al}_2\text{SiO}_7$ (gehlenite) $\text{Ca}_2\text{MgSi}_2\text{O}_7$ (akermanite) melilites: *Geochim. Cosmochim. Acta*, v. 45, p. 1609-1617.
67. Chase, M. W., Jr., Davies, C. A., Downey, J. R., Jr., Frurip, D. J., McDonald, R. A., and Syverud, A. N., 1985, JANAF Thermochemical Tables Third Edition, Part I, Al-Co; Part II, Cr-Zr: *Jour. Phys. Chem. Ref. Data*, v. 14, Supplement no. 1, p. 1-1856.
68. Chatterjee, N. D., Johannes, Wilhelm, and Leistner, Hans, 1984, The system $\text{CaO-Al}_2\text{O}_3\text{-SiO}_2\text{-H}_2\text{O}$: new phase equilibrium data, some calculated phase relations, and their petrological applications: *Contributions to Mineralogy and Petrology*, v. 88, p. 1-13.
69. Chatterton-Colinet, C., Kleppa, O. J., Newton, R. C., and Perkins, D., 1983, Enthalpy of formation of $\text{Fe}_3\text{Al}_2\text{Si}_3\text{O}_{12}$ (almandine) by high temperature alkali borate solution calorimetry: *Geochim. Cosmochim. Acta*, v. 47, p. 439-444.
70. Chernosky, J. V., Jr., and Autio, L. K., 1979, The stability of anthophyllite in the presence of quartz: *Am. Mineralogist*, v. 64, p. 294-303.
71. Chhor, K., Bocquet, J. F., Pommier, C., and Chardon, B., 1986, Heat capacity and thermodynamic behavior of Mn_3O_4 and ZnMn_2O_4 at low temperatures. *Jour. Chem. Thermodynamics*, v. 18, p. 88-99.
72. Chhor, K., Pommier, C., Gariner, P. and Abello, L., 1991, Low temperature behavior of $\alpha\text{-PbO}$ and $\text{Pb}_{1-x}\text{Ti}_{1+x}$ oxides from calorimetric spectroscopic and neutron diffraction studies: *Jour. Phys. Chem. Solids*, v. 52, p. 895-902.

73. Chisholm, R. C., and Stout, J. W., 1962, Heat capacity and entropy of CoCl_2 and MnCl_2 from 11° to 300° K. Thermal anomaly associated with antiferromagnetic ordering in CoCl_2 : Jour. Chem. Physics. v. 36, p. 972-979.
74. Cho, M., Maruyama, S., and Liou, J.G., 1987, An experimental investigation of heulandite-laumontite equilibrium at 1000 to 2000 bar P_{fluid} . Contributions to Mineralogy Petrology, v. 97, p. 43-50.
75. Cohen, E. R., and Taylor, B. N., 1987, The 1986 CODATA recommended values of the fundamental physical constants: U.S. Nat. Bur. Standards, Jour. Research v. 92, p. 85-95.
76. Cook, O. A., 1947, High-temperature heat contents of V_2O_3 , V_2O_4 , and V_2O_5 : Am. Chem. Soc. Jour., v. 69, p. 331-333.
77. Cordfunke, E. H. P., Konings, R. J. M., and Ouweltjes, W., 1990, The standard enthalpies of formation of $\text{MO}(\text{s})$, $\text{MCl}_2(\text{s})$, and $\text{M}_{+2}(\text{aq}, \infty)$ ($\text{M} = \text{Ba}, \text{Sr}$): Jour. Chem. Thermodynamics, v. 22, p. 991-996.
78. Cordfunke, E. H. P., Ouweltjes, W., and Prins, G., 1987, Standard enthalpies of formation of Tellurium compounds. I. Tellurium dioxide: Jour. Chem. Thermodynamics, v. 19, p. 369-375.
79. Coughlin, J. P., 1950, High-temperature heat contents of manganous sulfide, ferrous sulfide, and pyrite: Am. Chem. Soc. Jour., v. 72, p. 5445-5448.
80. Coughlin, J. P., 1951, High-temperature heat contents of nickel chloride: Am. Chem. Soc. Jour., v. 73, p. 5314-5315.
81. Coughlin, J. P., 1955, High-temperature heat contents, heats of transition, and heat of fusion of anhydrous sodium sulfate: Am. Chem. Soc. Jour., v. 77, p. 868-870.

82. Coughlin, J. P., and King, E. G., 1950, High-temperature heat contents of some zirconium-containing substances: *Am. Chem. Soc. Jour.*, v. 72, p. 2262-2265.
83. Coughlin, J. P., King, E. G., and Bonnickson, K. R., 1951, High-temperature heat contents of ferrous oxide, magnetite and ferric oxide: *Am. Chem. Soc. Jour.*, v. 73, p. 3891-3893.
84. Coughlin, J. P., and O'Brien, C. J., 1957, High temperature heat content of calcium orthosilicate: *Jour. Phys. Chemistry.*, v. 61, p. 767-769.
85. Cox, J. D., Wagman, D. D., and Medvedev, V. A., 1989, CODATA key values for thermodynamics: Hemisphere, New York, 271 p.
86. Dayal, R. R., Johnson, R. E., and Muan, A., 1967, Stability of mullite derived from equilibria in the system $\text{CaO-Al}_2\text{O}_3\text{-SiO}_2$: *Am. Chem. Soc. Jour.*, v. 50, p. 537-540.
87. DeKock, C. W., 1982, Thermodynamic properties of selected transition metal sulfates and their hydrates: U. S. Bur. Mines Information Circular 8910, 45 p.
88. DeKock, C. W., 1986, Thermodynamic properties of selected metal sulfates and their hydrates: U. S. Bur. Mines Information Circular 9081, 59 p.
89. Dellien, I., McCurdy, K. G., and Hepler, L. G., 1976, Enthalpies of formation of lead chromate, lead molybdate, and lead tungstate, and the entropy of aqueous tungstate ion: *Jour. Chem. Thermodynamics*, v. 8, p. 203-207.
90. Desai, P. D., 1986, Thermodynamic properties of iron and silicon: *Jour. Phys. Chem. Ref. Data*, v. 15, p. 967-983.

91. Desai, P. D., 1987, Thermodynamic properties of manganese and molybdenum: Jour. Phys. Chem. Reference Data, v. 16, p. 91-108.
92. Desai, P. D., 1987, Thermodynamic properties of aluminum: Int. Jour. Thermophysics, v. 8, p. 621-638.
93. Ditmars, P. D., and Douglas, T. B., 1971, Measurement of the relative enthalpy of pure α -Al₂O₃ (NBS heat capacity and enthalpy standard reference material no. 720) from 273 to 1173 K: U. S. Natl. Bur. Standards Jour. Research, v. 75A, p. 401-420.
94. Ditmars, D. A., Isihara, S., Chang, S. S., Bernstein, G., and West, E. D., 1982, Enthalpy and heat-capacity standard reference material: synthetic sapphire (γ -Al₂O₃) from 10 to 2250 K: U.S. Natl. Bur. Standards Jour. Research, v. 87, p. 159-163.
95. Donahoe, R. J., Hemingway, B. S., and Liou, J. G., 1990, Thermochemical data for merlinoite: 1. Low-temperature heat capacities, entropies, and enthalpies of formation at 298.15 K of six synthetic samples having various Si/Al and Na/(Na + K) ratios: Am. Mineralogist, v. 75, 188-200
96. Donahoe, R. J., Liou, J. G., and Hemingway, B. S., 1990, Thermochemical data for merlinoite: 2. Free energies of formation at 298.15 K of six synthetic samples having various Si/Al and Na/(Na + K) ratios and application to saline, alkaline lakes: Am. Mineralogist, v. 75, 201-208
97. Dzhavbarov, A.I., 1985, Heat capacity of the anisotropic antiferromagnetic semiconductor iron antimony sulfide (FeSb₂S₄) at low temperature: Zhur. Fiz. Khim., v. 59, p. 202-204.
98. Egami, Akira, Nagakawa, T., Oishi, T., Ono, K., and Moriyama, J., 1986, A thermodynamic study of the systems Ni-S and Co-S by CaF₂ solid electrolyte galvanic cell technique: Trans. Japan Institute of Metals, v. 27, p. 890-897.

99. Egan, E. P., Jr., Wakefield, Z. T., and Elmore, K. L., 1950, High-temperature heat content of hydroxyapatite: *Am. Chem. Soc. Jour.*, v. 72, p. 2418-2421.
100. Egan, E. P., Jr., Wakefield, Z. T., and Luff, B. B., 1961, Low temperature heat capacity, entropy and heat of formation of crystalline and colloidal ferric phosphate dihydrate: *Jour. Phys. Chemistry*, v. 65, p. 1265-1270.
101. Ellison, A.J.G., and Navrotsky, A. 1992, Enthalpy of formation of zircon. *Jour. Am. Ceramic Soc.*, v. 75, p. 1430-1433.
102. Eriksson, G. and Pelton, A. D., 1993, Critical evaluation and optimization of the thermodynamic properties and phase diagrams of the MnO-TiO₂, MgO-TiO₂, FeO-TiO₂, Ti₂O₃-TiO₂, Na₂O-TiO₂, and K₂O-TiO₂ systems: *Metallurgical Transactions*, v. 24B, p. 795-805.
103. Evans, L. G. and Muan, A., 1971, Activity-composition relations of solid solutions and stabilities of manganese and nickel titanates at 1250° C as derived from equilibria in the systems MnO-CoO-TiO₂ and MnO-NiO-TiO₂: *Thermochimica Acta*, v. 2, p. 277-292.
104. Fei, Y., and Saxena, S. K., 1987, An equation for the heat capacity of solids: *Geochim. Cosmochim. Acta*, v. 51, p. 251-254.
105. Fei, Y., Saxena, S.K. and Navrotsky, A., 1990, Internally consistent thermodynamic data and equilibrium phase relations in the system MgO-SiO₂ at high pressure and high temperature: *Jour. Geophys. Research*, v. 95B, p. 6915-6928.
106. Ferrante, M. J., 1972, Enthalpies above 298.15 K for copper sulfate and copper oxysulfate: *U. S. Bur. Mines Rept. Inv. 7600*, 8 p.

107. Ferrante, M. J., and Gokcen, N. A., 1982, Relative enthalpies of Ni_3S_2 : U. S. Bur. Mines Rept. Inv., no. 8745, 8 p.
108. Ferrante, M.J., Mrazek, R.V., and Brown, R.R., 1987, High-temperature relative enthalpies and related thermodynamic properties of CuI : U.S. Bur. Mines Rept. Inv. 9074, 10 p.
109. Ferrante, M. J., Stuve, J. M., Daut, G. E., and Pankratz, L. B., 1978, Low-temperature heat capacities and high-temperature enthalpies of cuprous and cupric sulfides: U.S. Bur. of Mines Rept. Inv. 8305, p. 1-22. See also High Temp Science, v. 14, p. 77-90.
110. Ferrante, M. J., Stuve, J. M., and Richardson, D.W., 1976, Thermodynamic data for synthetic dawsonite: U.S. Bur. Mines Rept. Inv. 8129, 13 p.
111. Fitzgibbon, G. C., Huber, E. J., Jr., and Holley, C. E., Jr., 1973, Enthalpy of formation of barium monoxide: Jour. Chem. Thermodynamics, v. 5, p. 577-582.
112. Flotow, H. E., and Osborne, D. W., 1974, The heat capacity of dicesium monoxide (Cs_2O) from 5 to 350 K and the Gibbs energy of formation to 763 K: Jour. Chem. Thermodynamics, v. 6, p. 135-140.
113. Fredrickson, D. R., and Chasanov, M. G., 1970, Enthalpy of uranium dioxide and sapphire to 1500 K by drop calorimetry: Jour. Chem. Thermodynamics, v. 2, p. 623-630.
114. Fredrickson, D. R., and Chasanov, M. G., 1971, The enthalpy of molybdenum disulfide to 1200° K by drop calorimetry: Jour. Chem. Thermodynamics, v. 3, p. 693-696.
115. Fredrickson, D. R., and Chasanov, M. G., 1973, The enthalpy of sodium oxide Na_2O to 1300 K by drop calorimetry: Jour. Chem. Thermodynamics, v. 5, p. 485-490.

116. Furukawa, G. T., and Saba, W. G., 1965, Heat capacity and thermodynamic properties of beryllium aluminate (chrysoberyl), $\text{BeO} \cdot \text{Al}_2\text{O}_3$, from 16 to 380°K: U. S. Natl. Bur. Standards Jour. Research., v. 65, p. 13-18.
117. Garvin, D., Parker, V. B., and White, H. J., 1987, CODATA thermodynamic tables. Selections for some compounds of calcium and related mixtures: A prototype set of tables. Hemisphere, New York, 356 p.
118. Gillet, P., Reynard, B., and Tequi, C., 1989, Thermodynamic properties of glaucophane: new data from calorimetric and spectroscopic measurements: Phys. Chem. Minerals, v. 16, p. 659-667.
119. Gillet, P., Richet, P., Guyot, F. and Fiquet, G., 1991, High temperature thermodynamic properties of forsterite: Jour. Geophys. Research, v. 96, p. 11805-11816.
120. Goates, J. R., Cole, A. G., and Gray, E. L., 1951, Free energy of formation and solubility product constant of mercuric sulfide: Amer. Chem. Soc. Jour., v. 73, p. 3596-3597.
121. Goates, J. R., Cole, A. G., Gray, E. L., and Faux, N. D., 1951, Thermodynamic properties of silver sulfide: Am. Chem. Soc. Jour., v. 73, p. 707-708.
122. Goldman, D. T., and Bell, R. J., 1986, The international system of units (SI): U.S. Natl. Bur. Standards Special Publication 330, 51 p.
123. Goldsmith, J. R., and Jenkins, D. M., 1985, The high-low albite relations revealed by reversal of degree of order at high pressures: Am. Mineralogist, v. 70, p. 911-923.
124. Good, W. D., Lacina, J. L., and McCullough, J. P., 1960, Sulfuric acid: heat of formation of aqueous solutions by rotating bomb calorimetry: Am. Chem. Soc. Jour., v. 82, p. 5589-5591.

125. Grimsey, E.J. and Reynolds, K.A., 1986, Equilibrium oxygen pressure of $(\text{Co}_3\text{O}_4 + \text{CoO})$ from 1173 to 1228K. *Jour. Chem Thermodynamics*, v. 18, p. 473-476.
126. Gronvold, F., 1973, Heat capacities and thermodynamic properties of hexagonal and liquid selenium in the range 298 to 1000 K. Enthalpy and temperature of fusion: *Jour. Chem. Thermodynamics*, v. 5, p. 525-531.
127. Gronvold, F., 1975, Heat capacity and thermodynamic properties of bismuth in the range 300 to 950 K. Fusion characteristics: *Acta Chem. Scandinavica*, v. 29A, p. 945-955.
128. Gronvold, F., Kveseth, N. J., Sveen, A., and Tichy, J., 1970, Thermodynamics of the UO_{2+x} phase 1. Heat capacities of $\text{UO}_{2.017}$ and $\text{UO}_{2.254}$ from 300 to 1000 K and electronic contributions: *Jour. Chem. Thermodynamics*, v. 2, p. 665-680.
129. Gronvold, F., and Meisingset, K. K., 1983, Thermodynamic properties and phase transitions of salt hydrates between 270 and 400 K. II. $\text{Na}_2\text{CO}_3 \cdot \text{H}_2\text{O}$ and $\text{Na}_2\text{CO}_3 \cdot 10\text{H}_2\text{O}$: *Jour. Chem. Thermodynamics*, v. 15, p. 881-889.
130. Gronvold, F. and Samuelsen, E.J., 1975, Heat capacity and thermodynamic properties of $\alpha\text{-Fe}_2\text{O}_3$ in the region 300-1050 K. Antiferromagnetic transition: *Jour. Phys. Chem. Solids*, v. 36, p. 249-256.
131. Gronvold, F., and Stolen, S., 1992, Thermodynamics of iron sulfides II. Heat capacity and thermodynamic properties of FeS and of $\text{Fe}_{0.875}\text{S}$ at temperatures from 298.15 K to 1000K, of $\text{Fe}_{0.98}\text{S}$ from 298.15 K to 800 K and of $\text{Fe}_{0.89}\text{S}$ from 298.15 K to about 650 K. Thermodynamics of formation: *Jour. Chem. Thermodynamics*, v. 24, p. 913-916.

132. Grønvold, F., Stølen, S., Tolmach, P. and Westrum, E. F., Jr., 1993, Heat capacities of the wüstites $\text{Fe}_{0.9379}\text{O}$ and $\text{Fe}_{0.9254}\text{O}$ at temperatures T from 5 K to 350 K. Thermodynamics of the reaction $x\text{Fe}(s) + (1/4)\text{Fe}_3\text{O}_4(s) = \text{Fe}_{(0.7500+x)}\text{O}(s) = \text{Fe}_{1-y}\text{O}(s)$ at ≈ 850 K, and properties of $\text{Fe}_{1-y}\text{O}(s)$ to $T = 1000$ K. Thermodynamics of formation of wüstite: Jour. Chem. Thermodynamics, v. 25, p. 1089-1117.
133. Gronvold, F. Stølen, S., Westrum, E. F., Jr., and Galeas, C. G., 1987, Thermodynamics of copper sulfides III. Heat capacities and thermodynamic properties of $\text{Cu}_{1.75}\text{S}$, $\text{Cu}_{1.80}\text{S}$ and $\text{Cu}_{1.85}\text{S}$ from 5 to about 700 K: Jour. Chem. Thermodynamics, v. 19, p. 1305-1324.
134. Gronvold, F., and Sveen, A., 1974, Heat capacity and thermodynamic properties of synthetic magnetite (Fe_3O_4) from 300 to 1050 K. Ferrimagnetic transition and zero-point entropy: Jour. Chem. Thermodynamics, v. 6, p. 859-872.
135. Gronvold, F., Svein, S., Labban, A. K., and Westrum, E. F., Jr., 1991, Thermodynamics of iron sulfides I. Heat capacity and thermodynamic properties of Fe_9S_{10} at temperatures from 5 K to 740 K: Jour. Chem. Thermodynamics, v. 23, p. 261-272.
136. Gronvold, F., Thurmann-Moe, T., and Westrum, E. F., Jr., and Chang, E., 1961, Low-temperature heat capacities and thermodynamic functions of some platinum group chalcogenides. I. Monochalcogenides: PtS, PtTe and PdTe: Jour. Chem. Physics, 35, p. 1665-1669.
137. Gronvold, F. and Westrum, E.F., Jr., 1959, α -ferric oxide: low temperature heat capacity and thermodynamic functions. Am. Chem. Soc. Jour., v. 81, p. 1780-1783.
138. Gronvold, F., and Westrum, E. F., Jr., 1962, Heat capacities and thermodynamic functions of iron disulfide (pyrite), iron-diselenide, and nickel diselenide from 5 to 350°K. The estimation of standard entropies of transition metal chalcogenides: Inorganic Chemistry, v. 1, p. 36-48.

139. Gronvold, F., and Westrum, E. F., Jr., 1976, Heat capacities of iron disulfides. Thermodynamics of marcasite from 5 to 700 K, pyrite from 350 to 770 K, and the transformation of marcasite to pyrite: *Jour. Chem. Thermodynamics*, v. 8, 1039-1048.
140. Gronvold, F., and Westrum, E. F., Jr., 1980, The anilite/ low-digenite transition: *Am. Mineralogist*, v. 65, p. 574-575.
141. Gronvold, F., and Westrum, E. F., Jr., 1986, Silver(I) sulfide: Ag_2S . Heat capacity from 5 to 1000 K, thermodynamic properties, and transitions: *Jour. Chem. Thermodynamics*, v. 18, p. 381-401.
142. Gronvold, F., and Westrum, E. F., 1987, Thermodynamics of copper sulfides. I. Heat capacity and thermodynamic properties of copper (I) sulfide, Cu_2S , from 5 to 950 K: *Jour. Chem. Thermodynamics*, v. 19, p. 1183-1198.
143. Gronvold, F., Westrum, E. F., Jr., and Chou, C., 1959, Heat capacities and thermodynamic properties of the pyrrhotites FeS and $\text{Fe}_{0.877}\text{S}$ from 5 to 350°K: *Jour. Chem. Physics*, v. 30, p. 528-531.
144. Gupta, A., and Chatterjee, N. D., 1978, Synthesis, composition, thermal stability and thermodynamic properties of bicchulite, $\text{Ca}_2[\text{Al}_2\text{SiO}_6](\text{OH})_2$: *Am. Mineralogist*, v. 63, p. 58-65.
145. Gurevich, V.M., Gorbunov, V.E., Gavrichev, K.S., and Khodakovskii, I.L., 1988, The low-temperature heat capacity of livingstonite (HgSb_4S_8): *Russ. Jour. Phys. Chemistry*, v. 62, p. 699-700.
146. Gurevich, V. M., Gorbunov, V. E., Gavrichev, K. S., and Khodakovsky, I. L., 1989, Low-temperature heat capacity of proustite Ag_3AsS_3 and smithite AgAsS_2 : *Geokhimiia*, p. 132-139.

147. Gurevich, V. M., Semenov, Yu. V., Sidorov, Yu. I., Gorbunov, V. E., Gavrichev, K. S., Zhananov, V. M., Turdakin, V. A., and Khodakovskiy, I. L., 1990, Low-temperature specific heat of epidote $\text{Ca}_2\text{FeAl}_2\text{Si}_3\text{O}_{12}(\text{OH})$. *Geochemistry International* 27(8), p.111-114.
148. Haas, J. L., Jr., and Hemingway, B. S., 1992, Recommended standard electrochemical potentials and fugacities of oxygen for the solid buffers and thermodynamic data in the systems iron-silicon-oxygen, nickel-oxygen, and copper-oxygen / by John L. Hass, Jr with comments and additions by Bruce S. Hemingway: U.S. Geological Survey Open-file Report 92-267.
149. Haas, J. L., Jr., Robinson, G. R., Jr., and Hemingway, B. S., 1981, Thermodynamic tabulations for selected phases in the system $\text{CaO-Al}_2\text{O}_3\text{-SiO}_2\text{-H}_2\text{O}$ at 101.325 kPa (1 atm) between 273.15 K and 1800 K: *Jour. Phys. Chem. Ref. Data*, v. 10, p. 575-669.
150. Halbach, H., and Chatterjee, N. D., 1984, An internally consistent set of thermodynamic data for twenty-one $\text{CaO-Al}_2\text{O}_3\text{-SiO}_2\text{-H}_2\text{O}$ phases by linear parametric programming: *Contributions to Mineralogy and Petrology*, v. 88, p. 14-23.
151. Harlov, D.E., and Newton, R.C., 1992, Experimental determination of the reaction 2 magnetite + 2 kyanite + 4 quartz = 2 almandine + O_2 at high pressure on the magnetite-hematite buffer: *Am. Mineralogist*, v. 77, p. 558-564.
152. Haselton, H. T., Jr., Cygan, G. L., and Jenkins, D. M., 1994, Experimental study of muscovite stability in pure H_2O and 1 molal KCl-HCl solutions: (unpublished report).
153. Haselton, H. T., and Goldsmith, J. R., 1987, The decarbonation and heat capacity of ZnCO_3 : *Geochim. Cosmochim. Acta*, v. 51, p. 261-265.

154. Haselton, H. T., Jr., Hemingway, B. S., and Robie, R. A., 1984, Low-temperature heat capacities of $\text{CaAl}_2\text{SiO}_6$ glass and pyroxene and thermal expansion of $\text{CaAl}_2\text{SiO}_6$ pyroxene: *Am. Mineralogist*, v. 69, p. 481-489.
155. Haselton, H. T., Jr., Hovis, G. L., Hemingway, B. S., and Robie, R. A., 1983, Calorimetric investigation of the excess entropy of mixing in analbite-sanidine solid solutions: Lack of evidence for Na, K short-range order and implications for two-feldspar thermometry: *Am. Mineralogist*, v. 68, p. 398-413.
156. Haselton, H. R., Jr., Robie, R. A., and Hemingway, B. S., 1987, Heat capacities of synthetic hedenbergite, ferrobustamite, and $\text{CaFeSi}_2\text{O}_6$ glasses: *Geochim. Cosmochim. Acta*, v. 51, p. 2211-2217.
157. Haselton, H. T., Jr., and Westrum, E. F., Jr., 1980, Low-temperature heat capacities of synthetic pyrope, grossular, and pyrope₈₀ grossular₄₀: *Geochim. Cosmochim. Acta*, v. 44, p. 701-709.
158. Hatton, W. E., Hildenbrand, D. L., Sinke, G. C., and Stull, D. R., 1959, The chemical thermodynamic properties of calcium hydroxide: *Am. Chem. Soc. Jour.*, v. 81, p. 5028-5030.
159. Helgeson, H. C., Delany, J. M., Nesbitt, H. W., and Bird, D. K., 1978, Summary and critique of the thermodynamic properties of rock-forming minerals: *Am. Jour. Science*, v.278-A, 220 p.
160. Hemingway, B. S., 1987, Quartz: Heat capacities from 340 to 1000 K and revised values for the thermodynamic properties: *Am. Mineralogist*, v. 72, p. 273-279.
161. Hemingway, B. S., 1990, Thermodynamic properties for bunsenite, NiO, magnetite, Fe_3O_4 , and hematite, Fe_2O_3 with comments on selected oxygen buffers: *Am. Mineralogist*, v. 75, p. 781-790.

162. Hemingway, B. S., 1991, Thermodynamic properties for anthophyllite and talc: Corrections and discussion of calorimetric data: *Am. Mineralogist*, v. 76, p. 1589-1596.
163. Hemingway, B. S., Anovitz, L. M., and Robie, R. A., 1990, Thermodynamic properties of dumortierite $(\text{Si}_3\text{B}(\text{Al}_{6.75}\text{[]}_{0.25}\text{O}_{17.25}(\text{OH})_{0.75})$: *Am. Mineralogist*, v. 75, 1370-1375.
164. Hemingway, B. S., Barton, M. D., Robie, R. A., and Haselton, H. T., Jr., 1986, Heat capacities and thermodynamic functions for beryl, $\text{Be}_3\text{Al}_2\text{Si}_6\text{O}_{18}$, phenakite, Be_2SiO_4 , euclase, $\text{BeAlSiO}_4(\text{OH})$, bertrandite, $\text{Be}_4\text{Si}_2\text{O}_7(\text{OH})_2$, and chrysoberyl, BeAl_2O_4 : *Am. Mineralogist*, v. 71, p. 557-568.
165. Hemingway, B. S., Evans, H. T., Jr., Nord, G. L., Haselton, H. T., Jr., Robie, R. A., and McGee, J. J., 1987, Akermanite: phase transitions in heat capacity and thermal expansion, and revised thermodynamic data: *Canadian Mineralogist*, v. 24, p. 425-434.
166. Hemingway, B. S. and Haselton, H. T., Jr., 1994, A reevaluation of the calorimetric data for the enthalpy of formation of some K- and Na-bearing silicate minerals: U. S. Geological Survey Open-file Report 94-576, 33 p.
167. Hemingway, B. S., Krupka, K. M., and Robie, R. A., 1981, Heat capacities of the alkali feldspars between 350 and 1000 K by differential scanning calorimetry. The thermodynamic functions of the alkali feldspars from 298.15 to 1400 K, and the reaction quartz + jadeite = analbite: *Am. Mineralogist*, v. 66, p. 1202-1215.70 p.
168. Hemingway, B. S., and Robie, R. A., 1972, The heat capacities at low temperatures and entropies at 298.15 K of huntite, $\text{CaMg}_3(\text{CO}_3)_4$, and artinite, $\text{Mg}_2(\text{OH})_2\text{CO}_3 \cdot 3\text{H}_2\text{O}$: *Am. Mineralogist*, v. 57, p. 1754-1767.

169. Hemingway, B. S., and Robie, R. A., 1973, A calorimetric determination of the standard enthalpies of formation of huntite, $\text{CaMg}_3(\text{CO}_3)_4$, and artinite, $\text{Mg}_2(\text{OH})_2\text{CO}_3 \cdot 3\text{H}_2\text{O}$ and their standard Gibbs free energies of formation: U.S. Geol. Survey Jour. Research, v. 1, p. 535-541.
170. Hemingway, B. S., and Robie, R. A., 1977, The entropy and Gibbs free energy of formation of the aluminum ion: Geochim. Cosmochim. Acta, v. 41, p. 1402-1404.
171. Hemingway, B. S., and Robie, R. A., 1977, Enthalpies of formation of low albite ($\text{NaAlSi}_3\text{O}_8$), gibbsite ($\text{Al}(\text{OH})_3$), and NaAlO_2 ; revised values for $\Delta H_{f,298}^\circ$ and $\Delta G_{f,298}$ of alumino-silicates: U.S. Geol. Survey Jour. Research, v. 5, p. 413-429.
172. Hemingway, B. S., and Robie, R. A., 1984, Heat capacity and thermodynamic functions for gehlenite and staurolite: Comments on the Schottky anomaly in staurolite: Am. Mineralogist, v. 69, p. 307-318.
173. Hemingway, B. S., and Robie, R. A., 1984, Thermodynamic properties of zeolites: low temperature heat capacities and thermodynamic functions for phillipsite and clinoptilolite. Estimates of the thermochemical properties of zeolitic water at low temperatures: Am. Mineralogist, v. 69, p. 692-700.
174. Hemingway, B. S., and Robie, R. A., 1990, Heat capacities and thermodynamic properties of annite (aluminous iron biotite): Am. Mineralogist, v. 75, p. 183-187
175. Hemingway, B. S. and Robie, R. A., 1994, Enthalpy and Gibbs energy of formation of dolomite, $\text{CaMg}(\text{CO}_3)_2$, at 298.15 K from HCl solution calorimetry: U. S. Geological Survey Open-File Report 94-575, 12 p.

176. Hemingway, B. S., Robie, R. A., and Apps, J. A., 1991, Revised values for the thermodynamic properties of boehmite, $\text{AlO}(\text{OH})$, and comments on the relative stabilities of the aluminum hydroxide and oxyhydroxide phases: *Am. Mineralogist*, v. 76, p. 445-457.
177. Hemingway, B. S., Robie, R. A., Evans, H. T., Jr., and Kerrick, D. M., 1991, Heat capacities and entropies of sillimanite, fibrolite, andalusite, kyanite, and quartz and the Al_2SiO_5 phase diagram. *Am. Mineralogist*, v. 76, p. 1597-1613.
178. Hemingway, B. S., Robie, R. A., Fisher, J. R., and Wilson, W. H., 1977, The heat capacities of gibbsite, $\text{Al}(\text{OH})_3$, between 13 and 480 K and magnesite, MgCO_3 , between 13 and 380 K and their standard entropies at 298.15 K, and the heat capacities of Calorimetry Conference benzoic acid between 12 and 316 K: *U.S. Geol. Survey Jour. Research*, v. 5, p. 797-806.
179. Hemingway, B. S., Robie, R. A., and Kittrick, J. A., 1978, Revised values for the Gibbs free energy of formation of $[\text{Al}(\text{OH})_4]^-$, diaspore, boehmite and bayerite at 298.15 K and 1 bar, the thermodynamic properties of kaolinite to 800 K, and the heats of solution of several gibbsite samples: *Geochim. Cosmochim. Acta*, v. 42, p. 1533-1543.
180. Hemingway, B. S., Robie, R. A., Kittrick, J. A., Grew, E. S., Nelen, J. A., and London, D., 1984, The heat capacities of osumilite from 298.15 to 1000 K, the thermodynamics properties of two natural chlorites to 500 K, and the thermodynamic properties of petalite to 1800 K: *Am. Mineralogist*, v. 69, p. 701-710.
181. Hemingway, B. S., Robie, R. A., and Krupka, K. M., 1992, Thermodynamic properties for berlinite, AlPO_4 : *U.S. Geol. Survey Open-File Rept. 92-510*, 8 p.

182. Henderson, C. E., Essene, E. J., Anovitz, L. M., Westrum, E. F., Jr., Hemingway, B. S., and Bowman, J. R., 1983, Thermodynamics and phase equilibria of clinocllore $(Mg_5Al)(Si_3Al)O_{10}(OH)_8$: EOS, v. 64, p. 466. Final term for C_p equation is missing, the value is $+ 1.4955 \times 10^5 T^{-2}$.
183. Henderson, C.M.B., and Thompson, A.B., 1980, The low-temperature inversion in sub-potassic nephelines: *Am. Mineralogist*, v. 65, p. 970-980.
184. Holland, T.J.B., 1980, The reaction albite = jadeite + quartz determined experimentally in the range 600 - 1200°C: *Am. Mineral.*, v. 65, p. 129-134.
185. Holland, T. J. B., 1988, Preliminary phase relations involving glaucophane and applications to high pressure petrology: new heat capacity and thermodynamic data: *Contributions to Mineralogy and Petrology*, v. 99, p. 134-142.
186. Holland, T. J. B., 1989, Dependence of entropy on volume for silicate and oxide minerals: A review and a predictive model: *Am. Mineralogist*, v. 74, p. 5-13.
187. Holland, T. J. B., and Powell, R., 1985, An internally consistent thermodynamic dataset with uncertainties and correlations: 2. Data and results: *Jour. Metamorphic Geology*, v. 3, p. 343-370.
188. Holland, T. J. B. and Powell, R., 1990, An enlarged and updated internally consistent thermodynamic dataset with uncertainties and correlation: the system $K_2O-Na_2O-CaO-MgO-MnO-FeO-Fe_2O_3-Al_2O_3-TiO_2-SiO_2-C-H_2O_2$: *Jour. Metamorphic Geology*, v. 8, p. 89-124.
189. Holm, J. L., Kleppa, O. J., and Westrum, E. F., Jr., 1967, Thermodynamics of polymorphic transformations in silica. Thermal properties from 5 to 1070°K and P-T stability fields for coesite and stishovite: *Geochim. Cosmochim. Acta*, v. 31, p. 2289-2307.

190. Holmes, R. D., Kersting, A. B., and Arculus, R. J., 1989, Standard molar Gibbs free energy of formation for Cu_2O : high-resolution electrochemical measurements from 900 to 1300 K: *Jour. Chem. Thermodynamics*, v. 21, p. 351-361.
191. Holmes, R.D., O'Neill, H.St.C., and Arculus, R.J., 1986, Standard Gibbs free energy of formation for Cu_2O , NiO, CoO, and Fe_xO : High resolution electrochemical measurements using zirconia solid electrolytes from 900-1400 K: *Geochim. Cosmochim. Acta*, v. 50, p. 2439-2452.
192. Hosmer, P. K., and Krikorian, O. H., 1980, The high-temperature enthalpies of zinc sulfate and zinc oxysulfate: *High Temperatures-High Pressures*, v. 12, p. 281-290.
193. Hostetler, P. B., 1963, The stability and surface energy of brucite in water at 25°C: *Am. Jour. Sci.*, v. 21, p. 238-258.
194. Hovis, G. L., 1988, Enthalpies and volumes related to K-Na mixing and Al-Si disorder in alkali feldspars: *Jour. Petrology*, v. 29, p. 731-763
195. Howell, D. A., Johnson, G. K., Tasker, I. R., O'Hare, P. A. G., and Wise, W. S., 1990, Thermodynamic properties of the zeolite stilbite: *Zeolites*, v. 10, p. 525-531.
196. Huber, E. J., Jr., Head, E. L., and Holley, C. E., Jr., 1964, The heats of formation of zirconium diboride and dioxide: *Jour. Phys. Chemistry*, v. 689, p. 3040-3042.
197. Hull, H., and Turnbull, A. G., 1973, A thermochemical study of monohydrocalcite: *Geochim. Cosmochim. Acta*, v. 37, p. 685-694.

198. Humphrey, G. L., King, E. G., and Kelley, K. K., 1952, Some thermodynamic values for ferrous oxide: U. S. Bur. Mines Rept. Inv. 4870, 16 p.
199. Huntzicker, J. J., and Westrum, E. F., Jr., 1971, The magnetic transition, heat capacity, and thermodynamic properties of uranium dioxide from 5 to 350 K: *Jour. Chem. Thermodynamics*, v. 3, p. 61-76.
200. Inaba, H., Miyahara, K., and Naito, K., 1984, Measurements of the molar heat capacities of MoO_2 and MoO_3 from 350 to 950K. *Jour. Chem. Thermodynamics*, v. 16, p. 643-651.
201. Itskevich, Ye. S., 1961, Thermodynamic investigations at low temperatures. XII. Specific heat of bismuth telluride between 1.4 and 65° K. Enthalpy and entropy of Bi_2Te_3 at 298.15 K: *Zhur. Fizicheskoi Khimii*, v. 35, no. 8, p. 1813-1815.
202. Jacobs, G. K., Kerrick, D. M., and Krupka, K. M., 1981, The high-temperature heat capacity of natural calcite (CaCO_3): *Phys. Chem. Minerals*, v. 7, p. 55-59.
203. Jeffes, J. H. E., Richardson, F. S., and Pearson, J., 1954, The heats of formation of manganous orthosilicate and manganous sulfide: *Faraday Society Transactions*, v. 50, p. 364-370.
204. Jenkins, D. M., and Chernosky, J. V., 1986, Phase equilibrium and crystallochemical properties of Mg-chlorite: *Am. Mineralogist*, v. 71, p. 924-936.
205. Jenkins, D.M., Holland, T.J.B., and Clarke, A., 1991, Experimental determination of the pressure stability and thermochemical properties of synthetic tremolite: *Am. Mineralogist*, v. 76, p. 458-469.

206. Johnson, G. K., Flotow, H. E., O'Hare, P. A. G., and Wise, W. S., 1982, Thermodynamic studies of zeolites: analcime and dehydrated analcime: *Am. Mineralogist*, v. 67, p. 736-748.
207. Johnson, G. K., Flotow, H. E., O'Hare, P. A. G., and Wise, W. S., 1983, Thermodynamic studies of zeolites: natrolite, mesolite, and scolecite: *Am. Mineralogist*, v. 68, p. 1134-1145.
208. Johnson, G. K., Flotow, H. E., O'Hare, P. A. G., and Wise, W. S., 1985, Thermodynamic studies of zeolites: Heulandite: *Am. Mineralogist*, v. 70, p. 1065-1071.
209. Johnson, G.K., Grow, R.T. and Hubbard, W.N., 1975, The enthalpy of formation of lithium oxide (Li_2O): *Jour. Chem. Thermodynamics*, v. 7, p. 781-786.
210. Johnson, G. K., Papatheodorou, G. N., and Johnson, C. E., 1980, The enthalpies of formation and high-temperature thermodynamic functions of As_4S_4 and As_2S_3 : *Jour. Chem. Thermodynamics*, v. 12, no. 6, p. 545-558.
211. Johnson, G. K., Papatheodorou, G. N., and Johnson, C. E., 1981, The enthalpies of formation of $\text{SbF}_5(\text{l})$ and $\text{Sb}_2\text{S}_3(\text{c})$ and the high-temperature thermodynamic functions of $\text{Sb}_2\text{S}_3(\text{c})$ and $\text{Sb}_2\text{S}_3(\text{l})$: *Jour. Chem. Thermodynamics*, v. 13, p. 745-754.
212. Johnson, G. K., Tasker, I. R., Flotow, H. E., and Wise, W. S., 1992, Thermodynamic studies of mordenite, dehydrated mordenite, and gibbsite: *Am. Mineralogist*, v. 77, p. 85-93. Note that quartz was taken as the reference phase for silica instead of silicalite.
213. Johnson, G. K., Tasker, I. R., Howell, D. A., and Smith, J. V., 1987, Thermodynamic properties of silicalite: *Jour. Chemical Thermodynamics*, v. 19, p. 617-632.

214. Johnson, G.K., Tasker, I.R., Jurgens, R., and O'Hare, P.A.G., 1991, Thermodynamic studies of zeolites, Clinoptilolite. *Jour. Chem. Thermodynamics*, v. 23, p. 475-484.
215. Kale, G. M. and Jacob, K. T., 1989, Gibbs energy of formation of Co_2SiO_4 and phase relations in the system Co-Si-O: *Trans. Instn. Min. Metallurgy. Sect. C: Mineral. Process. Extr. Metall.*, v. 98, p. C117-122.
216. Kale, G.M. and Jacob, K.T., 1992, Chemical potential of oxygen for iron-rutile-ilmenite and iron-ilmenite-ulvospinel equilibria: *Metal. Transactions*, v. 23B, p. 57-64.
217. Kelley, K. K., 1960, Contributions to the data on theoretical metallurgy. XIII. High-temperature heat-capacity, and entropy data for the elements and inorganic compounds: *U. S. Bureau of Mines Bulletin 584*, 232 p.
218. Kelley, K. K., Barany, R., King, E. G., and Christensen, A. U., 1959, Some thermodynamic properties of fluorphlogopite mica: *U.S. Bur. Mines Rept. Inv. 5436*, 16 p.
219. Kelley, K. K., Shomate, C. H., Young, F. E., Naylor, B. F., Salo, A. E., and Huffman, E. H., 1946, Thermodynamic properties of ammonium and potassium alums and related substances, with reference to extraction of alumina from clay and alunite: *U. S. Bur. Mines Tech. Paper 688*, 104 p.
220. Kelley, K. K., Todd, S. S., Or, R. L., King, E. G., and Bonnickson, K. R., 1953, Thermodynamic properties of sodium-aluminum and potassium-aluminum silicates: *U.S. Bur. Mines Rept. Inv. 4955*, 21 p.
221. Khodakovsky, I. L. written communication in 1993.

222. Khriplovich, L. M., Oppermann, H., and Paukov, I. E., 1979, The heat capacity of cobalt oxide (Co_3O_4) in the range 5.1 - 307.34 K: *Zuhr. Fiz Khimii*, v. 53, p. 1608-1610.
223. King, E. G., 1951, Heats of formation of crystalline calcium orthosilicate, tricalcium silicate and zinc orthosilicate: *Am. Chem. Soc. Jour.*, v. 73, p. 656-658.
224. King, E. G., 1952, Heats of formation of manganous metasilicate (rhodonite) and ferrous orthosilicate (fayalite): *Am. Chem. Soc. Jour.*, v. 74, p. 4446-4448.
225. King, E.G., 1957, Low-temperature heat capacities and entropies at 298.15° K. of some crystalline silicates containing calcium. *Am. Chem. Soc. Jour.*, v. 79, p. 5437-5438.
226. King, E. G., Barany, R., Weller, W. W., and Pankratz, L. B., 1967, Thermodynamic properties of forsterite and serpentine: *U.S. Bur. Mines Rept. Inv. 6962*, 19 p.
227. King, E. G., and Christensen, A. U., 1961, High-temperature heat contents and entropies of cerium dioxide and columbium dioxide: *U. S. Bur. Mines Rept. Inv. 5789*, 6 p.
228. King, E. G., Ferrante, M. J., and Pankratz, L. B., 1975, Thermodynamic data for $\text{Mg}(\text{OH})_2$ (brucite): *U. S. Bur. Mines Rept. Inv. 8041*, 13 p.
229. King, E.G., and Todd, S.S., 1953, Heat capacities at low-temperature and entropies at 298.16° K of stannic and stannus sulfides: *Am. Chem. Soc. Jour.*, v. 75, p. 3023-3029.
230. King, E. G., and Weller, W. W., 1961, Low-temperature heat capacities and entropies at 298.15°K of diaspore, kaolinite, dickite and halloysite: *U.S. Bur. Mines Rept. Inv. 5810*, 6 p.

231. King, E. G., and Weller, W. W., 1961, Low temperature heat capacities and entropies at 298.15°K of some sodium- and calcium-aluminum silicates: U.S. Bur. Mines Rept. Inv. 5855, 8 p.
232. King, E. G. and Weller, W. W., 1961, Low-temperature heat capacities and entropies at 298.15°K of monotungstates of sodium, magnesium, and calcium: U.S. Bur. Mines Rept. Inv. 5791, 6 p.
233. King, E. G., and Weller, W. W., 1962, Low-temperature heat capacity and entropy at 298.15°K of red mercuric sulfide: U.S. Bur. Mines Rept. Inv. 6001, 4 p.
234. King, E. G., and Weller, W. W., 1962, Low-temperature heat capacities and entropies at 298.15°K of antimony and indium sulfides: U.S. Bur. mines Rept. Inv. 6040, 5 p.
235. King, E. G., and Weller, W. W., 1970, Low-temperature heat capacities and entropies at 298.15°K of goethite and pyrophyllite: U.S. Bur. Mines Rept. Inv. 7369, 6 p.
236. King, E. G., Weller, W. W., and Christensen, A. U., 1960, Thermodynamics of some oxides of molybdenum and tungsten: U. S. Bur. Mines Rept. Inv. 5664, 29 p.
237. Kiseleva, I. A., 1984, The enthalpy of formation of grossular: *Geochemistry International*, v. 21(5), p. 138-141.
238. Kiseleva, I. A., Mel'chakova, L. V., and Ogorodnikova, L. P., 1986, Thermodynamical properties of beryllium minerals: chrysoberyl, beryl, euclase, and bertrandite: *Geokhimiya*, n. 5, p. 716-729.
239. Kiseleva, I. A., and Ogorodnikova, L. P., 1986, Calorimetric data on the thermodynamics of epidote, clinozoisite, and zoisite: *Geokhimiia*, n. 6, p. 846-853.

240. Kiseleva, I. A., Ogorodnikova, L. P., Topor, N. D., and Chigareva, O. G., 1980, A thermochemical study of the CaO-MgO-SiO₂ system: *Geochemistry International*, v. 16(6), p. 122-134
241. Kiseleva, I.A., Ogorodova, L.P., Melchakova, L.V., Bisengalieva, M.R., and Becturganov, N.S., 1992, Thermodynamic properties of copper carbonates-malachite Cu₂(OH)₂CO₃ and azurite Cu₃(OH)₂(CO₃)₂: *Phys. Chem. Minerals*, v. 19, p. 322-333.
242. Kiseleva, I. A., Ogorodova, L. P., and Sokolova, E. L., 1989, Enthalpy of formation of andradite: *Geokhimiia*, n. 1, p. 125-131.
243. Kiseleva, I. A., Topor, N. D., and Andreyenko, E. D., 1974, Thermodynamic parameters of minerals of the epidote group: *Geochemistry International*, v. 11, p. 389-398.
244. Kiseleva, I. A., Topor, N. D., and Melchakova, L. V., 1972, Experimental determination of heat content and heat capacity of andradite and pyrope: *Geokhimiia*, n. 11, p. 1372-1379.
245. Kiukkola, K., and Wagner, C., 1957, Measurements on galvanic cells involving solid electrolytes: *Jour. Electrochem. Soc.*, v. 104, p. 379-387.
246. Ko, H. C., Ahmad, N., and Chang, Y. A., 1982, Thermodynamics of calcination of calcite: U.S. Bur. Mines Rept. Inv. 8647, 9 p.
247. Ko, H. C., and Daut, G. E., 1980, Enthalpies of formation of α - and β -magnesium sulfate and magnesium sulfate monohydrate: U. S. Bur. Mines Rept. Inv. 8409, 8p.
248. Ko, H. C., Ferrante, M. J., and Stuve, J. M., 1977, Thermophysical properties of acmite: *Proceedings of the Seventh Symposium on Thermophysical Properties*, (Am. Soc. Mech. Eng.), p. 392-395.

249. Koehler, M. F., Barany, R., and Kelley, K. K., 1961, Heats and free energies of formation of ferrites and aluminates of calcium, magnesium, sodium, and lithium: U. S. Bur. Mines Rept. Inv. 5711, 14 p.
250. Koehler, M. F., and Coughlin, J. P., 1959, Heats of formation of ferrous chloride, ferric chloride and manganous chloride: Jour. Phys. Chemistry, v. 63, p. 605-608.
251. Kolesnik, Yu. N., Nogteva, V. V., Arkhipenko, D. K., Orekhov, B. A., and Ye, I., 1979, Thermodynamics of pyrope-grossular solid solutions and the specific heat of grossular at 13-300 K: Geokhimiia, n. 5, p. 713-721.
252. Komada, N., Westrum, E. F., Jr., and Hemingway, B. S., 1994, Thermodynamic properties of two iron silicates: heat capacities of deerite from 10 to 700 K and grunerite from 10 to 1000 K: Jour. Chem. Thermodynamics, (in press).
253. Konigsberger, E., and Gamsjager, H., 1987, Solid-solute phase equilibrium in aqueous solution: I solubility constant and free enthalpy of formation of huntite: Ber. Buns. Phys. Chemie., v. 91, p. 785-790.
254. Konings, R. J. M., Cordfunke, E. H. P., and Ouweltjes, W., 1988, The standard enthalpies of formation of hydroxides. II. The alkali hydroxides CsOH and KOH: Jour. Chem. Thermodynamics, v. 20, p. 777-780.
255. Kostryakov, V. N., and Kalinkina, I. N., 1964, Heat capacity and entropy for manganese, iron, cobalt, and nickel carbonates at low temperatures: Zhur. Fizicheskoi Khimii, v. 38, p 780-78.
256. Kornilov, A.N., Ushakova, I.M., Huber, E.T., Jr., and Holley, C.E., Jr., 1975, The enthalpy of formation of hafnium dioxide: Jour. Chem. Thermodynamics, v. 7, p. 21-26.

257. Krupka, K. M., Hemingway, B. S., Robie, R. A., and Kerrick, D. M., 1985, High-temperature heat capacities and derived thermodynamic properties of anthophyllite, diopside, dolomite, enstatite, bronzite, talc, tremolite, and wollastonite: *Am. Mineralogist*, v. 70, p. 261-271.
258. Krupka, K. M., Robie, R. A., and Hemingway, B. S., 1979, The heat capacities of corundum, periclase, anorthite, $\text{CaAl}_2\text{Si}_2\text{O}_8$ glass, muscovite, pyrophyllite, KAlSi_3O_8 glass, grossular, and $\text{NaAlSi}_3\text{O}_8$ glass: *Am. Mineralogist*, v. 64, p. 86-101.
259. Krupka, K. M., Robie, R. A., Hemingway, B. S., Kerrick, D. M., and Ito, Jun, 1985, Low-temperature heat capacities and derived thermodynamic properties of anthophyllite, diopside, enstatite, and wollastonite: *Am. Mineralogist*, v. 70, p. 249-260.
260. Landee, C. P., and Westrum, E. F., Jr., 1975, Thermophysical measurements on transition-metal tungstates. I. Heat capacity of zinc tungstate from 5 to 550 K: *Jour. Chem. Thermodynamics*, v. 7, p. 973-976.
261. Landee, C. P., and Westrum, E. F., Jr., 1976, Thermophysical measurements on transition metal tungstates. III. Heat capacity of antiferromagnetic manganese tungstate: *Jour. Chem. Thermodynamics*, v. 8, p. 663-674.
262. Lander, J. J., 1951, Experimental heat contents of SrO , BaO , CaO , BaCO_3 and SrCO_3 at high temperatures. Dissociation pressures of BaCO_3 and SrCO_3 : *Am. Chem. Soc. Jour.*, v. 73, p. 5794-5797.
263. Lange, R. A., Carmichael, I. S. E., and Stebbins, J. F., 1986, Phase transitions in leucite (KAlSi_2O_6), orthorhombic KAlSiO_4 , and their iron analogues: *Am. Mineralogist*, v. 71, p. 937-945.

264. Lattard, D. and Evans, B.W., 1992, New experiments on the stability of grunerite: Euro., Jour. Mineralogy, v. 4, p. 219-238.
265. Lyon, W. G., and Westrum, E. F., Jr., 1974, Heat capacities of zinc tungstate and ferrous tungstate from 5 to 550°K: Jour. Chem. Thermodynamics, v. 6, p. 763-80.
266. Lyon, W. G., and Westrum, E. F., Jr., 1974, High temperature thermal functions and the thermochemistry of zinc tungstate: Jour. Chem. Thermodynamics, v. 6, p. 781-786.
267. Mah, A. D., 1954, Heats of formation of chromium oxide and cadmium oxide from combustion calorimetry: Am. Chem. Soc. Jour., v. 76, p. 3363-3365.
268. Mah, A. D., 1957, Heats of formation of alumina, molybdenum trioxide, and molybdenum dioxide: Jour. Phys. Chemistry, v. 61, p. 1572-1573.
269. Mah, A. D., 1961, Heats of formation of cerium sesquioxide and bismuth sesquioxide by combustion calorimetry: U. S. Bur. Mines Rept. Inv. 5676, 7 p.
270. Mah, A. D., 1982, Thermodynamic data for arsenic sulfide reactions: U.S. Bur. Mines Rept. Inv. 8671, 85 p.
271. Mah, A. D., and Pankratz, L. B., 1976, Contributions to the data on theoretical metallurgy. XVI. Thermodynamic properties of nickel and its inorganic compounds: U.S. Bur. Mines Bull. 668, 125 p.
272. Mah, A. D., Pankratz, L. B., Weller, W. W., and King, E. G., 1967, Thermodynamic data for cuprous and cupric oxides: U. S. Bur. Mines Rept. Inv. 7026, 20 p.

273. Marland, G., 1975, The stability of $\text{CaCO}_3 \cdot 6\text{H}_2\text{O}$ (ikaite). *Geochem. Cosmochim. Acta.*, v. 39, p. 83-91.
274. Mazdab, F. K., Anovitz, L. M., Hemingway, B. S., Robie, R. A., and Navrotsky, A., 1992, Thermodynamic properties of some boron-bearing minerals: Abstracts with Program, 1992, Geological Society of America, p A258.
275. McBride, J. J., and Westrum, E. F., Jr., 1976, Low-temperature heat capacity of anisotropic crystals. Lamellar molybdenum disulfide: *Jour. Chem. Thermodynamics*, v. 8, p. 37-44.
276. Mehrotra, G. M., Tare, V. B., and Wagner, J. B., Jr., 1985, The Standard Gibbs Energy of Formation of $\text{Ni}_{3+x}\text{S}_2$: *Jour. Electrochem. Soc.*, v. 132, p. 247-250.
277. Metz, G. W., Anovitz, L. M., Essene, E. J., Bohlen, S. R., Westrum, E. F., and Wall, V. J., 1983, The heat capacity and phase equilibria of almandine: *EOS* v. 64, p. 346-347.
278. Mills, I., Cuitas, T., Homann, K., Kalloy, N., and Kuchitsu, K., 1988, Quantities, units and symbols in physical chemistry: Blackwell, Oxford, 134 p.
279. Mills, K.C., 1974, Thermodynamic data for inorganic sulfides, selenides and tellurides, Butterworths, London, 845 p.
280. Mizota, T., Tanada, H., Fujii, Y., and Koto, K., 1985, The heat capacity of cubanite and the anomaly in cubic CuFe_2S_3 : *Canadian Mineralogist*, v. 23, p. 77-82.
281. Moecher, D. P., and Chou, I-Ming, 1990, Experimental investigation of andradite and hedenbergite equilibria employing the hydrogen sensor technique, with revised estimates of $\Delta_f G_{m,298}^\circ$ for andradite and hedenbergite: *Am. Mineralogist*, v. 75, p. 1327-1341.

282. Moecher, D. P., and Essene, E. J., 1990, Phase equilibria for calcic scapolite and implications of variable Al-Si disorder for P-T, T-XCO₂ and a-X relations. *Jour. Petrology*, v. 31, 997-1024.
283. Moore, G. E., 1943, Heat content of manganese dioxide and carbonate at high temperatures: *Am. Chem. Soc. Jour.*, v. 65, p. 1398-1399.
284. Moore, G. E., 1943, Heat contents at high temperatures of the anhydrous chlorides of calcium, iron, magnesium, and manganese: *Am. Chem. Soc. Jour.*, v. 65, p. 1700-1703.
285. Morey, G. W., Fournier, R. O., and Rowe, J. J., 1962, Solubility of quartz in water in the temperature interval from 25° to 300°C: *Geochim. Cosmochim. Acta*, v. 26, p. 1029-1043.
286. Mosesman, M. A., and Pitzer, K. S., 1941, Thermodynamic properties of the crystalline forms of silica: *Am. Chem. Soc. Jour.*, v. 63, p. 2348-2356.
287. Nabutouskaya, O.A., Opperman, H., Paukov, I.E., and Khriplovich, L.M., 1985, Thermodynamic properties of cobalt monoxide at 5-328 K: *Zhur. Fiz. Khim*; v. 59, p. 1253-1254.
288. Navrotsky, Alexandra, 1989, Thermochemistry of perovskites in Navrotsky, Alexandra and Weidner, D.J. (eds.), *Perovskite: A structure of great interest to geophysics and materials science*: AGU Geophysical Monograph 45, p. 67-80.
289. Navrotsky, Alexandra, and Coons, W. E., 1976, Thermochemistry of some pyroxenes and related compounds: *Geochim. Cosmochim. Acta*, v. 40, p. 1281-1288.
290. Navrotsky, Alexandra, and Kleppa, O.J., 1968, Thermodynamics of formation of simple spinels: *Jour. Inorg. Nucl. Chemistry*, v. 30, p. 479-498.

291. Navrotsky, Alexandra, Pintchovski, F. S., and Akimoto, S. I., 1979, Calorimetric study of the stability of high pressure phases in the systems CoO-SiO_2 and $^*\text{FeO}^*\text{-SiO}_2$, and calculation of phase diagrams in MO-SiO_2 systems: *Physics of the Earth and Planetary Interiors*, v. 19, p. 275-292.
292. Naylor, B. F., 1944, High-temperature heat contents of ferrous and magnesium chromites: *Ind. Eng. Chemistry*, v. 36, p. 933-934.
293. Naylor, B. F., 1945, Heat contents at high temperatures of magnesium and calcium fluorides: *Am. Chem. Soc. Jour.*, v. 67, p. 150-152.
294. Naylor, B. F., 1946, High-temperature heat contents of TiO , Ti_2O_3 , Ti_3O_5 , and TiO_2 : *Am. Chem. Soc. Jour.* v. 68, p. 1077-1080.
295. Naylor, B. F., and Cook, O. A., 1946, High-temperature heat contents of the metatitanates of calcium, iron, and magnesium: *Am. Chem. Soc. Jour.*, v. 68, p. 1003-1005.
296. Newton, R. C., Charlu, T. V., Anderson, P. A. M., and Kleppa, O. J., 1979, Thermochemistry of synthetic clinopyroxenes on the join $\text{CaMgSi}_2\text{O}_6\text{-Mg}_2\text{Si}_2\text{O}_6$: *Geochim. Cosmochim. Acta*, v. 43, p. 55-60.
297. Newton, R. C., Charlu, T. V., and Kleppa, O. J., 1974, A calorimetric investigation of the stability of anhydrous magnesium cordierite with application to granulite facies metamorphism: *Contribution to Mineralogy and Petrology*, v. 44, p. 295-311.
298. Newton, R. C., Charlu, T. V., and Kleppa, O. J., 1977, Thermochemistry of high-pressure garnets and clinopyroxenes in the system $\text{CaO-MgO-Al}_2\text{O}_3\text{-SiO}_2$: *Geochim. Cosmochim. Acta*, v. 41, p. 369-377.

299. Newton, R. C., Thompson, A. B., and Krupka, K. M., 1977, Heat capacity of synthetic $\text{Mg}_3\text{Al}_2\text{SiO}_3\text{O}_{12}$ from 350 to 1,000 K and the entropy of pyrope: EOS Trans. Am. Geophys. Union, v. 58, p. 523.
300. O'Brien, C. J., and Kelley, K. K., 1957, High temperature heat contents of cryolite, anhydrous aluminum fluoride and sodium fluoride: Am. Chem. Soc. Jour., v. 79, p. 5616-5618.
301. Ogorodova, L. N., Kiseleva, I. A., and Shuriga, T. N., 1989, Enthalpies of formation and phase transformation of cryolite: Geokhimiia, N. 8, p. 1180-1183.
302. O'Hare, P.A.G., 1972, Thermochemical and theoretical investigations of the sodium-oxygen system, Part I. The standard enthalpy of formation of sodium oxide (Na_2O): Jour. Chem. Phys., v. 56, p. 4513-4516.
303. O'Hare, P. A. G., 1987, Inorganic chalcogenides: high-tech materials, low-tech thermodynamics: Jour. Chem. Thermodynamics, v. 19, p. 675-701.
304. O'Hare, P. A. G., Hubbard, W. N., Johnson, G. K., and Flotow, H. E., 1984, Calorimetric measurements of the low-temperature heat capacity, standard molar enthalpy of formation at 298.15 K, and high-temperature molar enthalpy increments relative to 298.15 K of tungsten disulfide (WS_2), and the thermodynamic properties to 1500 K: Jour. Chem. Thermodynamics, v. 16, p. 45-59.
305. O'Hare, P. A. G., Lewis, B. M., and Parkinson, B. A., 1988, Standard molar enthalpy of formation by fluorine-combustion calorimetry of tungsten diselenide (WSe_2). Thermodynamics of the high-temperature vaporization of WSe_2 . Revised value of the standard molar enthalpy of formation of molybdenite (MoS_2): Jour. Chem. Thermodynamics, v. 20, p. 681-691.

306. Okazaki, H. and Takano, A., 1985, The specific heat of Ag_2S in alpha-phase: *Zeit. Naturforsch.*, v. 40a, p. 986-988.
307. O'Neill, H. St. C., 1985, Thermodynamics of Co_3O_4 : A possible electron spin unpairing transition in Co^{3+} : *Phys. Chem. Minerals*, v. 12, p. 149-154.
308. O'Neill, H. St. C., 1987, Free energies of formation of NiO , CoO , Ni_2SiO_4 , and Co_2SiO_4 : *Am. Mineralogist*, v. 72, p. 280-291.
309. O'Neill, H. St. C., 1987, Quartz-fayalite-iron and quartz-fayalite-magnetite equilibria and the free energy of formation of fayalite (Fe_2SiO_4) and magnetite (Fe_3O_4): *Am. Mineralogist*, v. 72, p. 67-75.
310. O'Neill, H. St. C., 1988, Systems Fe-O and Cu-O: Thermodynamic data for the equilibria Fe-"FeO," Fe- Fe_3O_4 , "FeO"- Fe_3O_4 , Fe_3O_4 - Fe_2O_3 , Cu-Cu $_2\text{O}$, and Cu $_2\text{O}$ -CuO from emf measurements: *Am. Mineralogist*, v. 73, p. 470-486.
311. O'Neill, H. St. C., and Navrotsky, A., 1980, The thermodynamics of the clinopyroxene to pyroxenoid phase transition in the systems CaO-MnO-SiO $_2$: *EOS*, v. 61, p. 1147.
312. O'Neill, Hugh St. C., Pownceby, M. I., and Wall, V. J., 1988, Ilmenite-rutile-iron and ulvospinel-ilmenite-iron equilibria and the thermochemistry of ilmenite (FeTiO_3) and ulvospinel (Fe_2TiO_4): *Geochim. Cosmochim. Acta*, v. 52, p. 2065-2072.
313. Openshaw, R. E., Hemingway, B. S., Robie, R. A., Waldbaum, D. R., and Krupka, K. M., 1976, The heat capacities at low temperatures and entropies at 298.15 K of low albite, analbite, microcline, and high sanidine: *U.S. Geol. Survey Jour. Research*, v. 4, p. 195-204.

314. Orr, R. L., 1953, High temperature heat contents of magnesium orthosilicate and ferrous orthosilicate: Am. Chem. Soc. Jour., v. 75, p. 528-529.
315. Orr, R. L. and Christensen, A. U., 1958, High temperature heat contents of stannous and stannic sulfides: Jour. Phys. Chemistry, v. 62, p. 124-125.
316. Pankratz, L. B., 1964, High temperature heat contents and entropies of muscovite and dehydrated muscovite: U.S. Bur. Mines Rept. Inv. 6371, 6 p.
317. Pankratz, L. B., 1968, High-temperature heat contents and entropies of dehydrated analcite, kaliophilite, and leucite: U.S. Bur. Mines Rept. Inv. 7073, 8 p.
318. Pankratz, L. B., 1970, Thermodynamic data for silver chloride and silver bromide: U. S. Bur. Mines Rept. Inv. 7430, 12 p.
319. Pankratz, L. B., 1982, Thermodynamic properties of elements and oxides: U. S. Bur. Mines Bull. 672, 509 p.
320. Pankratz, L. B., 1984, Thermodynamic properties of halides: U. S. Bur. Mines Bull. 674, 826 p.
321. Pankratz, L. B., and Kelley, K. K., 1963, Thermodynamic data for magnesium oxide (periclase): U. S. Bur. Mines Rept. Inv. 6295, 5 p.
322. Pankratz, L. B., and Kelley, K. K., 1964, High-temperature heat contents and entropies of andalusite, kyanite, and sillimanite: U.S. Bur. Mines Rept. Inv. 6370, 7 p.

323. Pankratz, L. B., and Kelley, K. K., 1964, High-temperature heat contents and entropies of akermanite, cordierite, gehlenite, and merwinite: U.S. Bur. Mines Rept. Inv. 6555, 7 p.
324. Pankratz, L. B., and King, E. G., 1965, High-temperature heat contents and entropies of two zinc sulfides and four solid solutions of zinc and iron sulfides: U.S. Bur. Mines Rept. Inv. 6708, 8 p.
325. Pankratz, L. B., and King, E. G., 1970, High-temperature enthalpies and entropies of chalcopyrite and bornite: U.S. Bur. Mines Rept. Inv. 7435, 10 p.
326. Pankratz, L. B., Mah, A. D., and Watson, S. W., 1987, Thermodynamic properties of sulfides: U.S. Bur. Mines Bull., 689, 427 p.
327. Pankratz, L. B., and Weller, W. W., 1967, Thermodynamic properties of three lithium-aluminum silicates: U.S. Bur. Mines Rept. Inv. 7001, 13 p.
328. Pankratz, L. B., and Weller, W. W., 1969, Thermodynamic data for ferric sulfate and indium sulfate: U. S. Bur. Mines Rept. Inv. 7280, 8 p.
329. Pankratz, L. B., Weller, W. W., and Kelley, K. K., 1963, Low-temperature heat capacity and high-temperature heat content of mullite: U.S. Bur. Mines Rept. Inv. 6287, 7 p.
330. Parks, G. A., 1972, Free energies of formation and aqueous solubilities of aluminum hydroxides and oxide hydroxides at 25 °C: *Am. Mineralogist*, v. 57, p. 1163-1189.
331. Pashinkin, A.C., Muratova, V.A., Antyukhov, A.M., and Moiseyev, N.V., 1989, Heat capacity and thermodynamic functions of arsenopyrite (in Russian): *Izv. Akad. Nauk. SSSR, Neorg. Mater.*, v. 25, p. 225-227.

332. Pashinkin, A.C., Muratova, V.A., Moiseyev, N.V. and Bazhenov, J.V., 1991, Heat capacity and thermodynamic functions of iron diarsenide in the temperature range 5 K to 300 K: *Jour. Chem. Thermodynamics*, v. 23, p. 827-830.
333. Pashinkin, A. S., Rabinovich, I. B., Sheiman, M. S., Nistratov, V. P., and Vorobjova, O. I., 1985, Heat capacity and thermodynamic functions of tellurium dioxide in the range 5 to 300 K: *Jour. Chem. Thermodynamics*, v. 17, p. 43-47.
334. Perkins, D., III, Essene, E. J., Westrum, E. F., Jr., and Wall, V. J., 1979, New thermodynamic data for diaspore and their implications to the system $\text{Al}_2\text{O}_3\text{-SiO}_2\text{-H}_2\text{O}$: *Am. Mineralogist*, v. 64, p. 1080-1090.
335. Perkins, D., III, Westrum, E. F., Jr., and Essene, E. J., 1980, The thermodynamic properties and phase relations of some minerals in the system $\text{CaO-Al}_2\text{O}_3\text{-SiO}_2\text{-H}_2\text{O}$: *Geochim. Cosmochim. Acta*, v. 44, p. 61-84.
336. Plummer, L. N., and Busenberg, E., 1982, The solubilities of calcite, aragonite and vaterite in $\text{CO}_2\text{-H}_2\text{O}$ solutions between 0 and 90°C, and an evaluation of the aqueous model for the system $\text{CaCO}_3\text{-CO}_2\text{-H}_2\text{O}$: *Geochim. Cosmochim. Acta*, v. 46, p. 1011-1040.
337. Potter, R.W. II, 1977, An electrochemical investigation of the system copper-sulfur: *Economic Geology*, v. 72, p. 1524-1542.
338. Richards, A. W., 1959, The heats of formation and dissociation of zinc sulfide: *Jour. Appl. Chemistry*, v. 9, p. 142-145.

339. Richardson, D. W., and Brown, R. R., 1974, Enthalpy of formation of malachite $[\text{Cu}_2(\text{CO}_3)(\text{OH})_2]$: U.S. Bur. Mines Rept. Inv. 7851, 5 p.
340. Richet, P., and Bottinga, Y., 1984, Anorthite, andesine, wollastonite, diopside, cordierite and pyrope: thermodynamics of melting, glass transitions, and properties of the amorphous phases: Earth and Planetary Science Letters, v. 67, p. 415-432.
341. Richet, P., Bottinga, Y., Denielou, L., Petitot, J.P., and Tequi, C., 1982, Thermodynamic properties of quartz, cristobalite and amorphous SiO_2 : drop calorimetry measurements between 1000 and 1800 K and a review from 0 to 2000 K. Geochim. Cosmochim. Acta., v. 46, p. 2639-2658.
342. Richet, P., and Fiquet, G., 1991, High-temperature heat capacity and premelting of minerals in the system $\text{MgO-CaO-Al}_2\text{O}_3\text{-SiO}_2$: Jour. Geophys. Research, v. 96, No. B1, p. 445-456.
343. Richet, P., Robie, R. A., and Hemingway, B. S., 1987, Low-temperature heat capacity of diopside glass ($\text{CaMgSi}_2\text{O}_6$): A calorimetric test of the configurational-entropy theory applied to the viscosity of liquid silicates: Geochim. Cosmochim. Acta, v. 50, p. 1521-1533.
344. Richet, P., Robie, R. A., and Hemingway, B. S., 1991, Thermodynamic properties of wollastonite, pseudowollastonite and CaSiO_3 glass and liquid: Europ. Jour. Mineralogy, v. 3, p. 475-484.
445. Richet, P., Robie, R.A., and Hemingway, B.S., 1993, Entropy and structure of silicate glasses and melts: Geochim. Cosmochim. Acta, v. 57, p. 2751-2766.
346. Richet, P., Robie, R. A., Rogez, J., Hemingway, B. S., Courtial, P., and Tequi, C., 1990, Thermodynamics of open networks: ordering and entropy in $\text{NaAlSi}_3\text{O}_8$ glass, liquid, and polymorphs: Phys. Chem. Minerals, v. 17, p. 385-394.

347. Robie, R. A., 1965, Heats and free energies of formation of troilite, herzenbergite, magnesite, and rhodochrosite calculated from equilibrium data: U.S. Geol. Survey Prof. Paper 525-D, p. 65-72.
348. Robie, R. A., Bin, Zhao, Hemingway, B. S., and Barton, M. D., 1987, Heat capacity and thermodynamic properties of andradite garnet, $\text{Ca}_3\text{Fe}_2\text{Si}_3\text{O}_{12}$, between 10 and 1000 K and revised values for $\Delta_f G_m^\circ$ (298.15 K) of hedenbergite and wollastonite: *Geochim. Cosmochim. Acta*, v. 51, p. 2219-2224.
349. Robie, R. A., Evans, H. T., Jr., and Hemingway, B. S., 1988, Thermophysical properties of ilvaite $\text{CaFe}_2^+\text{Fe}^{3+}\text{Si}_2\text{O}_7(\text{OH})$: heat capacity from 7 to 920 K and thermal expansion between 298 and 856 K: *Phys. Chem. Minerals*, v. 15, p. 390-397.
350. Robie, R. A., Finch, C. B., and Hemingway, B. S., 1982, Heat capacity and entropy of fayalite (Fe_2SiO_4) between 5.1 and 383 K: comparison of calorimetric and equilibrium values for the QFM buffer reaction: *Am. Mineralogist*, v. 67, p. 463-469.
351. Robie, R. A., Haselton, H. T., Jr., and Hemingway, B. S., 1984, Heat capacities and entropies of rhodochrosite (MnCO_3) and siderite (FeCO_3) between 5 and 600 K: *Am. Mineralogist*, v. 69, p. 349-357.
352. Robie, R. A., Haselton, H. T., Jr., and Hemingway, B. S., 1989, Heat capacities and entropies at 298.15 K of MgTiO_3 (geikielite), ZnO (zincite), and ZnCO_3 (smithsonite): *Jour. Chem. Thermodynamics*, v. 21, p. 743-749.
353. Robie, R. A., and Hemingway, B. S., 1972, The heat capacities at low-temperatures and entropies at 298.15 K of nesquehonite, $\text{MgCO}_3 \cdot \text{H}_2\text{O}$, and hydromagnesite: *Am. Mineralogist*, v. 57, p. 1768-1781.

354. Robie, R. A., and Hemingway, B. S., 1973, The enthalpies of formation of nesquehonite, $\text{MgCO}_3 \cdot 3\text{H}_2\text{O}$, and hydromagnesite, $5\text{MgO} \cdot 4\text{CO}_2 \cdot 5\text{H}_2\text{O}$: U.S. Geol. Survey Jour. Research, v. 1, p. 543-547.
355. Robie, R. A., and Hemingway, B. S., 1984, Entropies of kyanite, andalusite, and sillimanite: additional constraints on the pressure and temperature of the Al_2SiO_5 triple point: Am. Mineralogist, v. 69, p. 298-306.
356. Robie, R. A., and Hemingway, B. S., 1984, Heat capacities and entropies of phlogopite ($\text{KMg}_3[\text{AlSi}_3\text{O}_{10}](\text{OH})_2$) and paragonite ($\text{NaAl}_2[\text{AlSi}_3\text{O}_{10}](\text{OH})_2$) between 5 and 900 K and estimates of the enthalpies and Gibbs free energies of formation: Am. Mineralogist, v. 69, p. 858-868.
357. Robie, R. A., and Hemingway, B. S., 1985, Low-temperature molar heat capacities and entropies of MnO_2 (pyrolusite), Mn_3O_4 (hausmannite) and Mn_2O_3 (bixbyite): Jour. Chem. Thermodynamics, v. 17, p. 165-181.
358. Robie, R. A., and Hemingway, B. S., 1991, Heat capacities of kaolinite from 7 to 380 K and of DMSO intercalated kaolinite from 20 to 310 K. The entropy of kaolinite $\text{Al}_2\text{Si}_2\text{O}_5(\text{OH})_4$: Clays and Clay Minerals, v. 39, p. 362-386.
359. Robie, R. A. and Hemingway, B. S., 1994, Heat capacities of synthetic grossular ($\text{Ca}_3\text{Al}_2\text{Si}_3\text{O}_{12}$), macro-crystals of magnesite ($(\text{Mg}_{0.991}\text{Fe}_{0.005}\text{Ca}_{0.003}\text{Mn}_{0.001})\text{CO}_3$), high-temperature superconductors $\text{YBa}_2\text{Cu}_3\text{O}_{6+x}$ and $\text{BiCaSrCu}_2\text{O}_{6+x}$, and type 321 stainless steel: U. S. Geological Survey Open-File Report 94-223, 12 p.
360. Robie, R. A., Hemingway, B. S., and Ditmars, D.A., unpublished data on C_p between 10 and 360 K for calcium metal.

361. Robie, R. A., Hemingway, B. S., and Fisher, J. R., 1978, Thermodynamic properties of minerals and related substances at 298.15 K and 1 bar (10^5 pascals) pressure and at higher temperatures: U.S. Geol. Survey Bull. 1452, 456 p.
362. Robie, R. A., Hemingway, B. S., Gillet, P., and Reynard, B., 1991, On the entropy of glaucophane $\text{Na}_2\text{Mg}_3\text{Al}_2\text{Si}_8\text{O}_{22}(\text{OH})_2$: Contributions to Mineralogy and Petrology, v. 107, p. 484-486.
363. Robie, R. A., Hemingway, B. S., Ito, J., and Krupka, K. M., 1984, Heat capacity and entropy of Ni_2SiO_4 -olivine from 5 to 1000 K and of Co_2SiO_4 from 360 to 1000 K: Am. Mineralogist, v. 69, p. 1096-1101.
364. Robie, R. A., Hemingway, B. S., and Takei, H., 1982, Heat capacities and entropies of Mg_2SiO_4 , Mn_2SiO_4 , and Co_2SiO_4 between 5 and 380 K: Am. Mineralogist, v. 67, p. 470-482.
365. Robie, R. A., Hemingway, B. S., and Wilson, W. H., 1976, The heat capacities of Calorimetry Conference copper and muscovite $\text{KAl}_2(\text{AlSi}_3)\text{O}_{10}(\text{OH})_2$, pyrophyllite $\text{Al}_2\text{Si}_4\text{O}_{10}(\text{OH})_2$, and illite $\text{K}_3(\text{Al}_7\text{Mg})(\text{Si}_{14}\text{Al}_2)\text{O}_{40}(\text{OH})_8$ between 15 and 375 K and their standard entropies at 298.15 K: U.S. Geol. Survey Jour. Research, v. 4, p. 631-644.
366. Robie, R. A., Hemingway, B. S., and Wilson, W. H., 1978, Low-temperature heat capacities and entropies of KAlSi_3O_8 , $\text{NaAlSi}_3\text{O}_8$, and $\text{CaAl}_2\text{Si}_2\text{O}_8$ glasses and of anorthite: Am. Mineralogist, v. 63, p. 110-123.
367. Robie, R.A., Huebner, J.S., and Hemingway, B.S., 1993, Heat capacities and thermodynamic properties of braunite ($\text{Mn}_7\text{SiO}_{12}$) and rhodonite (MnSiO_3): (unpublished report).

368. Robie, R. A., Russell-Robinson, S., and Hemingway, B. S., 1989, Heat capacities and entropies from 8 to 1000 K of langbeinite ($K_2Mg_2(SO_4)_3$), anhydrite ($CaSO_4$) and of gypsum ($CaSO_4 \cdot 2H_2O$) to 325 K: *Thermochimica Acta*, v. 139, p. 67-81.
369. Robie, R. A., Seal, R. R., II, and Hemingway, B. S., 1994, Heat Capacity and entropy of bornite (Cu_5FeS_4) between 6 and 760 K and the thermodynamic properties of phases in the Cu-Fe-S: *Canadian Mineralogist*, v. 32, 945-956.
370. Robie, R. A., and Stout, J. W., 1963, Heat capacity from 12 to 305°K and entropy of talc and tremolite: *Jour. Phys. Chemistry.*, v. 67, p. 2252-2256.
371. Robie, R. A., Wiggins, L. B., Barton, P. B., Jr., and Hemingway, B. S., 1985, Low-temperature heat capacity and entropy of chalcopyrite ($CuFeS_2$): estimates of the standard molar enthalpy and Gibbs free energy of formation of chalcopyrite and bornite (Cu_5FeS_4): *Jour. Chem. Thermodynamics*, v. 17, p. 481-488.
372. Romanovskii, V. A., and Tarasov, V. V., 1960, Heat capacity of the trisulfides of arsenic, antimony, and bismuth in connection with their structural and physical-chemical properties: *Sov. Phys.-Solid State*, v. 2, p. 1170-1175.
373. Sack, R.O. and Ghiorso, M.S., 1991, Chromium spinels as petrogenetic indicators: Thermodynamics and petrological applications: *Am. Mineralogist*, v. 76, p. 827-847.
374. Saxena, S. K., and Chatterjee, N., 1986, Thermochemical data on mineral phases: the system $CaO-MgO-Al_2O_3-SiO_2$: *Jour. Petrology*, v. 27, p. 827-842.
375. Schaefer, S. C., 1980, Electrochemical determination of Gibbs energies of formation of MnS and $Fe_{0.9}S$: U.S. Bur. Mines Rept. Inv., 8486, 17 p.

376. Schaefer, S. C., 1981, Electrochemical determination of Gibbs energies of formation of cobalt and nickel sulfides: U.S. Bur. Mines Rept. Inv., 8588, 18 p.
377. Schaefer, S. C., 1983, Electrochemical determination of thermodynamic properties of manganese sulfate and cadmium oxysulfate: U. S. Bur. Mines Rept. Inv. 8809, 20 p.
378. Schaefer, S. C., and Gokcen, N. A., 1982, Electrochemical determination of the thermodynamic properties of sphalerite, ZnS (beta): High Temperature Science, v. 15, p. 225-237.
379. Schuiling, R. D., Vergouwen, L., and Van der Rijst, J., 1976, Gibbs energies of formation of zircon ($ZrSiO_4$), thorite ($ThSiO_4$), and phenacite (Be_2SiO_4): Am. Mineralogist, v. 61, p. 161-168.
380. Seal, R.R., II, Essene, E.J. and Kelley, W.C., 1990, Tetrahedrite and tennantite: evaluation of thermodynamic data and phase equilibria: Canadian Mineralogist, v. 28, p. 725-738.
381. Seal, R. R., II, Robie, R. A., and Hemingway, B. S., 1991, Unpublished entropy and C_p data for enargite.
382. Seal, R. R., II, Robie, R. A., Hemingway, B. S., and Barton, P. B., Jr., 1992, Superambient heat capacities of synthetic stibnite, berthierite and chalcostibite: Revised thermodynamic properties and implications for phase equilibria: Economic Geology, v. 87, p. 1911-1918.
383. Semenov, Yu. V., Malinko, S. V., Kiseleva, I. A., and Khodakovsky, I. L., 1987, The formation conditions of endogenous calcium borates and borosilicates: Geokhimiya, No. 8, p. 1182-1190.
384. Settle, J. L., Johnson, G. K., and Hubbard, W. N., 1974, The enthalpy of formation of dicesium monoxide (Cs_2O): Jour. Chem. Thermodynamics, v. 6, p. 263-269.

385. Sharp, Z. D., Essene, E. J., Anovitz, L. M., Metz, G. W., Westrum, E. F., Hemingway, B. S., and Valley, J. W., 1983, The heat capacity of natural monticellite and phase equilibria in the system CaO-MgO-SiO₂-CO₂: *Geochim. Cosmochim. Acta*, v. 50, p. 1475-1484.
386. Shearer, J. A., and Kleppa, O. J., 1973, The enthalpies of formation of MgAl₂O₄, MgSiO₃, Mg₂SiO₄ and Al₂SiO₅ by oxide melt solution calorimetry: *Jour. Inorg. Nuc. Chemistry*, v. 35, p. 1073-1078.
387. Shomate, C. H., and Naylor, B. B., 1945, High-temperature heat contents of aluminum oxide, aluminum sulfate, potassium sulfate, ammonium sulfate and ammonium bisulfate: *Am. Chem. Soc. Jour.*, v. 67, p. 72-75.
388. Sirota, N. N., Lubyannikov, E. P., Novikov, V. V., and Sidorov, A. A., 1985, Low-temperature thermodynamic properties of cubic cubanite at temperatures of 5-300 K: *Soviet Physics Doklady*, v. 30, p. 789-791.
389. Southard, J. C., 1941, A modified calorimeter for high temperatures. The heat content of silica, wollastonite and thorium dioxide above 25°: *Am. Chem. Soc. Jour.*, v. 63, p. 3142-3150.
390. Southard, J. C., and Moore, G. E., 1942, High-temperature heat content of Mn₃O₄, MnSiO₃ and Mn₃C: *Am. Chem. Soc. Jour.*, v. 64, p. 1769-1770.
391. Southard, J. C., and Shomate, C. H., 1942, Heat of formation and high-temperature heat content of manganous oxide and manganous sulfate. High-temperature heat content of manganese: *Am. Chem. Soc. Jour.*, v. 64, p. 1770-1774.
392. Staveley, L. A. K., and Linford, R. G., 1969, The heat capacity and entropy of calcite and aragonite and their interpretation: *Jour. Chem. Thermodynamics*, v. 1, p. 1-11.

393. Stephenson, C. C., and Smith, D., 1968, Heat capacity of manganese titanate from 30° to 300°K: Jour. Chem. Physics, v. 49, p. 1814-1818.
394. Stolen, S., Gronvold, F., and Westrum, E. F., Jr., 1990, Thermodynamics of copper sulfides. IV. Heat capacity and thermodynamic properties of $\text{Cu}_{1.90}\text{S}$ from 5 K to 750 K, $\text{Cu}_{1.95}\text{S}$ from 5 K to 1000 K, $\text{Cu}_{1.98}\text{S}$ from 300 K to 750 K: Jour. Chem. Thermodynamics, v. 22, p. 1035-1057.
395. Stolen, S., Gronvold, F., Westrum, E. F., Jr., and Kolonin, G. R., 1991, Heat capacities and thermodynamic properties of synthetic heazlewoodite, Ni_3S_2 , and of the high-temperature phase $\text{Ni}_{3\pm x}\text{S}_2$: Jour. Chem. Thermodynamics, v. 23, p. 77-93.
396. Stout, J. W., and Robie, R. A., 1963, Heat capacity from 11 to 300°K. Entropy and heat of formation of dolomite: Jour. Phys. Chemistry, v. 67, p. 2248-2252.
397. Stubbles, J. R., and Birchenall, C. E., 1959, Redetermination of the lead-lead sulfide equilibrium between 585 and 920°C K: Trans. Metal. Soc. AIME., v. 215, p. 535-539.
398. Stuve, J. M., 1974, Low-temperature heat capacities of sphalerite and wurtzite: U.S. Bur. Mines Rept. Inv., 7940, 8 p.
399. Stuve, J. M., Beyer, R. P., and Brown, R. R., 1985, Thermodynamic properties of $\text{CoS}_{0.89}$, $\text{CoS}_{1.33}$, and CoS_2 : U.S. Bur. Mines Rept. Inv., 8994, 11 p.
400. Stuve, J. M., and Ferrante, M. J., 1980, Low-temperature heat capacities and high-temperature enthalpies of chiolite ($\text{Na}_5\text{Al}_3\text{F}_{14}$): U. S. Bur. Mines Rept. Inv. 8442, 8 p.
401. Stuve, J. M., Ferrante, M. J., and Ko, H. C., 1978, Thermodynamic properties of NiBr_2 and NiSO_4 from 10 to 1,200 K: U.S. Bur. Mines Rept. Inv. 8271, 15 p.

402. Tequi, C., Robie, R. A., Hemingway, B. S., Neuville, D., and Richet, P., 1991, Melting and thermodynamic properties of pyrope ($\text{Mg}_3\text{Al}_2\text{Si}_3\text{O}_{12}$): *Geochim. Cosmochim. Acta*, v. 55, p. 1005-1010.
403. Thompson, A. B., Perkins, D. III, Sonderegger, U., and Newton, R. C., 1978, Heat capacities of synthetic $\text{CaAl}_2\text{SiO}_6$ - $\text{CaMgSi}_2\text{O}_6$ - $\text{Mg}_2\text{Si}_2\text{O}_6$ pyroxenes: *EOS Transactions*, v. 59, p. 395.
404. Thompson, A. B., and Wennemer, M., 1979, Heat capacities and inversions in tridymite, cristobalite, and tridymite-cristobalite mixed phases: *Am. Mineralogist*, v. 64, p. 1018-1026.
405. Todd, S. S., 1951, Low-temperature heat capacities and entropies at 298.16°K of crystalline calcium orthosilicate, zinc orthosilicate and tricalcium silicate: *Am. Chem. Soc. Jour.*, v. 73, p. 3277-3278.
406. Todd, S. S., and Kelley, K. K., 1956, Heat and free-energy data for tricalcium dititanate, sphene, lithium metatitanate, and zinc-titanium spinel: *U.S. Bur. Mines Rept. Inv. 5193*, 18 p.
407. Topor, L., Kleppa, O. J., Newton, R. C., and Kerrick, D. M., 1989, Molten salt calorimetry of Al_2SiO_5 polymorphs at 1000 K. *EOS Transactions (Amer. Geophys. Union)*, v. 70, p. 493.
408. Torgeson, D. R., and Sahama, T. G., 1948, A hydrofluoric acid solution calorimeter and the determination of the heats of formation of Mg_2SiO_4 , MgSiO_3 , and CaSiO_3 : *Am. Chem. Soc. Jour.*, v. 70, p. 2156-2160.
409. Toulmin, P., III, and Barton, P. B., Jr., 1964, Thermodynamic study of pyrite and pyrrhotite: *Geochim. Cosmochim. Acta*, v. 28, p. 641-671.
410. Treiman, A. H., and Essene, E. J., 1983, Phase equilibria in the system $\text{CaO-SiO}_2\text{-H}_2\text{O}$: *Am. Jour. Science*, v. 283-A, p. 97-120.

411. Tremaine, P.R. and LeBlanc, J.C., 1980, The solubility of magnetite and the hydrolysis and oxidation of Fe^{2+} in water to 300°C: *Jour. Sol. Chemistry*, v. 9, p. 415-442.
412. Turnbull, A. G., 1973, A thermochemical study of vaterite: *Geochim. Cosmochim. Acta*, v. 37, p. 1593-1601.
413. Ulbrich, H. H., and Waldbaum, D., R., 1976, Structural and other contributions to the third-law entropies of silicates: *Geochim. Cosmochim. Acta*, v. 40, p. 1-24.
414. van Lier, J. A., de Bruyn, P. L., and Overbeek, J. Th. G., 1960, The solubility of quartz: *Jour. Phys. Chemistry*, v. 64, p. 1675-1682.
415. Vanderzee, C. E., Rodenburg, L. N., and Berg, R. L., 1974, Thermochemical studies on red and yellow orthorhombic and on red hexagonal mercuric oxide: *Jour. Chem. Thermodynamics*, v. 6, p. 17-33.
416. Vanderzee, C. E., and Wigg, D. A., 1981, The standard enthalpies of solution and formation of Wegscheider's salt: $\text{Na}_2\text{CO}_3 \cdot 3\text{NaHCO}_3(\text{s})$ and of trona: $\text{Na}_2\text{CO}_3 \cdot \text{NaHCO}_3 \cdot 2\text{H}_2\text{O}(\text{s})$ at 298.15 K: *Jour. Chem. Thermodynamics*, v. 13, p. 573-583.
417. Victor, A. C., and Douglas, T. B., 1961, Thermodynamic properties of thorium dioxide from 298 to 1,200°K: *U. S. Natl. Bur. Standards Jour. Research*, v. 65A, p. 105-111.
418. Victor, A. C., and Douglas, T. B., 1963, Thermodynamic properties of magnesium oxide and beryllium oxide from 298 to 1200°K: *U. S. Natl. Bur. Standards Jour. Research*, v. 67A, p. 325-329.
419. Wagman, D. D., Evans, W. H., Parker, V. B., Schumm, R. H., Halow, I., Bailey, S. M., Churney, K. L., and Nuttal, R. L., 1982, The NBS tables of chemical thermodynamic properties. Selected values for inorganic and C_1 and C_2 organic substances in SI units: *Jour. Phys. Chem. Ref. Data*, v. 11, supplement no. 2, 392 p.

420. Waldbaum, D. R., 1973, The configurational entropies of $\text{Ca}_2\text{MgSi}_2\text{O}_7$ - $\text{Ca}_2\text{SiAl}_2\text{O}_7$ melilites and related minerals: *Contributions to Mineralogy and Petrology*, v. 39, p. 33-54.
421. Waldbaum, D. R., and Robie, R. A., 1971, Calorimetric investigation of Na-K mixing and polymorphism in the alkali feldspars: *Zeit. Kristallographie*, v. 184, p. 381-420.
422. Walther, J. V., and Helgeson, H. C., 1977, Calculation of the thermodynamic properties of aqueous silica and the solubility of quartz and its polymorphs at high pressures and temperatures: *Am. Jour. Sci.*, v. 227, p. 1315-1351.
423. Watanabe, H., 1982, Thermochemical properties of synthetic high pressure compounds relevant to the earth's mantle. In Akimoto, S., and Manghnani, M. H., eds. *High-Pressure Research In Geophysics*, p. 441-464, Reidel, Dordrecht.
424. Waterfield, C. G., Linford, R. G., Goalby, B. B., Bates, T. R., Elyard, C. A., and Staveley, L. A. K., 1968, Thermodynamic investigation of disorder in the hydrates of sodium carbonate: *Faraday Soc. Trans.*, v. 69, p. 868-874.
425. Wechsler, B.A., and Navrotsky, A., 1984, Thermodynamics and structural chemistry of compounds in the system MgO-TiO_2 : *Jour. Solid State Chemistry*, v. 55, p. 165-180.
426. Welch, M.D., and Pawley, A.R., 1991, Tremolite: New enthalpy and entropy data from a phase equilibrium study of the reaction tremolite = 2 diopside + 1.5 ortho enstatite + β -quartz + H_2O : *Am. Mineralogist*, v. 76, p. 1931-1939.
427. Weller, W. W., and Kelley, K. K., 1963, Low-temperature heat capacities and entropies at 298.15°K of akermanite, cordierite, gehlenite, and merwinite: *U.S. Bur. Mines Rept. Inv. 6343*, 7 p.

428. Weller, W. W., and Kelley, K. K., 1964, Low-temperature heat capacities and entropies at 298.15°K of lead molybdate and lead tungstates: U.S. Bur. Mines Rept. Inv. 6357, 5 p.
429. Weller, W. W., and Kelley, K. K., 1964, Low-temperature heat capacities and entropies at 298.15°K of sulfides of arsenic, germanium and nickel: U.S. Bur. Mines Rept. Inv. 6511, 7 p.
430. Weller, W. W., and Kelley, K. K., 1966, Low-temperature heat capacities and entropies at 298.15°K of ferrous molybdate and ferrous tungstate: U.S. Bur. Mines Rept. Inv. 6782, 5 p.
431. Weller, W. W., and King, E. G., 1963, Low-temperature heat capacities and entropies at 298.15°K of monomolybdates of sodium, magnesium, and calcium: U.S. Bur. Mines Rept. Inv. 6147, 6 p.
432. Weller, W. W., and King, E. G., 1963, Low-temperature heat capacity and entropy at 298.15°K of muscovite: U.S. Bur. Mines Rept. Inv. 6281, 4 p.
433. Westrich, H. R., and Holloway, J. R., 1981, Experimental dehydration of pargasite and calculation of its entropy and Gibbs energy: *Am. Jour. Science*, v. 281, p. 922-934.
434. Westrich, H. R., and Navrotsky, A., 1981, Some thermodynamic properties of fluorapatite, fluorpargasite, and fluorphlogopite: *Am. Jour. Science*, v. 281, p. 1091-1103.
435. Westrum, E. F., Jr., written communication, September, 1959.
436. Westrum, E.F., Jr., and Beale, A.F., Jr., 1961, Heat capacities and chemical thermodynamics of cerium (III) fluoride and of cerium (IV) oxide from 5 to 300° K: *Jour. Phys. Chemistry*, v. 65, p. 353-355.
437. Westrum, E. F., Jr., Chou, C., and Gronvold, F., 1959, Heat capacities and thermodynamic properties of the iron tellurides $\text{Fe}_{1.11}\text{Te}$ and FeTe_2 from 5 to 350° K: *Jour. Chem. Physics*, v. 30, p. 761-764.

438. Westrum, E. F., Jr., Essene, E. J., and Perkins, D., III, 1977, Thermophysical properties of the garnet, grossular ($\text{Ca}_3\text{Al}_2\text{Si}_3\text{O}_{12}$): *Jour. Chem. Thermodynamics*, v. 11, p. 57-166.
439. Westrum, E.F., Jr., and Grimes, D.M., 1957, Low temperature heat capacities and thermodynamic properties of zinc ferrite: *Jour. Phys. Chem. Solids*, v. 3, p. 44-49.
440. Westrum, E.F., Jr., and Gronvold, F., 1969, Magnetite (Fe_3O_4) heat capacity and thermodynamic properties from 5 to 350° K low-temperature transition: *Jour. Chem. Thermodynamics*, v. 1, p. 543-557.
441. Westrum, E. F., Jr., and Gronvold, F., 1970, Manganese disulfide (hauerite) and manganese ditelluride. Thermal properties from 5 to 350° K and antiferromagnetic transitions: *Jour. Phys. Chem.*, v. 52, p. 3820-3826.
442. Westrum, E. F., Jr., Stolen, S., and Gronvold, F., 1987, Thermodynamics of copper sulfides II. Heat capacity and thermodynamic properties of synthetic covellite, CuS , from 5 to 780.5 K. Enthalpy of decomposition: *Jour. Chem. Thermodynamics*, v. 19, p. 1199-1208.
443. White, G. K., and Collocott, S. J., 1984, Heat capacity of reference materials: Cu and W: *Jour. Phys. Chem. Ref. Data*, v. 13, p. 1251-1257.
444. Wise, S. S., Margrave, J. L., Feder, H. M., and Hubbard, W. N., 1963, Fluorine bomb calorimetry. V. The heats of formation of silicon tetrafluoride and silica: *Jour. Phys. Chemistry*, v. 67, p. 815-821.
445. Woodland, A. B., and Wood, B. J., 1989, Electrochemical measurement of the free energy of almandine ($\text{Fe}_3\text{Al}_2\text{Si}_3\text{O}_{12}$) garnet: *Geochem. Cosmochim. Acta*, v. 53, p. 2277-2282.

446. Wruck, B., 1987, Thermodynamic behavior of the $P4_21m$ phase transition in anorthite (abs): Programme Physical Properties and Thermodynamic Behavior of Minerals (NATO), Cambridge.
447. Yakovlev, B. G., and Vozianova, O. V., 1983, Thermodynamical properties of almandine: *Geokimiia*, n. 1, p. 64-75.
448. Zhdanov, V. M., Turdakin, V. A., Arutyunov, V. S., Semenov, Yu. V., Malinko, S. V., and Kodakovsky, I. L., 1977, Low-temperature specific heat, standard entropy, and elastic parameters of datolite and danburyite: *Geochemistry International*, 14(6), p. 135-141.
449. Zhogin, D. Yu., Kosarukina, E. A., and Kolesov, V. P., 1980, Heat capacity in the 10-300 K range and thermodynamic functions of tetragonal tin dioxide: *Zhur. Fiz. Khimii*, v. 54(4), p. 916-920.
450. Heat capacity of hercynite estimated as $C_p(\text{FeAl}_2\text{O}_4) = \sum C_p(\text{FeO}) + C_p(\text{Al}_2\text{O}_3)$ by Robie. Entropy of MnSO_4 and other values estimated by Robie.
451. Enthalpies of solution of members of the nepheline-kalsilite series were reported by Hovis and Roux (Hovis, G.L. and Roux, J., 1993, Thermodynamic mixing properties of nepheline-kalsilite crystalline solutions: *Am. Jour. Sci.*, v. 293, p. 1108-1127.). Using enthalpy of solution values calculated from their equations 4 and 5, ancillary data from (166, tables 1-4), and unpublished enthalpy of solution data for KCl from Hemingway ($\Delta H(\text{soln}) = 6.045 - 0.0189t(^{\circ}\text{C})$), we calculate $\Delta_f H = -2090.4 \pm 2.5$ and $-2124.7 \pm 2.5 \text{ kJ} \cdot \text{mol}^{-1}$, respectively, for nepheline and kalsilite. These results are in good agreement with values given in (361) of -2092.1 ± 2.4 and $-2121.9 \pm 1.4 \text{ kJ} \cdot \text{mol}^{-1}$, respectively, but based on less pure samples (20, 171). These results are significantly less negative than the formation properties calculated by (188) from a limited number of phase equilibrium experiments. The calorimetrically determined value of $-3037.8 \pm 2.8 \text{ kJ} \cdot \text{mol}^{-1}$ for leucite (171, 20) is preferred to that derived by (188) from a limited number of phase equilibrium data ($-3020.0 \pm 2.7 \text{ kJ} \cdot \text{mol}^{-1}$).

452. Heat capacity measurements on a synthetic alunite are combined with earlier results by Kelley et al. (219) to estimate the entropy at 298.15 K. The reaction scheme used by Kelley et al. (219) is recalculated using modern values for the enthalpy of formation of the reference phases. See, Hemingway, B.S. and Robie, R.A., 1994, Heat capacity and enthalpy of formation of synthetic alunite: U.S. Geological Survey Open-file Report 94-688, 8 p.
453. High temperature heat capacities are derived from 244, 299, 402.
454. The Gibbs energy of livingstonite at 298.15 K is estimated from the study of (Sorokin, V.I., Dadze, T.P., and Pokronskiy, V.A., 1988, The Gibbs free energy of formation of livingstonite: *Geokhimiya*, No. 6, 897-900).

INDEX OF NAMES

	page		page
Acanthite (argentite)	11 45 122 148	Ca-Al pyroxene	34 61 345
Acmite	35 62 357	CaAl ₂ Si ₆ O ₆ glass	34 61
Akermanite	32 59 321	CaAl ₂ Si ₈ O ₈ glass	36 63 363
Alabandite	12 46 135 161	CaFeSi ₆ O ₆ glass	34 61
Albite	37 63 373	CaMgSi ₂ O ₆ glass	34 61 348
Almandine	33 60 333	CaSiO ₃ glass	34 61 344
Altaite	13 61 308	Ca ₂ Al ₂ Si ₃ O ₁₂ glass	31 58
Aluminum	5 41 68	Cadmium	6 41 79
Aluminum ion	5	Cadmium ion	6
Aluminum sulfate	28 56 283	Calcio-olivine	32 59 325
Alunite	28 56 290	Calcite	25 55 268
Ammonia	10 44 121	Calcium	6 41 78
Ammonia-niter	26 280		
Ammonium ion	10	Calcium ferrite	21 51 230
Analcite	2 37 64 374	Calcium ion	6
Analcime	37 64 379	Calcium nitrate	26 55 277
Anatase	19 50 223	Calomel	23
Andalusite	31 58 305	Carbon dioxide	15 47 181
Andradite	32 59 319	Carbon monoxide	15 47 180
Anglesite	29 57 297	Carbonate ion	15
Anhydrite	28 56 285	Carbonic acid (aqueous)	15
Anilite	11	Carnegieite	37 64 377
Annite	39 65 388	Cassiterite	19 50 219
Anorthite	2 36 63 362	Cattierite	11 45 125 151
Anthophyllite	35 62 360	Celestite	29
Antimony	9 43 106	Cerianite	16 47 184
Aragonite	25 55 267	Cerium	6 41 80
Arcanite	28 56 288	Cerussite	26
Arsenic	5 41 69	Cesium	6 84
Arsenolite	15	Cesium ion	6
Arsenopyrite	14	Chalcanthite	28
Artinite	25	Chalcocite	11 45 127 153
Azurite	25	Chalcocyanite	28 56 286
		Chalcopyrite	11 45 128 154
Baddeleyite	20 50 228	Chalcostibite	14 46 147 173
Barite	28 56 284	Chiolite	24 54 263
Barium	5 72	Chlorargyrite	23 53 247
Barium ion	5	Chloride ion	6
Barium monoxide	15 47 177	Chlorine	6 41 81
Berlinite	30 57 299	Chloromagnesite	23 53 253
Berndtite	13 46 142 168	Chromite	21 51 234
Berthierite	14 46 146 172	Chromium	6 41 83
Bertrandite	31 58 312	Chrysoberyl	21 51 229
Beryllium	5 41 73	Chrysotile (Antigorite)	39 65 394
Beryl	31 58 311	Cinnabar	12
Bianchite	29	Claudetite	15
Bicarbonate ion	15	Clausthalite	13
Bicchulite	36 63 364	Clinocllore	40
Bismite	15 47 179	Clinoenstatite	34 61 353
Bismuth	5 41 74	Clinoptilolite	36
Bismuthinite	11	Cobalt	6 41 82
Bixbyite	17 49 201	Cobalt monoxide	16 47 185
Boehmite	15 47 175	Cobalt-olivine	32 59 331
Borax	29	Cocconite	24
Boric oxide	16 176	Coesite	19 50 216
Bornite	11 45 129 155	Cohenite	10 44 120
Boron	5 41 71	Cooperite	13
Braunite	17 49 203	Copper	6 42 85
Bredigite	32 59	Copper ion	6
Brochantite	28	Cordierite	33 60 334
Bromargyrite	23 53 245	Corundum	15 47 174
Bromellite	15 47 178	Cotunnite	23 53 257
Bromide ion	5	Covellite	11 45 126 152
Bromine	5 41 75	Cristobalite	19 50 215
Bromine (ideal gas)	5 41 4	Cryolite	24 54 262
Brucite	17 48 198	Cubanite	12
Bunsenite	18 49 207	Cupric ion	6
		Cuprite	16 48 189
		Cuprous ion	6

	page		page
Danburite	36 63	Heazlewoodite	13 46 138 164
Datolite	32 59 317	Hedenbergite	34 61 346
Dawsonite	26 55 273	Hematite	16 48 192
Dehydrated analcime	38 64 380	Hercynite	21 51 233
Dehydrated mordenite	33	Herzenbergite	13 46 141 167
Diamond	5 41 77	Metaerolite	22
Diaspore	15 47	Heulandite	36
Diboron trioxide	15 47 176	Hexagonal anorthite	36
Dicalcium ferrite	21 51 231	Huebnerite	30
Dicesium monoxide	16	Huntite	25
Dickite	39 65 381	Hydrogen	7 42 89
Digenite	11	Hydrogen chloride	23 53 251
Dilithium monoxide	17 48 196	Hydrogen fluoride	24 54 259
Diopside	34 61 347	Hydrogen ion	7
Dipotassium monoxide	17 48 195	Hydrogen sulfide	12 46 134 160
Disodium monoxide	18 49 206	Hydrogen sulfide ion	12
Dititanium trioxide	19	Hydromagnesite	25
Djurleite	11	Hydrophilite	23 53 248
Dolomite	25 55 269	Hydroxide ion	16
Dumortierite	31 58 308	Hydroxyapatite	30 57 302
		Hypersthene	35 62
Edingtonite	36 63	Ikaite	25
Enargite	14	Illite	39 65
Enstatite	34 61 352	Ilmenite	21 51 235
Epidote	31 58	Ilvaite	32 59 318
Epsomite	29	Iodargyrite	24 54 264
Eskolaite	16 48 187	Iodide ion	7
Euclase	31 58 309	Iodine	7 42 91
Eucryptite	37 63 371	Iodine (ideal gas)	7
		Iron	2 7 87
Fayalite	32 60 332	Iron ion	7
Ferberite	30	Iron tennantite	14
Ferric ion	7	Iron tetrahedrite	14
Ferric sulfate	28 56 287		
Ferrobustamite	34 61	Jadeite	35 62 356
Ferroselite	12		
Ferrosilite	34 61 349	K-Al sulfate	28 56 289
Ferrous ion	7	KAlSi ₃ O ₈ glass	37 63 368
Ferrous oxide	16 48 191	Kaliophyllite (Kalsilite)	37 63 369
Fluorapatite	30 57 301	Kaolinite	39 65 382
Fluoride ion	6	Karelianite	19 50 225
Fluorine	6 42 86	Kyanite	31 58 304
Fluorite	24 54 258		
Fluor-pargasite	35	Langbeinite	28 56 291
Fluorophlogopite (Al/Si disordered)	39 65 391	Larnite (bredigite)	31 58 324
Fluorophlogopite (Al/Si ordered)	39 65 392	Laumontite	36
Forsterite	33 60 335	Lawrencite	23 53 249
Franklinite	22 52 243	Lawsonite	31 58 313
Frohbergite	12	Lead	8 43 102
		Lead ion	8
Galena	13 46 139 165	Leonhardite	36
Gaspeite	26	Leucite	37 63 370
Gehlenite	31 58 314	Liebenbergite	33 60 339
Geikielite	21 51 240	Lime	15 47 182
Germanium	7 42 88	Linnaeite	11
Gibbsite	15 47	Litharge	18 49 208
Glaucophanes	35 62 361	Lithium	7 93
Goethite	16	Lithium ion	7
Gold	5 41 70	Livingstonite	14
Goslarite	29	Loellingite	12
Graphite	5 41 76		
Greenockite	11 45 124 150	Magnesiochromite	21 51 238
Grossular	2 31 58 316	Magnesioferrite	21 51 239
Grunerite	35 62 359	Magnesite	25 55 271
Gypsum	28	Magnesium	8 42 94
		Magnesium ion	8
Hafnium dioxide	17	Magnesium nitrate	26 55 279
Halite	23 53 255	Magnesium sulfate	28 56 292
Halloysite	39 65	Magnetite	16 48 193
Haturite	32 59 326	Malachite	25
Hauerite	13	Manganese	8 42 95
Hausmannite	17 49 202		

	page		page
Manganese ion	8	Osumilite	33 60
Manganese sulfate	29 56 293	Otavite	25
Manganosite	17 48 199	Oxygen	8 42 100
Marcasite	12 45 133 159	Paragonite (Al/Si disordered)	40 66 395
Margarite	39 65 384	Paragonite (Al/Si ordered)	40 66 396
Marshite	24 54 265	Pargasite (Al/Si ordered)	35
Mascagnite	29 56 294	Pentlandite	13
Massicot	19	Periclase	17 48 197
Matildite	14	Perovskite	21 51 232
Meionite (Al-Si ordered)	36 63 365	Petalite	37 63 372
Melanterite	28	Phenakite	31 58 310
Mercuric ion	7	Phillipsite	38
Mercurous ion	7	Phlogopite (Al/Si disordered)	2 39 65 389
Mercury	7 42 90	Phlogopite (Al/Si ordered)	2 39 65 390
Merlinoite	38	Phosphate ion	18
Merwinite	32 59 322	Phosphorus	8 43 101
Mesolite	38	Phosphorus pentoxide	18
Metacinnabar	12	Platinum	8 43 103
Methane	10 44 119	Plattnerite	18 49 209
MgSiO ₃ glass	34 61	Pollucite	36 63
MgSiO ₃ -Ilmenite	35 62 354	Portlandite	16 47 183
MgSiO ₃ -Perovskite	35	Potassium	7 42 92
Mg ₂ Al ₂ Si ₃ O ₁₂ glass	33 60 337	Potassium aluminum sulfate	28 56 289
(Mg _{1.5} Ca _{1.5})Al ₂ Si ₃ O ₁₂ glass	33 60	Potassium bromide	23 53 246
(Mg _{1.8} Ca _{1.2})Al ₂ Si ₃ O ₁₂ glass	33 60	Potassium hydroxide	17
Miargyrite	14	Potassium ion	7
Microcline	36 63 366	Powellite	30
Millerite	13 46 137 163	Prehnite	39 65 385
Minium	18 49 210	Proustite	14
Mirabilite	29	Pseudobrookite	21 51
Molybdenite	13 46 136 162	Pseudowollastonite	34 61 343
Molybdenum	8 42 96	Pyrrargyrite	14
Molybdenite	17 49 204	Pyrite	12 45 132 158
Molysite	23 53 250	Pyrolusite	17 48 200
Monohydrocalcite	25	Pyrope	33 60 336
Monteponite	16	Pyrope-grossular	33 60
Monticellite	32 59 320	Pyrophanite	21 51 241
Montroydite	17	Pyrophyllite	39 65 383
Mordenite	38	Pyroxmangite	35
Morenosite	29	Pyrrhotite	12 45 131 157
Mullite	31 58 307	Quartz	18 49 214
Muscovite (Al/Si disordered)	2 39 65 386	Rankinite	32 59 327
Muscovite (Al/Si ordered)	2 39 65 387	Realgar	11 45 123 149
NaAlSi ₃ O ₈ glass	37 64 378	Retgersite	29
NaAlSi ₃ O ₆ glass	35 62	Rhodochrosite	26 55 272
NaAlSi ₃ O ₈ glass	37 64 375	Rhodonite	35 62 355
Na ₂₅ -K ₇₅ feldspar	37	Riebeckite	35 62
Na ₅₅ -K ₄₅ feldspar	37	Rosenhahnite	32 59 328
Na ₈₅ -K ₁₅ feldspar	37	Rutile	19 50 222
Nahecolite	26	Salammoniac	23 53
Nantokite	23	Sanidine	2 37 63 367
Natrolite	38	Sanmartinite	30
Nepheline-Na ₇₈ K ₂₂ AlSi ₃ O ₈	32 64	Sapphirine	33
Nepheline	37 64 376	Scacchite	23 53 254
Nesquehonite	25	Scheelite	30
NH ₄	10	Scolecite	36
Nickel	8 43 99	Selenium	9 43 107
Nickelous chloride	23 53 256	Sellaite	24 54 260
Nickelous ion	8	Siderite	25 55 270
Nickelous sulfate	29 56 289	Silica glass	19 50 218
Niningerite	12	Silicalite	19
Ni ₂ SiO ₄ -spinel	33 60 340	Silicic acid (aqueous)	9 19
Nifer	26 278	Silicon	9 43 108
Nitrate ion	17	Silicon monoxide	18 49 213
Nitrobarite	26 55 276	Sillimanite	31 58 306
Nitrogen	8 42 97	Silver	5 41 67
Nitrogen dioxide	17 49 205	Silver ion	5
Nukundamite	12	Smithite	14
Oldhamite	11		
Orpiment	11		

INDEX OF NAMES

	page		page	
Smithsonite	26	55 275	Wairakite	36
Soda-niter	27	55 281	Water	16
Sodium	8	42 98	Wegscheiderite	26
Sodium carbonate	26		Whitlockite	30 57 300
Sodium hydroxide	18		Willemite	33 60
Sodium ion	8		Witherite	25 55 266
Sphalerite	13	46 144 170	Wollastonite	34 61 342
Spinel	21	51 237	Wulfenite	30
α -spodumene	34	61 350	Wurtzite	13 46 145 171
β -spodumene	34	61 351	Wustite	16 48 190
Spurrite	32	59 329	Zinc	10 44 117
Staurolite	33	60	Zinc ion	10
Steam	17	48 194	Zinc tennantite	14
Stibnite	13	46 140 166	Zinc tetrahedrite	14
Stilbite	36		Zinc titanium spinel	22 52 244
Stishovite	19	50 217	Zincite	20 50 227
Stolzite	30		Zinkosite	29 57 298
Strengite	30		Zircon	33 60 341
Strontianite	26	55 274	Zirconium	10 44 118
Strontium	9	43 110	Zoisite	31 58 315
Strontium ion	9			
Strontium monoxide	19	50 220		
Strontium nitrate	27	55 282		
Sulfate ion	18			
Sulfide ion	9			
Sulfite ion	18			
Sulfur	3	8 43 104		
Sulfur (monoclinic)	9			
Sulfur (ideal gas)	3	9 43 105		
Sulfur dioxide	18	49 211		
Sulfur trioxide	18	49 212		
Sulfuric acid	28			
Sylvite	23	53 252		
Szomolnokite	28			
Talc	39	65 393		
Tellurite	19			
Tellurium	9	43 111		
Tellurobismuthite	11			
Tenorite	16	48 188		
Tephroite	33	60 338		
Thenardite	29	56 295		
Thermonatrite	26	55		
Thorianite	19	50 221		
Thorium	9	43 112		
Tialite	21	51		
Tilleyite	32	59 330		
Tin	9	43 109		
Titanite (sphene)	32	59 323		
Titanium	9	43 113		
Topaz	31	58 303		
Tremolite	35	62 358		
Trevorite	21	52 242		
Tricobalt tetraoxide	16	47 186		
Tridymite	19			
Troilite	12	45 130 156		
Trona	26			
Tungsten	9	44 116		
Tungsten dioxide	20	50 226		
Tungstenite	13	46 143 169		
Tungsten trioxide	20			
Ulvospinel	21	51 236		
Uraninite	19	50 224		
Uranium	9	43 114		
Valentinite	18			
Vanadium	9	44 115		
Vaterite	25			
Villiaumite	24	54 261		
Violarite	13			

INDEX OF FORMULAS

	page		page
Ag	5 41 67	CO	15 47 180
Ag ⁺	5	CO ₂ ²⁻	15 47 181
AgAsS ₂	14	CO ₃ ⁻	15
β-AgBiS ₂	14	Ca _{0.59} Sr _{0.18} Ba _{0.06} Na _{0.38} ⁻	36
AgBr	23 53 245	K _{0.13} Al _{2.16} Si _{6.84} O ₁₈ ·6H ₂ O	6 41 78
AgCl	23 53 247	Ca ²⁺	6
AgI	24 54 264	Ca ²⁺	6
α-AgSbS ₂	14	CaAl ₂ [Al ₂ Si ₂ O ₁₀](OH) ₂	39 65 384
Ag ₂ S	11 45 122 148	CaAl ₂ Si ₆ O ₆	34 61 345
Ag ₃ AsS ₃	14	CaAl ₂ [Si ₂ O ₇ (OH) ₂]·H ₂ O	31 58 313
Ag ₃ SbS ₃	14	CaAl ₂ Si ₂ O ₈	36 63 362 363
Al	5 41 68	CaAl ₂ Si ₃ O ₁₀ ·3H ₂ O	36
Al ³⁺	5	CaAl ₂ Si ₄ O ₁₂ ·2H ₂ O	36
Al(OH) ₃	15 47	CaAl ₂ Si ₄ O ₁₂ ·4H ₂ O	36
AlO(OH)	15 47	CaB(SiO ₄)(OH)	32 59 317
AlPO ₄	30 57 299	CaB ₂ Si ₂ O ₈	36 63
Al ₂ O ₃	15 47 174	CaCO ₃	25 55 267 268
Al ₂ (SO ₄) ₃	28 56 283	CaCO ₃ ·H ₂ O	25
Al ₂ Si ₄ O ₇ F ₂	31 58 303	CaCO ₃ ·6H ₂ O	25
Al ₂ SiO ₅	31 58 304 305 306	CaCl ₂	23 53 248
Al ₂ Si ₂ O ₅ (OH) ₄	39 65 381 382	CaF ₂	24 54 258
Al ₂ Si ₄ O ₁₀ (OH) ₂	39 65 383	CaFeSi ₂ O ₆	34 61 346
Al ₂ TiO ₅	21 51	CaFe ₂ O ₄	21 51 230
Al ₆ Si ₂ O ₁₃	31 58 307	CaFe ₃ (Si ₂ O ₇)O(OH)	32 59 318
Al _{6.75} [□ _{0.25} BSi ₃ O _{17.25} (OH) _{0.75}]	31 58 308	CaMg(CO ₃) ₂	25 55 269
As	5 41 69	CaMgSiO ₄	32 59 320
AsS	11 45 123 149	CaMgSi ₂ O ₆	34 61 347 348
As ₂ O ₃	15	CaMg ₃ (CO ₃) ₄	25
As ₂ S ₃	11	CaMoO ₄	30
Au	5 41 70	CaO	15 47 182
B	5 41 71	Ca(OH) ₂	16 47 183
B ₂ O ₃	15 47 176	CaS	11
Ba	5 72	CaSO ₄	28 56 285
Ba ²⁺	5	CaSO ₄ ·2H ₂ O	28
BaAl ₂ Si ₃ O ₁₀ ·3H ₂ O	36 63	CaSiO ₃	34 61 342 343 344
BaCO ₃	25 55 266	CaTiO ₃	21 51 232
Ba(NO ₃) ₂	26 55 276	CaTiSiO ₅	32 59 323
BaO	15 47 177	CaWO ₄	30
BaSO ₄	28 56 284	Ca _{1.02} Na _{0.14} K _{0.01} (Al _{2.18} Si _{6.82} O ₁₈)· 7.33H ₂ O	36
Be	5 41 73	Ca ₂ Al[AlSi ₃ O ₁₀](OH) ₂	39 65 385
BeAlSiO ₄ (OH)	31 58 309	Ca ₂ Al ₂ FeSi ₃ O ₁₂ (OH)	31 58
BeAl ₂ O ₄	21 51 229	Ca ₂ Al ₂ SiO ₆ (OH) ₂	36 63 364
BeO	15 47 178	Ca ₂ Al ₂ SiO ₇	31 58 314
Be ₂ SiO ₄	31 58 310	Ca ₂ Al ₃ Si ₃ O ₁₂ (OH)	31 58 315
Be ₃ Al ₂ (Si ₆ O ₁₈)	31 58 311	Ca ₂ Al ₄ Si ₈ O ₂₄ ·7H ₂ O	36
Be ₄ Si ₂ O ₇ (OH) ₂	31 58 312	Ca ₂ Fe ₂ O ₅	21 51 231
Bi	5 41 74	Ca ₂ MgSi ₂ O ₇	32 59 321
Bi ₂ O ₃	15 47 179	Ca ₂ Mg ₅ (Si ₈ O ₂₂)(OH) ₂	35 62 358
Bi ₂ S ₃	11	α-Ca ₂ SiO ₄	31 58 324
Bi ₂ Te ₃	11	β-Ca ₂ SiO ₄	31 58 324
Br	5	γ-Ca ₂ SiO ₄	32 59 325
Br ₂	5 41 75	Ca ₃ Al ₂ Si ₃ O ₁₂	2 31 58 316
C	5 41 76 77	Ca ₃ Fe ₂ Si ₃ O ₁₂	32 59 319
CH ₄	10 44 119	Ca ₃ Mg(SiO ₄) ₂	32 59 322
		Ca ₃ (PO ₄) ₂	30 57 300
		Ca ₃ SiO ₅	32 59 326

	page		page
Ca ₃ Si ₂ O ₇	32	59 327	2 7 87
Ca ₃ Si ₃ O ₈ (OH) ₂	32	59 328	7
Ca ₄ Al ₆ Si ₆ O ₂₄ CO ₃	36	63 365	7
Ca ₅ (PO ₄) ₃ F	30	57 301	21 51 233
Ca ₅ (PO ₄) ₃ OH	30	57 302	14
Ca ₅ (SiO ₄) ₂ CO ₃	32	59 329	12
Ca ₅ Si ₂ O ₇ (CO ₃) ₂	32	59 330	25 55 270
Cd	6	41 79	23 53 249
Cd ²⁺	6		23 53 250
CdCO ₃	25		21 51 234
CdO	16		16 48 191
CdS	11	45 124 150	12 45 130 156
Ce	6	41 80	30
CeO ₂	16	47 184	12 45 130 156
Cl ⁻	6		28
Cl ₂	6	41 81	28
Co	6	41 82	12 45 132 133
CoO	16	47 185	158 159
CoS ₂	11	45 125 151	14 46 146 172
Co ₂ SiO ₄	32	59 331	12
Co ₃ O ₄	16	47 186	34 61 349
Co ₃ S ₄	11		12
Cr	6	41 83	21 51 235
Cr ₂ O ₃	16	48 187	30
(Cs .65Na .19Rb .03)Al ₂ Si ₄ O ₁₂ ·H ₂ O	36	63	16 48 192
Cs	6	84	28 56 287
Cs ⁺	6		32 60 332
Cs ₂ O	16		21 51 236
Cu	6	42 85	21 51
Cu ⁺	6		33 60 333
Cu ²⁺	6		10 44 120
CuCl	23		16 48 193
CuFeS ₂	11	45 128 154	33 60
CuFe ₂ S ₃	12		35 62 359
CuI	24	54 265	
CuO	16	48 188	Ge 7 42 88
CuS	11	45 126 152	
CuSbS ₂	14	46 147 173	H ⁺ 7
CuSO ₄	28	56 286	HCO ₃ ⁻ 15
CuSO ₄ ·5H ₂ O	28		HCl 23 53 251
Cu _{1.75} S	11		HF 24 54 259
Cu _{1.80} S	11		HS ⁻ 12
Cu _{1.95} S	11		H ₂ 7 42 89
Cu ₂ (CO ₃)(OH) ₂	25		H ₂ CO ₃ 15
Cu ₂ O	16	48 189	H ₂ O 16 17 48 194
Cu ₂ S	11	45 127 153	H ₂ S 12 46 134 160
Cu ₃ AsS ₄	14		H ₂ SO ₄ 28
Cu ₃ (OH) ₂ (CO ₃) ₂	25		H ₄ SiO ₄ 9 19
Cu ₄ (SO ₄)(OH) ₆	28		HfO ₂ 17
Cu ₅ FeS ₄	11	45 129 155	Hg 7 42 90
Cu ₁₀ Fe ₂ As ₄ S ₁₃	14		Hg ²⁺ 7
Cu ₁₀ Fe ₂ Sb ₄ S ₁₃	14		HgCl 23
Cu ₁₀ Zn ₂ As ₄ S ₁₃	14		HgI ₂ 24
Cu ₁₀ Zn ₂ Sb ₄ S ₁₃	14		HgO 17
			HgS 12
F ⁻	6		HgSb ₄ S ₈ 14
F ₂	6	42 86	Hg ₂ ²⁺ 7
Fe .875S	12	45 131 157	I ⁻ 7
Fe .90S	12	45	I ₂ 7 42 91
Fe .947O	16	48 190	
			Fe 2
			Fe ²⁺ 7
			Fe ³⁺ 7
			FeAl ₂ O ₄ 21 51 233
			FeAs _{1.08} S _{0.92} 14
			FeAs ₂ 12
			FeCO ₃ 25 55 270
			FeCl ₂ 23 53 249
			FeCl ₃ 23 53 250
			FeCr ₂ O ₄ 21 51 234
			FeO 16 48 191
			FeO(OH) 12 45 130 156
			Fe(PO ₄)·2H ₂ O 30
			FeS 12 45 130 156
			FeSO ₄ ·H ₂ O 28
			FeSO ₄ ·7H ₂ O 28
			FeS ₂ 12 45 132 133
			158 159
			FeSb ₂ S ₄ 14 46 146 172
			FeSe ₂ 12
			FeSiO ₃ 34 61 349
			FeTe ₂ 12
			FeTiO ₃ 21 51 235
			FeWO ₄ 30
			Fe ₂ O ₃ 16 48 192
			Fe ₂ (SO ₄) ₃ 28 56 287
			Fe ₂ SiO ₄ 32 60 332
			Fe ₂ TiO ₄ 21 51 236
			Fe ₂ TiO ₅ 21 51
			Fe ₃ Al ₂ Si ₃ O ₁₂ 33 60 333
			Fe ₃ C 10 44 120
			Fe ₃ O ₄ 16 48 193
			Fe ₄ Al ₁₈ Si ₈ O ₄₆ (OH) ₂ 33 60
			Fe ₇ Si ₈ O ₂₂ (OH) ₂ 35 62 359

	page		page
$K_{0.80}Na_{0.20}AlSi_{1.94}O_{5.88} \cdot 1.81H_2O$	38	$Mg_3Al_2Si_3O_{12}$	33 60 336 337
$K_{0.91}Na_{0.09}AlSi_{1.81}O_{5.62} \cdot 1.79H_2O$	38	$Mg_3Si_2O_5(OH)_4$	39 65 394
K	7 42 92	$Mg_3Si_4O_{10}(OH)_2$	39 65 393
K^+	7	$Mg_5Al(AlSi_3O_{10})(OH)_8$	40
$KAl(SO_4)_2$	28 56 289	$4MgCO_3 \cdot Mg(OH)_2 \cdot 4H_2O$	25
$KAlSiO_4$	37 63 369	$Mg_7Si_8O_{22}(OH)_2$	35 62 360
$KAlSi_{1.81}O_{5.62} \cdot 1.69H_2O$	38	Mn	8 42 95
$KAlSi_{1.94}O_{5.88} \cdot 1.69H_2O$	38	Mn^{2+}	8
$KAlSi_2O_6$	37 63 370	$MnCO_3$	26 55 272
$KAlSi_3O_8$	2 36 37 63 366 367	$MnCl_2$	23 53 254
$KAl_2[AlSi_3O_{10}](OH)_2$	39 65 386 387	MnO	17 48 199
$KAl_3(OH)_6(SO_4)_2$	28 56 290	MnO_2	17 48 200
KBr	23 53 246	MnS	12 45 135 161
KCl	23 53 252	$MnSO_4$	29 56 293
$KFe_3[AlSi_3O_{10}](OH)_2$	39 65 388	MnS_2	13
$KMg_2Al_3[Si_{10}Al_2O_{30}] \cdot H_2O$	33 60	$MnSiO_3$	35 62 355
$KMg_3[AlSi_3O_{10}]F_2$	39 65 391 392	$MnTiO_3$	21 51 241
$KMg_3[AlSi_3O_{10}](OH)_2$	39 65 389 390	$MnWO_4$	30
KNO_3	26 278	Mn_2O_3	17 49 201
KOH	17	Mn_2SiO_4	33 60 338
$K_2Mg_2(SO_4)_3$	28 56 291	Mn_3O_4	17 49 202
K_2O	17 48 195	Mn_7SiO_{12}	17 49 203
K_2SO_4	28 56 288	Mo	8 42 96
$K_3(Al_7Mg)(Al_2Si_{14})O_{40}(OH)_8$	39 65	MoO_3	17 49 204
Li	7 93	MoS_2	13 46 136 162
Li^+	7	NH_3^+	10 44 121
$LiAlSiO_4$	37 63 371	NH_4^+	10
$LiAlSi_2O_6$	34 61 350 351	NH_4Cl	23 53
$LiAlSi_4O_{10}$	37 63 372	NH_4NO_3	26 280
Li_2O	17 48 196	$(NH_4)_2SO_4$	29 56 294
$(Mg_{0.85}Fe_{0.15})SiO_3$	35 62	NO_2^-	17 49 205
Mg	8 42 94	NO_3^-	17
Mg^{2+}	8	N_2	8 42 97
$MgAl_2O_4$	21 51 237	$(Na_{0.25}K_{0.75})AlSi_3O_8$	37
$MgCO_3$	25 55 271	$Na_{0.36}Ca_{0.29}Al_{0.94}Si_{5.06}O_{12}$	38
$MgCO_3 \cdot 3H_2O$	25	$Na_{0.36}Ca_{0.29}Al_{0.94}Si_{5.06}O_{12} \cdot 3.47H_2O$	38
$MgCl_2$	23 53 253	$(Na_{0.55}K_{0.45})AlSi_3O_8$	37
$MgCr_2O_4$	21 51 238	$Na_{0.68}Ca_{0.66}(Al_{1.99}Si_{3.01}O_{10}) \cdot 2.64H_2O$	38
MgF_2	24 54 260	$(Na_{0.78}K_{0.22})AlSiO_4$	32 64
$MgFe_2O_4$	21 51 239	$Na_{0.81}K_{0.19}AlSi_{1.81}O_{5.62} \cdot 2.18H_2O$	38
$Mg(NO_3)_2$	26 55 279	$Na_{0.81}K_{0.19}AlSi_{1.94}O_{5.88} \cdot 2.13H_2O$	38
MgO	17 48 197	$(Na_{0.85}K_{0.15})AlSi_3O_8$	37
$Mg(OH)_2$	17 48 198	Na	8 42 98
MgS	12	Na^+	8
β - $MgSO_4$	28 56 292	$NaAlCO_3(OH)_2$	26 55 273
$MgSO_4 \cdot 7H_2O$	29	$NaAlSiO_4$	37 64 376 377 378
$MgSiO_3$	34 61 352 353 355 62 354	$NaAlSi_2O_6$	35 62 356 380
$MgTiO_3$	21 51 240	$NaAlSi_2O_6 \cdot H_2O$	37 64 379
$(Mg_{1.5}Ca_{1.5})Al_2Si_3O_{12}$	33 60	$NaAlSi_3O_8$	2 37 63 64 373 374
$(Mg_{1.8}Ca_{1.2})Al_2Si_3O_{12}$	33 60	$NaAl_2[AlSi_3O_{10}](OH)_2$	40 66 395 396
$Mg_2Al_3(AlSi_5O_{18})$	33 60 334	$NaCa_2Mg_4Al(Al_2Si_6)O_{22}F_2$	35
$Mg_2Al_4O_6(SiO_4)$	33	$NaCa_2Mg_4Al(Al_2Si_6)O_{22}(OH)_2$	35
$Mg_2(OH)_2CO_3 \cdot 3H_2O$	25		
Mg_2SiO_4	33 60 335		

	page		page
NaCl	23 53 255	SO ₃ ²⁻	18 49 212
NaF	24 54 261	SO ₃ ²⁻	18
NaFeSi ₂ O ₆	35 62 357	SO ₄ ²⁻	18
NaHCO ₃	26	S ₂	3 9 43 105
NaNO ₃	27 55 281	Sb	9 43 106
NaOH	18	Sb ₂ O ₃	18
(Na _{1.1} K _{0.8})Al _{1.9} Si _{6.1} ·6H ₂ O	38	Sb ₂ S ₃	13 46 140 166
Na ₂ Al ₂ Si ₃ O ₁₀ ·2H ₂ O	38	Se	9 43 107
Na ₂ B ₄ O ₇ ·10H ₂ O	29	Si	9 43 108
Na ₂ CO ₃	26	SiO	18 49 213
Na ₂ CO ₃ ·H ₂ O	26 55	SiO ₂	18 19 49 50
Na ₂ CO ₃ ·NaHCO ₃ ·2H ₂ O	26		214 215 216
Na ₂ Fe ₃ Fe ₂ Si ₈ O ₂₂ (OH) ₂	35 62		217 218
Na ₂ Mg ₃ Al ₂ Si ₈ O ₂₂ (OH) ₂	35 62 361	Sn	9 43 109
Na ₂ CO ₃ ·3NaHCO ₃	26	SnO ₂	19 50 219
Na ₂ O	18 49 206	SnS	13 46 141 167
Na ₂ SO ₄	29 56 295	SnS ₂	13 46 142 168
Na ₂ SO ₄ ·10H ₂ O	29	Sr	9 43 110
Na ₃ AlF ₆	24 54 262	Sr ²⁺	9
Na ₅ Al ₃ F ₁₄	24 54 263	SrCO ₃	26 55 274
Ni	8 43 99	Sr(NO ₃) ₂	27 55 282
Ni ²⁺	8	SrO	19 50 220
NiCl ₂	23 53 256	SrSO ₄	29
NiCO ₃	26		
NiFe ₂ O ₄	21 52 242	Te	9 43 111
NiO	18 49 207	TeO ₂	19
NiS	13 46 137 163	Th	9 43 112
NiSO ₄	29 56 289	ThO ₂	19 50 221
NiSO ₄ ·6H ₂ O	29	Ti	9 43 113
NiSO ₄ ·7H ₂ O	29	TiO ₂	19 50 222 223
(Ni ₇ Fe ₃) ₃ S ₄	13	Ti ₂ O ₃	19
Ni ₂ SiO ₄	33 60 339 340		
Ni ₃ S ₂	13 46 138 164	U	9 43 114
Ni _{4.5} Fe _{4.5} S ₈	13	UO ₂	19 50 224
		V	9 44 115
OH ⁻	16	V ₂ O ₃	19 50 225
O ₂	8 42 100		
		W	9 44 116
P	8 43 101	WO ₂	20 50 226
PO ₄ ³⁻	18	WO ₃	20
P ₂ O ₅	18	WS ₂	13 46 143 169
Pb	8 43 102		
Pb ²⁺	8	Zn	10 44 117
PbCO ₃	26	Zn ²⁺	10
PbCl ₂	23 53 257	ZnCO ₃	26 55 275
PbMoO ₄	30	ZnFe ₂ O ₄	22 52 243
PbO	18 49 208	ZnMn ₂ O ₄	22
PbO ₂	18 49 209	ZnO	20 50 227
PbS	13 46 139 165	ZnS	13 46 144 145
PbSO ₄	29 57 297		170 171
PbSe	13	ZnSO ₄	29 57 298
PbTe	13 61 308	ZnSO ₄ ·6H ₂ O	29
PbWO ₄	30	ZnSO ₄ ·7H ₂ O	29
Pb ₃ O ₄	18 49 210	ZnWO ₄	30
Pt	8 43 103	Zn ₂ SiO ₄	33 60
PtS	13	Zn ₂ TiO ₄	22 52 244
		Zr	10 44 118
S	3 8 43 104	ZrO ₂	20 50 228
S ²⁻	09	ZrSiO ₄	33 60 341
SO ₂	18 49 211		

