

ANL/ET/CP-93096
CONF-9709168--
M97054218

Development of Mixed-Conducting Oxides for Gas Separation*

U. Balachandran, B. Ma, P. S. Maiya, R. L. Mieville, J. T. Dusek,
J. J. Picciolo, J. Guan, and S. E. Dorris
Energy Technology Division
Argonne National Laboratory
Argonne, Illinois 60439 USA

M. Liu
School of Materials Science and Engineering
Georgia Institute of Technology
Atlanta, Georgia 30332 USA

RECEIVED
SEP 22 1997
OSTI

August 1997

The submitted manuscript has been created by the University of Chicago as Operator of Argonne National Laboratory ("Argonne") under Contract No. W-31-109-ENG-38 with the U.S. Department of Energy. The U.S. Government retains for itself, and others acting on its behalf, a paid-up, nonexclusive, irrevocable worldwide license in said article to reproduce, prepare derivative works, distribute copies to the public, and perform publicly and display publicly, by or on behalf of the Government.

DISTRIBUTION OF THIS DOCUMENT IS UNLIMITED

MASTER

Paper to be published in proceedings of the 4th International Union of Materials Research Societies International Conference in Asia (IUMRS-ICA), Chiba, Japan, September 16-18, 1997

*Work supported by the U.S. Department of Energy, Federal Energy Technology Center, under Contract W-31-109-Eng-38.

DISCLAIMER

This report was prepared as an account of work sponsored by an agency of the United States Government. Neither the United States Government nor any agency thereof, nor any of their employees, makes any warranty, express or implied, or assumes any legal liability or responsibility for the accuracy, completeness, or usefulness of any information, apparatus, product, or process disclosed, or represents that its use would not infringe privately owned rights. Reference herein to any specific commercial product, process, or service by trade name, trademark, manufacturer, or otherwise does not necessarily constitute or imply its endorsement, recommendation, or favoring by the United States Government or any agency thereof. The views and opinions of authors expressed herein do not necessarily state or reflect those of the United States Government or any agency thereof.

DISCLAIMER

Portions of this document may be illegible electronic image products. Images are produced from the best available original document.

Development of Mixed-Conducting Oxides for Gas Separation

U. Balachandran,^{a,b} B. Ma,^b P. S. Maiya,^b R. L. Mieville,^b J. T. Dusek,^b
J. J. Picciolo,^b J. Guan,^{b,c} S. E. Dorris,^b and M. Liu^c

ABSTRACT

Mixed-conducting oxides have been used in many applications, including fuel cells, gas separation membranes, sensors, and electrocatalysis. We are developing a mixed-conducting, dense ceramic membrane for selectively transporting oxygen and hydrogen. Ceramic membranes made of Sr-Fe-Co oxide, which has high combined electronic and oxygen ionic conductions, can be used to selectively transport oxygen during the partial oxidation of methane to synthesis gas (syngas, CO + H₂). We have measured the steady-state oxygen permeability of SrFeCo_{0.5}O_x as a function of oxygen-partial-pressure gradient and temperature. At 900°C, oxygen permeability was $\approx 2.5 \text{ scc}\cdot\text{cm}^{-2}\cdot\text{min}^{-1}$ for a 2.9-mm-thick membrane and this value increases as membrane thickness decreases. We have fabricated tubular SrFeCo_{0.5}O_x membranes and operated them at 900°C for >1000 h during conversion of methane into syngas. The hydrogen ion (proton) transport properties of yttria-doped BaCeO₃ were investigated by impedance spectroscopy and open-cell voltage measurements. High proton conductivity and a high protonic transference number make yttria-doped BaCeO₃ a potential membrane for hydrogen separation.

^a Corresponding author, Tel: (630)252-4250, Fax: (630)252-3604,
e-mail: u_balachandran@qmgate.anl.gov

^b Energy Technology Division, Argonne National Laboratory, Argonne, Illinois 60439, USA.

^c School of Materials Science and Engineering, Georgia Institute of Technology, Atlanta, Georgia 30332, USA.

Key words: Mixed-Conductor, Gas Separation, Oxygen Permeation, Proton Conduction, Ceramic Membrane

1. INTRODUCTION

In recent years, mixed-conducting oxides, in which both ionic and electronic charge carriers exist, have received increased attention because of their technological importance in high-temperature electrochemical devices and in electrocatalysis. For example, they are used as sensors and as electrodes in solid-state fuel cells; if their ionic conductivity is high enough, they can be used as dense membranes for gas separation. It is generally accepted that mixed-conducting oxide membranes have great potential to meet the needs of many segments of the oxygen market. The applications envisioned range from small-scale oxygen pumps for medical applications to large-scale usage in combustion processes such as coal liquefaction.

In the early 1980s, Iwahara et al. [1-3] first reported protonic conduction in SrCeO_3 materials. Later, the BaCeO_3 system was extensively studied because of its higher conductivities [4-7]. Following their discovery by Teraoka et al. [8,9] in the late 1980s, mixed-conducting perovskites with combined electronic and oxide ionic conductivities and appreciable oxygen permeability have been investigated [10-15]. Recently, Balachandran et al. [16,17] have shown that Sr-Fe-Co oxides exhibit not only high combined electronic and oxygen ionic conductivities but also structural stability. Extruded tubes of these materials have been evaluated in a reactor operating at $\approx 850^\circ\text{C}$ to convert methane to syngas in the presence of a reforming catalyst. Methane conversion coefficients $>98\%$ [18,19] were observed, and some of the reactor tubes have been operated for more than 1000 h.

In this paper, we report our recent results on Sr-Fe-Co-O oxygen permeable and yttria-doped BaCeO₃ proton-conducting membrane materials. Oxygen permeation flux was measured as a function of oxygen partial pressure (p_{O_2}) difference and temperature. Oxygen permeation data obtained from an actual methane conversion reactor is compared with the steady-state oxygen permeation data measured with a gas-tight electrochemical cell. Hydrogen transport has been studied by impedance spectroscopy and open-cell voltage (OVC) methods.

2. EXPERIMENTAL

Oxygen-ion conductor SrFeCo_{0.5}O_x (SFC) samples were prepared by a solid-state reaction method with SrCO₃, Fe₂O₃, and Co(NO₃)₂·6H₂O as starting materials. Mixing and grinding were performed in isopropanol with zirconia medium. After drying, the mixtures were calcined at ≈850°C for 16 h in air with intermittent grinding. Phase purity was confirmed by X-ray diffraction (XRD). The resulting powders were pressed into pellets and sintered in air at 1200°C for 5 h. Sintered pellets were polished and used for permeation tests. Proton conductor BaCe_{0.95}Y_{0.5}O₃ (BCY) was also prepared by a solid-state-reaction method. Initial chemicals (BaCO₃, CeO₂ and Y₂O₃) were mixed in the desired mole ratios and ball-milled in isopropanol for at least 24 h and then calcined at 1000°C for 12 h in air. The obtained powders were ground and recalcined at 1200°C for 10 h in air. The resulting powders were examined by XRD, and pressed uniaxially with a 100-MPa load into pellets 22.5 mm in diameter and ≈2 mm thick. The pellets were then sintered in air at 1550°C for 10 h.

Total and oxygen ionic conductivities of SFC were measured as a function of p_{O_2} by conventional and electron-blocking four-probe methods [17,20], respectively. The experimental setup used to study oxygen permeation of SFC membranes has been reported earlier [21]. A sintered pellet of SFC was sealed to a yttria-stabilized zirconia (YSZ) crucible by a Pyrex glass seal. Oxygen-permeable electrodes were placed on the bottom and side of the YSZ crucible (as shown in Fig. 1). The bottom electrodes were used to pump oxygen from the gas-tight cell, while the other electrodes were used to detect the p_{O_2} inside the cell. The p_{O_2} inside the cell can be determined from the electromotive force (EMF), E , generated on the side wall of the YSZ crucible by solving the following equation:

$$p_{O_2}^{\text{II}} = p_{O_2}^{\text{I}} \exp\left(\frac{4FE}{RT}\right) \quad (1)$$

where $p_{O_2}^{\text{II}}$ and $p_{O_2}^{\text{I}}$ are the p_{O_2} values inside and outside the gas-tight cell, respectively. Other variables are as usual, i.e., F , Faraday's constant; R , gas constant; and T , absolute temperature.

The experimental setup for investigating proton transport in the BCY samples is illustrated in Fig. 2. Platinum mesh (#80) was cut to the appropriate size and attached to both polished sides of a sintered specimen. The specimen and platinum mesh were then heated to 150°C and kept at that temperature for 2 h, then heated at 850°C for 30 min for conditioning. Subsequently, the specimen was sealed with a glass sealant onto one end of the inner alumina tube of the setup [22]. The glass powder was mixed with ethylene glycol as binder and isopropyl alcohol as dispersant. The sealed

structure was first air-dried, then heated slowly (20°C/h ramp and 5 h dwell at 350°C) to burn out the binder, and finally devitrified at 780°C. The two-point method was used to measure the impedance spectra of the specimens and, thus, to determine the total conductivity. Ionic transference numbers were derived from OCV after exposing two sides of the specimen to different gaseous environments [23]. Gas flow rates were controlled to $\approx 100 \text{ scc}\cdot\text{min}^{-1}$.

3. RESULTS AND DISCUSSION

3.1. Oxygen Ionic Conductor SFC

By using the conventional four-probe and electron-blocking four-probe methods, we measured the total and ionic conductivities of SFC. Electronic conductivity can be deduced by subtracting ionic conductivity from the total conductivity. The results obtained in air at high temperatures showed that the electronic and ionic conductivities of the SFC sample are comparable, or, in another words, their ratio is close to unity. This makes SFC materials unique among other mixed conductors, in which electronic transference numbers are much greater than ionic transference numbers, or vice versa. The oxygen permeation flux j_{O_2} , through a membrane of thickness L can be deduced from conductivity data [20] as follows:

$$j_{\text{O}_2} = \frac{RT}{16F^2L} \int_{p_{\text{O}_2}^l}^{p_{\text{O}_2}^h} \sigma_{\text{tot}} t_{\text{ion}} t_{\text{el}} d \ln(p_{\text{O}_2}) \quad (2)$$

where σ_{tot} is total conductivity, t_{ion} is ionic transference number, and t_{el} is electronic transference number. The oxygen permeability of SFC was determined by using a gas-tight cell described earlier [20]. Reducing oxygen environments were achieved by pumping oxygen out from the gas-tight cell by

pumping electrodes on the YSZ crucible. Oxygen permeates the SFC disk membrane because of the p_{O_2} difference. Under steady-state conditions, the amount of oxygen that enters the cell (by permeating the specimen disk) is equal to that pumped out by the YSZ oxygen pump. Therefore, the flow of oxygen through the specimen can be determined by the current applied to the YSZ oxygen pump. Oxygen permeation flux j_{O_2} is related to the applied current I by

$$j_{O_2} = \frac{I}{4FS} \quad (3)$$

where S is the effective cross-sectional area of the specimen.



Oxygen permeation flux through a 2.9-mm-thick SFC disk, obtained by using Eq. 3, the experimental data of a steady-state pumping current I , and geometric parameters of the specimen, is plotted in Fig. 3 as a function of the p_{O_2} inside the gas-tight cell. Flowing air ($p_{O_2} = 0.21$ atm) was the reference atmosphere during oxygen permeation experiments. Figure 3 shows that j_{O_2} increases dramatically in the range between $p_{O_2} = 0.21$ and $\approx 10^{-3}$ atm, and its slope becomes flatter when p_{O_2} inside the cell is reduced further. Results on oxygen permeability at various p_{O_2} gradients and temperatures show that j_{O_2} increases, as expected, with temperature and p_{O_2} gradients. At 900°C, oxygen permeability was found to be ≈ 2.5 ssc·cm⁻²·min⁻¹ for a 2.9-mm-thick specimen and increases as membrane thickness decreases.

Sintered thin-wall tubes of SFC were tested in a methane conversion reactor for >1000 h [18,19,24]. Oxygen permeation flux determined from reactor experiments (with tubular SFC membrane) [24], calculated from conductivity data [20], and determined from out-of-reactor experiments in a gas-tight electrochemical cell have been plotted in Fig. 4 as a function of temperature. Results from these three independent experiments are in good agreement.

3.2. Protonic Conductor BCY

Figure 5 shows the total conductivity of BCY in various atmospheres, as determined by impedance spectroscopy. The total conductivity of 5% yttria-doped BaCeO₃ was low in pure argon, even at high temperatures ($\geq 600^\circ\text{C}$), but increased slightly with addition of 2% water vapor in the surrounding environment. The total conductivity of BCY was found to be higher in pure oxygen than in pure argon. At low temperatures, addition of water increases the total conductivity, whereas at high temperatures, total conductivity slightly decreased when water vapor was added. Total conductivity of the BCY sample increases from $\approx 5 \times 10^{-3} \Omega^{-1} \cdot \text{cm}^{-1}$ to $\approx 2 \times 10^{-2} \Omega^{-1} \cdot \text{cm}^{-1}$ at 600°C .

Transference numbers in an oxygen-containing atmosphere were determined by using the following concentration cells:



As shown in Table I, the measured OCVs of Cell 1 decreased as temperature increased, indicating that the electronic transference number

increases with temperature. In Cell 2, where the OCV was solely due to the partial-pressure difference of water vapor, the OCVs are directly related to the protonic transference number according to following equation [23]:



$$V_{oc} = \frac{RT}{4F} \left[t_{ion} \ln \left(\frac{p_{O_2}^{II}}{p_{O_2}^I} \right) - 2t_{H^+} \ln \left(\frac{p_{H_2O}^{II}}{p_{H_2O}^I} \right) \right] \quad (4)$$

where $t_{ion} = t_{H^+} + t_{O^{2-}}$ is the ionic transference number. The obtained transference numbers are plotted in Fig. 6, which shows that the protonic transference number decreases whereas the electronic transference number increases with increasing temperature.

Table I. Open-cell voltages (mV) of oxygen/water vapor concentration cells at various temperatures.

Temperature (°C)	Cell 1	Cell 2	Cell 3
500	32.0	14.8	-48.2
600	28.0	19.9	-36.8
700	27.2	22.1	-31.3
800	26.4	22.3	-29.7

Transference numbers in hydrogen/water vapor atmospheres were studied by employing the following cells:



The obtained OCVs are listed in Table II, and the ionic transference numbers were derived by solving following equation [23]:

$$V_{OC} = \frac{RT}{4F} \left[-t_{ion} \ln \left(\frac{P_{H_2}^{II}}{P_{H_2}^I} \right) + t_{O^{2-}} \ln \left(\frac{P_{H_2O}^{II}}{P_{H_2O}^I} \right) \right] \quad (5)$$

The obtained transference numbers are plotted in Fig. 7. Again, the protonic transference number decreases whereas the electronic transference number increases with increasing temperature. The protonic transference number decreases from 0.87 to 0.63, whereas the oxygen transference number increases from 0.03 to 0.15 as temperature increases from 600 to 800°C in the hydrogen/water vapor atmospheres.

Table II. Open-cell voltages (mV) of hydrogen/water vapor concentration cells at various temperatures.

Temperature (°C)	Cell 4	Cell 5	Cell 6
500	-63.13	-62.01	64.02
600	-66.43	-64.48	68.14
700	-70.55	-65.17	75.57
800	-76.39	-69.11	83.26

4. CONCLUSIONS

A mixed-conducting ceramic, SrFeCo_{0.5}O_x (SFC), has been developed. It exhibits high electronic and oxygen ionic conductivities, and its electronic and ionic transference number are comparable, making it unique among other mixed conductors. The oxygen permeability of membranes made of the SFC material is high. Direct measurement of oxygen permeation flux with a

gas-tight electrochemical cell is in good agreement with the values obtained from other independent oxygen permeation experiments and with values calculated from conductivity data. At 900°C, oxygen permeation flux, as determined with a gas-tight electrochemical cell, was $\approx 2.5 \text{ scc}\cdot\text{cm}^{-2}\cdot\text{min}^{-1}$ for a 2.9-mm-thick specimen. Oxygen permeability of the SFC membranes increases with increasing temperature and decreasing membrane thickness.

Transport properties of 5% yttria-doped BaCeO_3 were studied with impedance spectroscopy and open-cell voltage (OCV) measurements. Proton conduction has been observed in this material in hydrogen-containing atmospheres. Proton and oxygen transference numbers, deduced from OCV data, showed that the protonic transference numbers decrease whereas the electronic transference number increase with increasing temperature. Total conductivity of the BCY sample increased from $\approx 5 \times 10^{-3} \Omega^{-1}\cdot\text{cm}^{-1}$ to $\approx 2 \times 10^{-2} \Omega^{-1}\cdot\text{cm}^{-1}$ at 600°C, whereas the protonic transference number decreased from 0.87 to 0.63 and the oxygen transference number increased from 0.03 to 0.15 as temperature increased from 600 to 800°C in hydrogen/water vapor atmospheres.


5. ACKNOWLEDGMENTS

This work was supported by the U.S. Department of Energy, Federal Energy Technology Center, under Contract W-31-109-Eng-38.


REFERENCES:

1. H. Iwahara, T. Esaka, H. Uchida, and N. Maeda, *Solid State Ionics*, **3/4**, 359 (1981).
2. T. Yajima, H. Suzuki, T. Yogo, and Iwahara, *Solid State Ionics*, **51**, 101 (1992).
3. H. Iwahara, *Solid State Ionics*, **77**, 289 (1995).
4. J. F. Liu and A. S. Nowick, *Mater. Res. Soc. Symp. Proc.*, **210**, 673 (1991).
5. N. Bonanos, *Solid State Ionics*, **53-56**, 967 (1992).
6. N. Taniguchi, K. Hato, J. Niikura, and T. Gamo, *Solid State Ionics*, **53-56**, 998 (1992).
7. D. A. Steveson, N. Jiang, R. M. Buchanan, and F. E. G. Henn, *Solid State Ionics*, **62**, 279 (1993).
8. Y. Teraoka, H. Zhang, S. Furukawa, and N. Yamazoe, *Chem. Lett.*, 1743 (1985).
9. Y. Teraoka, H. Zhang, K. Okamoto, and N. Yamazoe, *Mater. Res. Bull.*, **23**, 51 (1988).
10. Y. Nigara, J. Mizusaki, and M. Ishigame, *Solid State Ionics*, **79**, 208 (1995).
11. H. Arashi, H. Naito, and M. Nakata, *Solid State Ionics*, **76**, 315 (1995).
12. R. H. E. Van Doorn, H. Kruidhof, H. J. M. Bouwmeester, and A. J. Burggraaf, *Mater. Res. Soc. Symp. Proc.*, **369**, 377 (1991).
13. Y. Teraoka, T. Nobunaga, K. Okamoto, N. Miura, and N. Yamazoe, *Solid State Ionics*, **48**, 207 (1991).
14. H. W. Brinkman, H. Kruidhof, and A. J. Burggraaf, *Solid State Ionics*, **68**, 173 (1994).
15. U. Balachandran, S. L. Morissette, J. T. Dusek, R. L. Mieville, R. B. Poeppel, M. S. Kleefisch, S. Pei, T. P. Kobylinski, and C. A. Udovich, *Proc. Coal Liquefaction and Gas Conversion Contractor Review Conf.*, S. Rogers et


- al., editors, **Vol. 1**, pp. 138-160, U.S. Dept. of Energy, Pittsburgh Energy Technology Center (1993).
16. U. Balachandran, M. S. Kleefisch, T. P. Kobylinski, S. L. Morissette, S. Pei, U.S. Patent 5580497, Dec. 1996.
 17. B. Ma, J.-H. Park, C. U. Segre, and U. Balachandran, *Mater. Res. Soc. Symp. Proc.*, **393**, 49 (1995).
 18. U. Balachandran, T. J. Dusek, S. M. Sweeney, R. B. Poeppel, R. L. Mieville, P. S. Maiya, M. S. Kleefisch, S. Pei, T. P. Kobylinski, C. A. Udovich, and A. C. Bose, *Am. Ceram. Soc. Bull.*, **74**, 71 (1995).
 19. U. Balachandran, J. T. Dusek, P. S. Maiya, B. Ma, R. L. Mieville, M. S. Kleefisch, and C. A. Udovich, *Catalysis Today*, **36**, 265 (1997).
 20. B. Ma, U. Balachandran, and J.-H. Park, *J. Electrochem. Soc.*, **143**, 1736 (1996).
 21. B. Ma, U. Balachandran, C.-C. Chao, and J.-H. Park, *Ceram. Trans. Series Am. Ceram. Soc.*, **Vol. 73**, p. 169 (Westerville, OH, 1997).
 22. K. L. Ley, M. Krumplet, R. Kumar, J. H. Meiser, and I. Bloom, *J. Mater. Res.*, **11**, 1489 (1996).
 23. J. Guan, S. E. Dorris, U. Balachandran, and M. Liu, *Solid State Ionics*, in press (1997).
 24. P. S. Maiya, U. Balachandran, J. T. Dusek, R. L. Mieville, M. S. Kleefisch, and C. A. Udovich, *Solid State Ionics*, in press (1997).

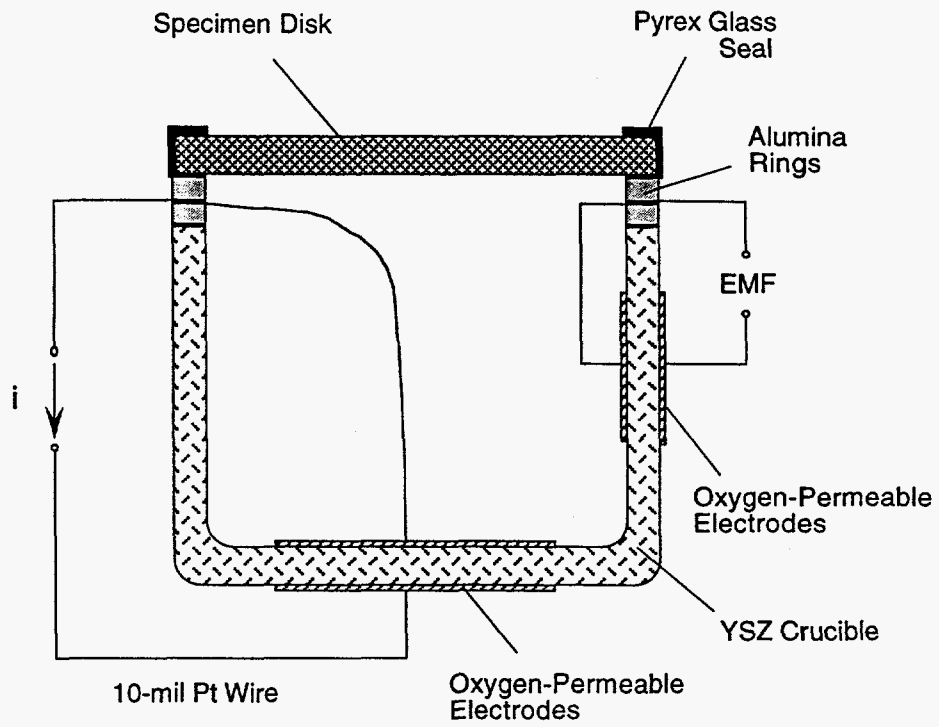


1. Schematic drawing of cross-sectional view of gas-tight electrochemical cell used to measure oxygen permeability.

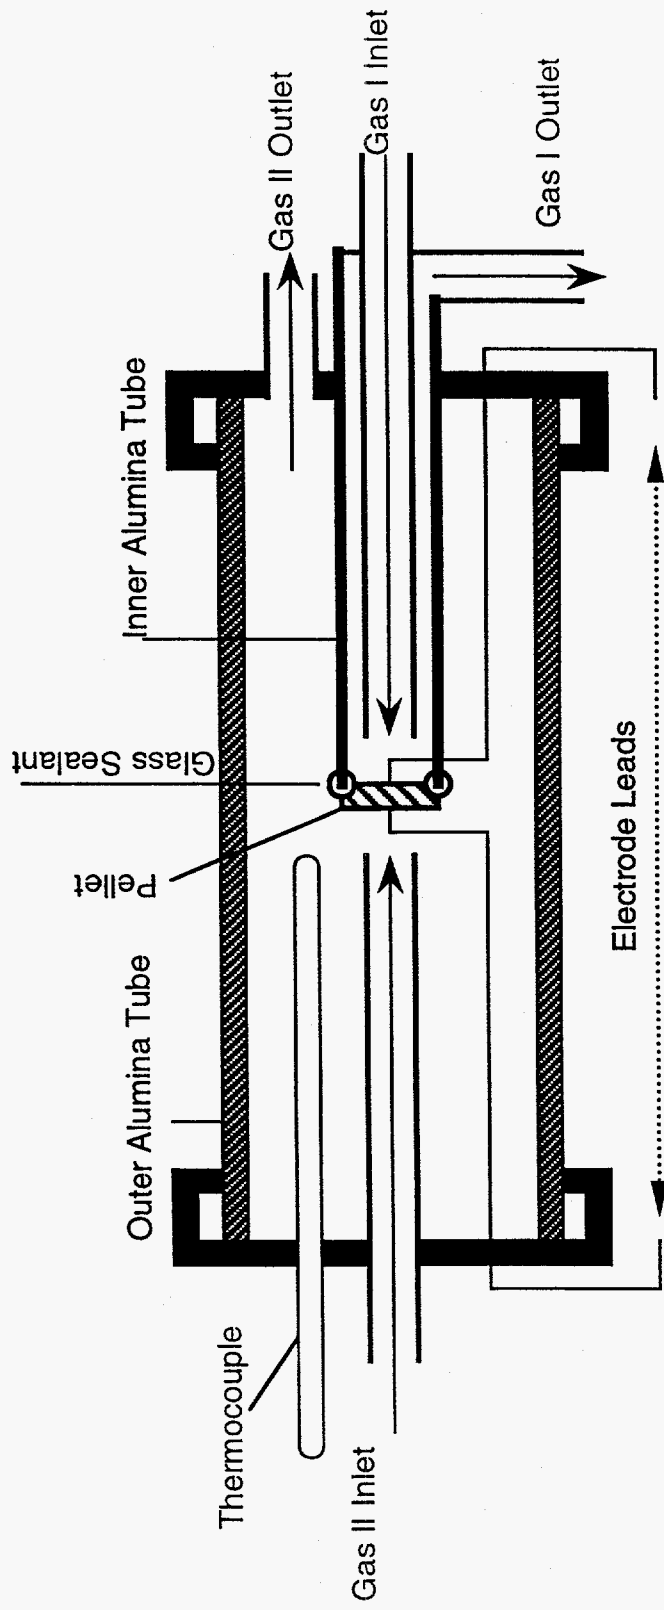


2. Schematic illustration of experimental setup for testing proton conductors.

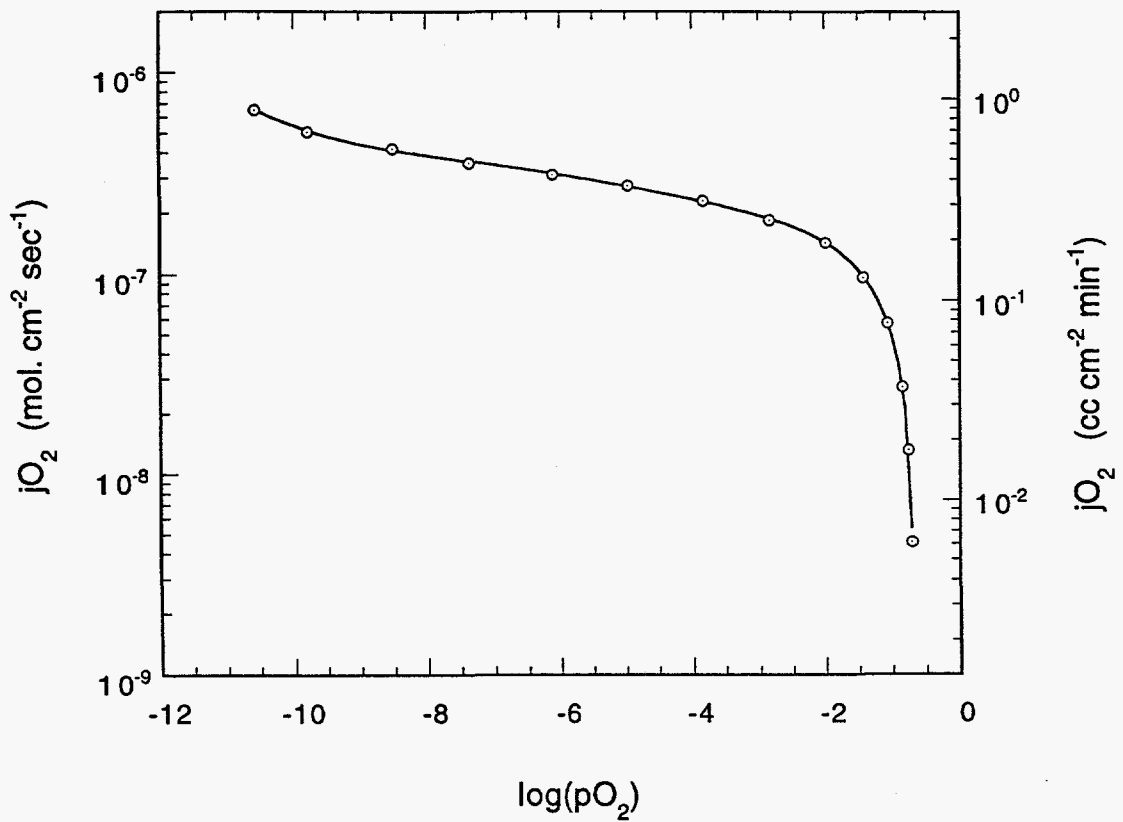


- Oxygen permeation flux as a function of oxygen partial pressure inside a gas-tight cell. Specimen thickness = 2.9 mm.

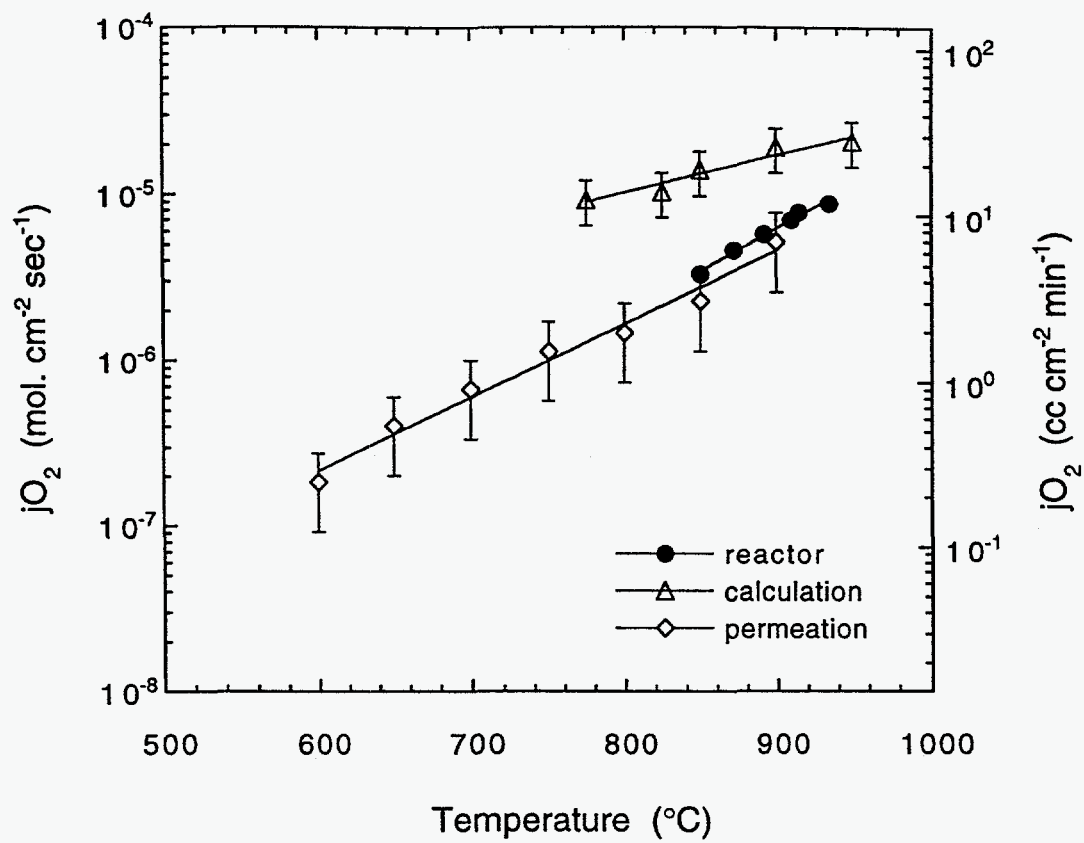


4. Temperature dependence of oxygen permeation flux determined by three methods.

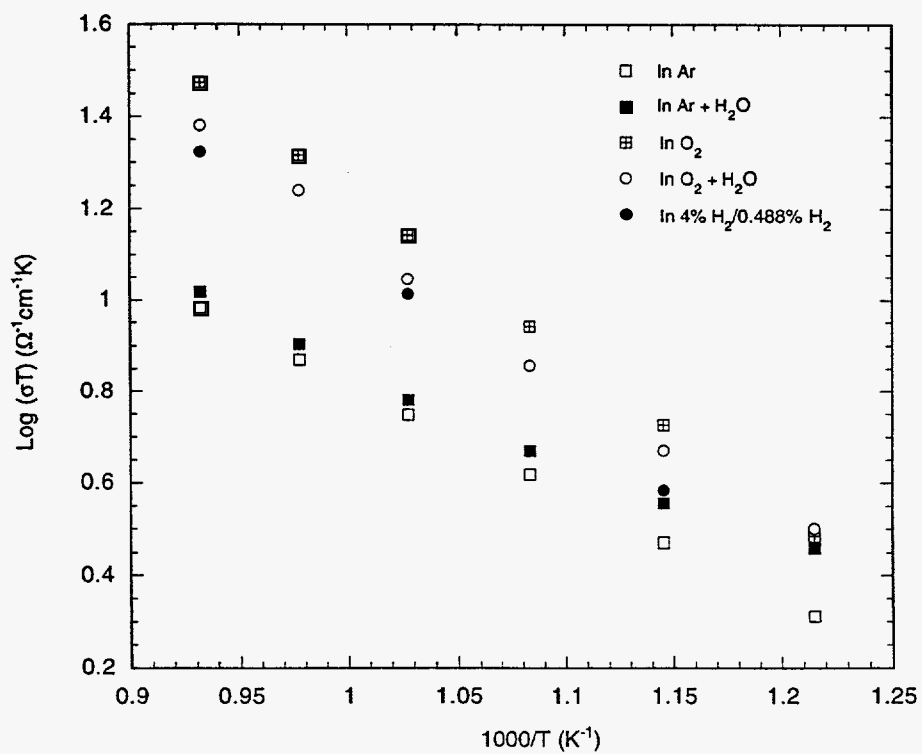

5. Total conductivity of 5% yttria-doped BaCeO₃ sample measured in various atmospheres.

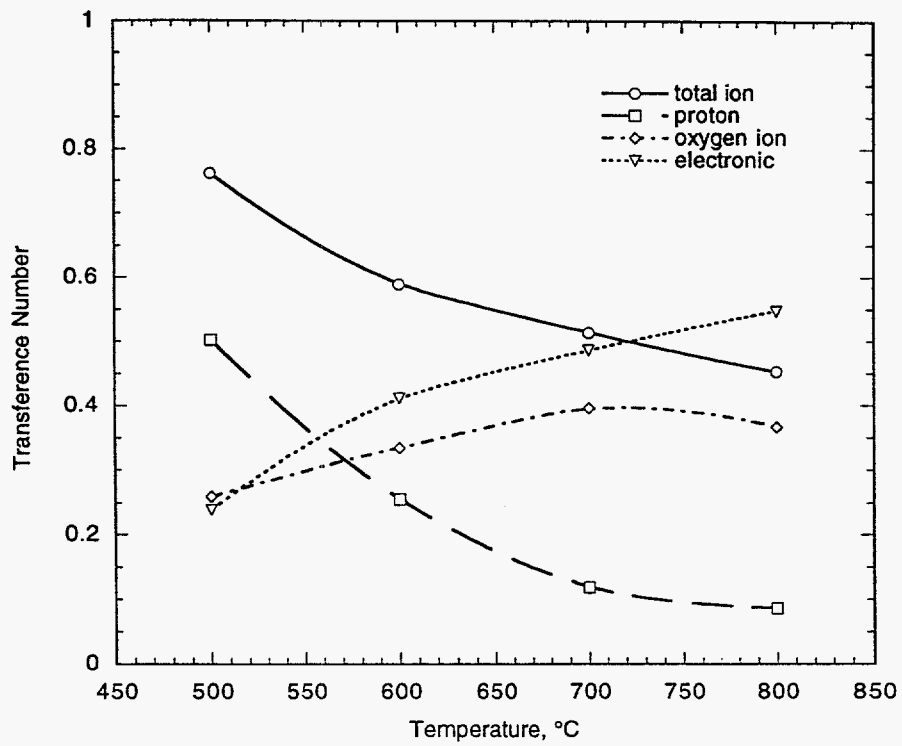

6. Transference numbers of 5% yttria-doped BaCeO₃ samples as determined in oxygen-containing environments.

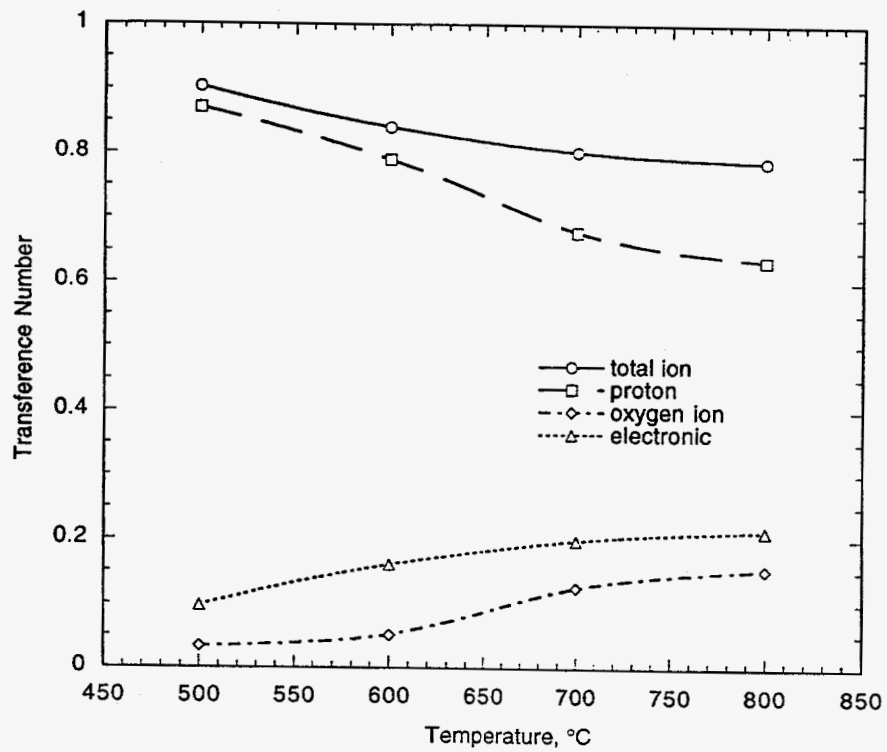

7. Transference numbers of 5% yttria-doped BaCeO₃ samples as determined in hydrogen-containing environments.