


MASTER

ORNL-2816  
UC-4 Chemistry-General

REDUCTION OF CUPRIC OXIDE BY HYDROGEN.  
II. CONVERSION OF HYDROGEN TO  
WATER OVER FIXED BEDS

W. D. Bond  
W. E. Clark

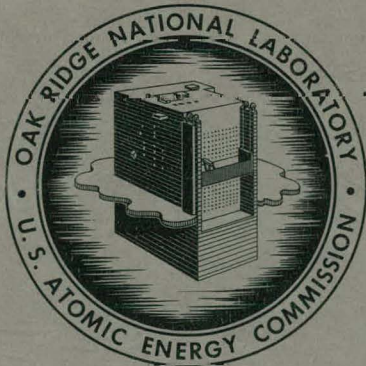

**OAK RIDGE NATIONAL LABORATORY**

operated by

**UNION CARBIDE CORPORATION**

for the

**U.S. ATOMIC ENERGY COMMISSION**

## DISCLAIMER

**This report was prepared as an account of work sponsored by an agency of the United States Government. Neither the United States Government nor any agency Thereof, nor any of their employees, makes any warranty, express or implied, or assumes any legal liability or responsibility for the accuracy, completeness, or usefulness of any information, apparatus, product, or process disclosed, or represents that its use would not infringe privately owned rights. Reference herein to any specific commercial product, process, or service by trade name, trademark, manufacturer, or otherwise does not necessarily constitute or imply its endorsement, recommendation, or favoring by the United States Government or any agency thereof. The views and opinions of authors expressed herein do not necessarily state or reflect those of the United States Government or any agency thereof.**

## **DISCLAIMER**

**Portions of this document may be illegible in electronic image products. Images are produced from the best available original document.**



Printed in USA. Price \$0.75 . Available from the  
Office of Technical Services  
Department of Commerce  
Washington 25, D.C.

#### LEGAL NOTICE

This report was prepared as an account of Government sponsored work. Neither the United States, nor the Commission, nor any person acting on behalf of the Commission:

- A. Makes any warranty or representation, expressed or implied, with respect to the accuracy, completeness, or usefulness of the information contained in this report, or that the use of any information, apparatus, method, or process disclosed in this report may not infringe privately owned rights; or
- B. Assumes any liabilities with respect to the use of, or for damages resulting from the use of any information, apparatus, method, or process disclosed in this report.

As used in the above, "person acting on behalf of the Commission" includes any employee or contractor of the Commission, or employee of such contractor, to the extent that such employee or contractor of the Commission, or employee of such contractor prepares, disseminates, or provides access to, any information pursuant to his employment or contract with the Commission, or his employment with such contractor.

Contract No. W-7405-eng-26

CHEMICAL TECHNOLOGY DIVISION

Chemical Development Section B

REDUCTION OF CUPRIC OXIDE BY HYDROGEN. II. CONVERSION OF  
HYDROGEN TO WATER OVER FIXED BEDS

W. D. Bond

W. E. Clark

Technician: J. F. Talley

DATE ISSUED

FEB 12 1960

OAK RIDGE NATIONAL LABORATORY  
Oak Ridge, Tennessee  
Operated by  
UNION CARBIDE CORPORATION  
for the  
U. S. ATOMIC ENERGY COMMISSION

ABSTRACT

The conversion of  $H_2$  to  $H_2O$  by reduction of  $CuO$  in fixed beds was quite rapid at  $300^\circ C$ . Residence times required for 99% conversion in a 1-in.-dia bed were 0.6 and 1.2 sec for 30% hydrogen-70% argon and 10% hydrogen-90% argon mixtures, respectively, at a total gas flow of 1 liter/min. The  $CuO$  used was 25-mil-dia wires with a surface area of  $0.019 \text{ m}^2/\text{g}$ . The residence time required for a given value of conversion decreased about 10% when the total flow rate was increased from 1 to 1.7 liters/min, which indicates that the reduction is mass-transfer controlled to a slight extent under the experimental conditions used.

CONTENTS

	<u>Page</u>
1.0 INTRODUCTION	4
2.0 DISCUSSION OF RESULTS	4
2.1 Temperature and Mesh Size	4
2.2 Bed Length	6
2.3 Residence Time	6
3.0 EXPERIMENTAL	9
3.1 Fixed Bed Studies	9
3.2 Thermogravimetric Studies	11
4.0 REFERENCES	12
5.0 APPENDIX	13
5.1 Experimental Parameters	13
5.2 Data Obtained	14
5.3 Sample Calculations of Residence Time	15

## 1.0 INTRODUCTION

The purpose of this investigation was to determine the conditions under which hydrogen can be quantitatively recovered from mixtures of gases by oxidation over fixed beds of CuO. The recovery of hydrogen from hydrogen-argon mixtures was studied initially, with the plan that the specific effects of chemically active diluent gases, such as O<sub>2</sub> and CO, would be determined later.

A convenient way to recover hydrogen is to convert it to water and condense the water vapor. The two most widely known methods of converting hydrogen to water are direct combination of H<sub>2</sub> and O<sub>2</sub> at low temperatures over a catalytic surface such as platinized asbestos and bed reduction of CuO at temperatures from 200 to 400°C. The bed reduction of copper oxide was chosen as the possibility with the best chance of success since catalytic surfaces for H<sub>2</sub> and O<sub>2</sub> recombination are easily poisoned by impurities in the gas. The effects of temperature and of particle size were confirmed by thermogravimetric studies.

Although the literature<sup>1-8</sup> contains a variety of data on the reduction of CuO, it is necessary to have information on several parameters in order to design a plant-scale facility. Parameters included in this study were mesh size of copper oxide, hydrogen concentration in the inlet gas stream, temperature, flow rate, and bed length.

The authors express sincere appreciation to R. A. Suehrstedt, R. H. Wick, and D. W. Jeffrey of the Massachusetts Institute of Technology Engineering Practice School who performed a large portion of the experimental work and who made many helpful suggestions. The authors also acknowledge the help of the groups headed by W. R. Laing, J. R. Sites, and R. L. Sherman of the Analytical Chemistry Division who made surface area determinations, gas analyses, and x-ray identifications, respectively.

## 2.0 DISCUSSION OF RESULTS

The conversion of H<sub>2</sub> to H<sub>2</sub>O on a fixed bed of CuO increased with increasing bed length, temperature, hydrogen/argon ratio and decreasing mesh size of CuO. Bed residence time of the gas phase was found to be a useful comparative parameter. Thermodynamic data were taken from the literature to show theoretical conversion factors and the heat of reaction.

### 2.1 Temperature and Mesh Size

The percentage conversion of H<sub>2</sub> to H<sub>2</sub>O increased with temperature in both fixed bed and thermogravimetric (Figs. 1 and 2) studies (see Sect. 3.0) and decreased with mesh size of the CuO (Fig. 3). Reduction was rapid at temperatures approaching 300°C. The thermogravimetric data



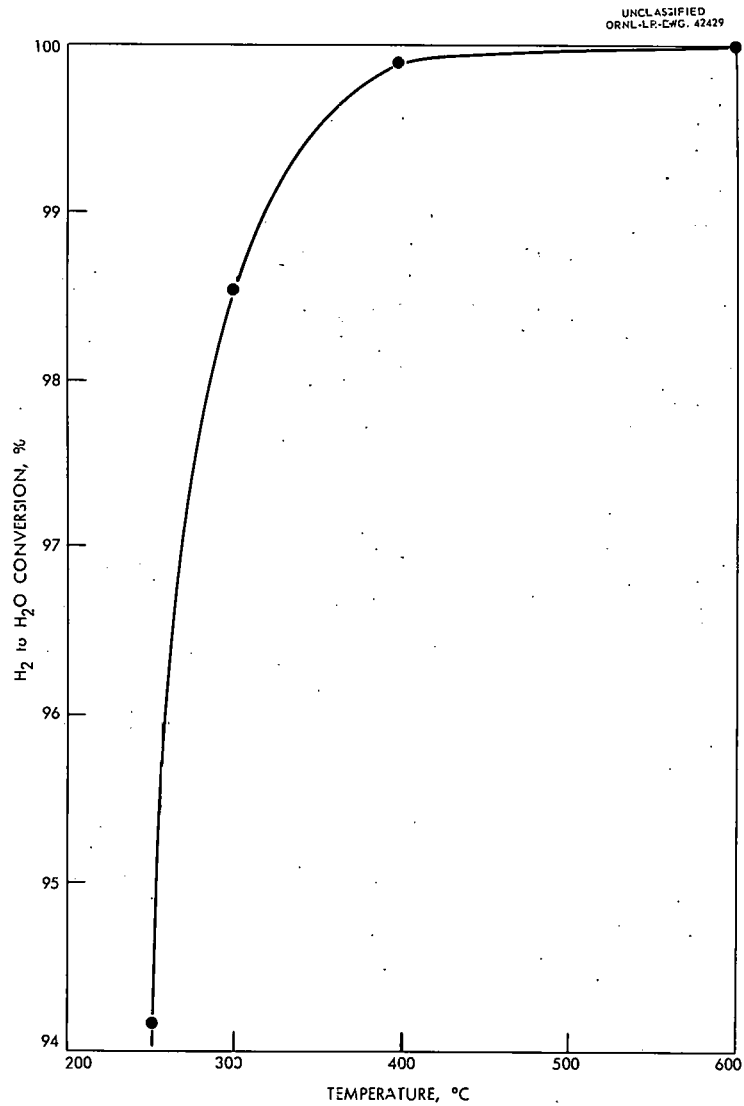


Fig. 1. Effect of temperature on oxidation of hydrogen by a fixed bed of CuO. Bed dimensions: 1 in. dia, 6 in. long. 25-mil-dia CuO wire, 0.019 m<sup>2</sup>/g. Reduction gas: 66% H<sub>2</sub> - 33% argon, 150 cc/min.

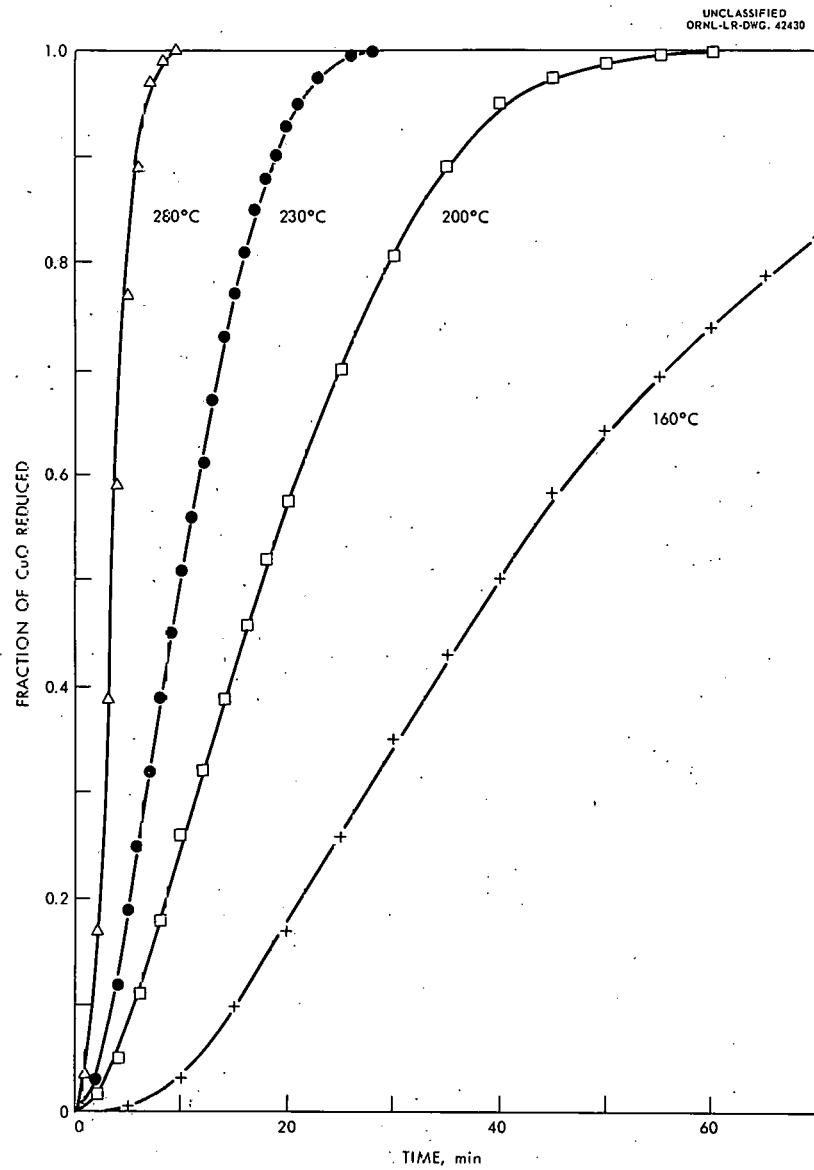


Fig. 2. Effect of temperature on the CuO-H<sub>2</sub> reaction. Thermogravimetric study. H<sub>2</sub>, 2000 cc/min; 1.00 g of wire-form CuO (25 mil dia), 0.019 m<sup>2</sup>/g.

are plotted as weight fraction of CuO reduced vs time since the total reduction time was independent of the mass of the oxide. Little appeared to be gained by crushing the commercial wire-form oxide, since at 280°C the reduction rate of the uncrushed oxide was adequate. Theoretical conversion was not achieved in a CuO bed 6 in. long and 1 in. dia at any of the temperatures investigated (Figs. 1 and 4).

## 2.2 Bed Length

The percentage conversion of H<sub>2</sub> increased as the bed length was increased from 0.25 to 1.25 in. (Fig. 5). Varying the hydrogen concentration from 1 to 30% did not change the characteristics of the reduction shown by the curves in Fig. 5 for 30%. Complete data are tabulated in the appendix (Sects. 5.1 and 5.2).

In general, the reduction curves show an induction period, then an increase in reduction rate to a maximum, and finally a slow decline. These curves are of the general type that would be predicted from previous kinetic studies.<sup>1-8</sup> The reduction behavior can be explained by reaction at active centers on the copper oxide followed by rapid growth of the active nuclei as a result of the initial reaction. Thus, active centers are first multiplied at the bed inlet where hydrogen initially meets the copper oxide. Because of the rapid growth of nuclei, active centers are soon being created at a rate such that a sufficient number are available to remove most of the hydrogen at the bed inlet before it progresses very far down the bed. Under such conditions the rate of conversion is nearly constant. Finally, as the active zone approaches the end of the bed, the number of active centers begins to decrease rapidly and the conversion rate drops abruptly. The length of curve corresponding to a near-constant reduction rate should increase with increasing bed length according to this theory, and this was observed experimentally. Also, visual observation showed most of the reaction taking place at the bed entrance and a sharp band between the copper and the copper oxide. There were a few scattered specks of copper in the CuO about 1 mm from the CuO-Cu boundary.

In an actual process the induction period could be eliminated by pre-treating the bed with hydrogen. Hydrogen would be passed through the bed at reduction temperature until water was produced abundantly and then the hydrogen would be shut off. The bed would be flushed free of H<sub>2</sub> and H<sub>2</sub>O by an inert gas and stored under inert gas for future use. Several copper oxide beds were treated in this way and stored overnight under argon. The following day the beds were immediately reactive to hydrogen, showing no evidence of an induction period.

## 2.3 Residence Time

The percentage conversion of hydrogen increased with residence time of the gas stream in the void volume of the CuO bed at 300°C (Fig. 6). The points on the curve are accurate to ±10%, and were calculated from

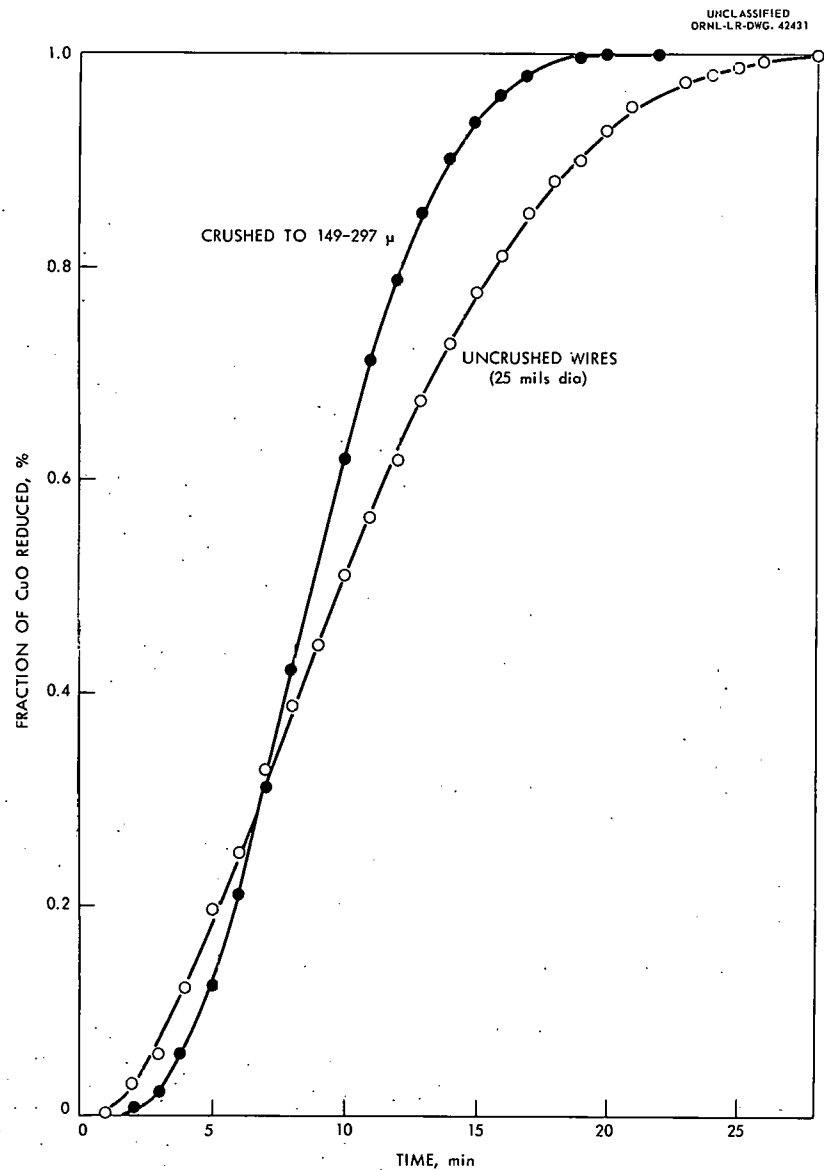


Fig. 3. Effect of particle size on the  $\text{CuO-H}_2$  reaction. Thermogravimetric study. Temperature  $200^\circ\text{C}$ ;  $\text{H}_2$ , 2000 cc/min; 1.00 g of  $\text{CuO}$ .

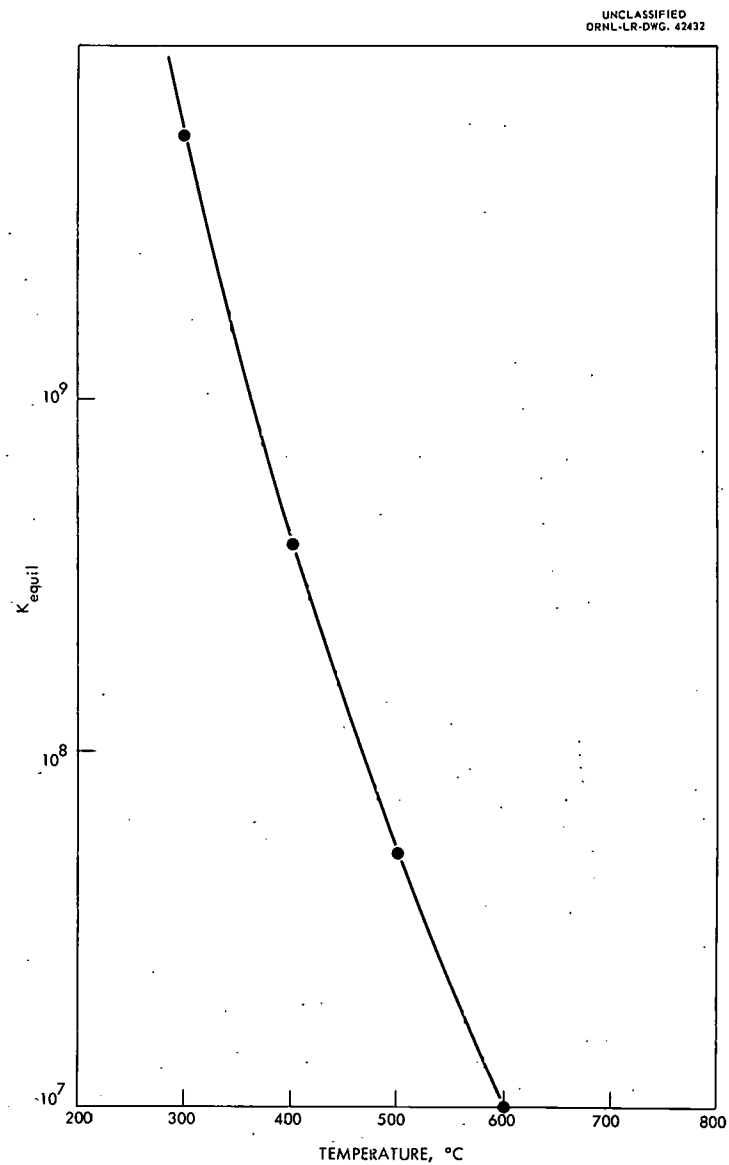


Fig. 4. Thermodynamic equilibrium constants for the reaction  $\text{CuO} + \text{H}_2 \rightleftharpoons \text{Cu} + \text{H}_2\text{O}$ . Data from Dustman's tabulation.<sup>10</sup>  $K = P_{\text{H}_2\text{O}}/P_{\text{H}_2}$ ;  $\Delta H$  at  $25^\circ\text{C} = 22.94$  kcal.

UNCLASSIFIED  
ORNL-LR-DWG. 42433

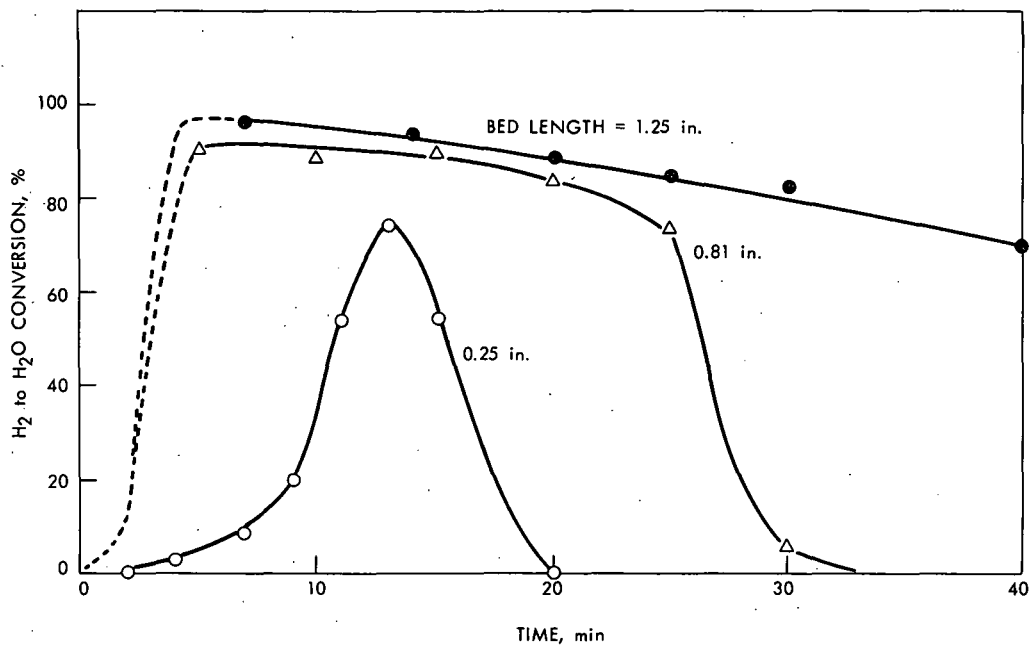


Fig. 5. Effect of bed length on conversion of hydrogen to water. Reduction gas: 30% H<sub>2</sub> - 70% argon, 1200 cc/min. Temperature 300°C; bed dia 1 in.; 34 g of Cu per inch; 25-mil-dia CuO wires, 0.019 m<sup>2</sup>/g.

UNCLASSIFIED  
ORNL-LR-DWG. 42434

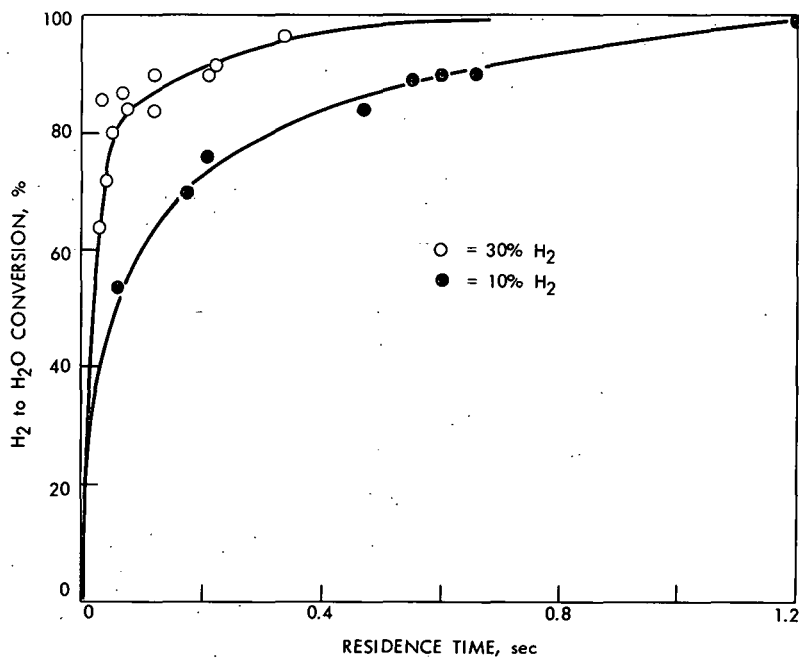


Fig. 6. Effect of residence time in the conversion of hydrogen to water in a fixed bed of CuO. Temperature 300°C. Bed dia, 1 in. 25-mil-dia CuO wire, 0.019 m<sup>2</sup>/g.

the peak values and constant conversion sections of the previously determined percentage conversion vs time curves. The details of the calculations are shown in the appendix (Sect. 5.2). Relatively short residence times were required for 99% conversion, about 1.2 and 0.6 sec for 10 and 30% H<sub>2</sub> concentrations, respectively. For long residence times the curves approach 100% conversion asymptotically. Thus the residence time required for 99% conversion is about twice that for 90% conversion.

One experimental determination was made with 1% H<sub>2</sub> in order to observe the order-of-magnitude effect of a fairly low inlet H<sub>2</sub> concentration. With 0.4 sec residence time and a temperature of 300°C, conversion was not very different from that with 10% H<sub>2</sub>:

Inlet H <sub>2</sub> Concentration, %	H <sub>2</sub> Conversion, %
1	76
10	84
30	97

This indicates that extremely long residence times will not be required for the conversion of moderately dilute H<sub>2</sub> streams.

The flow rate had a minor effect on H<sub>2</sub> conversion. Increasing the total flow rate of the 10% H<sub>2</sub> gas stream to 1670 cc/min increased the conversion 15% above that at 1000 cc/min. This increase, which is slightly greater than the experimental error (+ 10%), indicates that the reduction is to a slight degree mass-transfer controlled under these conditions.

### 3.0 EXPERIMENTAL

#### 3.1 Fixed Bed Studies

The experimental apparatus is shown schematically in Fig. 7. Hydrogen and argon were metered through calibrated rotameters and mixed in a Y tube. When the flow rate reached steady state, the flow was diverted through a vertically supported silica reaction tube containing a packed bed of CuO of known weight and length. The reaction tube was 18 in. long and 15/16 in. i.d. Heating was by a split-tube electric furnace mounted vertically around the reaction tube. After leaving the reaction tube, the gases were passed through a drying bulb containing indicating Drierite before entering the exit sample bottles. Inlet and exit gas samples were taken in 100- or 300-cc sample bottles by appropriate stopcock arrangements. Sampling times varied from 2 to 45 min depending on the bed length and inlet hydrogen concentrations.

The inlet gas was preheated in the upper part of the reduction tube with electrical heating tape. Wads of glass wool were placed at three equally spaced points along the preheated zone to induce turbulence and thus assure complete mixing and uniform temperature. The inlet gas temperature was measured by a glass-encased thermocouple placed in the glass

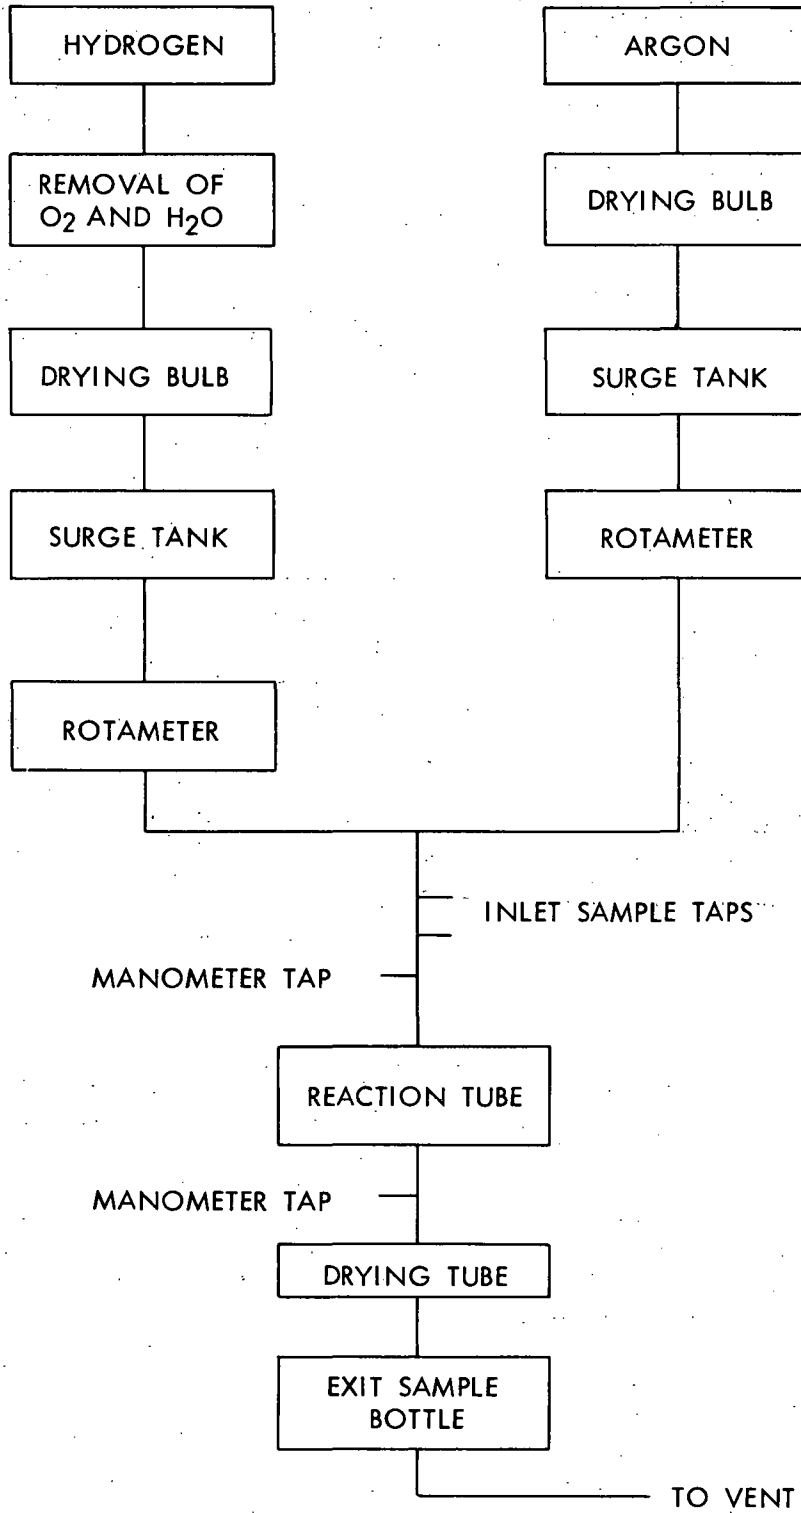


Fig. 7. Block diagram of apparatus.



wool packing above the bed. The temperature of the furnace was controlled by an auxiliary thermocouple placed against the outside of the reaction tube at the bed-gas interface.

In order to achieve a cylindrical bed of CuO with well-defined edges, approximately 1 in. of sand was placed on a glass wool support in the tube. The copper oxide was placed on the sand. Pressure taps were located at points immediately before and after the bed, and the pressures at these points were measured by open-end manometers. The manometer fluid was Meriam Red Oil, sp. gr. 0.827. The pressure drop across the bed was approximately 5 cm of the oil and was independent of the bed length.

The copper oxide was obtained from Mallinckrodt as the reagent grade wire form and was used as obtained. The wires were about 20 mils dia and their length varied from about 1 to 10 mm. Chemical analysis showed 83.8% Cu. The only impurities found by qualitative x-ray diffraction analysis were metallic copper and Cu<sub>2</sub>O. The nitrogen adsorption surface area of the material was 0.019 m<sup>2</sup>/g.

Electrolytic hydrogen was used and was purified of O<sub>2</sub> and H<sub>2</sub>O by being passed through a Deoxo unit and a Drierite bulb before entering the reaction tube. The argon received only the drying treatment.

### 3.2 Thermogravimetric Studies

The experimental technique and apparatus have been discussed elsewhere.<sup>8-9</sup> One-gram samples of CuO and a hydrogen flow rate of 2000 cc/min were used.

#### 4.0 REFERENCES

1. R. N. Pease and H. S. Taylor, "Reduction of Cupric Oxide by Hydrogen," J. Am. Chem. Soc., 43: 2179 (1921).
2. A. J. Larson and F. E. Smith, "The Synthesis of Water over Nickel and Copper Catalysts," J. Am. Chem. Soc., 47: 346 (1925).
3. Y. Okayama, "The Reduction of Copper Oxide," J. Soc. Chem. Ind. Japan, 31: 300 (1928) (Chem. Abs., 23: 2873).
4. G. I. Chufarov et al., "Inhibiting Effect of Gaseous Reduction Products on the Rate of Reduction of CuO by H<sub>2</sub> and CO<sub>2</sub>," Zur. Fiz. Khim., 26: 31 (1952) (Chem. Abs., 47: 4712).
5. S. Hasegawa, "Formation of the Reaction of Nuclei in the Reduction of CuO by Hydrogen," Proc. Imp. Acad Tokyo, 19: 393 (1943).
6. J. S. Lewis, "The Reduction of Copper Oxide by Hydrogen," J. Chem. Soc., 1932: 820.
7. M. M. Pavylunchenko and Y. S. Rubinchik, "The Reduction of Cupric Oxide with Hydrogen," J. Appl. Chem. USSR, 24: 751 (1951).
8. W. D. Bond and W. E. Clark, "Reduction of Cupric Oxide by Hydrogen. I. Fundamental Kinetics," ORNL-2815 (in press).
9. L. M. Ferris, "Kinetics of the Reaction of Uranium Tetrafluoride and Oxygen," Ind. Eng. Chem., 51: 200 (1959).
10. S. Dushman, "Vacuum Techniques," John Wiley and Sons, Inc., New York, 1955, pp. 810-817.

5.0 APPENDIX

5.1 Experimental Parameters

Run No.	Bed Length, in.	Gas Flow Rate, cc/min	H <sub>2</sub> Concentration, %	Wt of H <sub>2</sub> O Formed, g
1	3.3	1000	10	4.6656
2	0.75	1000	10	4.3183
3	0.375	1200	30	2.326
4	0.91	1200	30	4.8761
5	0.25	1200	30	1.2162
6	0.25	1000	10	0.9107
7	1.25	1200	30	7.6523
8	1.75	1000	10	4.6318
9	1.5	1670	10	7.2086
10	1.2	1000	1	1.1936

All experiments were carried out at 300°C.



### 5.3 Sample Calculations of Residence Time

For Run 2:

Pure CuO = 5.94 g/cc

Wt of CuO in bed = 25.4 g

Volume of CuO =  $25.4/5.94 = 4.28$  cc

Bulk volume of bed =  $(1.90)(3.14)(1.19)^2 = 8.48$  cc

Void volume = 4.20 cc

Residence time =  $4.20/1000 = 0.00420$  min = 0.252 sec (based on total unreactive bed)

To get the residence time at any time the percentage conversion—time curves are graphically integrated to find the total quantity of H<sub>2</sub> reacted. The percentage of the bed that is reacted can be computed from the hydrogen consumed. The residence time is given by the product of the fraction of the bed unreacted and the residence time for the initial unreacted bed.

**THIS PAGE  
WAS INTENTIONALLY  
LEFT BLANK**



INTERNAL DISTRIBUTION

- |  |  |
|--|--|
| 1. C. E. Center                                | 53. W. K. Eister   |
| 2. Biology Library                             | 54. F. R. Bruce  |
| 3. Health Physics Library                      | 55. W. E. Clark  |
| 4-5. Central Research Library                  | 56. D. E. Ferguson   |
| 6. Reactor Experimental<br>Engineering Library | 57. R. B. Lindauer   |
| 7-26. Laboratory Records Department            | 58. H. E. Goeller  |
| 27. Laboratory Records, ORNL R.C.              | 59. C. W. Hancher  |
| 28. A. M. Weinberg                             | 60. R. A. Charpie  |
| 29. L. B. Emler (K-25)                         | 61. J. A. Lane   |
| 30. J. P. Murray (Y-12)                        | 62. M. J. Skinner  |
| 31. J. A. Swartout                             | 63. R. E. Blanco   |
| 32. E. H. Taylor                               | 64. G. E. Boyd   |
| 33. E. D. Shipley                              | 65. W. E. Unger  |
| 34-35. F. L. Culler                            | 66. A. T. Gresky   |
| 36. M. L. Nelson                               | 67. E. D. Arnold   |
| 37. W. H. Jordan                               | 68. C. E. Guthrie  |
| 38. C. P. Keim                                 | 69. J. W. Ullmann  |
| 39. J. H. Frye, Jr.                            | 70. K. B. Brown  |
| 40. S. C. Lind                                 | 71. K. O. Johnsson   |
| 41. A. H. Snell                                | 72. J. C. Bresee   |
| 42. A. Hollaender                              | 73. P. M. Reyling  |
| 43. K. Z. Morgan                               | 74. R. G. Wymer  |
| 44. T. A. Lincoln                              | 75. J. F. Talley   |
| 45. M. T. Kelley                               | 76. D. L. Katz (consultant)                                      |
| 46. R. S. Livingston                           | 77. I. Perlman (consultant)                                      |
| 47. A. S. Householder                          | 78. M. Benedict (consultant)                                     |
| 48. C. S. Harrill                              | 79. C. E. Larson (consultant)                                    |
| 49. C. E. Winters                              | 80. H. Worthington (consultant)                                  |
| 50. H. E. Seagren                              | 81. J. H. Rushton (consultant)                                   |
| 51. D. Phillips                                | 82. ORNL - Y-12 Technical Library,<br>Document Reference Section |
| 52. W. D. Bond                                 |  |

EXTERNAL DISTRIBUTION

83. Division of Research and Development, AEC, ORO  
84-640. Given distribution as shown in TID-4500 (15th ed.) under Chemistry-General category (75 copies - OTS)